

Recycling of Materials in Civil Engineering

by

Margaret Mary O'Mahony

A Thesis submitted to the
University of Oxford for the
Degree of Doctor of
Philosophy

New College

Trinity Term, 1990.

ABSTRACT

Margaret Mary O'Mahony
New College

Doctor of Philosophy
Trinity Term, 1990.

Recycling of Materials in Civil Engineering

Although Britain is relatively rich in natural aggregate reserves, planning approvals to develop new quarries are running at about half the rate of aggregate extraction. The use of secondary materials, such as recycled aggregate, might not create a major source of aggregate but if secondary materials were used in less demanding situations, the quantity of natural aggregate required by the construction industry would be reduced.

This dissertation reports mainly on laboratory tests conducted on crushed concrete and demolition debris to examine the potential use of these materials in new construction. Standard aggregate tests were conducted on the materials to check their compliance with the Specification for Highway Works (1986), particularly for use as aggregate in road sub-base layers. A more detailed examination of the aggregates was conducted with regard to CBR, shear strength and frost susceptibility where the influences of moisture content, density and particle packing on these properties were investigated. One part of the study involved examining the use of recycled aggregate as the coarse aggregate fraction in new concrete.

An analysis of the shear strength data was conducted using the dilatancy index defined by Bolton (1986). From the frost susceptibility results, it was concluded that further work would be required in this area to determine the main factors which influence the frost heave of recycled aggregates. The recycled aggregate concrete compared well with the natural aggregate concrete and appeared to be of superior quality than that produced in other research. During the study, it became evident that the recycled aggregates could perform as well as limestone in most cases and therefore could be considered for many potential uses. Some recommendations are presented at the end of this dissertation for the development of a standard on recycled materials which would help to promote the use of recycled aggregates in the construction industry in Britain.

To Bridie and Jerry O'Mahony

*"Holy Spirit light all roads so
that I can attain my goal"*

CONTENTS

ABSTRACT

Contents	(i)
Acknowledgements	(iii)
List of Terms and Symbols	(iv)

CHAPTER 1 INTRODUCTION	1-1
-------------------------------------	-----

CHAPTER 2 RECYCLING - PROCESSES AND CURRENT STANDARDS	2-1
2.1 Introduction	2-1
2.2 The recycling process	2-3
2.2.1 Crushers	2-6
2.2.2 Sorting techniques	2-8
2.3 State-of-the-art and standards	2-11
2.3.1 Britain	2-12
2.3.2 The Netherlands	2-16
2.3.3 Denmark	2-18
2.3.4 Belgium	2-19
2.3.5 Japan	2-20
2.3.6 Germany	2-22
2.3.7 United States of America	2-23

CHAPTER 3 STANDARD AGGREGATE TESTS	3-1
3.1 Introduction	3-1
3.2 Sub-base requirements	3-2
3.3 Particle grading	3-4
3.4 Plasticity	3-12
3.5 10% fines test	3-13
3.6 Specific gravity	3-14
3.7 Density tests on site	3-17
3.8 Impurities	3-22
3.9 Discussion	3-23
3.10 Conclusions	3-23

CHAPTER 4 COMPACTION AND CALIFORNIA BEARING RATIO TESTS	4-1
4.1 Compaction	4-1
4.1.1 Introduction	4-1
4.1.2 Compaction apparatus and test procedures	4-2
4.1.3 Results	4-10
4.2 California Bearing Ratio	4-18
4.2.1 Introduction	4-18
4.2.2 The CBR test	4-19
4.2.3 Results	4-24
4.2.4 Analysis	4-36
4.3 Discussion	4-40
4.4 Conclusions	4-41

CHAPTER 5 DIRECT SHEAR TESTS	5-1
5.1 Introduction	5-1
5.2 300mm shear box	5-1
5.3 Preparing the samples	5-4
5.4 Running the shear box test	5-5

5.5	Test conditions of aggregates	5-6
5.6	Leighton Buzzard sand tests	5-11
5.7	Results	5-12
5.8	Shear box tests for road sub-base materials	5-23
5.9	Analysis	5-25
5.9.1	The flow rule analysis	5-26
5.9.2	Analysis using dilatancy index	5-31
5.10	Discussion	5-38
5.11	Conclusions	5-40
CHAPTER 6	FROST SUSCEPTIBILITY TESTS	6-1
6.1	Introduction	6-1
6.2	The explanation of frost heave	6-2
6.3	Development of the frost heave test	6-4
6.4	Frost heave testing	6-5
6.4.1	Preparing the test specimens	6-5
6.4.2	Test conditions	6-9
6.4.3	Setting up the self-refrigerating unit	6-12
6.4.4	Placing the specimens in the SRU	6-14
6.5	Classification of materials	6-16
6.6	Results	6-17
6.7	Discussion	6-25
6.8	Conclusions	6-27
CHAPTER 7	RECYCLED AGGREGATE CONCRETE	7-1
7.1	Introduction	7-1
7.1.1	Mix design	7-1
7.1.2	Workability	7-2
7.1.3	Strength of concrete	7-3
7.1.4	Young's modulus	7-3
7.1.5	Shrinkage and creep	7-4
7.1.6	Impurities	7-4
7.2	An examination of recycled aggregate concrete	7-6
7.2.1	Mix design of recycled aggregate concrete	7-6
7.2.2	Workability of concrete mixes	7-8
7.2.3	Compressive strength results	7-8
7.2.4	Young's modulus results	7-13
7.2.5	Shrinkage	7-14
7.2.6	Creep	7-18
7.3	Discussion	7-22
7.4	Conclusions	7-25
CHAPTER 8	DISCUSSION	8-1
8.1	Global review of test results	8-1
8.2	Recycling in civil engineering	8-9
8.3	Possible uses of recycled materials	8-12
8.4	Estimates of errors	8-15
CHAPTER 9	CONCLUDING REMARKS	9-1
9.1	Conclusions	9-1
9.2	Suggestions for a standard on recycled materials in Britain	9-5
9.3	Further research	9-6
REFERENCES	R-1

Acknowledgements

The Institute of Demolition Engineers and Dr. Peter Lindsell are acknowledged for the initiation of this research project, their support and the funding of this work in the early stages.

I would like to thank the University of Oxford and New College for financial assistance in my third year. I am also grateful for the financial support of the Geotechnical Consulting Group as part of a contract from the Transport and Road Research Laboratory.

Hughes and Salvidge Ltd., Foster Yeoman Ltd. and Fitzpatrick & Sons Ltd. are thanked for the provision of materials.

I extend my gratitude to everyone who was involved with my work, particularly the following:-

Dr. Mike Mulheron at the University of Surrey for his constant support and encouragement.

Members of the Civil Engineering Department at the University of Surrey for their help and assistance when needed.

Members of the Transport and Road Research Laboratory, particularly Dr. M. P. O'Reilly, Mr. Ken Brady, Mr. Guy Watts and the other members of the Ground Engineering Unit for their support and help.

Mr. Bill Birch and his assistants in the Maintenance Section of the Department of Engineering Science at the University of Oxford who were always obliging when their assistance was required.

I am privileged to have been a member of the Soil Mechanics Group at the University of Oxford and am very grateful to Professor Peter Wroth for taking a personal interest in my work and welfare during my stay in Oxford. I would also like to express my gratitude to past and present members of the Soil Mechanics Group for making it a pleasant place in which to work. Dr. Richard Jewell deserves an extra note of thanks for his advice and guidance.

I would like to express my sincere gratitude to my supervisor Dr. George Milligan who was instrumental in providing me with the chance to complete this research, for his organisation of funding, for his guidance and support at all times and for his constructive criticism and advice during the preparation of this thesis.

Finally, I would like to thank my family, particularly my parents to whom I am indebted for their continual support, encouragement, understanding and patience over many years.

List of Terms and Symbols

Crushed concrete	Clean aggregate obtained from the break up, crushing and screening of concrete slabs from road pavements.
Demolition debris	Aggregate obtained from the demolition, crushing and screening of demolition rubble. This recycled product can contain many constituents as well as concrete such as brick, glass, asphalt and wood.
Recycled aggregate	Aggregate produced from the break up, crushing and screening of any demolition waste.
Recycled aggregate concrete	Concrete made using recycled aggregate in either of the coarse or fine aggregate fractions.

A	Area of shear box
c	Cohesion
CBR	California bearing ratio
CIV	Clegg impact value
CLD	Constant level device
C_u	Coefficient of uniformity
d	Depth of footing
dx	Increment of shear displacement
dy	Increment of vertical displacement
dy/dx	Rate of dilation
$d\gamma_{yx}$	Increment of shear strain
$d\varepsilon_{yy}$	Increment of vertical strain
$d\varepsilon_{yy}/d\gamma_{yx}$	Rate of dilation
D_{10}	Diameter at which 10% of the material is finer
D_{50}	Diameter at which 50% of the material is finer
D_{60}	Diameter at which 60% of the material is finer
e	Voids ratio

e_{\max}	Maximum voids ratio
e_{\min}	Minimum voids ratio
g	Gravitational constant
G_s	Specific gravity
h	Height of deforming zone in shear box sample
H	Height of shear box
I_d	Relative density
I_r	Dilatancy index
L	Length of shear box
LVDT	Linear variable differential transformer
m	Constant
MC	Moisture content
N_c, N_q and N_γ	Bearing capacity factors
OMC	Optimum moisture content
OPC	Ordinary Portland cement
p'	Mean effective stress
P_s	Shear force
P_v	Vertical force
Q	Constant depending on material type, as defined by Bolton (1986)
q_u	Ultimate bearing capacity
r	Radius of footing
R	Constant = 1
s	Mean principal stress
S.D.	Standard deviation
SRU	Self-refrigerating unit
t	Maximum shear stress
V_{fw}	Proportion of volume occupied by free water
V_s	Proportion of volume occupied by solids
W_a	Water absorption

w/c	Water/cement
γ	Unit weight
ρ_b	Bulk density
ρ_d	Dry density
$\rho_{d,peak}$	Peak dry density
σ_1	Major principal stress
σ_2	Intermediate stress
σ_3	Minor principal stress
σ_v	Vertical stress
σ_{yy}	Vertical stress measured on central plane
τ	Shear stress
τ_{yx}	Shear stress measured on central plane
τ/σ_v	Stress ratio
$(\tau/\sigma_v)_p$	Peak stress ratio
τ_{yx}/σ_{yy}	Stress ratio measured on central plane
ϕ	Angle of internal friction
ϕ_{cv}	Critical state plane strain angle of friction
ϕ_{ds}	Direct shear angle of friction
ϕ_{ps}	Plane strain angle of friction
$(\phi_{ds})_{cv}$	Critical state direct shear angle of friction
$(\phi_{ds})_p$	Peak direct shear angle of friction
$(\phi_{ps})_p$	Peak plane strain angle of friction
ψ	Angle of dilation

CHAPTER 1

INTRODUCTION

Recycling of demolition rubble is not a new idea and some reported cases of recycling demolition waste date back to the 2nd World War. In several countries, particularly in Europe, it is an important process which is used to produce a useful source of aggregate for the construction industry. Britain has been slow to adopt recycling on a large scale because it possesses substantial mineral reserves. However, planning approvals to develop new quarries are running at only half the rate of aggregate extraction, which means that in the future the rate of production of crushed rock will be too slow to meet the aggregate demand of the construction industry. The use of secondary materials may not completely remove the problem of the resulting shortage of aggregate but it could alleviate it. The more successful cases of recycling reported in Europe are those where the recycling plant is located in a large city and where there is likely to be sufficient demolition to provide a consistent supply of rubble.

The increasing price of land in recent years has led to high dumping costs at landfill sites, particularly in London. Demolition contractors, wishing to dispose of rubble, have found that it is now more expensive to dump demolition waste than to recycle it. Some demolition contractors unfortunately resort to fly-tipping i.e. tip rubble illegally on private or public land, to dispose of what is a potentially valuable material. To promote recycling, incentives should be given to demolition contractors by installing recycling plants in urban locations and allowing the use of recycled aggregate instead of natural aggregate for some purposes.

The research project commenced with a study of the equipment which was available to demolition contractors for the recycling of demolition rubble. In the Netherlands, recycled

products are used almost exclusively as aggregate for unbound layers in road construction because natural aggregate is scarce. Consequently the Dutch have refined the recycling process to produce good quality recycled aggregate. The recycling plants in Britain were compared with those in operation in the Netherlands and were found to be less well equipped with cleaning and sorting devices.

The recycled products from some recycling plants were examined and their physical properties were compared with those of natural aggregate. The ability of the recycled aggregates to comply with existing specifications, particularly for use as granular sub-base material, was also checked.

Shortly after the research project commenced, the opportunity arose to conduct a field trial on a stretch of road in the development of Portsmouth Marina. Demolition debris and limestone were placed in the top part of the capping layer and the densities and gradings of the materials were compared. It would have been more useful if the materials could have been placed in the sub-base layer but the client would not permit this.

The research project progressed into a detailed examination of the properties of crushed concrete and demolition debris. The crushed concrete was a clean aggregate obtained from the break up, crushing and screening of concrete slabs during repair work on the M25 motorway at the Potters Bar junction and the demolition debris was an aggregate obtained from the recycling of demolition rubble and therefore included a random mix of materials. These aggregates were compared with a carboniferous limestone from a quarry in Somerset.

The influence of the inclusion of particles larger than 37.5mm on compaction was examined in a 300mm diameter mould and the results of more conventional compaction tests were also studied. The relationship between dry density and moisture content obtained from these

tests formed the basis for an investigation into the CBR of the materials in different test conditions. A comparison was made between CBR values calculated using the respective friction angles of the materials and the measured CBR values.

The shear strength of the aggregates was examined in a 300mm x 300mm x 179mm shear box located at the Transport and Road Research Laboratory. The influence of density and vertical stress on the shear strength of the aggregates was investigated and an analysis was conducted on the test data using the dilatancy index defined by Bolton (1986).

Due to the strong emphasis on the use of recycled materials for road sub-base in the research project and because of the restrictions on the frost susceptibility of materials to be placed within 450mm of a road surface, the frost susceptibility of the recycled materials was studied. The influence of the initial moisture content on frost heave was also examined to observe whether frost heave was dependent, not only on the flow of water into the material from below, but also on the initial moisture content.

The major part of the work was conducted with a view to using the recycled aggregates in unbound conditions e.g. as road sub-base or fill to structures. In addition, a study was carried out on the properties of concrete made using crushed concrete as the coarse aggregate fraction. Tests were performed on fresh and hardened concrete and the performance of recycled aggregate concrete was compared with that of concrete made using a Thames valley gravel.

From the results of the tests conducted on the aggregates in unbound conditions, some conclusions were made on the best conditions in which to place recycled aggregates on site. At the end of this dissertation, the strengths and weaknesses of recycled materials are discussed and some suggestions are made for the improvement of material which does not

comply with current specifications. On a more general note, some proposals are made to the construction industry on how to come to terms with and accept recycled material as a useful aggregate source.

Although some recycled materials are allowed to be used for certain purposes in Britain, no standard includes definitions of these materials or the levels of acceptable contamination. The main aim of the research project was to examine the properties of recycled materials and it was expected that the conclusions would be a basis from which the production of a standard for recycled aggregates would develop.

CHAPTER 2

RECYCLING - PROCESSES AND CURRENT STANDARDS

2.1 Introduction

In 1985, approximately 191 million tonnes (mt) of crushed rock, sand and gravel were used as aggregate for construction in England and Wales (DoE, MPG6, 1989). This report will be referred to hereafter as MPG6 (1989). Aggregate consumption had increased to 202mt by 1986 and is expected to rise to 226mt by 1995 and 245mt by 2005 (MPG6, 1989). In 1972, the British government appointed an advisory committee on aggregate (the Verney Committee) to consider the future supply of aggregate for the construction industry. This committee concluded that the object of a policy for aggregates should be to achieve an adequate and steady supply of material to meet the needs of the construction industry at minimum financial and social cost (the Verney Report, 1976). The committee realised that the environmental nuisance caused by aggregate production and distribution could not be totally avoided but it suggested that every effort should be made to keep damage to the environment to a minimum.

It was stated in MPG6 (1989) that the use of secondary materials such as blast furnace slag, power station ash and aggregates produced from the recycling of construction waste, such as crushed concrete, should be encouraged. If the reuse of waste was increased, the demand for conventional aggregate would be reduced. Therefore there would be less tipping and at the same time there would be a reduction in the amount of land required for the extraction of natural aggregate. It was reported in MPG6 (1989) that waste material was unlikely to become a major source of aggregate because of transport considerations. MPG6 (1989) appears to have placed the emphasis on the wrong reason because there are also transport

problems for natural aggregate producers e.g. a source in Scotland providing aggregate for construction in London. The main reason is more likely to be the lack of an organised approach to recycling.

The main areas currently supporting recycling in Britain are London and the South-East with virtually no recycling being carried out in Wales or Scotland. Seventy per cent of demolition waste produced in Britain is from England (Mulheron, 1988). It was estimated by Environmental Resources Ltd. (1980) that by 1990 approximately 27mt of concrete waste and 16mt of brick waste would be dumped each year at land fill sites in Britain. If this material could be recycled for use in the construction industry, the environment would benefit in two ways. First, the amount of land needed for dumping would be reduced and secondly there would be a slower release of land required for aggregate extraction.

Research into the recycling of construction material has been conducted extensively in some European countries and in the United States. This research was prompted by the possible environmental and economic benefits of reusing such material. In Britain, recycled materials have been used as fill and hard-core but have not been used very much in the more selective areas of construction. Recently, however, there have been comments in the media (New Civil Engineer, 1989) about the possible shortages of aggregate in the future, not because natural aggregate reserves will become depleted but because the release of land is becoming more restricted due to the detrimental effect of quarrying on the environment. Britain, in comparison with some other European countries such as the Netherlands, is relatively rich in natural aggregate and this may be partly the reason why clients select conventional aggregate in preference to recycled aggregate.

2.2 The recycling process

A recycling plant is quite similar to a plant producing crushed natural aggregate. The closed system, illustrated in Figure 2.1, is the layout which is normally recommended for the production of recycled aggregate (Hansen, 1985). The open system, which is shown in Figure 2.2, has greater capacity but the maximum particle size is less well defined and this can lead to larger variations in the size of the end product. As clean concrete is not always available, provision must be made in a recycling plant for the extraction of contaminants from the material. The layout of a stationary recycling plant, which produces a high quality product, is shown in Figure 2.3.

Recycling plants can be mobile or stationary. Normally a mobile plant consists of one crusher and some sorting devices. The removal of contaminants and steel is mainly conducted by hand sorting and self-cleaning electromagnets. In some cases mobile plants can consist of two crushers, as was demonstrated by Somerset County Council on the repair of the Taunton Bypass in 1989. The main advantages of a mobile installation are as follows (Lindsell and Mulheron, 1985):-

- (i) Transport in the vicinity of the site is reduced, particularly if the rubble is produced, recycled and reused on the same site.
- (ii) Disposal costs are reduced because of less dumping.
- (iii) The local supply of aggregate is increased and therefore less aggregate needs to be imported into the area.
- (iv) The recycling plant can be moved relatively easily to another site.

The disadvantages of a mobile recycling plant are as follows:-

- (i) There are limited cleaning facilities in this type of installation and therefore the recycled product is normally of low quality.

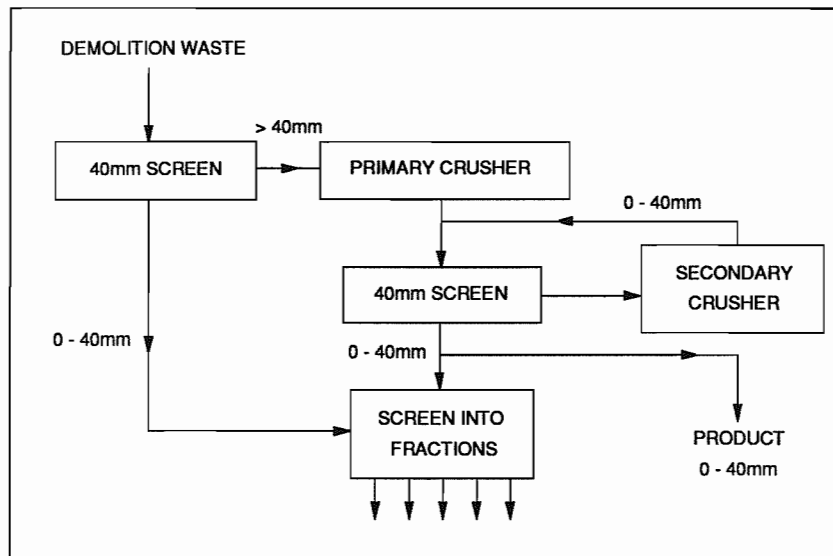


Figure 2.1 Flow chart of a typical closed system recycling plant, set up to produce a grading of 0 - 40mm (after Hansen, 1985)

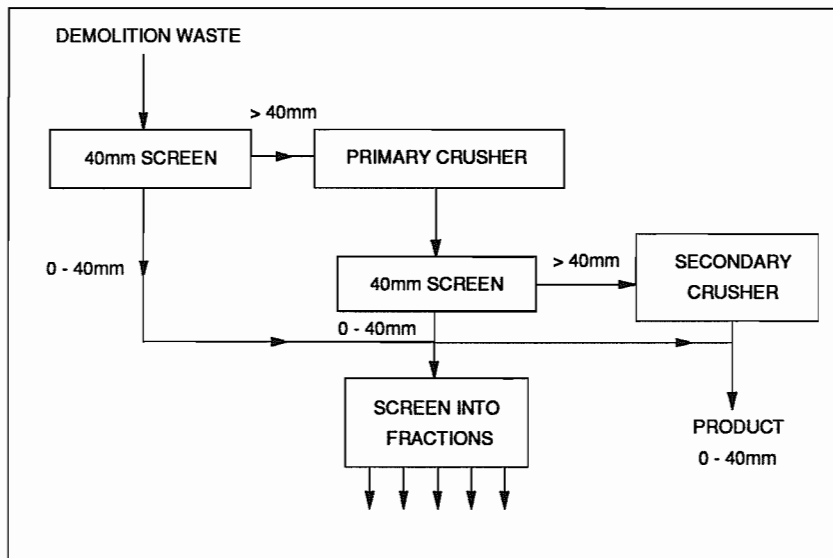


Figure 2.2 Flow chart of a typical open system recycling plant, set up to produce a grading of 0 - 40mm (after Hansen, 1985)

- (ii) The recycling plant can cause high levels of dust and noise which would be unacceptable close to residential areas.
- (iii) This type of plant can only be used if there is a sufficient quantity of rubble on the site to justify the expense of setting up the recycling plant.

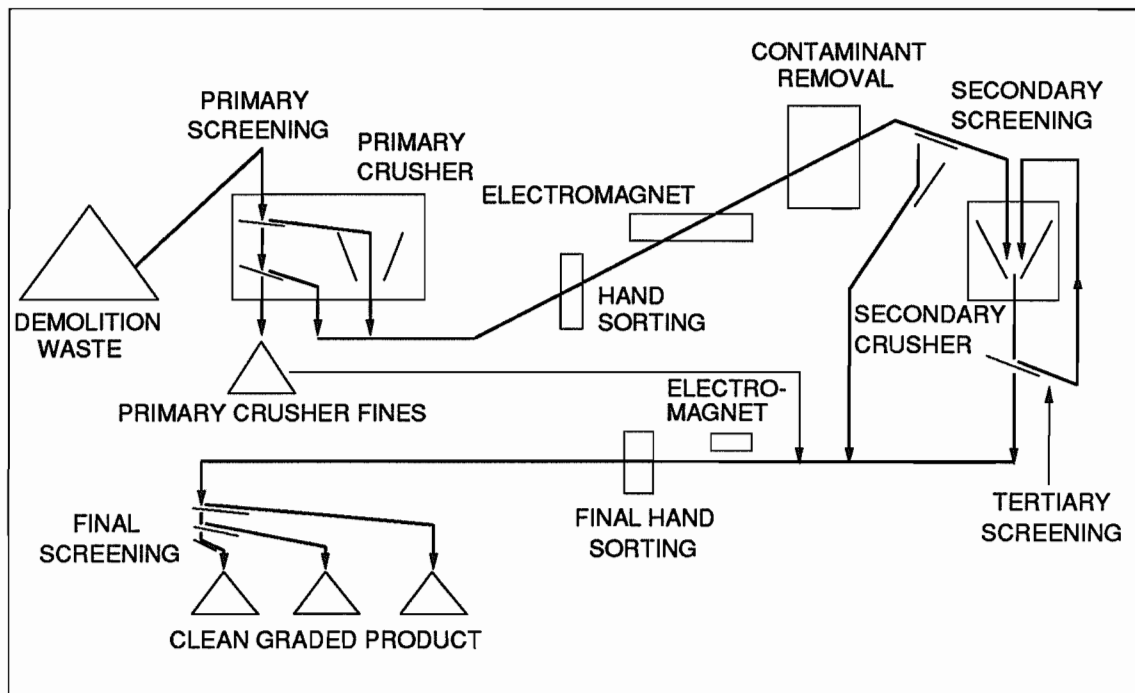


Figure 2.3 Typical layout of a stationary recycling plant (after Lindsell and Mulheron, 1985)

A stationary recycling plant usually incorporates a large primary crusher working in conjunction with a secondary crusher and also includes various cleaning and sorting devices to produce high quality aggregate. In Britain, this type of plant normally combines two jaw crushers and is capable of yielding a range of graded products. Self-cleaning electromagnets, sieves and hand sorting are employed to produce a relatively clean recycled aggregate from a mixed and contaminated input material (Mulheron, 1988). A Dutch stationary plant is illustrated in Plate 2.1. Recently some stationary recycling plants have been set up in

Manchester, Birmingham and Portsmouth and approximately six have been installed in London. The main advantages of a stationary recycling plant are as follows (Lindsell and Mulheron, 1985):-

- (i) The recycling plant is capable of producing a high quality product.
- (ii) The efficiency of the plant is better than that of a mobile recycling plant because different recycled products of various gradings can be produced.
- (iii) Disposal costs are reduced because of less dumping.
- (iv) The local supply of aggregate is increased and therefore less aggregate needs to be imported into the area.

The disadvantages of a stationary recycling plant are as follows:-

- (i) The initial investment of setting up such a plant can be in excess of several million pounds.
- (ii) There is an increase in transport in the vicinity of the recycling plant.
- (iii) The recycling plant can cause an increase in noise levels.
- (iv) The efficiency of production depends on the local supply of rubble and unfortunately demolition contractors are rarely able to ensure a constant supply of demolition waste.

2.2.1 Crushers

The crushers which are used at present for the recycling of rubble were not designed or developed specifically for the purpose. The majority of crushers originate from coal and ore processing or from natural stone crushing plants (Boesman, 1985). Modifications have been made to these crushers to alter the degree of size reduction and the particle size distribution, to reduce wear and to prevent high levels of dust and noise.

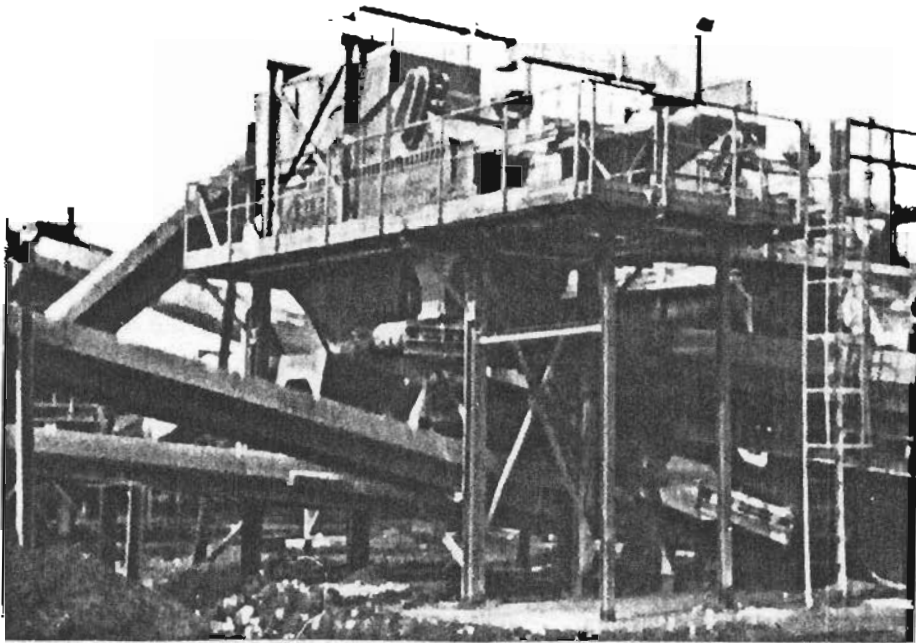


Plate 2.1 A stationary recycling plant consisting of a primary jaw crusher and a secondary impact crusher

The suitability of three types of crushers for crushing construction waste was investigated by Boesman (1985). They included a jaw crusher, an impact crusher and a cone crusher. A cone crusher cannot accept material which is larger than 200mm in size and therefore only jaw and impact crushers should be considered for use as primary crushers (Boesman, 1985).

A jaw crusher consists of two plates fixed at an angle - one plate remains stationary while the other plate oscillates back and forth relative to the fixed plate. This action crushes material passing between the two plates. The degree of particle size reduction depends on the maximum and minimum size of the gap at the base of the plates. An impact crusher breaks the material up by striking it with a high speed rotating impactor which imparts a

shearing force on the rubble. Almost all recycling plants in Britain incorporate jaw crushers whereas recycling plants in Europe usually employ impact crushers (Lindsell and Mulheron, 1985).

The particle size distribution of the output material is affected by the type of crusher used (Boesman, 1985). In general, the impact crusher has a large reduction factor. The reduction factor is defined as the ratio of the particle size of the input to the particle size of the output material (Lindsell and Mulheron, 1985). A jaw crusher crushes only a small proportion of the original aggregate particles but an impact crusher crushes mortar and aggregate particles alike and for the same maximum size of particle generates twice the amount of fines. One advantage of the impact crusher is its high efficiency and relatively low sensitivity to material which cannot be crushed e.g. reinforcement. Consequently, impact crushers suffer high wear and tear which means that maintenance costs are high.

2.2.2 Sorting techniques

There are several methods of removing contaminants from demolition debris and they can be separated into two groups, (i) pre-crushing separation and (ii) post-crushing separation.

(i) Pre-crushing separation

Rubble can be sorted while a structure is being demolished but this type of separation can be expensive and time consuming for the demolition contractor and therefore is not normally carried out unless there are definite incentives on a particular demolition site. Most sorting takes place when the rubble reaches the recycling plant. When the waste arrives, it is stockpiled according to its major constituent or the amount of contamination present. The plant operator can therefore deal with very large or undesirable material separately (Lindsell and Mulheron, 1985). This initial sorting

can help to optimise crushing time because e.g. a large quantity of clean rubble which has accumulated in a stockpile can be crushed in a single, continuous crusher run.

At most recycling installations, primary screening is conducted by passing the rubble over a sieve before it reaches the primary crusher. Therefore material, which is already of the required size and which needs no further crushing, bypasses the primary crusher. This fraction is usually screened further to remove soil and other fine contaminants and the remainder is returned at a later stage to the recycling process.

(ii) Post-crushing separation

After the rubble has been crushed, a number of contaminant removal techniques can be applied to the material. The simplest method is hand sorting which involves removing contaminants by hand from the conveyor belts. The efficiency of this system depends on the concentration of the operator and on the speed of the conveyor belt. The main advantage of this method is that the human eye can recognise contaminants which would be difficult to remove by mechanical means e.g. glass.

Automatic methods of contaminant removal include the following:-

a) Electromagnetic removal of steel

Self-cleaning electromagnets for the removal of steel are commonly employed in recycling plants. Usually the magnet is located across the conveyor belt between the primary and secondary crushers. The efficiency of the magnet depends on the distance between the magnet and the conveyor belt, the conveyor belt speed, the density of the passing demolition debris and the angle at which

the magnet is inclined to the conveyor. A magnet works most efficiently when it is positioned directly above and parallel to a slow moving, lightly loaded conveyor belt (Lindsell and Mulheron, 1985).

b) Dry sieving

Dry sieving can be used to separate the material into fractions which can be recombined later to produce well graded aggregate. The main disadvantage of dry sieving methods is the production of large quantities of dust. According to the Building Contractors Society of Japan (1981), coarse materials can be separated more efficiently by using inclined screens vibrating at low frequencies and large amplitudes while horizontal screens, vibrating at high frequencies and small amplitudes, are more effective for separating fine material.

c) Wet separation

Low density contaminants can be removed from demolition debris using an aquamator (Lindsell and Mulheron, 1985). This method of separation is conducted by placing the material in a tank full of water. The water in the tank is circulated at a fast rate and currents are set up by water jets. Wood and other lightweight impurities which float in water are removed by combs which move from one end of the tank to the other. This cleaning technique is normally restricted to material of particle size greater than 10mm because of the excessive quantities of sludge which would be produced if material from a smaller fraction was added to the tank.

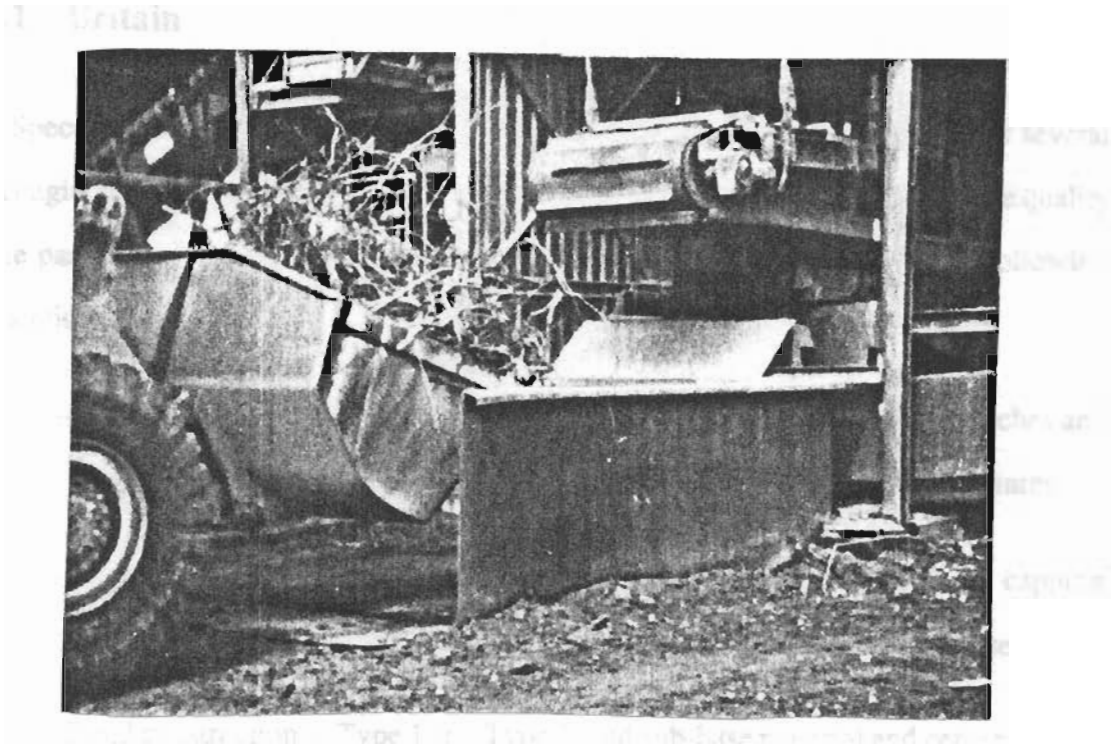


Plate 2.2 The removal of steel after electromagnetic separation from the rubble

2.3 State-of-the-art and standards

To increase the use of recycled aggregate in construction, present standards in Britain must be modified or updated and where possible new standards should be introduced to help in the promotion of recycled aggregates. In 1992, there is likely to be a common European standard for recycled materials but at present some European countries are more advanced than others in their appreciation of recycling. The state-of-the-art in recycling in some countries is described in this section.

2.3.1 Britain

The Specification for Highway Works (1986) allows the use of crushed concrete for several civil engineering purposes and it could be considered for many more depending on the quality of the particular recycled product. Crushed concrete is allowed for use in the following applications:-

- a) Drainage works - bedding and surrounding of pipes, backfilling of trenches and filter drains, backfilling to pipe bays and backing to earth retaining structures.
- b) Earthworks - fill to structures, fill above structural concrete foundations, capping material, cement or lime stabilised capping material and earthworks noise bunds.
- c) Road construction - Type 1 and Type 2 road sub-base material and cement bound materials of grade CBM1 and CBM2, as defined in the Specification for Highway Works (1986).

One of the main aims of this research is to examine the ability of recycled aggregate to perform in the unbound aggregate layer of a flexible road pavement i.e. as sub-base material. The sub-base lies between the basecourse and the subgrade, as can be seen in Figure 2.4. It performs three main functions.

- a) It acts as a structural component of the pavement.
- b) It is not frost susceptible and it insulates the subgrade against freezing.
- c) It provides a working platform for construction traffic.

The stresses generated in a road pavement by traffic decrease rapidly with depth which implies that the stresses exerted on the sub-base are only slightly greater than those on the subgrade. If the sub-base was designed on this basis, the material used would only need to

be a little stronger than the subgrade. However, the third of the functions listed above, rather than the first, determines the minimum sub-base strength because after compaction the sub-base should be able to support construction traffic. If the sub-base suffers large deformations during this time, it might be impossible to place the overlying layers and permanent damage could be suffered by the subgrade.

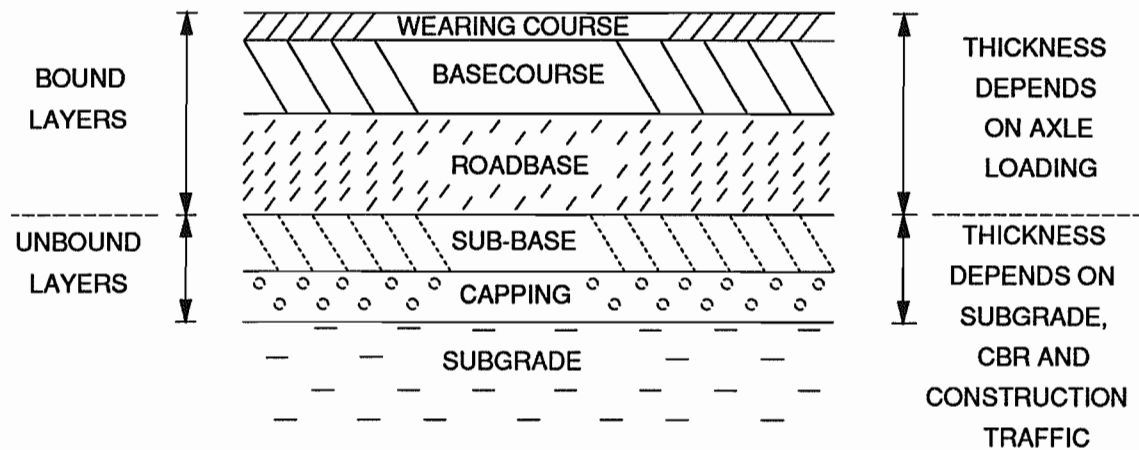


Figure 2.4 Road pavement structure (after Biczysko, 1989)

Brown (1985) concluded that elastic stiffness and permanent deformation resistance are the most important properties of a compacted, unbound layer in a road pavement and are controlled by the amount of drainage allowed in the material. Jones and Jones (1989) pointed out that strength and stiffness are improved if the pore pressures, which are generated on loading, dissipate quickly. Good drainage could help to achieve this and the risk of damage due to frost would also be reduced. It appears from work conducted by Sweere (1989) that recycled aggregate would provide a stiffer layer than conventional aggregate because it possesses a self-cementing quality which is apparent a few weeks after placement.

Jones (1985) and Biczysko (1985) discussed the contradiction in the functions of a sub-base. The material must be densely packed to produce a stiff layer while the sub-base also needs

to be a drainage layer of high permeability. A good drainage layer also has the advantage of low capillary rise which reduces the possibility of frost heave (Jones, 1985). The solution to the apparent contradiction in the functions of a sub-base is to make more use of an open packed capping layer for good drainage and to construct the sub-base as a dense, stiff layer.

In situ pavement recycling has developed into a useful method of reusing construction waste and its description is included in the Specification for Highway Works (1986). This process involves crushing damaged concrete pavement with a specially designed machine which pulverises the concrete slab as it proceeds along the length of a pavement. Cement is then spread on the crushed material followed by water which is delivered from a spray bar connected to a water tank. The material is mixed and compacted by several passes of a vibrating roller and the recycled layer is then covered with a surface dressing (Kennedy and Clark, 1986).

The reputation of recycled material in Britain could be improved if a standard was produced to regulate the quality of both crushed concrete and other recycled materials, such as demolition debris. BS 6543 (1985), the use of industrial by-products and waste materials in building and civil engineering, includes some comments on the use of waste materials in both road construction and building and it considers crushed concrete for sub-base and basecourse applications. It also approves, in principle, the use of clean crushed concrete and demolition debris for use as aggregate in concrete of low strength.

No standard in Britain exists in which crushed concrete, demolition debris or other recycled materials are defined. All waste material is likely to contain various constituents as well as concrete and brick. Crushed concrete is allowed to be used as sub-base material (Specification for Highway Works, 1986) but there should be some specific limits on contamination and a minimum limit on the amount of crushed concrete which should be

present.

Recently in Britain, several demolition contractors have purchased crushers and screens to recycle construction waste so that they might avoid high dumping costs and the difficulties of disposing of waste material. In general, these recycling plants are restricted to single crusher, on-site installations and usually consist of a jaw crusher working with sieves and sorting devices. This type of plant is capable of producing a crushed and graded material but is normally only used where there is sufficient debris to justify the expense of setting up the plant. The quality of the output normally depends on hand sorting and the electromagnetic removal of steel.

The recycled products from these mobile recycling operations are likely to vary considerably depending on the source of the rubble and the type of crushing and screening operation used. Some recycled products comply with existing standards for conventional aggregates but others do not. Material engineers and clients therefore do not have confidence in these materials because of the large variation in products from different operations. More respect for recycled materials could be instilled in engineers if sophisticated plant was used to produce less variable material and if a standard was written which included limits on contamination, to which demolition contractors would be forced to make their materials comply. This would be a significant step forward for recycling of demolition rubble in Britain.

Due to the increasing problem of fly-tipping on public and private streets in London and due to the high cost of dumping, the government within the last year has become more interested in recycling. The Aides to the Secretary of State for the Environment (1989) have said that the production of a standard for recycled materials is under consideration although financial support is lacking.

2.3.2 The Netherlands

The Netherlands has relatively poor reserves of natural aggregate and has become more dependent on recycled material for the construction of unbound aggregate road layers. Recycling in the Netherlands is mostly financed by the government and consequently recycled material has become an important source of aggregate for the Dutch construction industry.

Ten years ago, a number of roads constructed using unbound sub-base in the Netherlands had failed and there was some doubt concerning the empirical knowledge which existed then and whether the design of roads using this knowledge should be continued. A research project was started in 1983 as a joint venture between the Delft University of Technology and the Road and Hydraulic Engineering Division of Rijkswaterstaat in which the properties of recycled and conventional aggregates were examined. The research programme consisted of laboratory and field testing. It was found that visual inspection of the material composition was important because of the influence of particle strength and stiffness on the behaviour of unbound sub-base layers (Penning, 1989). Based on the results of this research project, which were described by Penning in 1989, an additional specification was issued by Centre Row (1988) for secondary materials which included crushed concrete, crushed masonry and demolition debris. Some of the main requirements in this specification (Centre Row, 1988) for crushed concrete and demolition debris are listed in Table 2.1.

When recycled material is to be used as aggregate for sub-base, it must pass the requirements listed in Table 2.1. It must also comply with the Dutch crushing test (similar to the ten per cent fines test) and the particle size distribution limits listed in the Dutch specification for conventional sub-base aggregate (Rijkswaterstaat, 1978).

MATERIAL TYPE	CRUSHED CONCRETE OR MATERIAL OF SIMILAR SPECIFIC GRAVITY	CRUSHED MASONRY	GYPSUM, PLASTIC, RUBBER, etc.	ASPHALT	ORGANIC MATTER SUCH AS WOOD OR PLANTS
Crushed concrete	not less than 90% by mass		not more than 1% by mass and by volume	not more than 5% by mass	not more than 0.1% by mass
Demolition debris	not less than 50% by mass	not more than 50% by mass	not more than 5% by mass		not more than 0.1% by mass

Table 2.1 Dutch specifications for recycled sub-base material (Centre Row, 1988).

Another standard, CUR (1986), has been developed in the Netherlands for the use of recycled material as aggregate in concrete. The specific gravity of the recycled aggregate should not be less than 2.1 and the material should contain at least 95% crushed concrete by mass. The remaining 5% of the material can be natural stone, lightweight concrete, ceramic material, brick or mortar with a minimum of 1% bituminous material by mass. The contamination of the aggregate should be determined by weighing or measuring the volume of the constituents contained in the > 8mm fraction. The amount of sulphate in the material should not exceed 1% and the amount of wood should be less than 0.5% by mass in the 0mm-4mm fraction and less than 0.1% in the fraction containing particles larger than 4mm.

CUR (1986) concluded that concrete made using recycled aggregate could achieve a strength equal to that of conventional aggregate concrete without the addition of extra cement, although in some cases some extra cement might be required. It also stated that the same durability could be attained, but deformation due to shrinkage and creep would normally be greater than for concrete made with natural aggregate. Therefore CUR (1986) suggested

that the depth of a concrete member should be increased by 10%, if 100% of the coarse aggregate used was recycled aggregate. If less than 20% of the coarse aggregate fraction was replaced by recycled aggregate, no increase in depth should be necessary.

It is likely that extra cement would need to be added to a concrete mix in which crushed masonry is used as the aggregate, if a similar strength to that of conventional aggregate concrete is to be achieved. The durability of concrete containing crushed masonry is likely to be similar to that of natural aggregate concrete but there may be a higher risk of frost attack (CUR, 1986).

2.3.3 Denmark

There is less incentive to recycle in Denmark than in Britain because natural aggregate is cheap and can be easily obtained (Jacobsen, Elle and Lauritzen, 1988). The disposal of waste material is inexpensive and is not restricted. Recycled material produced by Danish demolition contractors is considered to be unsuitable for many purposes because demolition and recycling operations are not properly designed to produce high quality material (Jacobsen, Elle and Lauritzen, 1988). However, a "recommendation for the use of recycled aggregates for concrete of passive environmental class" was produced by the Danish Concrete Association (1989). This recommendation suggested that the design and manufacture of recycled aggregate concrete would be similar to that used for conventional aggregate concrete but it stated that standard tests should be conducted more frequently because of the variation in the content of recycled aggregate.

In one research project conducted by Jacobsen, Elle and Lauritzen (1988), it was found when recycling was carried out, instead of the use of natural aggregate, that transport to and from a site was reduced by one third. The noise level due to crushing in the recycling operation

operation was higher than the average noise level, but there were no complaints from neighbours. Dust, on the crushing site, was gathered in a dust precipitator which was connected to the crusher and the stockpiles of recycled aggregate were sprinkled with water. Jacobsen, Elle and Lauritzen (1988) concluded that an expected output of 20,000 tonnes of material would be needed to warrant setting up a mobile recycling plant.

2.3.4 Belgium

Two major research projects into the recycling of construction waste have been conducted in Belgium. During the expansion of the port of Antwerp it was decided to construct a new lock (Morlion, Venstermans and Vyncke, 1988). The embankment walls of the old lock had to be demolished to provide better access. The demolition was carried out using explosives and yielded 80,000m³ of demolition waste. The quantity of new concrete which had to be cast was 650,000m³. Due to environmental and economic considerations, it was decided to recycle and reuse the demolition waste as aggregate for the new concrete (Morlion, Venstermans and Vyncke 1988). By performing cube tests on large lumps of the concrete produced from demolition and by using a Schmidt hammer it was found that the compressive strength of the old concrete was 30N/mm² with a standard deviation of 6N/mm². The 4mm-28mm fraction of crushed concrete was used as the coarse aggregate in the new concrete and a natural sand was used as the fines. The water/cement ratio was as low as possible so that shrinkage would be kept to a minimum and a cement content of 350kg/m³ was imposed in the project specifications. The outcome of this research project was favourable because the new concrete had a compressive strength of 35N/mm² and no deterioration has been reported (Morlion, Venstermans and Vyncke, 1988).

In another research project, crushed concrete was used in the construction of the basecourse and sub-base of seven test roads (Gorle and Saeys, 1988). The conclusions from this project were as follows:-

- (i) Some of the materials used were coarser than the specification required.
- (ii) The average density of crushed concrete was much lower than that of conventional aggregate.
- (iii) Using plate bearing tests immediately after construction it was found that the elastic modulus of the crushed concrete layer was lower than that of a layer constructed using conventional aggregate. However, after several weeks, the elastic modulus of the recycled aggregate layer had increased whereas no change was evident in the conventional aggregate layer.
- (iv) When recycled aggregate was used for these roads, 70% of the total cost saving was due to reduced transport. A 20% saving in cost was achieved due to the lower price of recycled material and a 10% saving was made because of the reduction in dumping costs.

2.3.5 Japan

In Japan, land is used very efficiently and to avoid having to provide many dumping sites, the Japanese have examined the possibility of recycling demolition waste for use as basecourse material in road construction. In 1976, a stationary recycling plant was set up in the suburbs of Nagoya city. As a result of the success of this recycling plant, a report called *The Technical Guide to Reuse of Waste for Pavements* was written by the Japan Road Association in 1984. At that time, the amount of demolition debris produced in Japan was estimated to be 10mt/year and the quantity of concrete rubble reused in roadbase construction

throughout the country was estimated to be about 100,000t/year. The amount of recycled material to be reused was expected to rise rapidly because the report written by the Japan Road Association (1984) was issued by the Ministry of Construction (Kasai, 1985).

The requirements listed in the report (Japan Road Association, 1984) are similar to those for conventional aggregate in Japan. The source of material for recycling which is preferred is concrete from road pavements because it is relatively clean. It has been found that the strength of a basecourse increases with time if it is constructed using crushed concrete (Yoshikane, 1988). Kawamura and Torii (1988) found that crushed concrete from an old pavement had better physical properties as an aggregate for concrete pavement construction than demolition debris.

A proposed standard for the use of recycled aggregate and recycled aggregate concrete was written by the Building Contractors Society of Japan in 1981. The Japanese continue to invest in research on recycling and recently a substantial amount of research has been conducted into the reuse of construction waste as aggregate for new concrete. Many projects have included an examination of the total replacement of conventional aggregate with recycled aggregate as the coarse fraction in new concrete. Yamato et al (1988), Ikeda et al (1988) and Fujii (1988) found that the compressive strength of concrete made with recycled aggregate as the total coarse aggregate fraction was 7%-20% less than that of conventional aggregate concrete.

Some interesting research projects in Japan have included the recycling of waste sludge from ready-mix concrete plants to produce cement (Yoda et al, 1988). This was performed by drying the sludge at 200^oC. The recycled cement was then used to make concrete but the concrete had a lower workability than that of concrete made using OPC because the characteristics of the recycled cement were different. The compressive strength of concrete

made using recycled cement was half that of conventional concrete. It was suggested by Yoda et al (1988) that OPC should be added to recycled cement as an accelerator and that a low water/cement ratio should be used in concrete mixes made using recycled cement.

Kakizaki et al (1988) examined the possibility of using recycled aggregate as aggregate for structural concrete and found that the bonding strength between the concrete and reinforcement was 25%-40% lower than that in conventional structural concrete. The tests for this research were conducted on cubes of concrete containing steel bars. The coarse aggregate fraction in the concrete consisted totally of crushed concrete. Mukai and Kikuchi (1988) examined reinforced concrete beams made using a coarse aggregate fraction which consisted of 30% crushed concrete and 70% natural aggregate. The bonding and bending strengths were found to be similar to those of ordinary structural concrete. However, extra stirrups had to be added to the recycled aggregate beams so that the same shear strength could be attained.

2.3.6 Germany

After the 2nd World War, 11.5 million cubic metres of brick were recycled as aggregate for concrete in West Germany (Schulz, 1988). In 1951, a standard was introduced for concrete made with recycled aggregate but was withdrawn shortly afterwards and reproduced later as a standard for lightweight aggregates because the quantity of recycled aggregate available for recycling was decreasing. This standard in its current form is known as DIN 4226 (1983). At present, recycled aggregate cannot be reused for particular construction jobs without permission from the building authorities (Schulz, 1988). If permission is granted, the recycled material must conform to the Dutch standard, CUR (1986). DIN 4226 (1983) does not allow the inclusion of fine material in the aggregate because it considers that this fraction is likely to have the highest contamination level.

When recycled aggregate was used in the unbound layers of roads, Straube, Beckedahl and Gerlach (1989) found that deformation was higher than that observed in layers constructed using conventional aggregate. These results contradicted those of Sweere (1989) who found that the long-term stiffness of a compacted layer was improved if recycled aggregate was used. It was suggested by Straube, Beckedahl and Gerlach (1989) that when recycled aggregate is used, a factor of 2.5 should be applied to the layer thickness. It was concluded that recycled aggregate should only be used in the construction of lightly trafficked roads.

Recently in Germany, the dumping of construction waste was stopped in certain areas and consequently contractors are now forced to recycle waste material (Suss, 1989). However, the progress of recycling is impeded because there remains strong resistance to the use of recycled material due to the fear of high levels of contamination even though specifications for these materials have been drawn up (Suss, 1989).

2.3.7 United States of America

As a result of the increase in awareness that deposits of natural sand, gravel and stone have become depleted or exhausted in some areas or have become excessively expensive in the U.S., there has been a growing interest in waste concrete for reuse as aggregate in new construction (Mather, 1980). Marek (1972) recognised that the technical capability existed or could be developed for the manufacture of new supplementary aggregate materials and for the upgrade of poor quality aggregates. One of the conclusions of this report stated that research would be needed to characterise suitable aggregates before the use of recycled materials instead of conventional aggregates could be properly assessed.

Miller and Collins (1976) recommended that a strong central agency should be given the responsibility to coordinate research and development relating to waste material and to

provide encouragement for the acceptance of the resulting recycled products. It was also suggested that existing specification requirements for aggregates should be thoroughly reviewed and analysed with a view to the relaxation of certain stipulations, particularly in areas where shortages of conventional aggregates were likely to exist. It was concluded that consideration should be given to the adoption of performance specifications, even on a trial basis, to allow more latitude in the selection of highway materials. Britain at present appears to be facing the same difficulties which the U.S. encountered in 1976. Since these recommendations were made by Miller and Collins (1976), some state highway departments have developed their own specifications for recycled aggregate concrete pavements and in 1982, the specification for aggregate for concrete, ASTM C33-82, included crushed concrete in its definition of coarse aggregate.

The Edens Project: Show-case for Recycling (1980) summarised an operation involving the use of recycling for the repair of a fifteen mile stretch of major road on an interstate highway near Chicago. When the asphalt layer of the road had been removed, the badly deteriorated concrete underneath was broken up and crushed. Two materials were produced from the crusher output, a 25mm - 75mm rubble product which was later used as a porous granular backfill and a 0mm - 25mm capping material which was also used in the new construction.

Sadler (1973) reported on a recycling trial in Minnesota. Although the input to the recycling plant was a random mix of demolition waste, the recycled aggregate which was produced possessed a high degree of uniformity and was suitable for use as the base material in a road pavement. When the aggregate was compacted in a wet condition, the cement in the aggregate bonded the rough angular particles together. Recycled rubble was also used on a \$9.4 million project in California as sub-base aggregate (Crushing converts rubble into

sub-base aggregates, 1971). The recycled aggregate in this project performed well and its success was attributed to unhydrated cement in the concrete rubble which became a binder when the aggregate was mixed with water.

CHAPTER 3

STANDARD AGGREGATE TESTS

3.1 Introduction

Standard tests on recycled aggregates were conducted to provide a representative account of recycled products, currently on the market in Britain. British and Dutch recycled aggregates were compared with reference mainly to index testing to observe if similarities existed between the materials. As recycled aggregates are used extensively for sub-base layers in road construction in the Netherlands, it was thought if similarities did exist, then it would be a useful argument in persuading clients in Britain to opt for recycled aggregate products instead of conventional aggregates.

Although the Specification for Highway Works (1986) allows the use of crushed concrete, several demolition contractors have pointed out that there is resistance to its use even though it has been used successfully for many years. Demolition contractors tend to refer loosely to any aggregate produced from demolition rubble as crushed concrete. This could be clarified if a British specification existed which included definitions for both. In this research, the term crushed concrete refers to very clean crushed concrete produced from the break up and crushing of concrete slabs from road pavements. It is likely that this also is the definition which is inferred by the Specification for Highway Works (1986). Any material containing other constituents as well as crushed concrete e.g. brick, glass, asphalt, wood and block, is referred to as demolition debris. From the results of standard aggregate tests conducted during this research, it was apparent that demolition debris could perform as well as crushed concrete if it was used as sub-base material. Some demolition contractors believe that demolition debris would be too plastic due to its brick content. However, plasticity tests revealed that the recycled materials examined in this research were non-plastic.

3.2 Sub-base requirements

The recycled aggregates under review were tested mainly in accordance with the Specification for Highway Works (1986). In Clauses 803 and 804, the specification stipulates the requirements for Type 1 and Type 2 granular sub-base materials. All material intended for use within 450mm of a road surface is required not to be frost susceptible. The specification for Type 1 and Type 2 granular sub-base materials permits the use of crushed rock, crushed slag, crushed concrete and well-burnt non-plastic shale. Type 1 material is intended to withstand substantial trafficking by construction plant whereas Type 2 material can be used in less demanding circumstances and the specification therefore includes natural sands and gravels in this category. The grading envelope for Type 2 is wider than that for Type 1 to permit the use of material of lower maximum size and finer grading.

The quality of Type 1 material is governed by three laboratory tests, which include sieve analysis, plasticity and 10% fines tests. The fourth requirement is that the material should be transported, laid and compacted without drying out or segregation. For Type 2 material there is an extra condition specifying that the aggregate should not have a CBR (California Bearing Ratio) of less than 30%. This CBR requirement is assumed to be fulfilled automatically for Type 1 sub-base material.

The opportunity arose for part of the research to be carried out on site. A field trial was performed in Portsmouth to observe the differences between using Type 1 graded demolition debris and Type 1 limestone in the capping layer of two lengths of road. The demolition debris used in the Portsmouth field trial was specified as having a Type 1 grading and the limestone was a Type 1 certified sub-base material. It would have been more useful if the materials could have been placed as the sub-base of the road and monitored after completion but the client would not permit this.

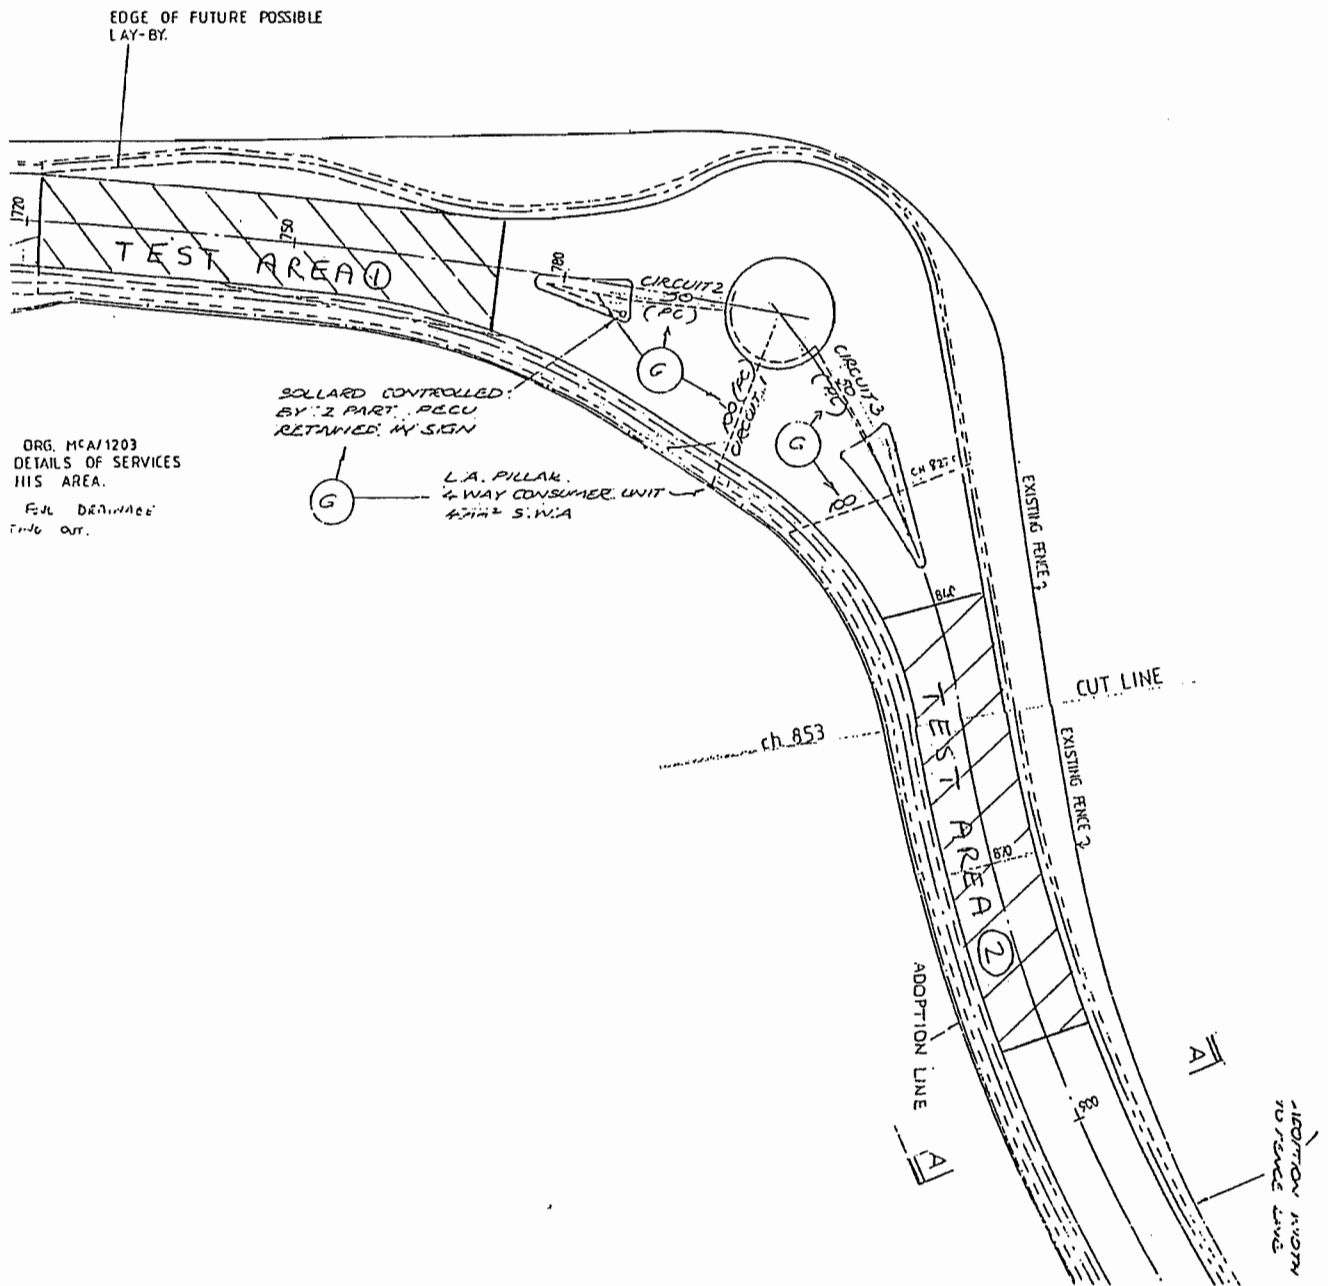


Figure 3.1 Plan of test areas in the Portsmouth field trial

The capping layer was divided in two for the field trial. The lower part was constructed using a coarsely graded, demolition debris capping material and the upper layer was used to compare the Type 1 graded demolition debris and Type 1 limestone. Two similar test areas were chosen on either side of a roundabout. Figure 3.1 shows the test areas on plan and Figure 3.2 outlines more specifically the test area details. The tests conducted for the trial were in situ density tests, sieve analyses and determination of the moisture content at which the aggregates were placed.

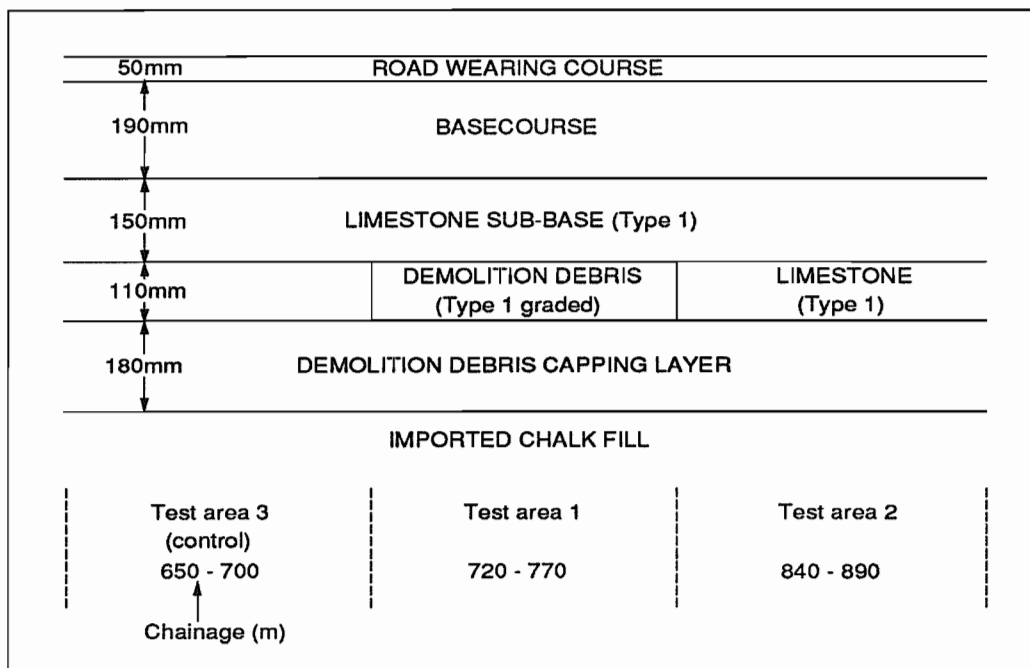


Figure 3.2 Composition of the test areas and the standard road

3.3 Particle grading

Sieve analysis of all material was carried out using the dry sieving method outlined in BS 812: part 102 (1985). The particle grading of an aggregate confirms whether the crusher setting and screening at a recycling plant is adequate to produce Type 1 and Type 2 gradings. Demolition debris, taken directly from the output of a single jaw crusher without screening,

was first examined. It can be seen from Figure 3.3 that there was considerable variation in the proportion of large particles in the samples which was caused by the change in the width of the gap between the crusher jaws. When a new set of jaws had been installed the crusher had a minimum setting of 65mm and a maximum setting of 100mm. However, as the jaws deteriorated on crushing, the settings measured a minimum of 90mm and a maximum of 128mm. Figure 3.3 shows that the aggregate could be considered for use as capping material although some of the samples were too coarse.

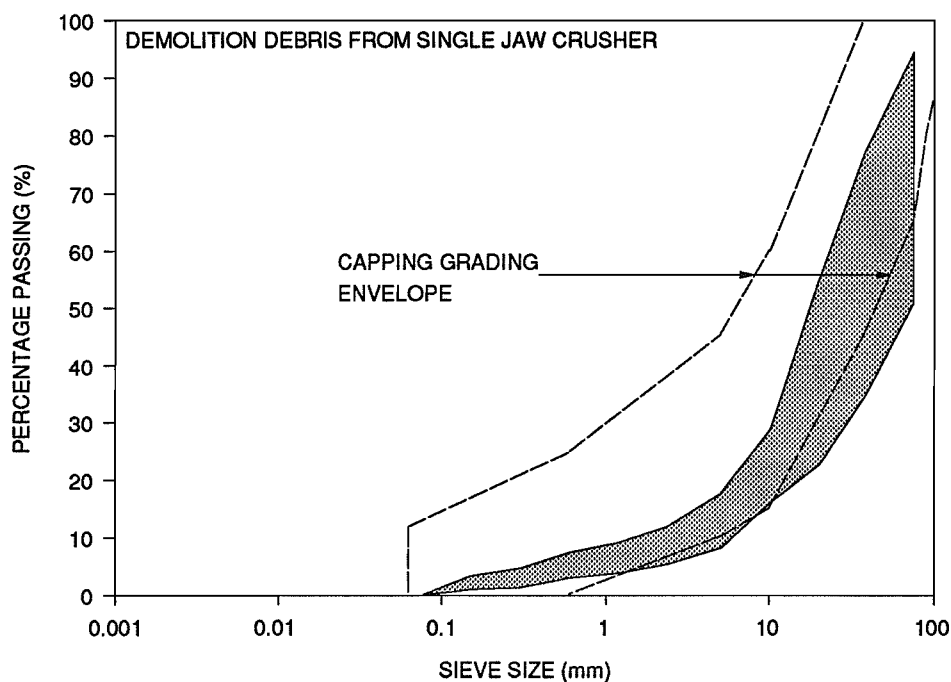


Figure 3.3 Direct output from jaw crusher

Type 2 graded material, produced from a single jaw crusher operation and simple sieving, was less coarse but its grading was close to the coarser end of the Type 2 grading envelope. In this case, the material was passed through 15mm, 10mm and 6mm screens according to Hughes and Salvidge Ltd. (1988). The volumes of aggregate allowed to pass the 6mm and 10mm screens were varied depending on the amount of fines required in the recycled product.

Demolition debris, produced from a double crusher operation consisting of a primary jaw crusher and a secondary impact crusher, was examined next. This material was screened to be a Type 1 grading but it can be seen in Figure 3.4 that although the particle grading was close to the specified grading envelope, it was too coarse for the most part. A Type 2 graded material, produced by the same operation, was much coarser and it can be seen in Figure 3.5 that the samples were consistently outside the limits.

In this recycling operation, run by Griffiths-McGee Demolition Co. Ltd. (1988), dirt, plaster and fines were removed by passing the material over a shaking screen. The aggregate was then deposited via a chute onto a conveyor to be transported to the jaw crusher. In this particular crushing operation the jaws were set to crush at 150mm-175mm. During crushing, most of the steel was dislodged from the rubble and removed by an electromagnet positioned over the conveyor belt which lead from the primary crusher. As the material was passed to the secondary crusher, aggregate which had already been crushed to the correct size was extracted and not processed further. The remainder of the material was passed to the secondary crusher where the jaw setting was 40mm-150mm. After secondary crushing the material was loaded for transportation or passed through a set of screens to achieve any grading of material required. It is clear from Figures 3.4 and 3.5 that the screening method used to obtain Type 1 and Type 2 gradings of demolition debris was not fully satisfactory. If recycled aggregates are to be used successfully in large quantities in the future, demolition contractors must be able to produce consistent gradings which are within the specification limits.

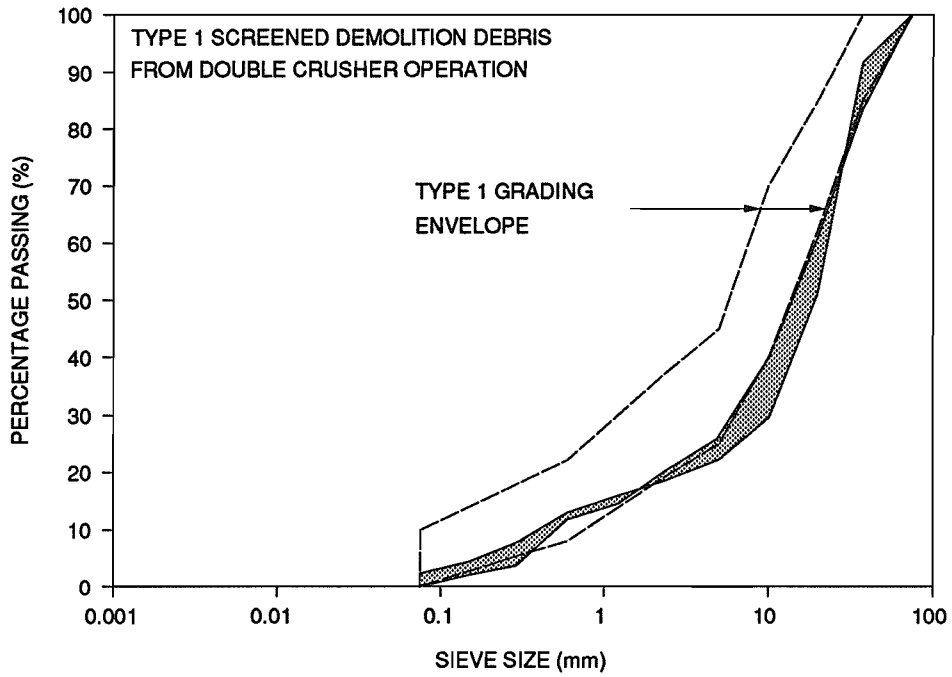


Figure 3.4 Type 1 screened demolition debris

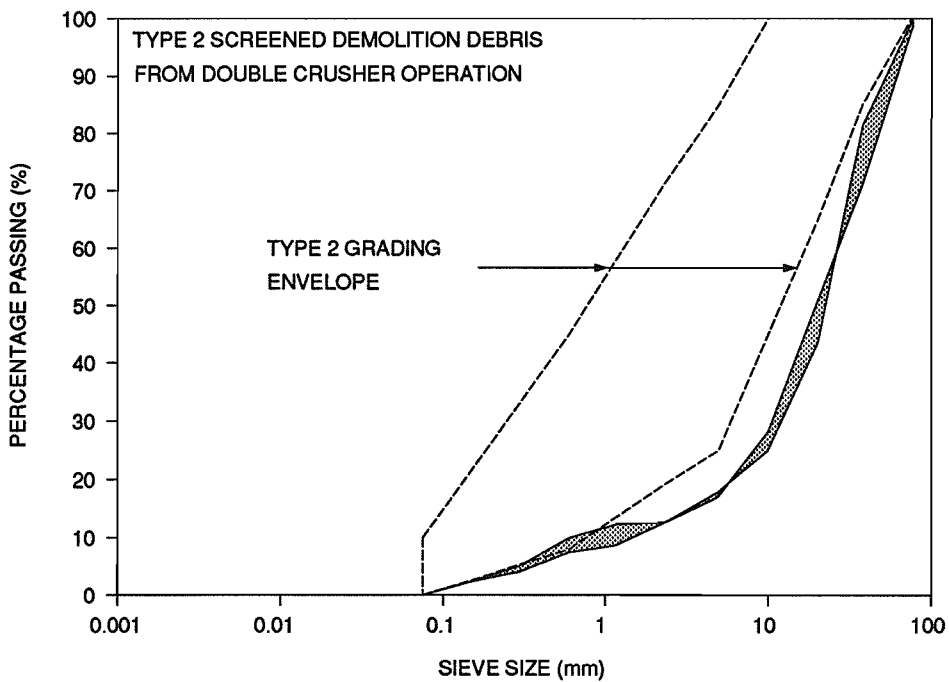


Figure 3.5 Type 2 screened demolition debris

The grading curves of Type 1 crushed concrete and Type 1 limestone are shown in Figure 3.6. The limestone, chosen as a conventional aggregate for use as a control in the sieve analysis tests, seemed slightly coarser than required and therefore fell outside the grading curve for the most part. The crushed concrete was produced by a single jaw crusher and had a better particle size range and an ideal Type 1 grading.

The particle grading of the demolition debris, used for the upper layer in the Portsmouth field trial, was generally within the Type 1 grading limits. This can be seen in Figure 3.7. The aggregate was processed in the same single crushing and sieving operation as the Type 2 graded demolition debris mentioned earlier (Hughes and Salvidge Ltd., 1988). However, variation of the amount of particles in the 6mm-10mm range changed the grading of the material to Type 1. The grading of this demolition debris compared favourably with the range of grading of limestone shown in Figure 3.8. In Figure 3.9, it can be seen that all demolition debris used in the lower layer in the Portsmouth field trial had a grading which was inside the capping material grading limits (Specification for Highway Works, 1986).

Type 1 and Type 2 graded material can be produced from both single and double crusher operations. However, the consistency of the grading depends on the crusher setting, wear and tear of the jaws and the screening process conducted after crushing. Some of the operations described earlier did not produce satisfactory gradings. It was also apparent that the production of limestone at a consistent Type 1 grading was difficult as limestone samples, tested for comparison purposes, had gradings which fell outside the Type 1 grading envelope.

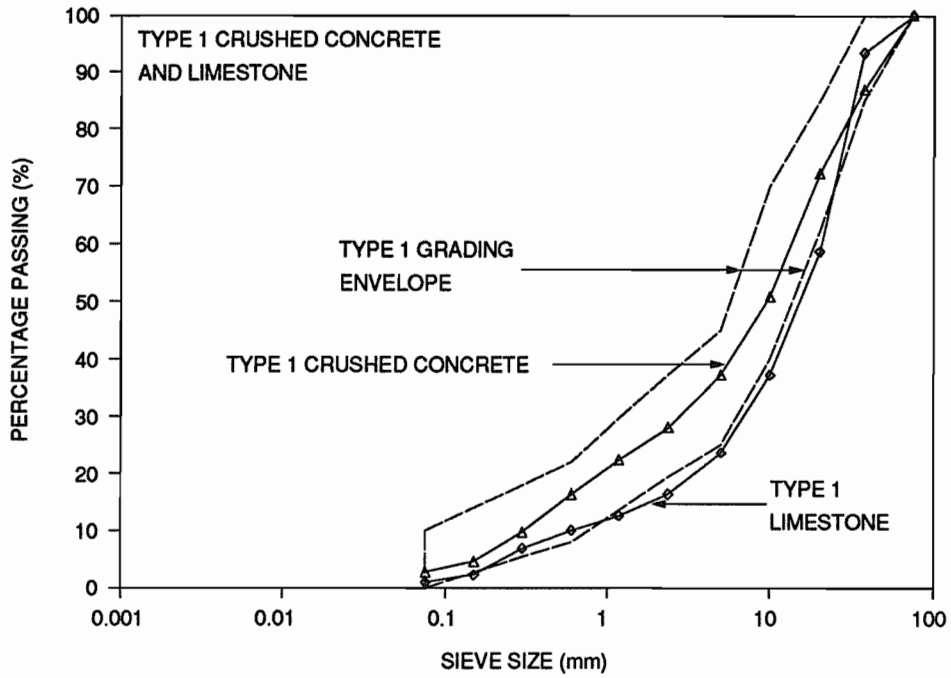


Figure 3.6 Type 1 limestone and crushed concrete

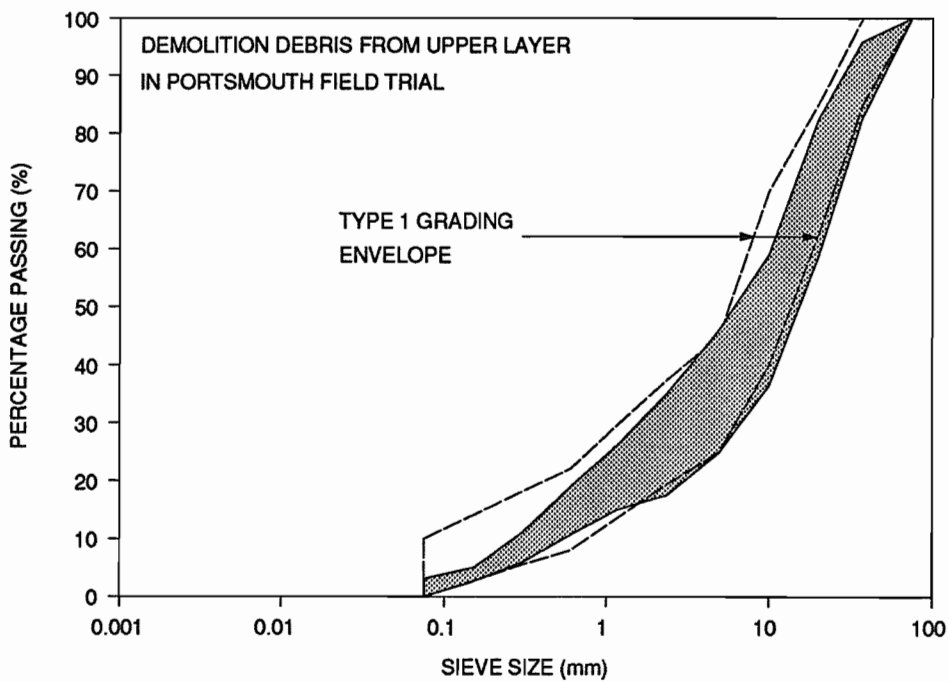


Figure 3.7 Demolition debris from the upper layer in the Portsmouth field trial

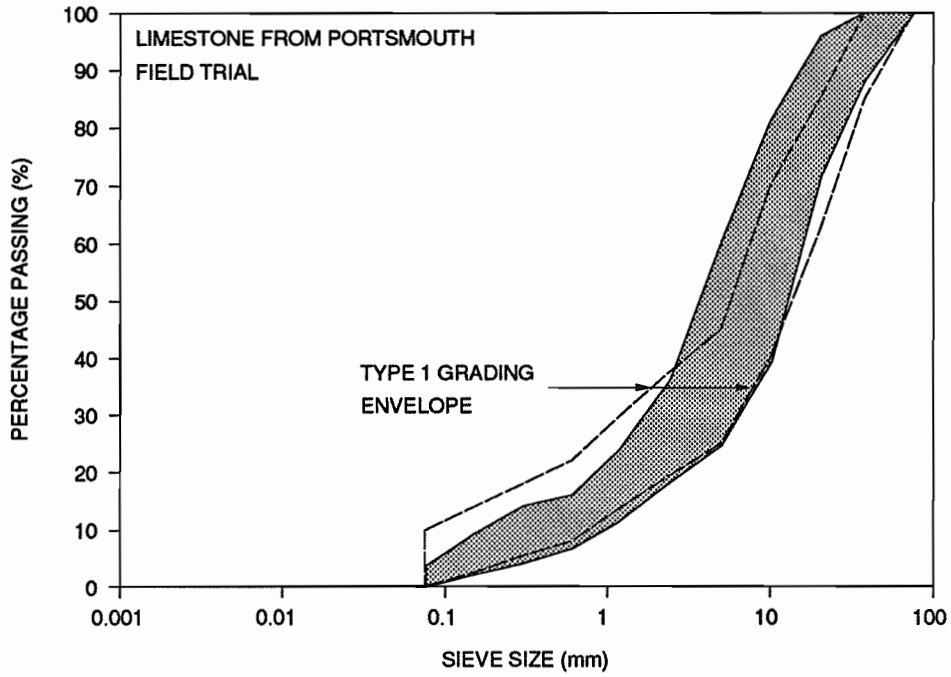


Figure 3.8 Limestone from the Portsmouth field trial

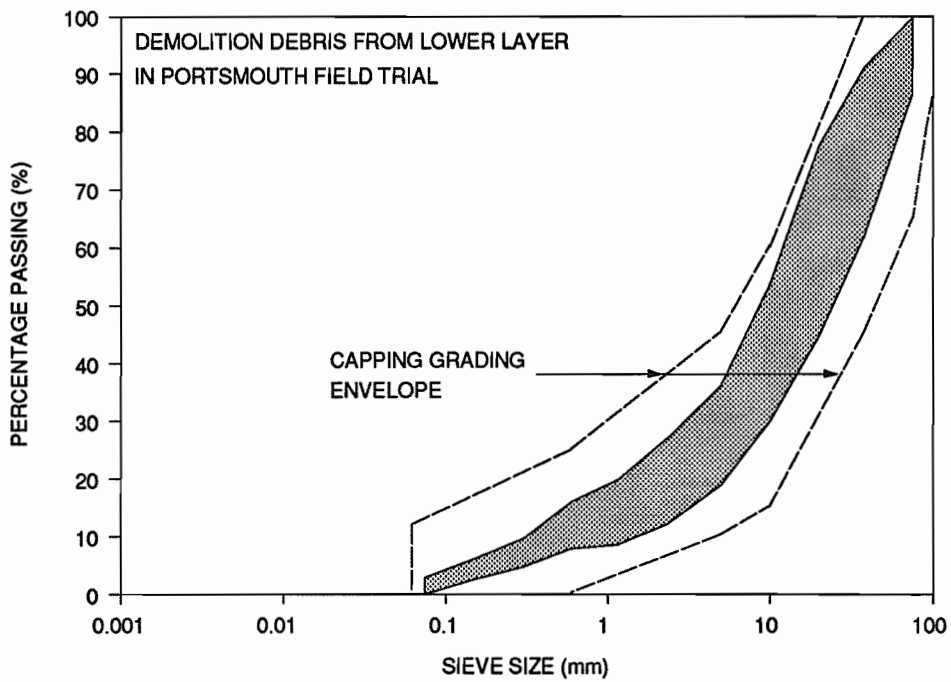


Figure 3.9 Demolition debris from the lower layer in the Portsmouth field trial

The particle gradings of crushed concrete, crushed masonry and a mixture of both from a Dutch double crusher operation were also examined. This recycling plant consisted of a primary jaw crusher and a secondary impact crusher and had better working conditions, a more organised layout and more scope for the production of a variety of recycled products than any plant in Britain at present. Both crushed brick and crushed rubble had gradings which were, for the most part, within the Type 1 grading envelope. This can be seen in Figure 3.10 where the particle grading of the Dutch brick falls almost centrally between the limits of the Type 1 grading envelope. The Dutch crushed concrete and crushed rubble did not comply with the Dutch specification grading limits (Rijkswaterstaat, 1978). This was surprising as the recycling plant was well equipped with screens and sorting equipment to combine various sizes of material to produce any grading required.

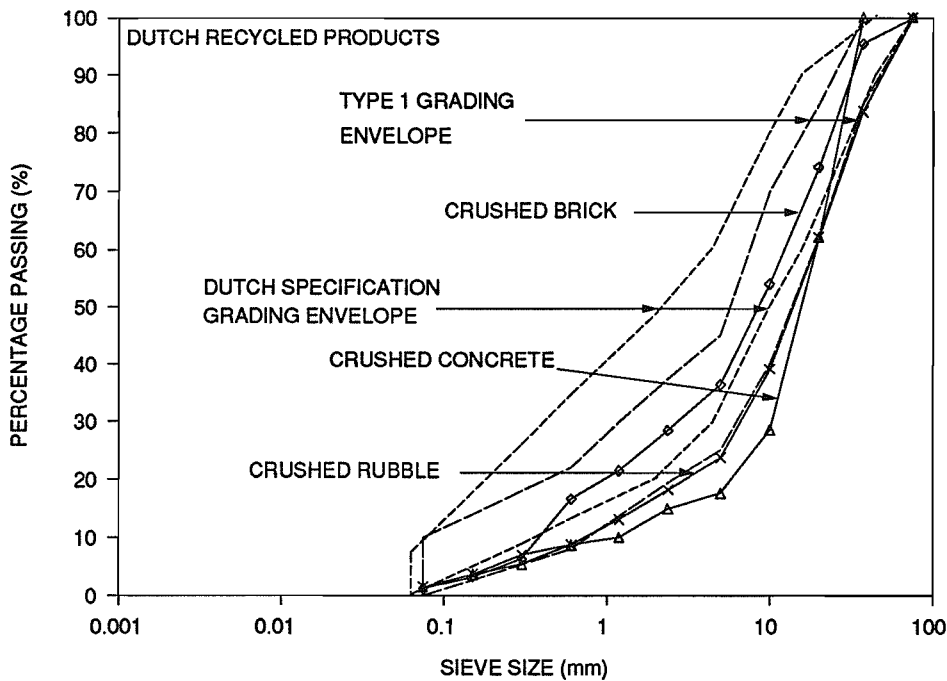


Figure 3.10 Dutch recycled products

3.4 Plasticity

According to the Specification for Highway Works (1986), aggregate to be used as Type 1 sub-base material should be non-plastic as defined by Test 3 of BS 1377 (1975) and Type 2 material should have a plasticity index of less than 6.

Demolition contractors express the view frequently that they assume recycled aggregate to be too plastic because of its brick content. All recycled aggregates tested during this research were found to be non-plastic, even a sample containing 11% brick. However, in comparison, a conventional limestone aggregate, certified as Type 1, had a plasticity index of 4. This material therefore should not be marketed as a Type 1 sub-base material. As the plasticity requirements for Type 2 sub-base material are less stringent, the limestone could be considered for use as a Type 2 material. It appears from the above results that, with respect to plasticity, recycled aggregate could be used as Type 1 or Type 2 sub-base material. The Dutch recycled products including crushed brick also proved to be non-plastic. There are no restrictions on plasticity in the Dutch specification, Rijkswaterstaat (1978). The samples of all recycled aggregates tested felt too gritty which suggested that the proportion of particles close to 0.425mm was quite large and the amount of clay sized particles present was too small to make the whole sample plastic.

The current Specification for Highway Works (1986) allows a maximum of 10% of a Type 1 sub-base material to pass the 0.075mm sieve, provided that the material passing the 0.425mm sieve is non-plastic. In previous editions of the specification, the fines passing the 0.075mm sieve were limited to a maximum of 2% although this percentage was permitted to rise to 10%, if the fines of this size were non-plastic. This relaxation, recommended by Dunn (1966), allowed the use of many crushed aggregates which prior to the relaxation had

been used successfully but did not meet the restrictions on plasticity. Dunn (1966) showed that maximum CBR values often occurred with a fines content of 4%-9%, even when the fines (<0.425mm) were plastic.

3.5 10% fines test

The 10% fines test was carried out in accordance with BS 812: part 3 (1975). The apparatus consisted of a cylinder with an internal diameter of 152mm into which a metal plunger of the same diameter fitted. The test was carried out using the following procedure which is detailed in BS 812: part 3 (1975). Aggregate in the 10mm-14mm fraction was added in thirds to the mould, each third being subjected to 25 strokes from a tamping rod. The plunger was placed on the aggregate so that it rested horizontally and the apparatus was placed between the plates of a compression testing machine. A force was applied to the plunger to cause a penetration of 20mm in about 10 minutes at as uniform a rate of penetration as possible. The maximum force achieved was noted and the percentage of the aggregate by mass passing the 2.36mm sieve after crushing was measured. The 10% fines value is the force required to produce 10% fines in the material and is calculated using the formula in BS 812: part 3 (1975) as follows:-

$$\text{The force required to produce } \frac{14(x)}{y+4} \text{ 10\% fines} \quad \dots \text{Eqn } 3.1$$

where x is the maximum force (kN) exerted on the plunger and
 y is the mean percentage fines (<2.36mm) from two tests at x kN force.

It can be seen in Table 3.1 that British and Dutch crushed concrete had 10% fines values of 89% and 51% that of limestone respectively, but all materials tested had values greater than 50kN and therefore complied with the sub-base requirements listed in the Specification for

Highway Works (1986). The Dutch recycled products had 10% fines values similar to those of British demolition debris. The crushed masonry appeared to be the weakest material although at present it is the best selling recycled product in the Netherlands.

There is a crushing requirement listed in the Dutch specification, Rijkswaterstaat (1978), which is based on a test used only in the Netherlands but similar to the 10% fines test. This crushing test and particle grading limits form the Dutch specification requirements for sub-base materials (Rijkswaterstaat, 1978). There exists a separate specification for recycled aggregates, Centre Row (1988), which is mainly concerned with limiting the quantities of contaminants.

MATERIAL	TEN PER CENT FINES (kN)
Thames Valley gravel	175
Limestone	168
British crushed concrete	150
British Demolition debris	72-105
Dutch crushed concrete	85
Dutch crushed masonry	70
Dutch crushed rubble	75

Table 3.1 Ten per cent fines values

3.6 Specific gravity

The specific gravity (G_s) of the materials obtained in this research is that which Head (1980) defines as the apparent specific gravity. It is the specific gravity of the aggregates as they occur naturally and is the ratio between the mass of dry solids and the mass of distilled water displaced by the dry aggregate particles. The water absorption (W_a) of an aggregate is the moisture content at which the pores in the aggregate are full of water.

Specific gravity and water absorption tests, as described in BS 812: part 2 (1975), were conducted on the 40mm-5mm fraction and on material less than 5mm. The test method for each fraction was similar but 1kg of the large aggregate was tested in a glass bowl whereas a 1 litre pycnometer was used to test 500g of the finer material. The aggregate was washed thoroughly and immersed in water overnight before testing.

The larger material was placed in the bowl with water and any trapped air was removed by gentle agitation. The bowl was filled until it was overflowing and a glass plate was slid across the top taking care to trap no air bubbles. The bowl was dried and weighed (mass B). The vessel was emptied, refilled with water, dried and again weighed (mass C). The aggregate was spread on a dry cloth and allowed to dry in air until no films of water were apparent on its surface. It was then weighed in this saturated and surface dry condition (mass A). The aggregate was dried in an oven at 105⁰C for 24 hours, cooled in an airtight container and again weighed (mass D).

The finer aggregate was placed in the pycnometer and water was added until it was level with the small hole in the lid. One finger was placed on the hole and the pycnometer was rolled on its side gently until air bubbles had accumulated in the water. The air was removed by placing the pycnometer upright and removing the finger from the hole. This procedure was conducted several times until all air was removed and the pycnometer was topped up again with water, dried and weighed (mass B). The remaining part of the test was conducted in a similar manner to that used on the large fraction but the finer material was dried using a warm current of air from a heater until it was in a free running condition. This state is defined in BS 812: part 2 (1975) as the condition in which no particles stick to the surface of a glass funnel, when some of the material is placed on its sloping surface.

Using the masses described above, the specific gravity can be calculated using the formula

$$G_s = \frac{D}{C - (B - D)} \quad \dots \text{Eqn } 3.2$$

and the formula for water absorption, expressed as a percentage, is

$$W_a = 100 \frac{(A - D)}{D} \quad \dots \text{Eqn } 3.3$$

Table 3.2 contains the range of results obtained from the specific gravity tests conducted on each material used in the Portsmouth field trial and the results for the materials which were used in the laboratory tests, described later in Chapters 4, 5 and 6, are also included. The water absorption values of the materials are also listed in Table 3.2.

MATERIAL	USE	SPECIFIC GRAVITY	WATER ABSORPTION (%)
Demolition debris	Upper layer in Portsmouth field trial	2.19-2.34	7.5-9.32
Limestone	Portsmouth field trial	2.55-2.67	0.5-1
Limestone	Laboratory testing	2.69	0.45
Demolition debris	Laboratory testing	2.56	8
Crushed concrete	Laboratory testing	2.58	3.76

Table 3.2 Specific gravity and water absorption of the aggregates

There appeared to be some difference between the specific gravity of the demolition debris used in the Portsmouth field trial and the demolition debris used for laboratory testing. This may be due to heavier constituents, such as stone, contained in the batch of material used for the laboratory tests. The water absorption of both batches of demolition debris was similar and it appeared to be quite high when compared with that of limestone. This was due to the porous nature of concrete and brick in the recycled aggregate.

3.7 Density tests on site

The locations at which density tests were conducted in the Portsmouth field trial are indicated in Figure 3.11 and reference should be made to Figure 3.1 for chainage positions. The lower capping layer of the road was first laid and compacted using a vibrating roller which had a mass per metre width of 3600kg. The upper capping layer was then placed and the compaction of this material can be seen in Plate 3.1. The method for measuring in situ density was based on the water replacement method for determining the density of rockfill or similar materials, which is described in Clause 27.8 of the Code of Practice for Site Investigations (BS 5930, 1981).



Plate 3.1 Compaction of the upper capping layer in the Portsmouth field trial

A 300mm diameter hole was dug to a depth equivalent to that of the top layer. The material was collected, stored in sealed bags and later weighed. The hole was lined with a polythene sheet and subsequently filled with water, the volume of which was known. Using the volume of water required to fill the hole and the mass of material collected, the dry density of the layer could be calculated. The same procedure was conducted on the lower layer. It is apparent from Figure 3.12 that demolition debris had a lower dry density than limestone, due mainly to its lower specific gravity, but the density of demolition debris was more consistent.

The dry density and moisture content of the aggregates used in the field trial are listed in Tables 3.3, 3.4 and 3.5. The demolition debris used in the upper layer had a dry density of 77% that of the limestone. This lower density was partly due to the difference in specific gravity of the materials. The demolition debris had a specific gravity of 2.19-2.34 which was 82%-92% that of the limestone.

To examine the particle packing of the materials, the results are best compared in terms of the proportion of volume occupied by solids (V_s) which is defined in BS 5835 (1980) (the compactibility test for graded aggregates) as

$$V_s = \frac{\rho_d}{10G_s} \quad \dots Eqn \quad 3.4$$

where ρ_d is the dry density expressed in kg/m^3 and

G_s is the specific gravity.

It can be seen in Table 3.4 that the demolition debris in the upper layer filled 79.9% of the volume on average whereas 90.3% of the volume of the limestone layer was filled with limestone particles (Table 3.5). Therefore the limestone particles were packed more closely together than those of demolition debris.

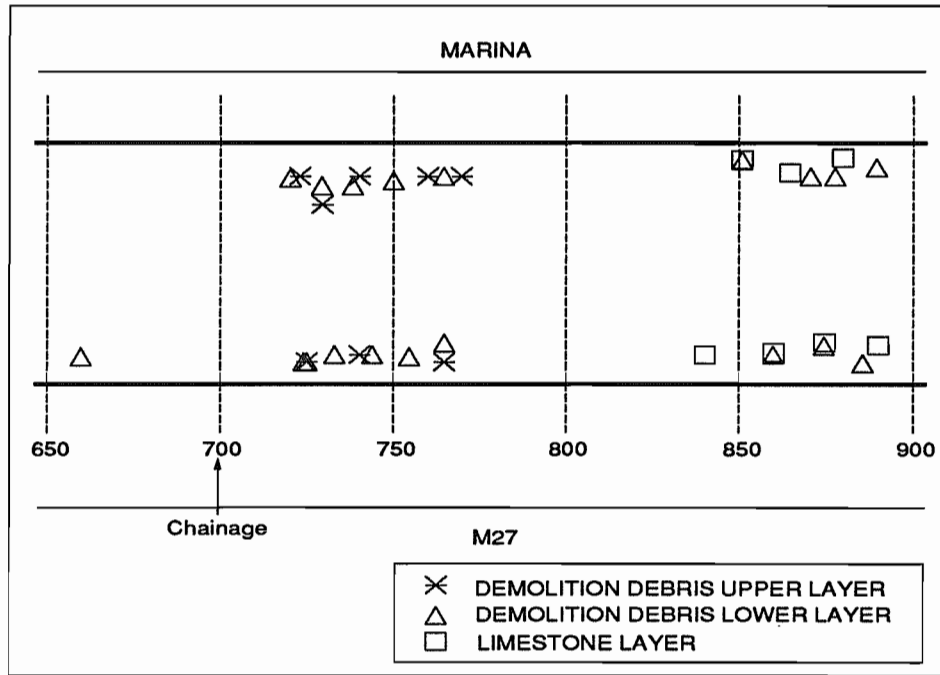


Figure 3.11 Locations of in situ density tests

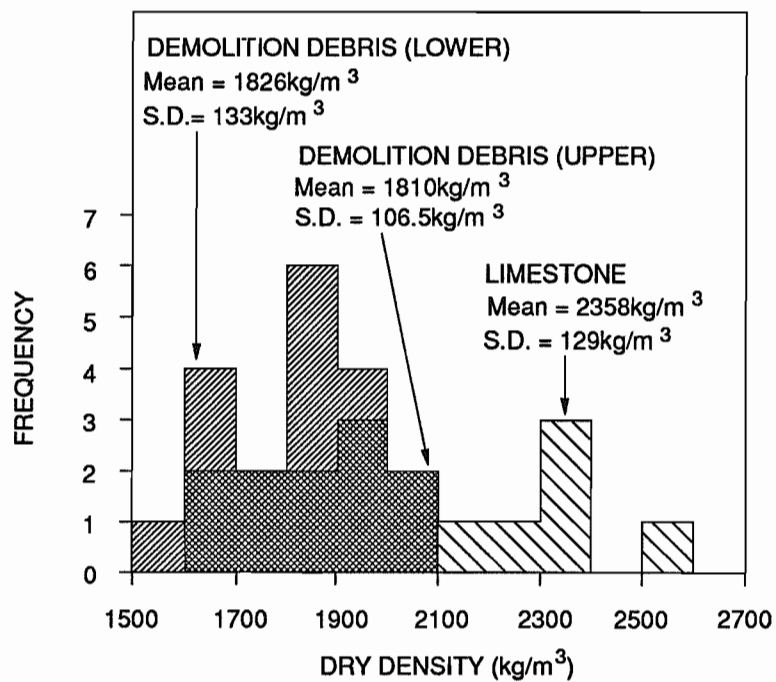


Figure 3.12 Dry densities of Portsmouth field trial materials

DEMOLITION DEBRIS LOWER LAYER					
LOCATION	CHAINAGE (m)	DRY DENSITY (kg/m ³)	V _s (%)	MOISTURE CONTENT (%)	FREE WATER CONTENT (%)
M27 SIDE	660	1850	81.7	8.2	-0.21
	725	1632	72	5.5	-2.91
	734	1908	84.2	9.3	0.89
	745	1886	83.3	5.7	-2.71
	755	1938	85.6	6	-2.41
	765	1583	69.9	5.5	-2.91
	726	1809	79.9	9.2	0.79
	860	1890	83.4	6.9	-1.51
	886	1636	72.3	8.2	-0.21
	875	1889	83.4	3.7	-4.71
MARINA SIDE	721	1861	82.2	9	0.59
	739	1927	85.1	8.5	0.09
	765	1739	76.8	7.5	-0.91
	730	1774	78.3	8.4	-0.01
	750	1694	74.8	8.6	-0.19
	851	2058	90.9	6.2	-2.21
	871	2041	90.1	5.7	-2.71
	878	1667	73.6	8	-0.41
890	1914	84.5	5.5	-2.91	
AVERAGE		1826	80.6	7.14	-1.27
STANDARD DEVIATION		133	5.88	1.58	1.578

Table 3.3 Conditions of the demolition debris lower layer in the Portsmouth field trial

Note: M27 side and marina side refer to the location of the test positions on the road (see Figure 3.11)

The limestone was placed at a moisture content of 0.96%-4.1% whereas the demolition debris used in the upper layer had a moisture content of 8.5%-13.3% compared with 3.7%-9.3% in the lower layer. It can be seen in Tables 3.3, 3.4 and 3.5 that the deviation from the average moisture content was between 1% and 1.6% for the three materials. The free water content of the samples was compared i.e. the effect of water absorption was removed. Free water is the active part of the moisture content during compaction. Limestone was found to have

a free water content of 0.06%-3.6% compared with 0.09%-4.89% for the demolition debris upper layer. Therefore the free water contents of limestone and demolition debris were quite similar.

A negative value of free water content means that the material was placed at a moisture content lower than its water absorption value. It can be seen from Table 3.3 that demolition debris in the lower layer was placed in relatively dry conditions. In Chapter 4, the peak dry density and optimum moisture content for limestone obtained in the laboratory are found to be 2320kg/m³ and 3.5%. It is clear from Table 3.5 that generally a higher density was obtained on site than in the laboratory at a moisture content lower than the laboratory optimum which suggests that site compaction was more effective than compaction in the laboratory. A comparison is made between in situ and laboratory density in Chapter 8.

DEMOLITION DEBRIS UPPER LAYER					
LOCATION	CHAINAGE (m)	DRY DENSITY (kg/m ³)	V _s (%)	MOISTURE CONTENT (%)	FREE WATER CONTENT (%)
M27 SIDE	726	1721	76	13.3	4.89
	740	1919	84.7	8.5	0.09
	765	1606	70.9	11.7	3.29
MARINA SIDE	722	1842	81.3	9	0.59
	730	1739	76.8	10.3	1.89
	740	1817	80.2	12	3.59
	760	1900	83.9	11	2.59
	770	1933	85.3	9.5	1.09
AVERAGE		1810	79.9	10.66	2.25
STANDARD DEVIATION		106.5	4.69	1.535	1.53

Table 3.4 Conditions of the demolition debris upper layer in the Portsmouth field trial

LIMESTONE LAYER					
LOCATION	CHAINAGE (m)	DRY DENSITY (kg/m ³)	V _s (%)	MOISTURE CONTENT (%)	FREE WATER CONTENT (%)
M27 SIDE	840	2520	96.5	1.6	1.1
	860	2139	81.95	1.9	1.4
	875	2394	91.72	1.4	0.9
	890	2355	90.23	0.96	0.06
MARINA SIDE	851	2234	85.6	3.2	2.7
	865	2519	96.5	4.1	3.6
	880	2344	89.8	1.6	1.1
AVERAGE		2358	90.3	2.1	1.55
STANDARD DEVIATION		129	4.94	1.04	1.1

Table 3.5 Conditions of the limestone layer in the Portsmouth field trial

3.8 Impurities

Kasai (1985) suggested that particles of demolition debris larger than 8mm should be examined for impurities by visual inspection and weighing. When the demolition debris used in this study was examined, the amount of brick and block present was found to be 17.5% by mass whereas the gypsum content was 2.7%. Steel and wood were also present in quantities of 1.2% and 0.25% by mass respectively. The volume of wood contained in the material was 2.5% assuming that the wood had a specific gravity of 0.5. This was below the suggested maximum level of 4% quoted by the Building Contractors Society of Japan (1981) but was higher than the maximum level of 0.1% by mass quoted in the Dutch specification, Centre Row (1988). It is likely therefore that recycling operations in Britain will need to employ aquamators, similar to those in operation in the Netherlands, to ensure low levels of lightweight impurities.

3.9 Discussion

While conducting the standard tests on the aggregates, it appeared that limestone was just as likely not to comply with the sub-base requirements in the Specification for Highway Works (1986) as recycled aggregate. When recycled aggregate is to be used for a particular purpose, the client usually requires that it undergo the full series of compliance tests. However, when a conventional aggregate such as limestone is to be used, the only limits to which it must conform are those for particle grading. It is suggested that all aggregates be tested in a similar manner because it was found that the Type 1 certified limestone, examined in this research, did not comply with the Type 1 requirements for grading and plasticity.

The plasticity test (BS 1377, 1975) is a test which is very operator dependent and the reproduction of results is difficult, particularly at low values of plasticity. Due to the problems associated with this test, some scope should be included in the Specification for Highway Works (1986) for the variation in plasticity results which are likely to exist in practice. Alternatively, another test should be considered which would take into account the effect on plasticity of large particles in the aggregate. It was agreed at the Symposium on Unbound Aggregates in Roads (1989) that the plasticity test described in BS 1377 (1975) was satisfactory for the testing of soils but it was suggested that a new test should be devised for testing aggregates. Highway engineers would like to see more standard tests conducted on aggregate on site rather than in the laboratory, due to the difficulty of calibrating laboratory tests with site conditions.

3.10 Conclusions

- (i) It appears to be difficult to obtain consistent gradings of both conventional and recycled aggregates. The wear and tear on the crusher jaws is probably the main cause of the variations in grading of the recycled materials.

- (ii) All recycled materials tested were non-plastic unlike a Type 1 certified limestone which had a plasticity index of 4. Some consideration should be given to the development of a new test for the determination of the plasticity of aggregates.
- (iii) The specific gravity of limestone was 2.69 compared with 2.58 and 2.56 for crushed concrete and demolition debris respectively. The water absorption values were 0.45% for limestone, 8% for demolition debris and 3.76% for crushed concrete. The high value for demolition debris was attributed to the porosity of the mortar and brick in the material.
- (iv) The quantity of wood present in the demolition debris was less than the maximum contaminant level suggested by the Building Contractors Society of Japan (1981) but higher than the maximum level stipulated in the Dutch specification (Centre Row, 1988).
- (v) It appears that site compaction is more effective than compaction in the laboratory. This comparison is discussed more fully in Chapter 8.
- (vi) Both natural and secondary aggregates should be made to undergo the same series of compliance tests because it was found that a Type 1 certified limestone did not conform to some of the sub-base requirements. It is likely that the use of recycled aggregates in construction would increase if a fair testing system existed.

CHAPTER 4

COMPACTION AND CALIFORNIA BEARING RATIO TESTS

4.1 Compaction

4.1.1 Introduction

When aggregate is used as road sub-base material or fill, one of the most important influences on its behaviour is density. Deformation, shear strength, frost susceptibility and permeability are greatly influenced by the density at which the material is first placed and generally a high density improves the performance of a sub-base or fill. Increasing the density of a granular material is achieved by compaction which involves reducing the air voids, without reducing the moisture content (Head, 1980). Air voids cannot be eliminated altogether by compaction but they can generally be reduced to 5%. This is necessary so that ingress of water after compaction is reduced. When many air voids exist in a material after compaction, swelling may occur if the moisture content increases after placement (Cobbe and Threadgold, 1988). Hill (1985) agrees that obtaining minimum air voids at the time of placement may be satisfactory but states that compacted aggregates are sensitive to moisture change and voids soon become filled with water which does not drain away easily.

The requirement in the Specification for Highway Works (1986) for compaction of a Type 1 sub-base material is that the material should be compacted without drying out or segregation. If an aggregate is to be used as a Type 2 sub-base material, it should be compacted at a moisture content within the range 1% above to 2% below the optimum moisture content. This moisture content is determined by conducting the compactibility test for aggregates, described in BS 5835 (1980), on the material.

The two factors which have the greatest effect on density are moisture content and the compactive effort exerted on the material. To examine the effect of moisture content, a series of tests is normally conducted using a standardised test i.e. with a constant compactive effort, for a range of moisture content.

As the moisture content of a fine grained soil is increased, the dry density (ρ_d) also increases until it reaches a point of peak density ($\rho_{d,peak}$). The moisture content at which this occurs is termed the optimum moisture content (OMC). When the OMC has been reached and the moisture content is increased further, the excess water begins to push the particles apart so that ρ_d is reduced (Head, 1980). Cohesionless soils do not respond to variations in moisture content in the same manner as fine grained soils. A peak density is reached but on the dry side of OMC the curve is quite flat, particularly for well graded materials, and it is not uncommon for a second peak to be recorded at a low moisture content (Lee, White and Ingles, 1983). The two peaks on the dry density/moisture content curve are normally separated by a point of low density. Lambe and Whitman (1979) concluded that this point of low density, obtained at a low moisture content, is due to capillary forces resisting rearrangement of the particles.

Lambe and Whitman (1979) noted that the term dry density is usually used as another expression for dry unit weight. They are, however, not equal because density is actually $1/g$ times unit weight where g is the gravitational constant.

4.1.2 Compaction apparatus and test procedures

Compaction tests were carried out on limestone and demolition debris following the procedure of the compactibility test for aggregates, detailed in BS 5835 (1980), using the apparatus designed for this test in the Pavement Materials and Construction Division of the Transport and Road Research Laboratory. Pike and Acott (1975) designed the test because

the vibrating hammer method, described as Test 14 in BS 1377 (1975), which is normally used for compaction tests on granular soils, could not produce the compactive effort required to reproduce the density of aggregate likely to be obtained in the field. Compaction on site has become more effective. The BS 5835 (1980) test involves compacting aggregate in a mould with a vibrating hammer hung from a frame under a standard surcharge. Pike and Acott (1975) found that this test method was capable of producing densities similar to those obtained in the field and as the test was not dependent on the operator, the results were more repeatable than for compaction tests used previously.

Samples of aggregate at a range of moisture content were tested using the following procedure, which is covered in detail by BS 5835 (1980), to determine the relationship between moisture content and dry density. All particles larger than 37.5mm were removed and the aggregates were oven-dried. Each material was then divided into portions of between 2.4kg and 2.6kg. Three of these portions were mixed at each target moisture content and left to stand overnight in sealed containers.

The 150mm diameter mould, in which the portions were compacted, is illustrated in Figure 4.1. The depth of a compacted sample was approximately 70mm. The mould was connected to a base plate which contained recesses to allow for the collection of excess water expelled from the sample during compaction. At the bottom of the mould there was a filter assembly, which is also shown in Figure 4.1, consisting of two perforated plates and filter fibre to allow drainage of water from the samples. The anvil (see Figure 4.1), which was placed on the aggregate before compaction, fitted the mould snugly and had a rounded protrusion on its upper face on which the hammer tool was placed during compaction. In the centre of this protrusion was a small hole for locating the depth gauge when measuring the height of a sample.

To obtain accurate results, it was necessary to measure precisely the height of the sample after compaction. Before the aggregate was placed in the mould, the distance between the bottom of the mould and its top was measured using the following procedure (BS 5835, 1980). Two filter papers were placed in the bottom of the mould and the anvil was inserted. The vibrating hammer was applied to the anvil for 5 seconds and the distance between the hole in the anvil and the top of the mould was measured to 0.1mm. The apparatus was dismantled three times and this procedure was repeated. The average of the three depth readings was calculated and this average was considered to be the datum. The mould was reassembled and one filter paper was placed at the bottom.

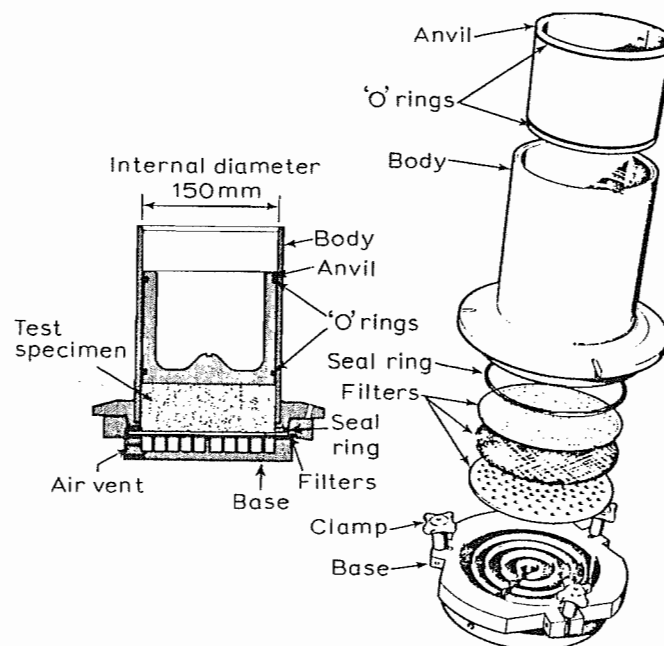


Figure 4.1 Mould and anvil for the compactibility test (after Head, 1980)

One of the portions of aggregate was placed in the mould and roughly levelled. A filter paper was placed on top of the sample followed by the anvil. The whole mould assembly

was placed under the loading frame inside a noise reducing cabinet (Plate 4.1). The hammer tool was placed on the anvil followed by the vibrating hammer whose top was connected to the loading frame. The surcharge weight required to produce a steady downward force of 400N on the sample was hung from the end of the lever arm of the frame, as illustrated in Plate 4.1. The door of the noise reducing cabinet was closed and the vibrating hammer was operated for 180 seconds. After compaction, the mould assembly was removed from the frame taking care not to disturb the anvil and the distance between the anvil and the top of the mould was measured to an accuracy of 0.1mm. The height of the sample was found by subtracting the depth reading after compaction from the datum. The aggregate was extracted from the mould, weighed and dried at 105⁰C until it reached constant mass. The dry density was calculated by dividing the mass of dried aggregate by the volume of the sample. The calculation of moisture content was the same as that used in Test 1 of BS 1377 (1975). The whole process was repeated on the remaining portions. BS 5835 (1980) stated that the results at one moisture content should be averaged but in this work the results from all tests were plotted to form the dry density/moisture content relationship for each material.

The main disadvantage of the test is that the size of the mould limits the maximum size of particle to be tested to 37.5mm although the Specification for Highway Works (1986) allows 15% of particles in an aggregate for use as road sub-base to be larger than 37.5mm.

When the limestone and crushed concrete aggregates were obtained from the suppliers they contained very few particles larger than 37.5mm. However, about 10% of the demolition debris particles were too large to be tested by the BS 5835 (1980) test. This suggested that the compaction test might not simulate the compaction of demolition debris in the field due to the difference in particle grading. To investigate whether the density would change if the grading was altered, the following apparatus and test were devised.

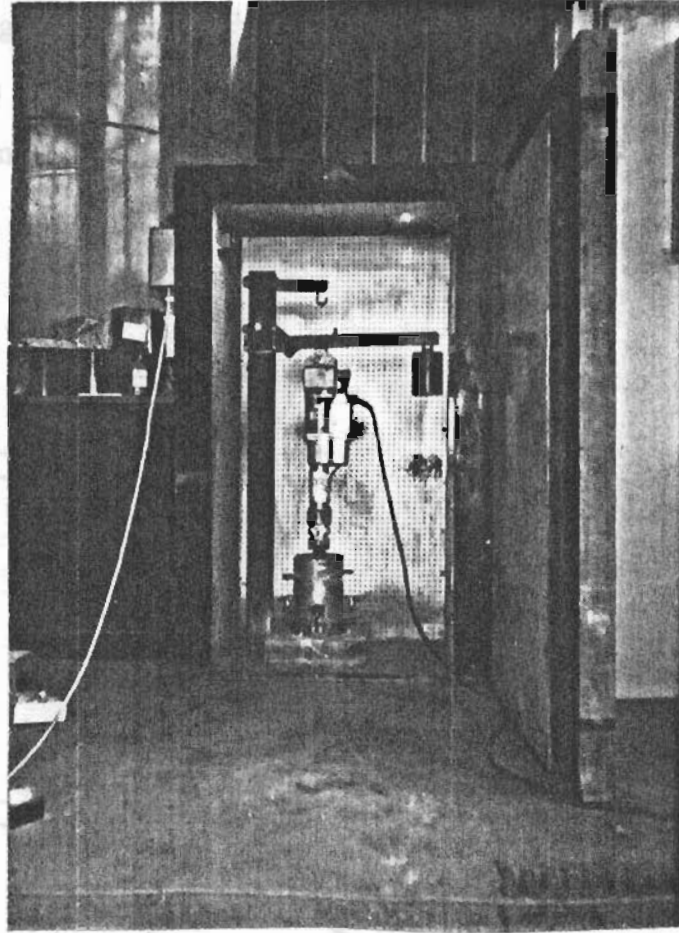


Plate 4.1 BS 5835 (1980) compaction test apparatus located at TRRL

A steel mould of 300mm internal diameter was used with 5mm diameter holes drilled in its end to allow excess water to drain away during compaction. A 3.2mm thick layer of filter fibre, known as Vyon, sandwiched between two perforated plates was used as the filter assembly and was positioned at the bottom of the mould supported on a 20 mm thick spiral spacer so that excess water could drain from the samples. The mould assembly and plate are shown in Figure 4.2. The filter assembly was temporarily sealed to the edge of the mould using silicon sealant. Two filter papers were placed on the upper filter plate and the

steel plate (see Figure 4.2) was placed on top. The distance between the plate and the top of the mould was measured at twelve positions around the perimeter of the mould. The average of these measurements was used as a datum.

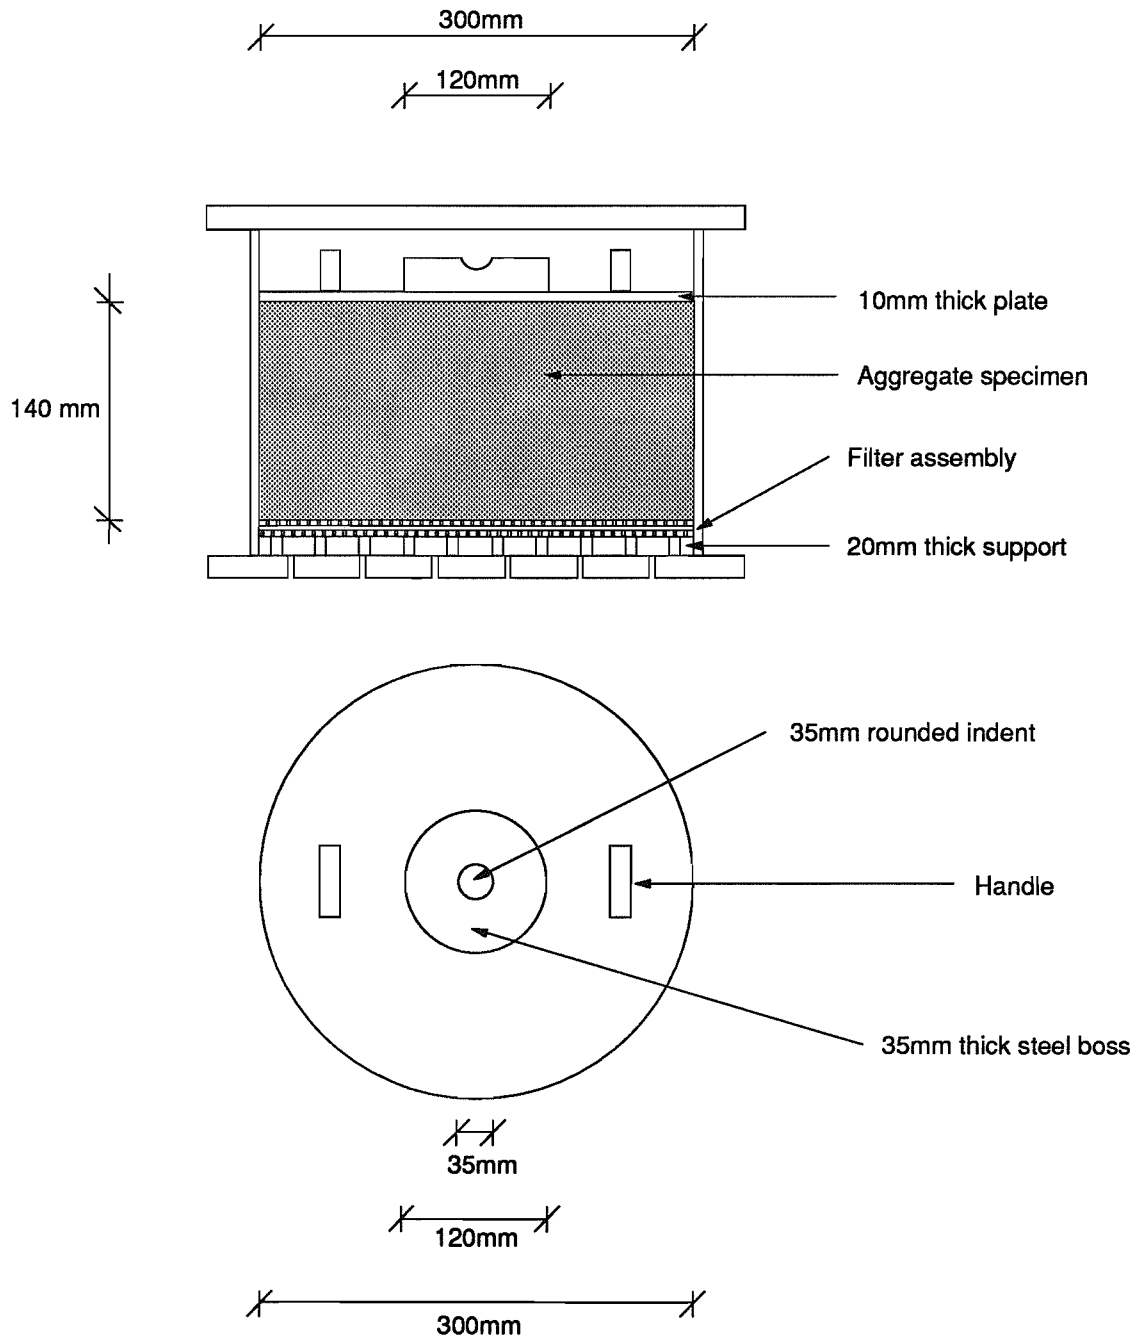


Figure 4.2 300mm diameter compaction mould and plate for large apparatus

The maximum particle size which was tested in this apparatus was 75mm. It was considered that the height of a sample to be compacted in the 300mm diameter mould should be 140mm to maintain the same maximum particle size/height of sample ratio which was used in the BS 5835 test (1980). The volume of a sample in the large mould was eight times larger than that in the BS 5835 (1980) apparatus and therefore 20kg of material was required for each test.

During construction of the apparatus, a large steel boss of 120mm in diameter and of thickness 25mm was welded to the upper surface of a 10mm thick plate (see Figure 4.2). A rounded indent was made in the centre of the boss into which a modified vibrating hammer tool fitted. Originally the tool had been connected by a weld to the plate but this was not very satisfactory due to the following reason. The vibrating hammer was hand held during compaction and it was difficult to keep the hammer central at all times. Consequently, the welded joint snapped due to bending stresses and the vibrations produced by the hammer. It was decided therefore to allow the tool free movement within the indentation and this proved to be a better arrangement.

One of the tools supplied with the vibrating hammer was modified for the compaction tests. The shaped end of the tool was cut off and the raw edge was rounded so that it would fit in the indentation in the boss. After a few tests had been completed it was found that the end of the tool had mushroomed quite badly. Generally tools for vibrating hammers are heat treated during manufacture to harden the surface but not the inner steel. Therefore when the tool was cut the softer steel was exposed and consequently was damaged by the stress placed on the hammer. To prevent further deterioration of the tool, advice on heat treatment was sought from the supplier of the vibrating hammer (Kango Tools Ltd., 1989) and following this advice the tool was heated in a furnace to 800⁰C for five minutes and then cooled rapidly in water to harden the steel. It was then heated again to 260⁰C and cooled in air to remove

some of the brittleness caused by the first stage of heat treatment. After this procedure had been conducted, deterioration of the tool during testing was slower but the tool was not fully protected against damage and had to be reshaped at intervals during the test series.

All samples of aggregate were mixed at the target moisture contents on the day before test to ensure uniformity of the moisture content throughout the sample. In the BS 5835 test (1980), the whole portion of aggregate was added to the mould and compacted in one layer. However, the only hammer on the market which was considered suitable for the purpose of compaction in the large apparatus was the same hammer as that used in the BS 5835 test (1980) but it did not have the capacity to compact 20kg of material in one layer. Therefore the 20kg sample of aggregate was divided into three and one of these portions was placed in the mould on a filter paper and another filter paper was placed on top followed by the metal plate.

The tool was inserted and clamped in the vibrating hammer which was hand held during the three minute vibration time allotted to each layer in the compaction tests. The vibration time was decided upon after a series of trial tests. Increasing the compaction time per layer beyond three minutes did not change the density but a compaction time less than this was insufficient to produce a sample of constant volume. After compaction the hammer and tool were removed and depth readings from the top of the mould to the top of the plate were taken. The sample and mould were weighed so that the density could be calculated. The material was removed from the mould and weighed. A sample of 5kg was dried at 105°C for 24 hours and weighed to determine the moisture content. From the depth measurements, the mass of wet material and the moisture content, the bulk density (ρ_b , defined as the mass of wet material divided by the volume of the sample) and the dry density (ρ_d) could be calculated using the same method as described in the BS 5835 test (1980).

4.1.3 Results

Both compaction test methods were conducted on samples of limestone and demolition debris containing particles smaller than 37.5mm, to assess the ability of the large apparatus to reproduce the densities obtained using the BS 5835 test (1980). The results for limestone are shown in Figure 4.3 where the curves for both test methods appear to be similar except at a moisture content of 0% where the samples in the large apparatus achieved higher densities. This difference in density was caused by the friction forces which developed between the dry aggregate and the sides of the mould. These forces were likely to have greater influence in the smaller mould making the samples more difficult to compact. When moisture was added to the aggregate, the friction forces were overcome more easily and consequently the densities obtained in both apparatus at moisture contents greater than 1% were similar. Some difference existed between the optimum moisture contents achieved in the two tests where the OMC achieved in the BS 5835 test (1980) was 3.5% and that attained in the large test was 4.5%.

The results for demolition debris are shown in Figure 4.4 along with results of tests conducted in the large apparatus on demolition debris containing particles larger than 37.5mm. At low moisture contents the effect of friction on the sides of the moulds is again evident. There appears to be little difference in the results for the two gradings of demolition debris. It can be concluded therefore that the removal of particles greater than 37.5mm did not affect the density of the aggregate significantly.

Compaction tests were conducted on crushed concrete in the large apparatus and as this test produced similar densities to those obtained in the BS 5835 test (1980) for limestone and demolition debris, it was decided that testing in the large apparatus would be adequate for

the determination of the dry density/moisture content relationship of crushed concrete. The results for crushed concrete are shown in Figure 4.5 where the relationship can be seen to be quite well defined.

In Figures 4.3, 4.4 and 4.5, the 0%, 5% and 10% air voids lines were plotted using the specific gravity values of 2.69, 2.56 and 2.58 for limestone, demolition debris and crushed concrete respectively which were listed in Chapter 3. It can be seen in Figures 4.4 and 4.5 that some of the densities obtained in the compaction tests corresponded with 0% air voids and in a few cases fell to the right of the 0% air voids line. Head (1980) stated that it is impossible for this to happen but there are two likely reasons why it occurred in these tests.

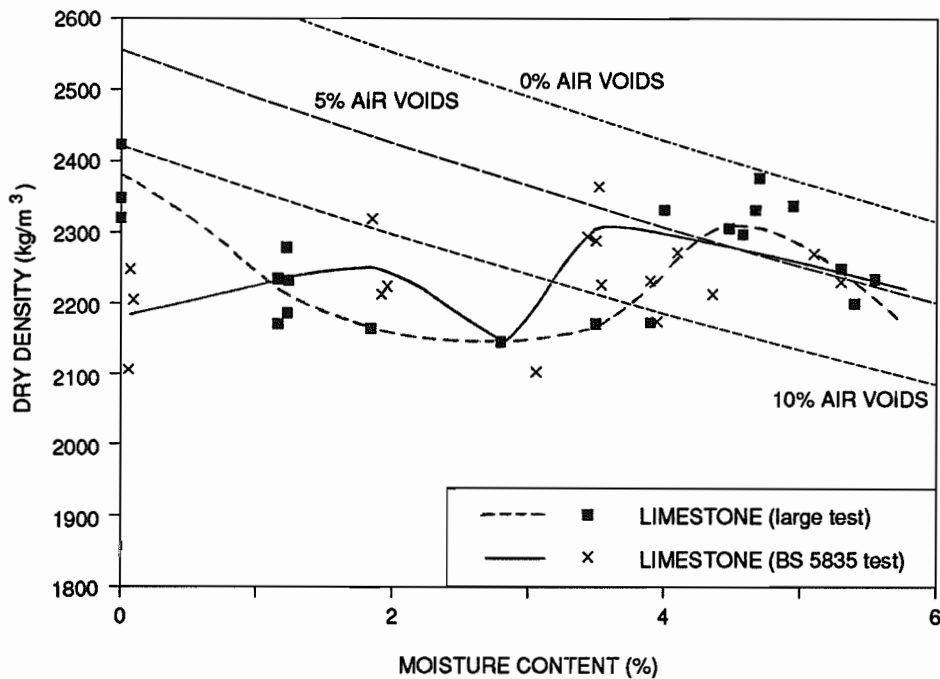


Figure 4.3 Relationship between moisture content and dry density for limestone

The curves in Figures 4.3 and 4.5 cannot be justified by the data alone but have been drawn in a tentative manner in light of previous knowledge quoted by Lee, Wight and Ingles (1983). This also applies to Figure 4.10 which is presented later.

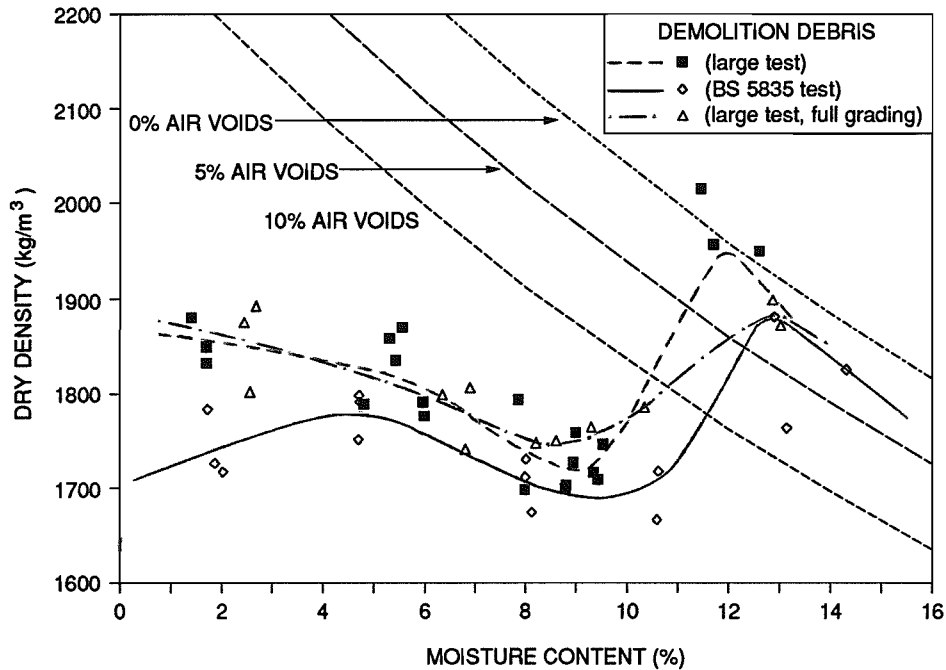


Figure 4.4 Relationship between moisture content and dry density for demolition debris

First, the measurements of specific gravity may not have been accurate due to the variation in content of the recycled materials and secondly, the measurement of moisture content may not have been exact. The tests used to determine specific gravity were carried out several times because there appeared to be variations in the results, particularly for demolition debris which contained assorted materials. These materials would also have had various water absorption values. In a demolition debris sample the constituents would not have been dispersed equally throughout the material. Therefore one sample of aggregate when dried could be found to have had a higher moisture content if a large proportion of the material had the ability to absorb a large quantity of water.

To examine the amount of crushing caused by compaction, particle grading tests on the aggregates were conducted before and after the compaction tests and the results are shown in Figure 4.6 for limestone, Figure 4.7 for demolition debris of particle size less than 37.5mm, Figure 4.8 for demolition debris, as obtained from site, and in Figure 4.9 for crushed concrete.

It can be seen that little crushing of limestone particles occurred but some crushing of demolition debris and crushed concrete particles was evident and may have contributed to the high densities in the dry density/moisture content relationships. The OMC and $\rho_{d,peak}$ obtained from the compaction tests are listed in Table 4.1 for all materials.

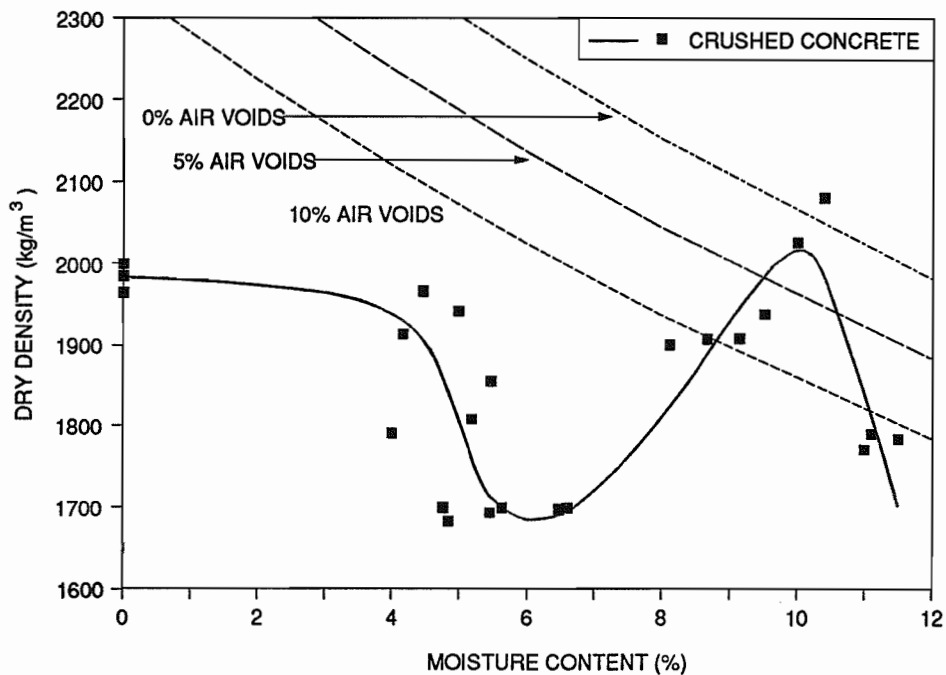


Figure 4.5 Relationship between moisture content and dry density for crushed concrete

By comparing the results in Table 4.1 for the two test methods, it can be seen that both series of tests on limestone gave similar results but the series on demolition debris (< 37.5mm), conducted in the large apparatus, produced a relatively high $\rho_{d,peak}$. This density value, however, corresponded to 0% air voids and might not have been representative due to variations in the specific gravity of demolition debris and moisture content measurement. It can be seen in Table 4.1 that the free water available at peak density for the three materials was in the range 3% - 5.5%. Free water is the part of the moisture content which plays an active part in compaction and for the three materials appeared to be quite similar.

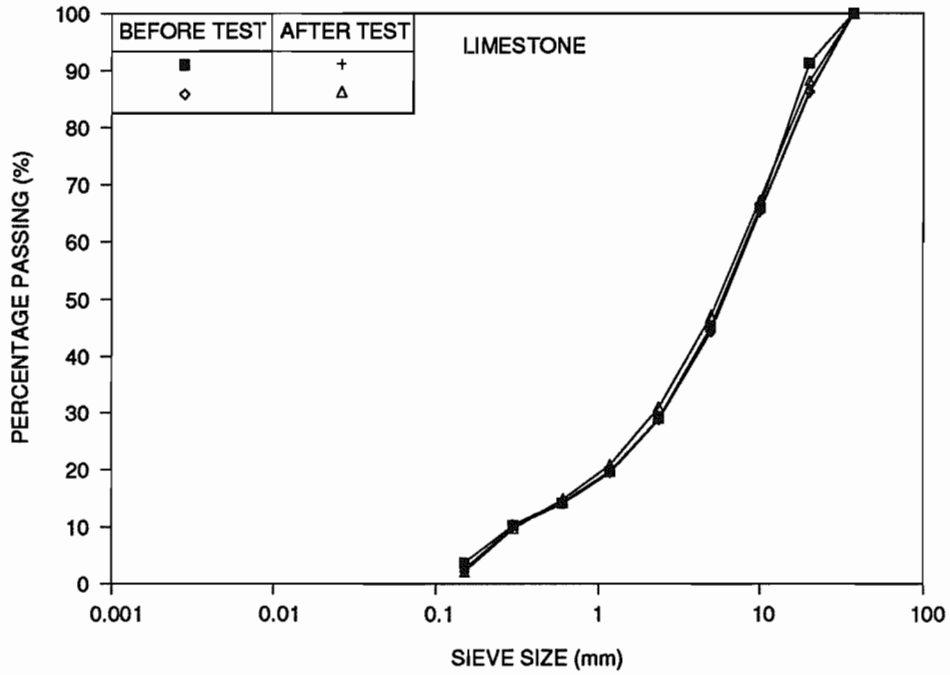


Figure 4.6 Particle gradings of limestone

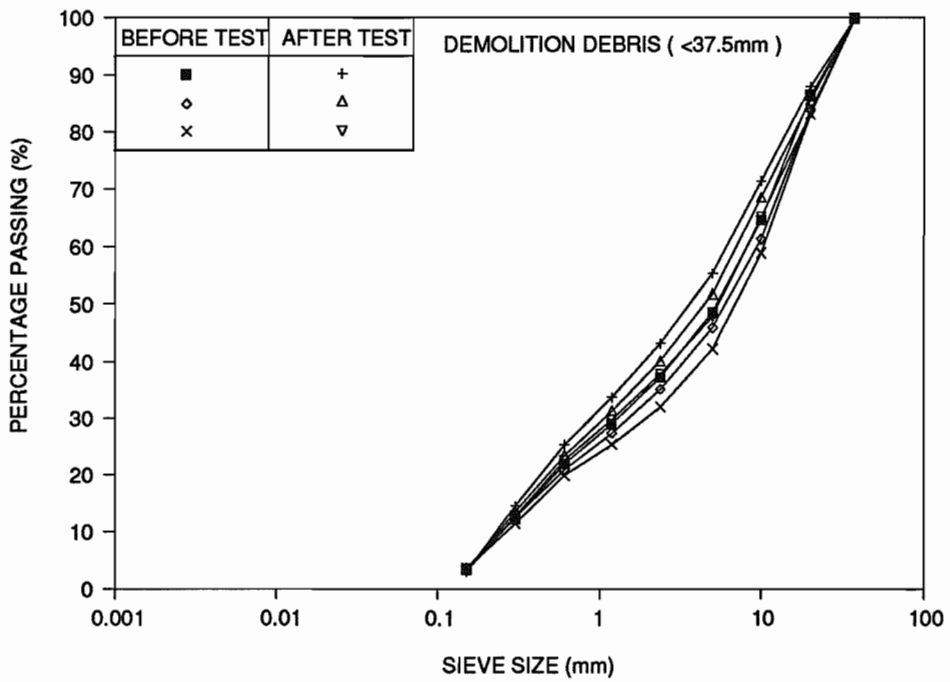


Figure 4.7 Particle gradings of demolition debris (<37.5mm)

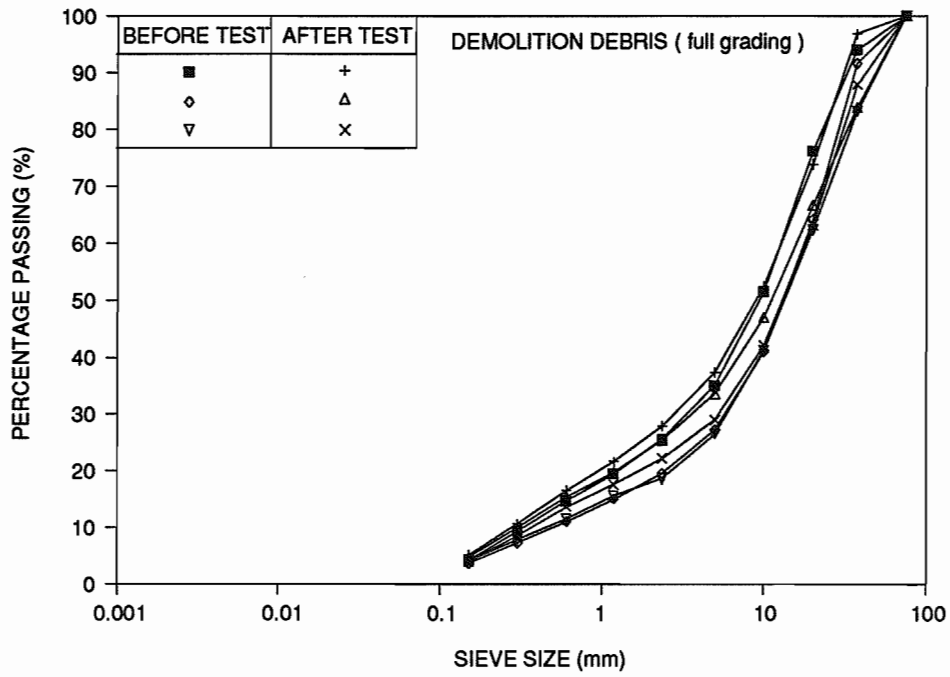


Figure 4.8 Particle gradings of demolition debris (full grading)

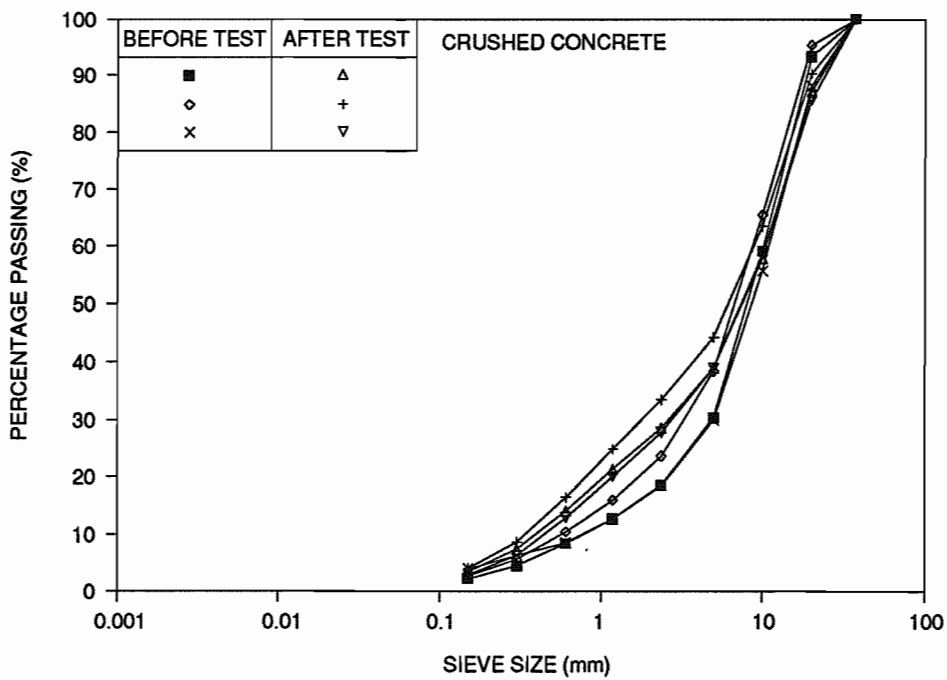


Figure 4.9 Particle gradings of crushed concrete

MATERIAL TYPE	TEST TYPE		OMC (%)	FREE WATER (%)	$\rho_{d,peak}$ (kg/m ³)
	LARGE TEST	(BS 5835) TEST			
LIMESTONE		X	3.5	3.1	2320
LIMESTONE	X		4.5	4.1	2320
DEMOLITION DEBRIS		X	13	5	1880
DEMOLITION DEBRIS	X		12	4	1950
DEMOLITION DEBRIS (full grading)	X		12	4	1880
CRUSHED CONCRETE	X		10	5.3	2000

Table 4.1 OMC and $\rho_{d,peak}$ results for all materials

BS 5835 (1980) suggests a method for the expression of compaction results in volumetric terms. This is useful for the comparison of materials with different values of water absorption and specific gravity. Density is expressed in another form known as the proportion of volume occupied by solids which was defined in Eqn 3.4. Moisture content can be expressed as the proportion of volume occupied by free water which is defined as

$$V_{fw} = \frac{\rho_d(MC - W_a)}{1000} \quad \dots Eqn \ 4.1$$

where ρ_d is the dry density (kg/m³),
 MC is the moisture content (%) and
 W_a is the water absorption (%).

These formulae for V_s and V_{fw} , listed in BS 5835 (1980), can be derived from the basic definitions of soil mechanics (Bowles, 1984). This alternative method of presenting results allows the packing of particles in the samples to be examined. It can be seen in Figure 4.10 that demolition debris and crushed concrete have similar relationships and therefore their particles can be assumed to pack in a similar manner. This may be due to similar surface texture and angularity. The maximum V_s obtained for demolition debris and crushed concrete was 73.5% and 78% respectively. Limestone achieved a higher V_s of 87% which means that the packing of limestone particles was more effective.

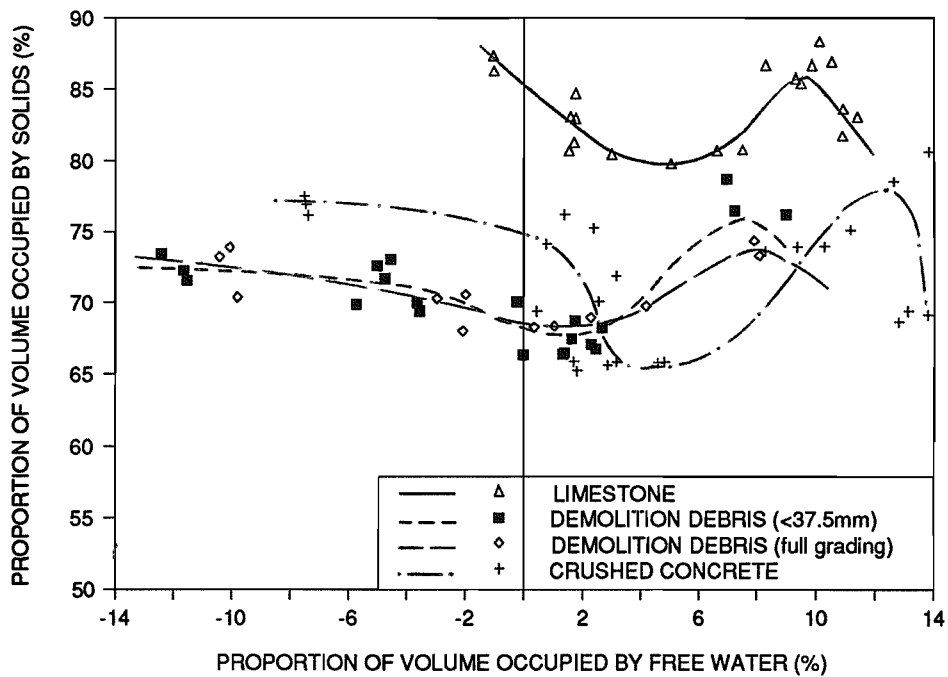


Figure 4.10 Results of compaction tests expressed in volumetric terms

4.2 California Bearing Ratio

4.2.1 Introduction

The California Bearing Ratio test or the CBR test, as it is commonly called, is a penetration test which estimates the bearing capacity of sub-bases and subgrades. Much doubt exists about the relevance of the test and its usefulness because of the difficulty in producing a sample in a 152mm diameter mould at the same conditions expected in the field. Engineers would prefer to use a site test such as the plate bearing test or the Clegg impact soil tester so that the full grading of aggregate could be tested in actual site conditions. The CBR test and the plate bearing test exert stresses on the aggregate statically although generally road pavements are loaded dynamically (Hill, 1985). Another disadvantage of the plate bearing test is that not only is it influenced by the stiffness of the sub-base layer but also by the stiffness of the layers below (Sweere and Galjaard, 1989).

The Clegg impact soil tester consists of an accelerometer attached to a 4.5kg drop hammer of the type used for compaction tests on soils. The hammer is dropped on to the material and the reading of peak deceleration is recorded as the Clegg impact value (CIV). This test involves loading the material dynamically but a disadvantage of the test is that CIV, expressed in units of gravitational acceleration, cannot be used directly for pavement design.

Each of the three tests therefore has disadvantages and this highlights the difficulty of designing a test which reproduces the effects of traffic loading and yields results which can be used directly for pavement design. Trafficking trials are the best method of determining the ability of sub-base material to withstand traffic loading. Unfortunately, however, trials in most cases would be considered too expensive and time consuming.

The Specification for Highway Works (1986) does not include CBR requirements in Clause 803 for Type 1 road sub-base material because the aggregates allowed for use in this category are assumed automatically to achieve high CBR values. CBR requirements are listed for Type 2 materials because of the inclusion of natural sands and gravels in this category. If traffic loading is to be more than 2 million standard axles (msa), the CBR of Type 2 material should not be less than 30%. For traffic loading less than 2 msa, a minimum CBR of 20% is required. However, if more than 10% of the material is retained on a 20mm sieve, the material as a whole can be assumed without test to have a CBR of 30% or more. The conditions at which CBR tests should be conducted are OMC and the density relating to an air voids content of 5% (Specification for Highway Works, 1986).

Although more than 10% of each of the recycled materials tested in this research was retained on a 20mm sieve, CBR tests were conducted on demolition debris and crushed concrete and the results were compared with those of a Type 1 limestone to investigate the bearing capacity of recycled materials. Some tests were carried out at OMC and $\rho_{d,peak}$ but the CBR of the aggregates was also examined at the same range of moisture content and dry density conditions which were obtained from the compaction tests listed in Section 4.1.3.

4.2.2 The CBR test

Test 16 of BS 1377 (1975) describes the CBR test which involves pushing a standard 50mm diameter plunger into a compacted material at a fixed rate of penetration. Particles greater than 20mm in size were removed from the aggregates, as required by BS 1377 (1975), and samples of each material were mixed at a range of moisture contents. The 152mm diameter mould was attached to the base plate and a filter paper was placed at the bottom. The mass of material needed to obtain the required density for each test was weighed and placed in the mould under continual tamping with a 20mm diameter rod. A filter paper was placed on top of the material followed by a metal plug.

BS 1377 (1975) lists compaction procedures including static and vibratory methods and any of these can be used to compact aggregate in a CBR mould provided that the method is noted in the results. A method of static compaction using a compression testing machine was used in this research. It would have been more consistent to use the same compaction method as that used in the compaction tests (Section 4.1.2) but the BS 5835 (1980) apparatus was located at TRRL. The mould and plug were placed centrally in the compression testing machine and the aggregate was loaded until the height of the sample was reduced to 127mm. The load was held constant for one minute so that rebound would not occur.

This method of compaction for the CBR tests was very severe and crushing of particles could be heard when the materials were under compression. The particle gradings of the samples, before and after compaction and penetration, were examined. It can be seen in Figures 4.11, 4.12 and 4.13 that limestone and demolition debris had better resistance to crushing than crushed concrete.

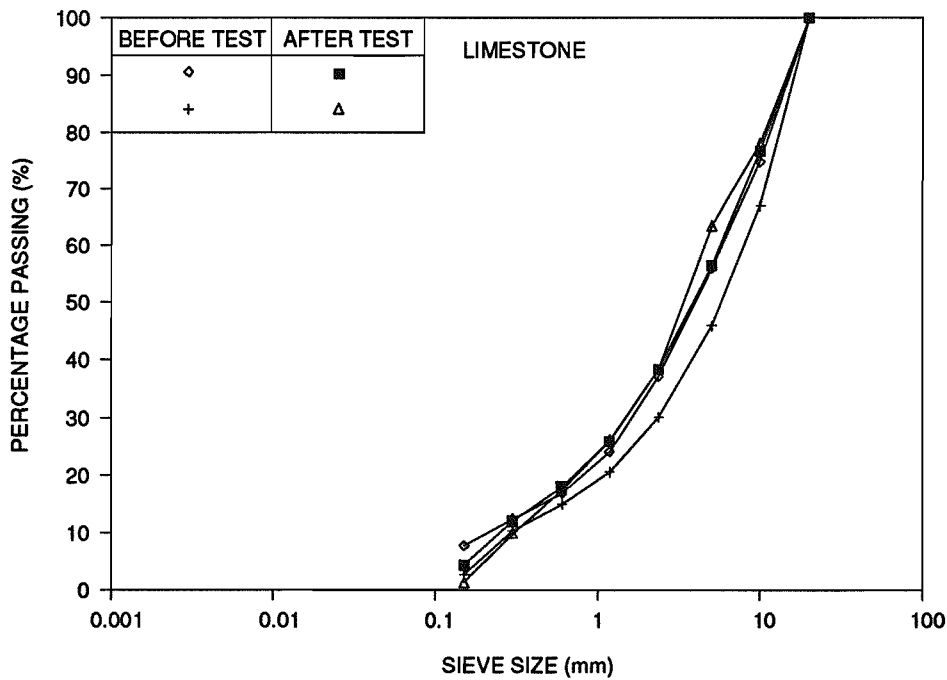


Figure 4.11 Particle gradings of limestone

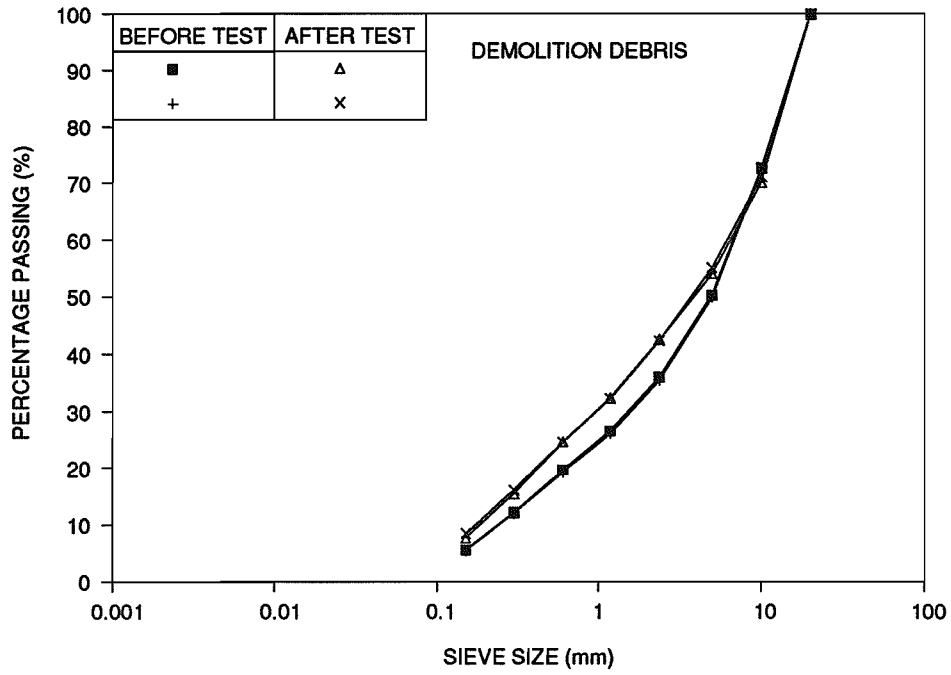


Figure 4.12 Particle gradings of demolition debris

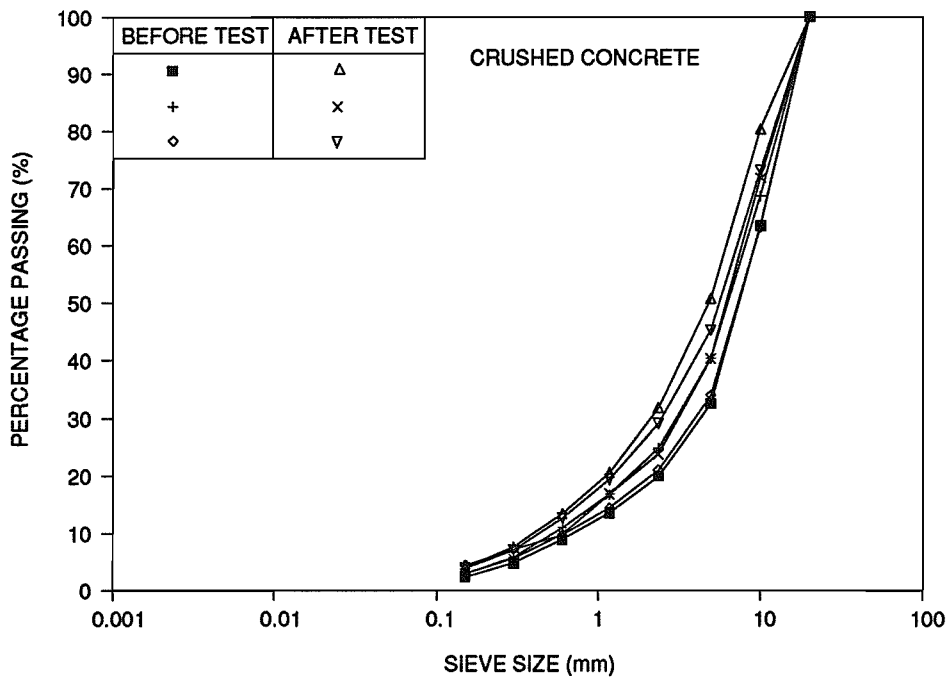


Figure 4.13 Particle gradings of crushed concrete

Usually penetration was carried out shortly after compaction but a couple of saturated samples were allowed to stand to facilitate the dissipation of any pore pressures set up by the compaction process. The plug and filter paper were removed from the mould and the sample was placed under the 50mm diameter plunger in the compression testing machine. No surcharge weights were placed on the samples as it was considered that most damage due to rutting would occur when the sub-base was acting as a construction platform. In this condition the sub-base would be without surcharge.

The plunger was made to penetrate the sample at a rate of 1mm/min, as required by BS 1377 (1975), and readings of force on the plunger were noted at every 0.25mm of penetration until the indentation was 7.5mm in depth. Penetration was measured using a dial gauge with an accuracy of 0.01mm. BS 1377 (1975) suggests when the top surface of a specimen has been tested that the sample can be inverted and a similar test can be performed on the bottom surface. As the height of the sample was only 127mm, it was considered that stresses built up in the sample during penetration of the top surface would cause the CBR of the bottom surface to be higher. It was decided therefore that each sample should be tested only once.

Initially, as stated in BS 1377 (1975), the average result from two samples was taken as the CBR for a particular test condition. However, for some pairs of samples one result could be considerably higher than the other and in these cases additional samples were tested. The large variation in results was particularly obvious for tests on limestone and crushed concrete and was evident at high CBR values in the range of 250% to 500%. As these values were well above the range for which the CBR test was designed, it was likely that large differences at this level were not significant. A CBR value greater than 100% can only be interpreted as meaning that the material had a greater bearing capacity than crushed rock.

The force on the plunger was plotted against penetration for each test and the forces applied at penetrations of 2.5mm and 5mm were noted. BS 1377 (1975) states that if the initial

portion of the curve is concave upwards, the following correction should be made. A tangent should be drawn at the point of maximum slope, as shown in Figure 4.14, and extended to intersect the horizontal axis. The whole curve should then be moved to the left until this intersection coincides with the origin. The forces for 2.5mm and 5mm penetration should then be read from this corrected curve. The CBR is calculated using the formula

$$CBR = \frac{\text{Measured force}}{\text{Standard force}} \times 100\% \quad \dots \text{Eqn 4.2}$$

where the standard force is the force required for the same penetration into a sample of compacted crushed rock (BS 1377, 1975). The standard forces for 2.5mm and 5mm penetration are 13.24kN and 19.96kN respectively and CBR is calculated for both levels of penetration. BS 1377 (1975) states that the higher of the two CBR values should be taken as the final result. For this work, an average of the two results was taken as a more conservative estimate.

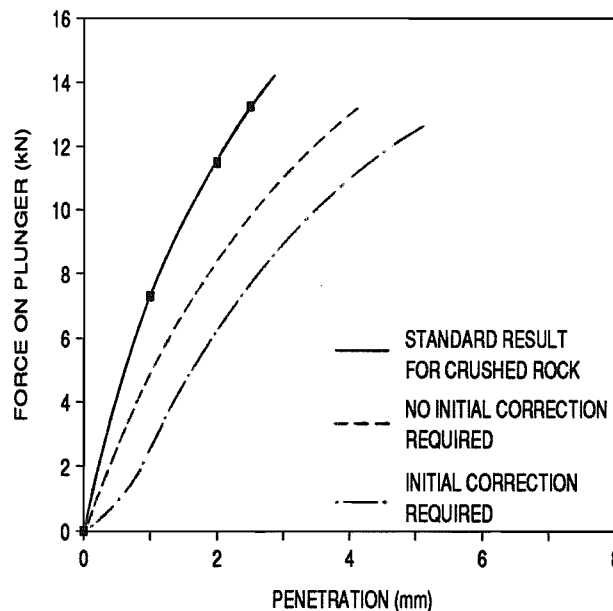


Figure 4.14 Typical force/penetration curves (after BS 1377, 1975)

4.2.3 Results

The force/penetration curves for limestone at moisture contents of approximately 1%, 2% and 3.5% are shown in Figures 4.15, 4.16 and 4.17 respectively. From these data, it can be seen that the initial parts of the plots were concave upwards in most cases so corrections were made using the method described in Section 4.2.2. In Figure 4.17, it can be seen that there were large differences in force between the four samples and in one of the tests, a CBR of 560% was obtained whereas in another test the CBR was 200%. The average CBR of the four tests was 389% and the maximum and minimum CBR values deviated by 44%-49% from this mean. This deviation is very high but, as stated previously, in practical terms high CBR values of this kind are difficult to interpret which consequently makes these large variations in results also hard to understand.

A selection of force/penetration curves for tests on demolition debris are shown in Figures 4.18, 4.19 and 4.20. The scale of the force axis on these graphs is larger than in the previous figures so that interpretation would be easier. The forces in these plots are much lower than those in the figures for limestone although there is less scatter in the results of the demolition debris samples. In Figure 4.19, it can be seen that the force/penetration curves for two demolition debris samples are nearly identical.

Similar data for some of the crushed concrete tests are plotted in Figures 4.21, 4.22 and 4.23 where it can be seen that the forces are higher than those exerted on demolition debris but lower than those on the limestone samples. The curves for each moisture content appear to be similar. These figures are plotted on the same scale as those for limestone.

The CBR results are listed in Tables 4.2, 4.3 and 4.4 for limestone, demolition debris and crushed concrete respectively. The test conditions which include moisture content (MC), bulk density (ρ_b), and dry density (ρ_d) for each of the samples, are also listed in the Tables.

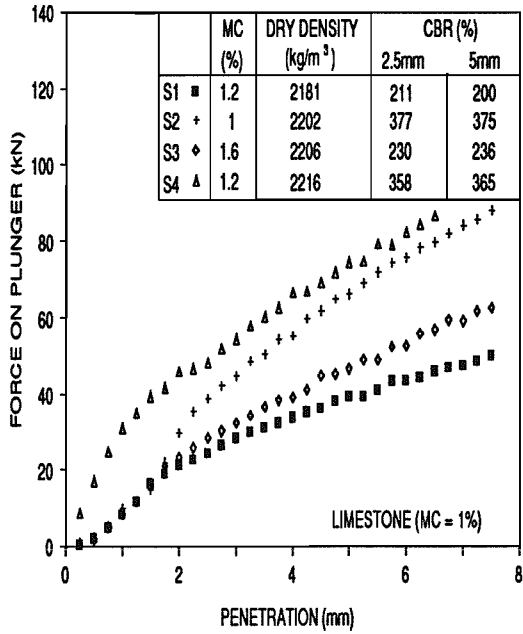


Figure 4.15 Force/penetration curves for limestone at a moisture content of 1%

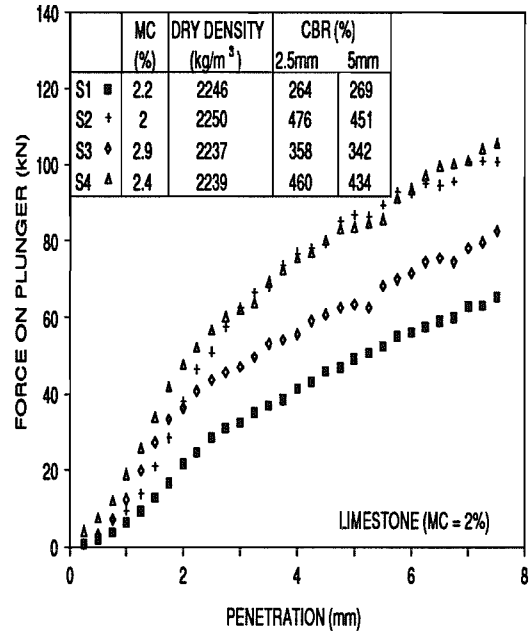


Figure 4.16 Force/penetration curves for limestone at a moisture content of 2%

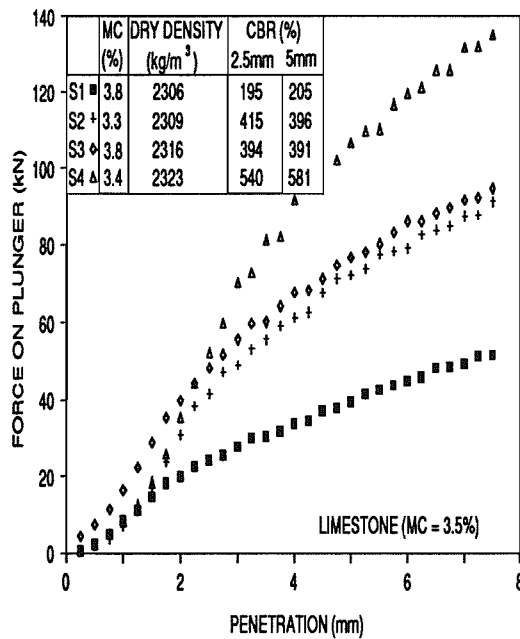


Figure 4.17 Force/penetration curves for limestone at a moisture content of 3.5%

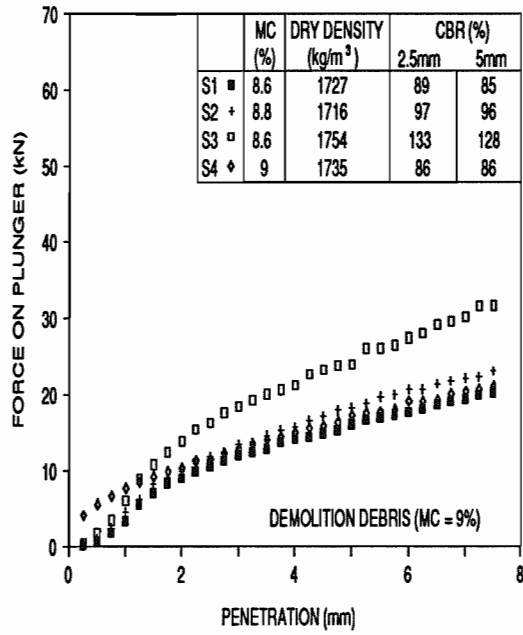


Figure 4.18 Force/penetration curves for demolition debris at a moisture content of 9%

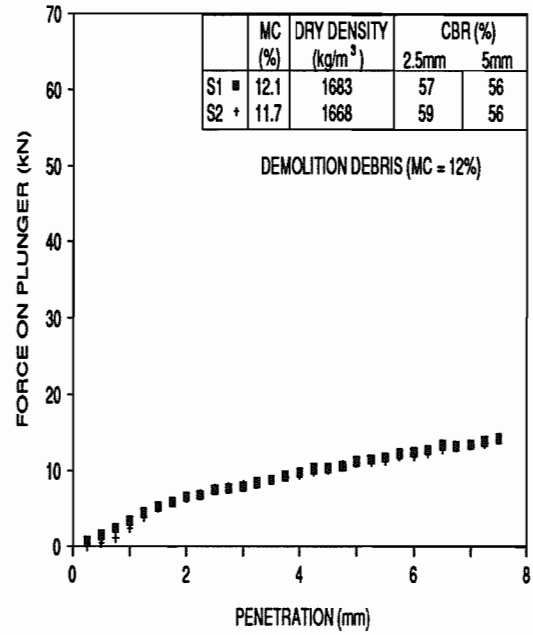


Figure 4.19 Force/penetration curves for demolition debris at a moisture content of 12%

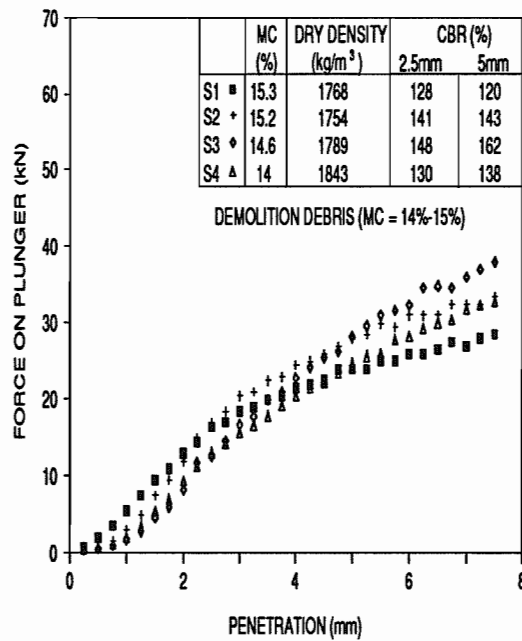


Figure 4.20 Force/penetration curves for demolition debris at a moisture content of 14%-15%

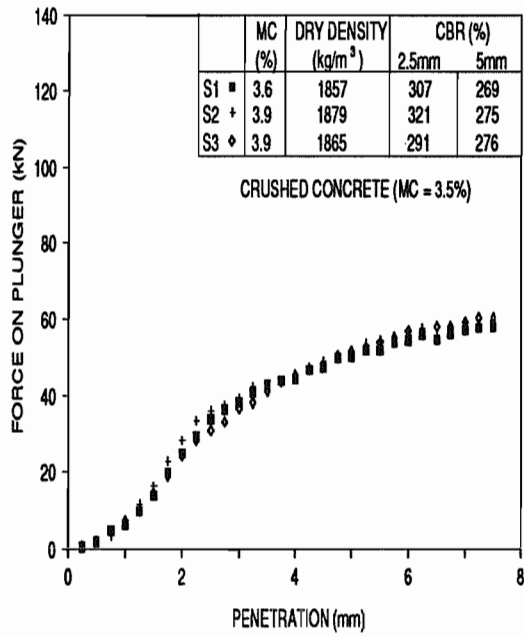


Figure 4.21 Force/penetration curves for crushed concrete at a moisture content of 3.5%

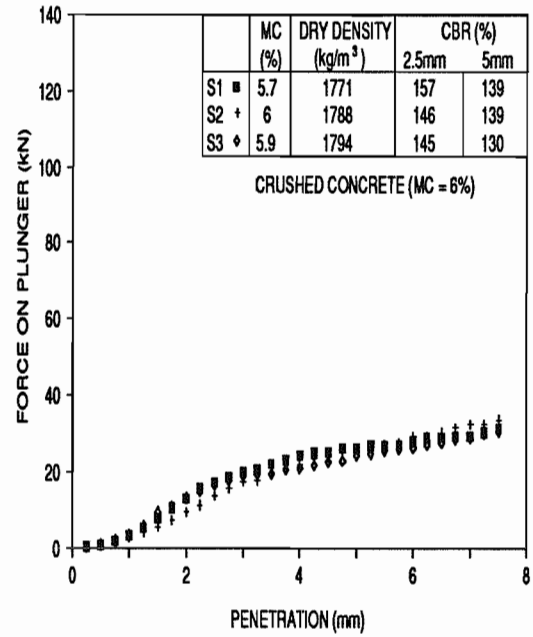


Figure 4.22 Force/penetration curves for crushed concrete at a moisture content of 6%

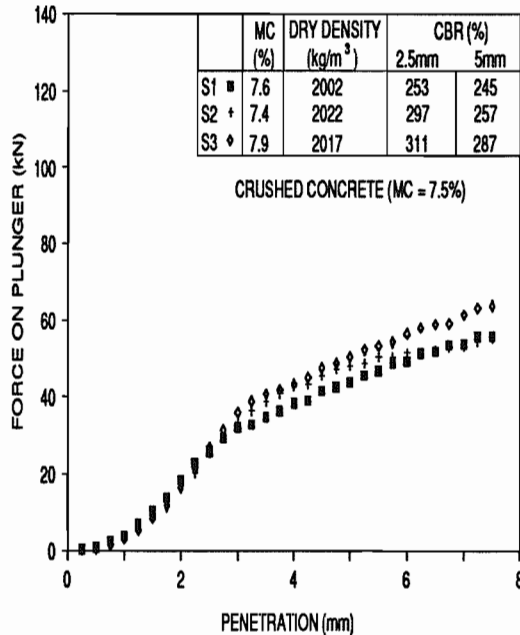


Figure 4.23 Force/penetration curves for crushed concrete at a moisture content of 7.5%

MATERIAL TYPE	MC (%)	ρ_b (kg/m ³)	ρ_d (kg/m ³)	CBR (%)		AVERAGE CBR (%)	STANDARD DEVIATION (%)	
				2.5mm	5mm			
Limestone	0	2167	2167	320	328	324	4	
	0	2149	2149	408	386	397	11	
	1	2225	2202	377	375	376	1	
	1.2	2206	2181	211	200	205.5	5.5	
	1.2	2243	2216	358	365	361.5	3.5	
	1.6	2243	2206	230	236	233	3	
	2	2296	2250	476	451	463.5	12.5	
	2.2	2296	2246	264	269	266.5	2.5	
	2.4	2293	2239	460	434	447	13	
	2.9	2302	2237	358	342	350	8	
	3.3	2385	2309	415	396	405.5	9.5	
	3.4	2406	2323	540	581	560.5	20.5	
	3.8	2404	2316	394	391	392.5	1.5	
	3.8	2393	2306	195	205	200	5	
	4.5	2305	2206	146	132	139	7	
	4.7	2262	2161	104	110	107	3	
	4.9	2337	2229	162	183	172.5	10.5	
	5	2317	2207	177	180	178.5	1.5	
							Average	= 6.8
							S.D.	

Table 4.2 Test conditions and CBR results for limestone

The maximum CBR of demolition debris was about 28% that of the maximum CBR of limestone and crushed concrete and its lowest CBR was between 37% and 39% that of the lowest CBR values of the other two materials which implied that demolition debris had a much lower bearing capacity than the other aggregates. All three materials in any condition, not only at OMC and $\rho_{d,peak}$, complied with the Specification for Highway Works (1986).

The CBR results from 2.5mm and 5mm penetration for each test were averaged and the standard deviation was calculated. It can be seen from the tables that the average of all standard deviations calculated for limestone, demolition debris and crushed concrete were 6.8%, 2.6% and 17.2% respectively. Therefore demolition debris followed more closely the

force/penetration trend of the standard crushed rock referred to in BS 1377 (1975). It was difficult to conduct a statistical analysis on the results of the tests for each target moisture content because there was more scatter than expected.

MATERIAL TYPE	MC (%)	ρ_b (kg/m ³)	ρ_d (kg/m ³)	CBR (%)		AVERAGE CBR (%)	STANDARD DEVIATION (%)
				2.5mm	5mm		
Demolition debris	2.8	1752	1704	120	108	114	6
	3.2	1748	1694	154	138	146	8
	8.6	1876	1727	89	85	87	2
	8.6	1905	1754	133	128	130.5	2.5
	8.8	1867	1716	97	96	96.5	0.5
	9	1891	1735	86	86	86	0
	11.3	1888	1697	68	63	65.5	2.5
	11.3	1882	1691	63	59	61	2
	11.5	1859	1667	48	46	47	1
	12.1	1863	1662	43	40	41.5	1.5
	11.7	1863	1668	59	56	57.5	1.5
	12.1	1887	1683	57	56	56.5	0.5
	14	2101	1843	130	138	134	4
	14.5	2039	1781	88	89	88.5	0.5
	14.6	1965	1714	64	59	61.5	2.5
	14.6	2051	1789	148	162	155	7
15.2	2021	1754	141	143	142	1	
15.3	2039	1768	128	120	124	4	
						Average S.D.	= 2.6

Table 4.3 Test conditions and CBR results for demolition debris

The force/penetration curves for two tests in the crushed concrete series, i.e where the moisture content was 7.8% and 8%, followed an unusual trend. Unlike any of the curves shown earlier, the curves peaked before 5mm penetration and then the slopes decreased. The CBR values measured at a penetration of 2.5mm were very high. Large particles, situated close to the surface under the plunger in the tests, may have had an influence on the

unusual response. Head (1982) states that if the maximum force on a sample is achieved before the end of a test, a CBR value should only be calculated from the part of the curve where the slope is increasing. Therefore the CBR at a penetration of 5mm could not be calculated for these specimens.

MATERIAL TYPE	MC (%)	ρ_b (kg/m ³)	ρ_a (kg/m ³)	CBR (%)		AVERAGE CBR (%)	STANDARD DEVIATION (%)
				2.5mm	5mm		
Crushed concrete	2.2	1964	1922	331	298	314.5	16.5
	2.2	1968	1924	402	334	368	34
	2.3	1982	1938	415	452	433.5	18.5
	2.7	1914	1863	367	340	353.5	13.5
	2.9	1998	1942	542	432	487	55
	2.9	2028	1970	576	444	510	66
	3.6	1925	1857	307	269	288	19
	3.9	1937	1865	291	276	283.5	7.5
	3.9	1953	1879	321	275	298	23
	4.5	1844	1765	149	153	151	2
	4.6	1835	1754	118	104	111	7
	5.1	1838	1749	129	111	120	9
	5.7	1871	1771	157	139	148	9
	5.9	1900	1794	145	130	137.5	7.5
	6	1894	1788	146	139	142.5	3.5
	7.4	2171	2022	297	257	277	20
	7.6	2154	2002	253	245	249	4
	7.8	2345	2174	566	-	566	-
	7.9	2176	2017	311	287	299	12
	8	2066	1913	702	-	702	-
8.1	2325	2151	579	522	550.5	28.5	
10.4	2220	2010	248	216	232	16	
11.2	2149	1933	136	127	131.5	4.5	
11.8	2162	1933	163	169	166	3	
						Average	= 17.2
						S.D.	

Table 4.4 Test conditions and CBR results for crushed concrete

It can be seen in Figure 4.24 that limestone achieved its highest CBR value close to OMC and $\rho_{d,peak}$. Head (1982) states that CBR decreases sharply as a material reaches saturation. This was confirmed by the results of CBR tests conducted on samples above OMC and can be seen in Figure 4.24. Some iso-CBR contours were drawn by interpolation on the plot. If a full investigation was conducted, including tests executed at lower densities, the CBR for any conditions in the field could be estimated. However, as the Specification for Highway Works (1986) requires that aggregate to be used as sub-base material should be compacted to a high density, samples at lower densities were not tested.

Plots, similar to Figure 4.24, are shown for demolition debris and crushed concrete in Figures 4.25 and 4.26 respectively. It is evident from Figure 4.25 that CBR did not decrease close to saturation. When the BS 5835 (1980) compaction test was conducted on demolition debris, an OMC of 13% was determined (Table 4.1). However, it appeared for the CBR series that an OMC of 15% was achieved. This difference in OMC is possibly due to the variation in content of demolition debris. If tests were conducted at higher moisture contents than shown in Figure 4.25, it is likely that there would be a decrease in CBR. In Figure 4.26, which shows the CBR results for crushed concrete, it can be seen that the data are much more useful for plotting iso-CBR contours than in Figures 4.24 and 4.25.

Penetration was conducted immediately after compaction in most cases but some samples of demolition debris were allowed to stand for 24 hours and 72 hours after compaction. This was to observe whether pore pressures, built up during compaction, were released before penetration was conducted or whether a longer period was needed for dissipation to occur. The results of two of these tests are shown in Figure 4.25 (marked 24 hours and 72 hours). Close to the moisture content where these points are plotted, some scatter exists in the results of tests carried out immediately after compaction. The CBR values of the 24 hour and 72

hour tests fall within the range of the other CBR values but it is difficult to determine whether pore pressures existed in the samples. Normally pore pressures built up in granular materials dissipate quite quickly.

In Figure 4.24, it can be seen that the limestone samples were compacted to a density corresponding to more than 5% air voids whereas in Figures 4.25 and 4.26, the saturation of the demolition debris and crushed concrete samples appeared to be much higher. This can be explained by the same reasons given in Section 4.1.3 where it was noted that the difficulty in obtaining an accurate value of the specific gravity of recycled materials was likely to be the main cause of density values falling very close to or to the right of the 0% air voids line.

The influence of V_s (proportion of volume occupied by solids) on CBR for all three materials is shown in Figure 4.27. The CBR values obtained on samples tested at moisture contents above OMC are omitted from this plot. It appears that CBR is a function of the particle packing of the materials although the relationships are not well defined because there is wide scatter in the results. If the values obtained at very high moisture contents were included in this plot, the influence of V_s on CBR would not be as clear.

In Figure 4.28, the effect of moisture content on CBR is examined for crushed concrete. At a certain V_s , CBR appears to be greatly reduced when the moisture content is increased. A similar relationship exists for demolition debris which can be seen in Figure 4.29. In these figures the data at low V_s , which do not appear to follow the general trend of the other results, correspond to the low density point on the dry density/moisture content curve which is normally observed for well graded materials at a moisture content below OMC. It can be seen in Figure 4.30 that moisture content appears to have more of an influence on CBR for limestone but to achieve a certain CBR value, material at a high moisture content must also have a high V_s value. Some caution is needed in the interpretation of these data because of wide scatter in the results.

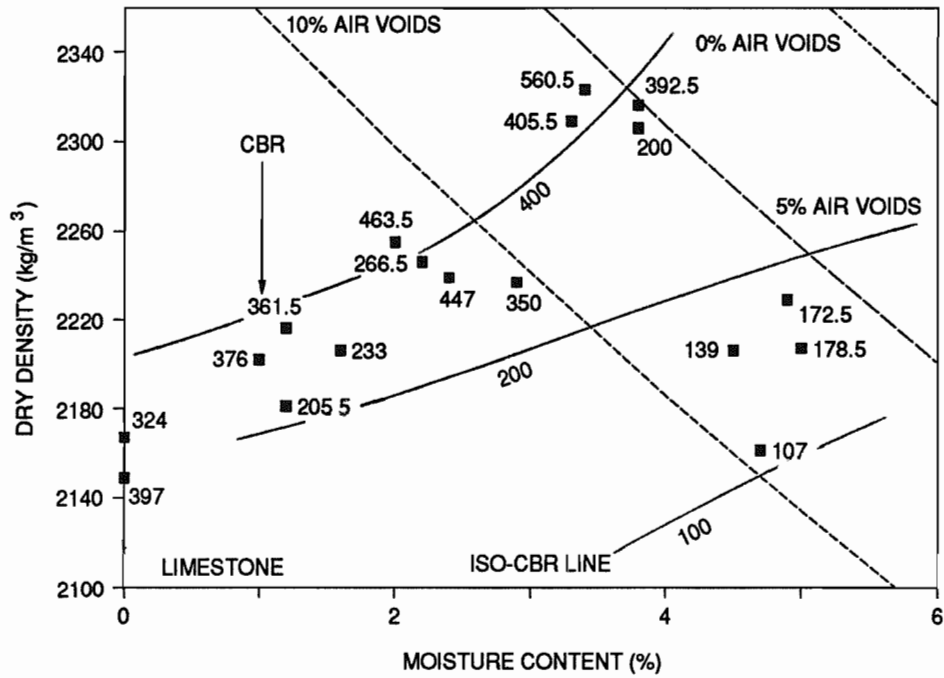


Figure 4.24 CBR values of limestone in relation to dry density and moisture content

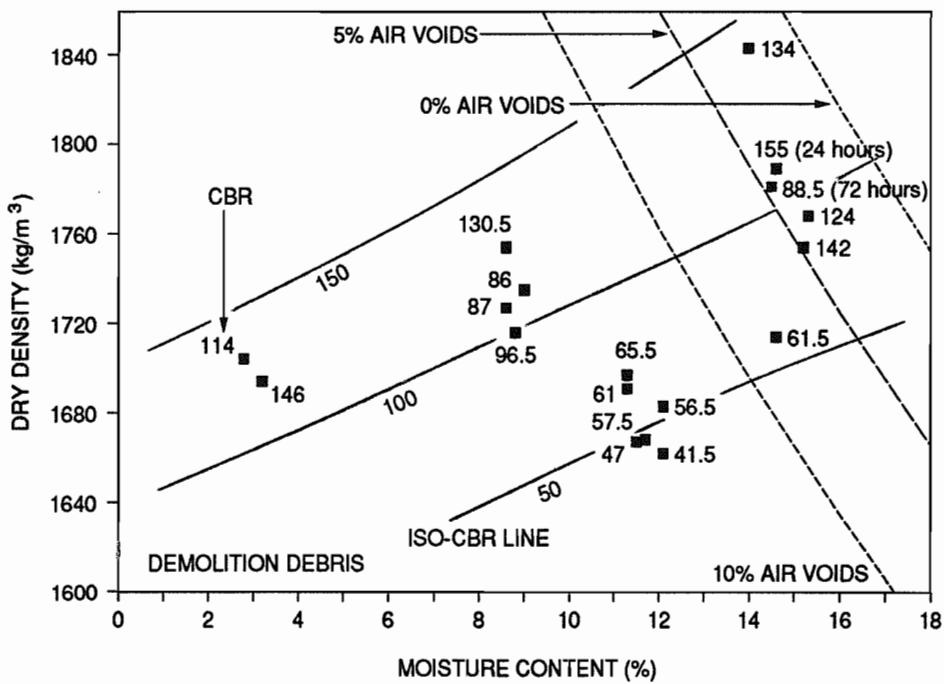


Figure 4.25 CBR values of demolition debris in relation to dry density and moisture content

Note: In Figure 4.25, 24 hours and 72 hours refer to the length of time between compaction and penetration.

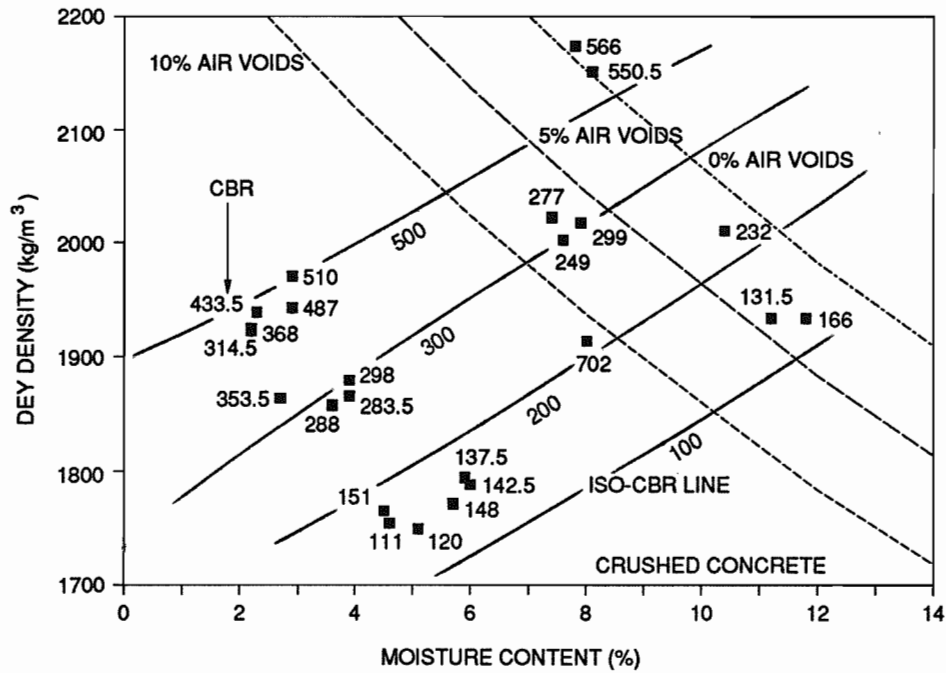


Figure 4.26 CBR values of crushed concrete in relation to dry density and moisture content

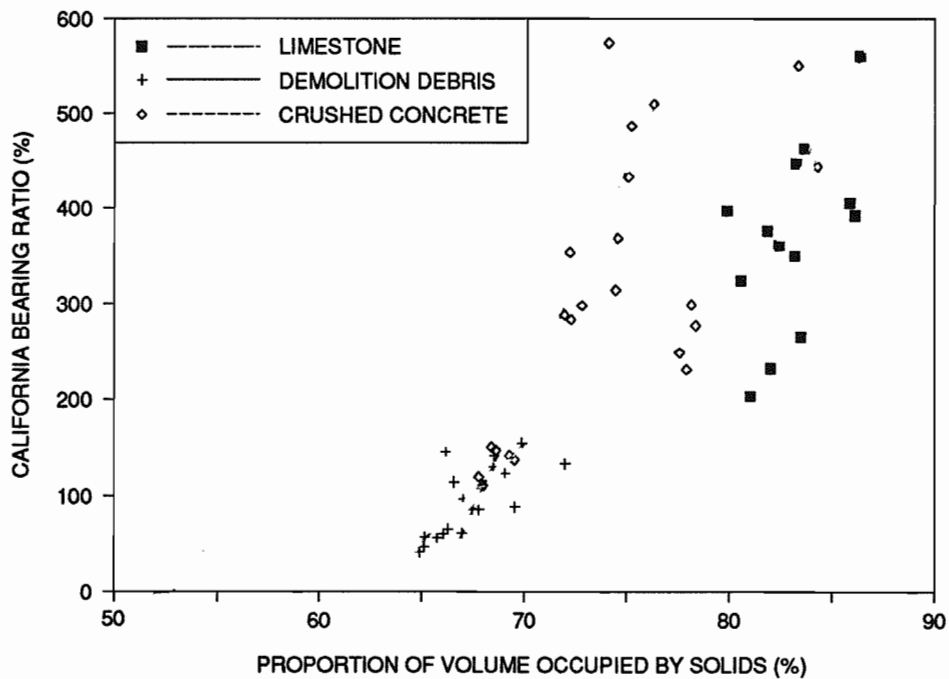


Figure 4.27 Influence of V_s on CBR for the three materials

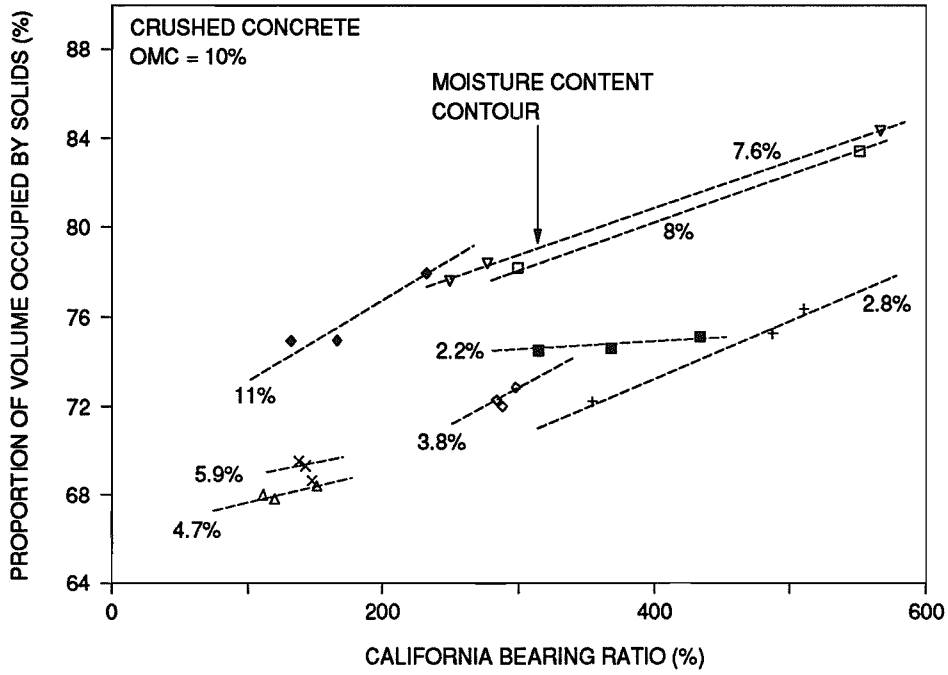


Figure 4.28 Examination of the influence of moisture content on the CBR of crushed concrete

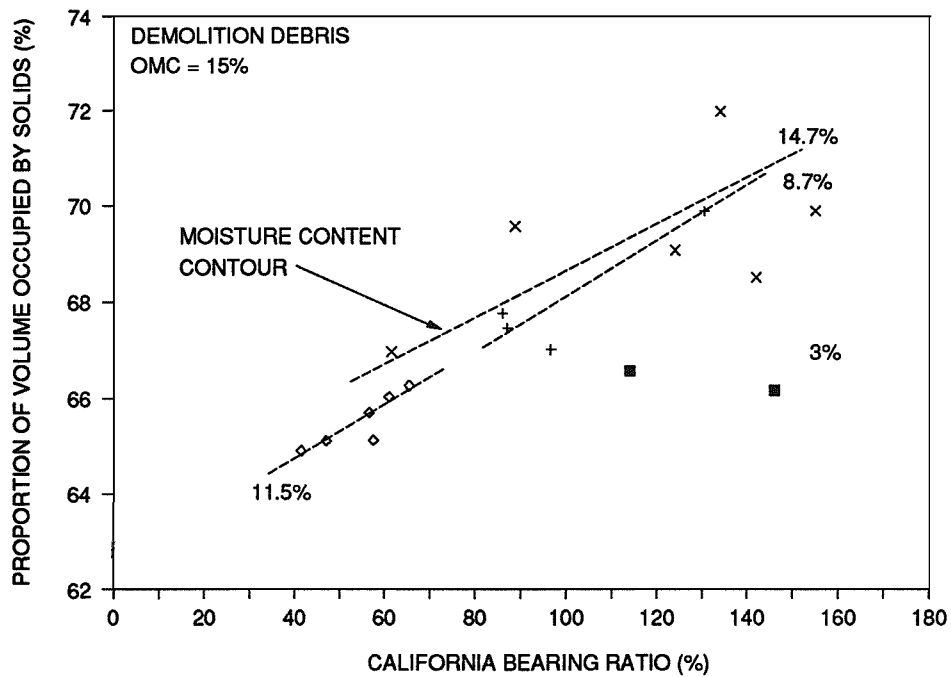


Figure 4.29 Examination of the influence of moisture content on the CBR of demolition debris

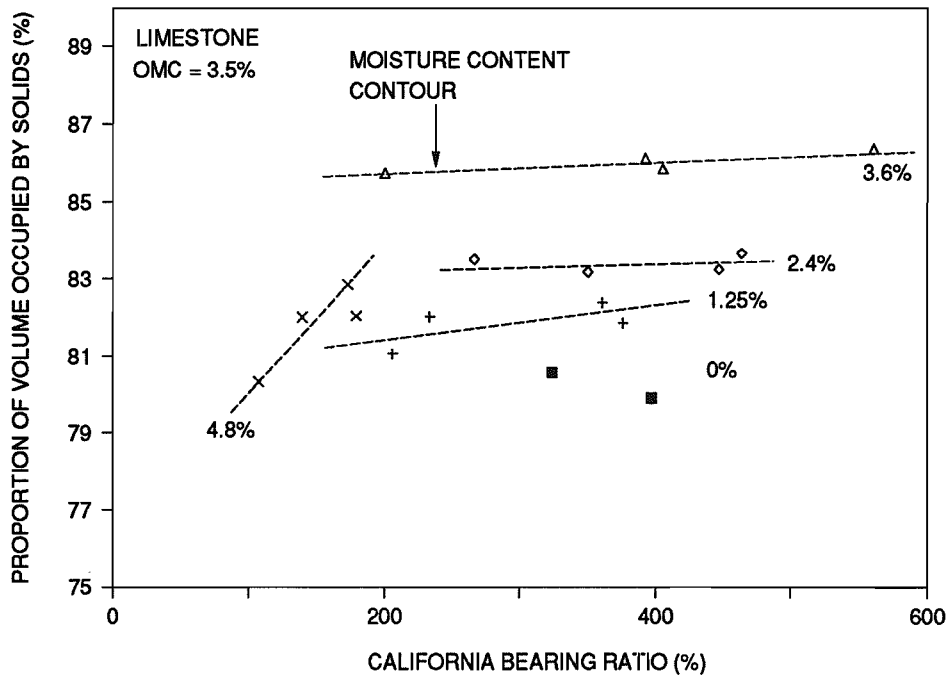


Figure 4.30 Examination of the influence of moisture content on the CBR of limestone

At moisture contents above OMC, V_s is reduced due to the high moisture content and CBR is also reduced e.g. in Figure 4.30 at a V_s of 82%, the CBR at a moisture content of 4.8% is 158% whereas a CBR of 353% is apparent at a moisture content of 1.25%. This is likely to be due to increased lubrication, caused by the excess water, and the reduction of pore suction which would reduce the shear strength of the material.

4.2.4 Analysis

Black (1961) found for clays and sands that in situ values of CBR could be calculated from measurements of cohesion, angle of internal friction and suction using a bearing capacity formula for round footings, developed by Terzaghi (1943), of the form

$$q_u = 1.2cN_c + \gamma dN_q + 0.6\gamma rN_\gamma \quad \dots Eqn \quad 4.3$$

where q_u = ultimate bearing capacity
 c = cohesion
 γ = unit weight of the soil
 d = depth of footing
 r = radius of footing

and N_c , N_q & N_γ are the bearing capacity factors.

Black (1961) stated that in a CBR test the soil is generally close to its ultimate bearing capacity at 2.5mm penetration. The definition for CBR, expressed as

$$CBR = \frac{q_u}{729.6} \times 100 \quad \dots Eqn \ 4.4$$

was used in the analysis, where 729.6 kN/m² is the standard stress required for a penetration of 2.5mm into compacted crushed rock. For sand and clay, Black (1961) obtained good correlation between measured and calculated values of CBR.

A similar procedure was conducted on the data presented in Section 4.2.3. No cohesion existed in the aggregates, suction was assumed to be negligible and no surcharge was placed on the samples in the CBR tests. Therefore, for this analysis Eqn 4.3 reduced to

$$q_u = 0.6\gamma r N_\gamma \quad \dots Eqn \ 4.5$$

For smooth footings, Vesic (1975) used the following formula to obtain N_γ :-

$$N_\gamma \sim 2(N_q - 1) \tan \phi \quad \dots Eqn \ 4.6$$

where
$$N_q = \tan^2 \left(45 + \frac{\phi}{2} \right) e^{\pi \tan \phi} \quad \dots Eqn \ 4.7$$

and ϕ is the angle of internal friction.

Vesic (1975) stated that by using Eqn 4.6, the N_γ values could be approximated with an error not exceeding 10% on the safe side for angles of internal friction in the range $15^\circ < \phi < 45^\circ$.

Eqns 4.6 and 4.7 are the formulae most commonly used for the determination of N_γ and N_q .

For comparison purposes, some bearing capacity factors were calculated using formulae developed by Meyerhof (1951). Vesic (1975) stated that the formulae by Meyerhof (1951) could explain quite well the behaviour of long rectangular plates because the plane strain angle of friction should be used in the formulae. However, interpretation of the behaviour of round footings would be difficult using the Meyerhof values (1951). This may be the reason why much higher bearing capacity factors were obtained when the formulae by Meyerhof (1951) were used.

The ϕ values used in Eqns 4.6 and 4.7 were found by conducting shear box tests on the aggregates at various densities (see Chapter 5). Shear box tests were not conducted at some of the higher densities obtained in the CBR tests so values of ϕ_{ds} (direct shear angle of friction) at these densities were calculated by extrapolation of the lines in Figure 5.22. It is recognised, for an element of material located below the plunger in a CBR test that the loading conditions are similar to those in a triaxial test. However, for an element of material on the shear plane at some distance from the plunger, the conditions are closer to plane strain.

Mayhew (1985) stated that the measured value of CBR on a granular sub-base material in the laboratory could be twice the CBR value which would be obtained if a similar test was conducted in the field. This difference is due to the rigid boundary of the mould in the laboratory test which inhibits the natural failure mechanism and requires a higher stress to be placed on the plunger for penetration. The confining effect of the mould increases as ϕ_{ds}

increases. In the field, the lateral restraint is normally provided by aggregate or soil which would not create as high a confining stress as that exerted by the mould on a sample in the laboratory. Eqn 4.3 was developed for situations in the field and therefore the measured values of CBR in the laboratory were halved before comparing them with the calculated values. It can only be assumed that Black (1961) did not halve his results for clay and sand because of less difference between site CBR values and those obtained in the laboratory for these materials.

The relationship between the measured and calculated values of CBR is shown in Figure 4.31. Due to the high values of ϕ_{ds} corresponding to high dry density values, very few calculated values of CBR could be obtained for limestone and therefore the comparison in Figure 4.31 is for demolition debris and crushed concrete. At low values of ϕ_{ds} and density, the measured values compare well with the calculated values for demolition debris. However, the measured values of CBR for crushed concrete were higher than the calculated values for a wide range of CBR. The scale effects of the test were likely to be the cause of this difference because the ratio of the plunger diameter to the maximum particle size was 2.5. If a particle of 20mm in size was positioned directly below the plunger, the measured CBR would be higher than if the particles under the plunger were e.g. 1/10th to 1/20th of its diameter. Analysis of the problem would be complicated further if a large particle was situated directly on the shear plane. A good correlation between measured and calculated values of CBR was not expected due to the problems mentioned above.

It is clear from Figure 4.31 that the measured CBR values should not have been halved because the difference between site and laboratory values of CBR is likely to be dependent on the type of material. The suggestion by Mayhew (1985) that a factor of a 1/2 should be applied to CBR values measured in the laboratory was a general comment.

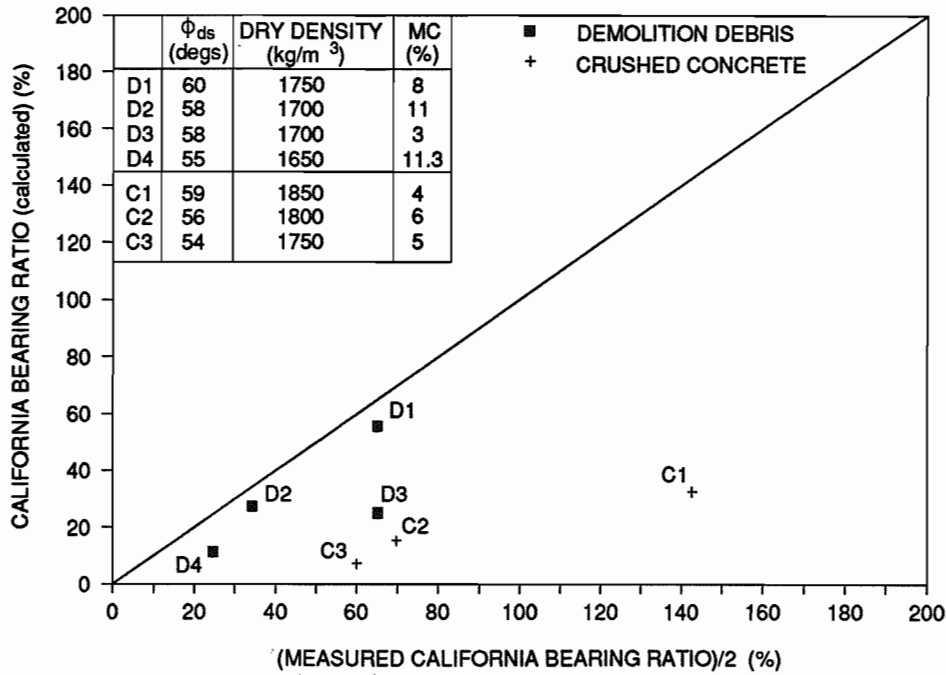


Figure 4.31 Comparison between measured and calculated values of CBR

4.3 Discussion

The standard compaction and CBR tests are conducted in 150mm and 152mm diameter moulds respectively. However, the BS 5835 test (1980) allows particles up to 37.5mm in size to be tested whereas the CBR test, described in BS 1377 (1975), restricts the maximum particle size to 20mm. The Specification for Highway Works (1986) includes both tests for the classification of road sub-base materials but the particle grading to be used in each test is different. It would be more consistent if tests on aggregates, to be used for the same purpose, were conducted on material of the same particle grading and a more useful approach would be to conduct the tests on a similar grading to that expected to be used on site.

When compaction tests were conducted on dry material in the large apparatus, higher densities were obtained than those achieved in the BS 5835 (1980) test. This was due to the greater influence of friction on the sides of the smaller mould during compaction. The

effect of the inclusion of particles greater than 37.5mm in the compaction tests was negligible. It was concluded by Dawson and Jones (1989) that compaction plant, capable of monitoring and recording its own performance together with the response of the material to compaction, would be very useful equipment for pavement construction.

The CBR values obtained for limestone and crushed concrete were similar but it is likely if CBR tests were conducted in the field a few months after placement that the bearing capacity of crushed concrete would be higher due to the self-cementing effect determined by Sweere (1989). In tests conducted by Sweere (1989), it was found after placement that the structural contribution of a 25cm granular sub-base consisting of crushed concrete was equal to that of a 6cm bituminous base. After accelerated loading on trial pavements, Sweere (1989) found that increased bonding due to the self-cementing effect in the recycled material made the material more resistant to rutting than the 6cm bituminous base. Although the CBR of demolition debris in this research was lower than that of limestone and crushed concrete it may be that several months after placement the CBR of demolition debris would also be improved due to the bonding effect.

4.4 Conclusions

- (i) Although the BS 5835 test (1980) was conducted on particles less than 37.5mm in size, it can be concluded from the results of tests conducted in a large apparatus that the inclusion of up to 15% of particles larger than 37.5mm should not alter density significantly.
- (ii) There appeared to be large differences in the $\rho_{d,peak}$ values of the three materials when dry density was plotted against moisture content. However, when the results

were presented in volumetric terms, particle packing of the recycled materials appeared to be similar but the proportion of volume occupied by solids in the limestone samples was higher.

- (iii) In any test condition examined, all aggregates complied with the CBR requirements listed in Clause 804 for Type 2 sub-base materials in the Specification for Highway Works (1986). However, the CBR values of limestone and crushed concrete were significantly higher than those of demolition debris.
- (iv) Although the interpretation was conducted on results of considerable scatter, it appeared that CBR was mainly influenced by particle packing but that moisture content also affected CBR.
- (v) The calculated values of CBR using ϕ_{ds} gave reasonable correlation for demolition debris but the influence of boundary and scale effects was too large to expect any analysis to provide an accurate estimate of CBR.

CHAPTER 5

DIRECT SHEAR TESTS

5.1 Introduction

The shear strength of an aggregate needs to be examined when the aggregate is to be used as fill to a structure and if an aggregate is to be used as road sub-base material, an investigation of the shear strength is also useful. Measurements of shear strength should be made on samples which are in a similar condition to that expected on site. As the state of packing of the particles is an important influence on the shear strength of a material, the density of the aggregates was the main parameter under investigation in this research. Direct shear box tests were conducted on three aggregates - limestone, demolition debris and crushed concrete - to obtain the angle of friction of the materials in different test conditions. A 300mm shear box test, developed by the Pavement Materials and Construction Division of TRRL to ascertain the suitability of various aggregates for use as road sub-base, was also carried out on the materials.

5.2 300mm shear box

The shear box tests were conducted in a large shear box located at the Ground Engineering Unit of the Transport and Road Research Laboratory. The internal dimensions of the shear box were 300mm x 300mm x 179mm and the two halves of the box were made of steel and plated for protection against corrosion. The arrangement was similar to that of the standard Casagrande 60mm shear box. The top and bottom platens were both ridged and the areas of the platens were slightly smaller than the area of the shear box. The top platen was heavier than the lower one and its flat top allowed a load cell to be placed on it. This type of shear box (see Plate 5.1) is produced by Wykehan Farrance for testing aggregates and materials

containing particles as large as 37.5mm.

The shearing force was generated by an electrical motor driving a mechanical screw jack via a 42 speed gear box with speeds ranging from 0.125×10^{-3} mm/min to 6.1mm/min. Rapid and reverse movements were performed manually by disengaging the clutch and using the hand wheel at the front of the shear box unit. The proving ring which measured the shear force on the original system had been replaced by a 10 tonne load cell by TRRL.

The vertical force was exerted by a fully self-contained hydraulic pressure system. In the original shear box, the seals between the load piston and its outer cylinder were inflatable causing large friction forces to develop during loading. Consequently, the friction angles recorded were 3° greater than they should have been. The load piston was replaced by one containing PTFE seals which had very low friction resistance. When these new seals had been installed, the hanger system on the shear box was capable of falling under its own weight whereas it did not before. Using the same hydraulic system and the new load piston, it was found by TRRL (Brady, Awcock and Wightman, 1983) that the measured friction angles were comparable with results from a Casagrande 60mm shear box. It was concluded therefore that friction between the seals and the cylinder had been reduced considerably. This improvement was carried out by the staff at TRRL before this research began.

The horizontal cross beam and tie rods for vertical loading pivoted on a universal joint which allowed both the beam and the rods to be swung out of the way when the shear box halves were being placed in position. The vertical force was measured by a 20kN load cell which was placed between the vertical cross beam and the top of the box during a test. The horizontal displacement of the box and the vertical displacement of the top platen were measured using linear variable differential transformers (LVDTs).

The measurement of displacement and force was controlled by a Commodore Graphic 8296d computer. The programmable switching unit contained a series of relays to which were attached the 10V power supply, the LVDTs and the load cells. The output voltages from these devices were monitored using a digital voltmeter. All devices were checked when a set of readings was taken every 30 seconds.

An uninterruptable power supply, with a back-up supply of 240V for 2 hours, supported the computer and peripherals. The forces were converted by the computer into vertical and shear stresses and subsequently the friction angles were calculated. The readings were printed on a MUTEK PPM Printer. The shear and normal forces were plotted against horizontal displacement on a standard plotter.

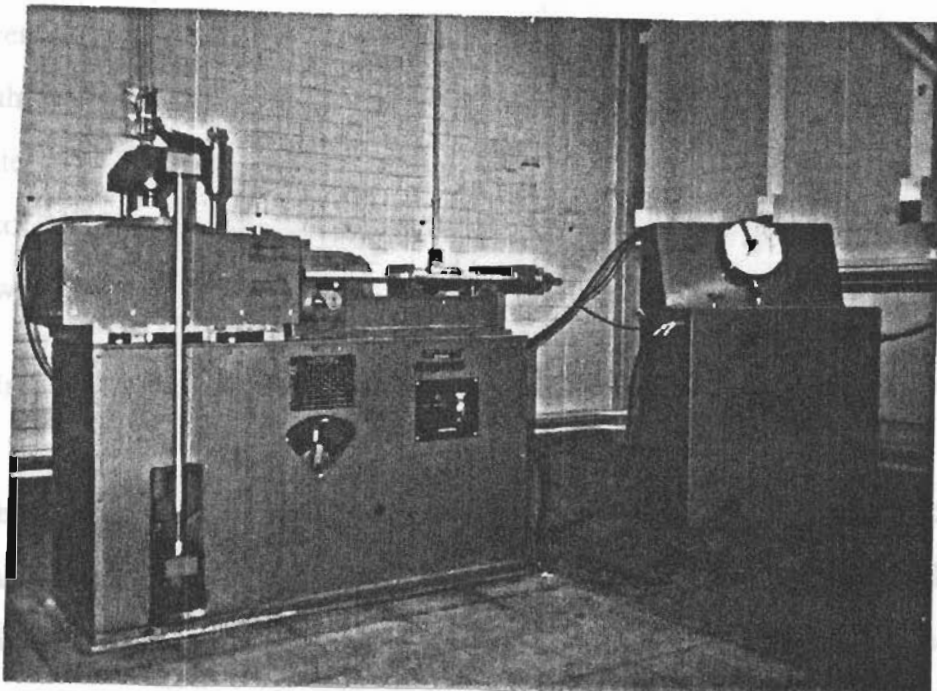


Plate 5.1 300mm shear box apparatus

5.3 Preparing the samples

The optimum moisture content (OMC) and peak dry density ($\rho_{d,peak}$) were obtained using the BS 5835 compactibility test for graded aggregates (1980). Each of the aggregates to be tested in the shear box was mixed at a moisture content just below its OMC. It was considered, if the samples were compacted at OMC, that low density samples would be difficult to obtain. By varying only one parameter i.e. density, the data from the tests could be analysed more easily. The moisture contents for limestone, demolition debris and crushed concrete, at which the tests were carried out, were 3%, 10% and 7% respectively.

The test procedure was conducted using a method described by Head (1982) and by following some suggestions by Brady (1989). At the beginning of each test the two halves of the shear box were cleaned and coated with a thin layer of oil. The two halves and the bottom platen were then placed in the chamber and the top half was bolted to the shear yoke. A portion of material weighing 5kg was placed in the box, levelled roughly with a palette knife and then compacted. To vary the density of the samples, various methods of compaction were used which are listed in Table 5.1.

The flat rectangular foot attached to the vibrating hammer was 1/6th of the area of the box so the foot had to be moved around on the material until the surface was level. When each layer had been compacted the surface was broken up gently using the edge of a palette knife with a scraping action so that no possible shear failure planes would exist in the material. The next 5kg portion of material was then added and compacted as before. When the height of the sample approached the middle section of the box, care was taken to ensure that the surface of a compacted layer did not coincide with the split in the shear box. The last portion was added so that its level was 5mm-10mm above the top of the box. The compaction time for this layer was half that of previous layers. The top platen was then lowered onto the material and was made level using the vibrating hammer.

State of material	Method of compaction
Loose	Tamped 30 times with a 20mm diameter rod
Lightly compacted	Vibrating hammer for 2 seconds
Moderately compacted	Vibrating hammer for 6 seconds
Dense	Vibrating hammer for 10 seconds

Table 5.1 Methods of compaction

5.4 Running the shear box test

The output of the unloaded vertical load cell was read four times and the mean was taken as the zero load reading. The total weight above the shear plane was calculated by adding the weights of the top platen, load cell and the soil above the shear plane to the weight of the top half of the box. The vertical stress caused by this weight was deducted when the total vertical stress to be exerted on the sample was calculated. The load cell was then placed on the top platen and the cross beam was manoeuvred onto a ball bearing on top of the load cell until the hanger system was central and level. The pressure was increased in the hydraulic system until the required vertical force reading was reached.

The protrusion of the platen above the top of the box was then measured eight times around the perimeter using callipers so that the total volume of the sample could be calculated. A volume correction was made assuming that the granular material filled half the ridges of the top and bottom platens. The density of the sample could then be determined.

The vertical LVDT was placed in position on the cross beam and zero readings were taken on it and on the shear displacement LVDT. When a zero reading had also been taken on

the shear load cell, the clutch was engaged and shearing was started. A slow rate of displacement of 0.117mm/min was decided upon so that the peak shear stress would not be missed.

5.5 Test conditions of aggregates

Two test series were conducted on each of the aggregates; the first, series A, consisted of varying the density of the aggregate samples and the second, series B, involved varying the vertical stress. Preparation of samples at peak dry density was avoided because it was considered that this would cause a considerable amount of particle crushing and therefore the highest dry density achieved was $0.9\rho_{d,peak}$. The densities of the aggregates were also expressed in terms of relative density so that the data could be analysed in a conventional manner. Relative density is defined as follows:-

$$I_d = \frac{e_{max} - e}{e_{max} - e_{min}} \quad \dots Eqn \ 5.1$$

where e_{max} is the maximum voids ratio and is achieved when a cylinder containing the dry material is inverted quickly (Bolton, 1986),

e_{min} is the minimum voids ratio and is achieved at the maximum achievable density obtained by vibration and

e is the voids ratio of the material.

The data which Bolton (1986) examined were from tests on sands but the tests in this research were conducted on aggregates which contained particles from about 0.050mm to 37.5mm in size. The limestone, demolition debris and crushed concrete had coefficients of uniformity

(C_u) of 23, 35 and 14 respectively. Bolton (1986) obtained the minimum density by inverting a 75mm diameter cylinder containing sand and measuring the resulting density. It would not be possible to carry out this test on the aggregates described above.

A test for measuring the minimum density of gravelly soils is described by Head (1980). Material is tipped quickly from a bucket into a 152mm diameter mould, similar to that used in the CBR test (BS 1377, 1975). The material in the mould is weighed and the density of the material in this condition corresponds to the minimum density which can be obtained. This test can be conducted on materials containing particles up to 20mm in size. When the test was carried out on the aggregates, it was found that the densities were not low enough to be the minimum densities obtainable. Similar densities were obtained in the shear box when some compaction had been conducted using a tamping rod. According to Jones (1989), this type of minimum density test could only be used as a guide and may not be accurate. It was concluded from the results that the preparation of very loose samples of these types of well graded materials would be difficult.

The method used for the determination of $\rho_{d,peak}$ was the BS 5835 compactibility test (1980). This test was found to cause some crushing of the aggregate particles (Chapter 4). Due to the problems in measuring minimum and maximum densities accurately, some assumptions for I_d were made. These assumptions were influenced by the results of the compaction tests conducted on the materials.

It can be seen from results reported by Bolton (1986) that the critical state plane strain angle of friction (ϕ_{cv}) is difficult to obtain at $I_d < 0.22$. Therefore an I_d of 0.35 was assumed for the loosest samples of aggregate in the shear box tests and an I_d of 0.9 was used for the densest samples. These limits of I_d were chosen using the results of the tests conducted at varying density. By using the dry densities of the shear box samples, I_d could be found by linear interpolation. The particle grading of each of the aggregate samples after shear testing

was compared with the particle gradings of samples taken from the stockpiles of aggregate. These results can be seen in Figures 5.1, 5.2 and 5.3 where it is apparent that some crushing did occur, particularly in the recycled aggregate samples.

The vertical stress, at which series A was carried out, was 50kN/m^2 and the other test conditions, including the dry density (ρ_d) and the relative density (I_d), are listed in Table 5.2. The demolition debris, when it was obtained from the supplier, contained particles greater than 37.5mm. Two tests were carried out using the full grading to establish whether the larger particles made a considerable difference to the shear strength. These tests are listed in Table 5.2 as D13 and D14. All other tests were conducted on samples containing particles smaller than 37.5mm.

The tests in series B were carried out at similar densities but the vertical stress (σ_v) was varied from 50kN/m^2 to 200kN/m^2 . The test conditions for this series are listed in Table 5.3. Some tests were also performed on samples when the chamber surrounding the box was filled with water to determine whether pore suctions were developing in the unsaturated samples. The conditions for these tests are listed in the second part of Table 5.3.

TEST SERIES LA			TEST SERIES DA			TEST SERIES CA		
TEST No.	ρ_d (kg/m ³)	I_d	TEST No.	ρ_d (kg/m ³)	I_d	TEST No.	ρ_d (kg/m ³)	I_d
L1	2103	0.9	D1	1700	0.76	C1	1805	0.9
L2	2063	0.85	D2	1674	0.72	C2	1729	0.78
L3	1991	0.75	D3	1645	0.68	C3	1714	0.76
L4	1768	0.44	D4	1550	0.54	C4	1665	0.68
L5	1705	0.35	D5	1480	0.44	C5	1528	0.47
			D6	1418	0.35	C6	1450	0.35
			D13	1802	0.9			
			D14	1441	0.39			

Table 5.2 Test conditions for Series A

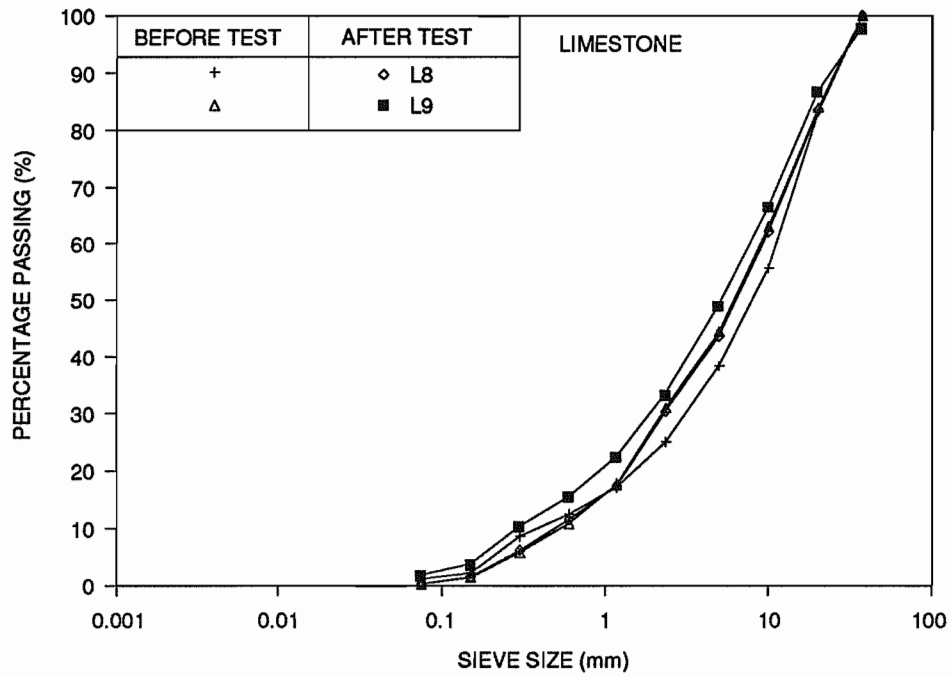


Figure 5.1 Particle gradings of limestone samples

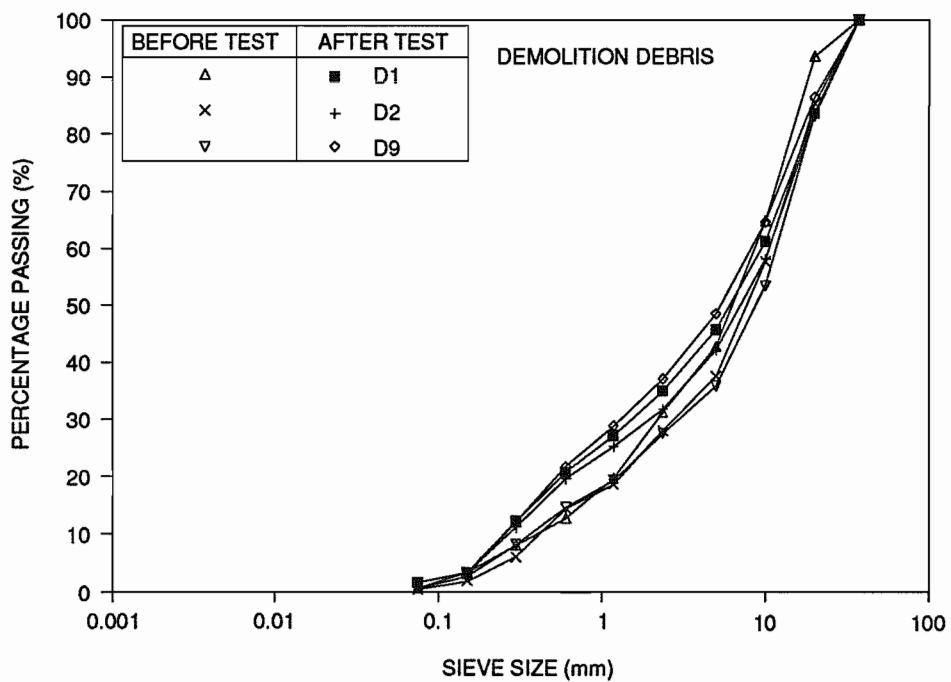


Figure 5.2 Particle gradings of demolition debris samples

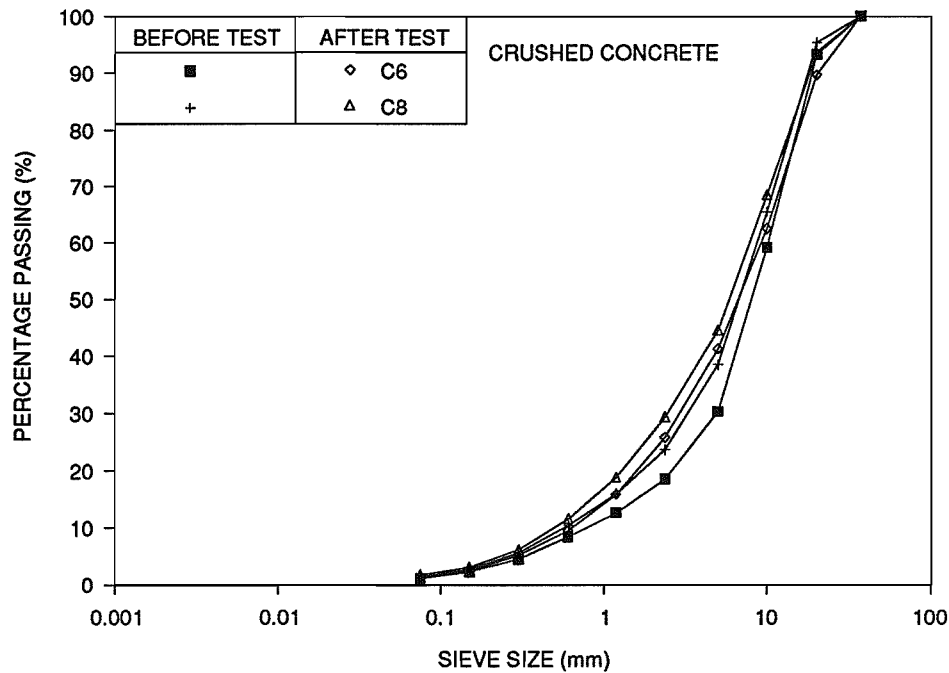


Figure 5.3 Particle gradings of crushed concrete samples

Note: In these figures, L = limestone, D = demolition debris and C = crushed concrete. The test details are listed in Tables 5.2 and 5.3.

σ_v (kN/m ²)	TEST SERIES LB			TEST SERIES DB			TEST SERIES CB		
	TEST No.	ρ_d (kg/m ³)	I_d	TEST No.	ρ_d (kg/m ³)	I_d	TEST No.	ρ_d (kg/m ³)	I_d
50	L2	2063	0.85	D4	1550	0.54	C2	1729	0.78
50				D2	1674	0.72			
75	L7	2081	0.87	D7	1591	0.6	C7	1662	0.68
100	L8	2104	0.9	D8	1573	0.58	C8	1731	0.78
150	L9	2106	0.9	D9	1651	0.69	C9	1708	0.75
200	L10	2097	0.89	D10	1640	0.67	C10	1650	0.66
100	L11	2009	0.77	D11	1535	0.52	C11	1662	0.68
200	L12	2127	0.93	D12	1656	0.7	C12	1664	0.68

Table 5.3 Test conditions for series B

5.6 Leighton Buzzard sand tests

Shear box tests were conducted on 14-25 Leighton Buzzard sand to confirm that the 300mm shear box yielded results which were comparable with those obtained in other research. It also proved useful to compare the results for sand with those of the tests on aggregates. The extreme voids ratios, e_{\min} and e_{\max} , for the sand were 0.49 and 0.78 respectively. Its particle grading is listed in Table 5.4. Two series of tests were carried out on the sand; series SA at varying density and series SB at varying vertical stress. The test conditions are listed in Table 5.5.

SIEVE SIZE (mm)	PERCENTAGE PASSING (%)	OTHER INFORMATION
2.36	100	D ₁₀ = 0.64mm D ₆₀ = 0.99mm C _u = 1.5
1.18	83.1	
0.60	0.67	
0.30	0.11	

Table 5.4 Particle grading of Leighton Buzzard sand

Note: D₁₀ = 0.64mm means that 10% of the sand grains are smaller than 0.64mm.

TEST SERIES SA				TEST SERIES SB			
σ_v (kN/m ²)	TEST No.	ρ_d (kg/m ³)	I _d	σ_v (kN/m ²)	TEST No.	ρ_d (kg/m ³)	I _d
50	S1	1682	0.7	50	S1	1682	0.7
50	S2	1621	0.5	100	S4	1707	0.78
50	S3	1520	0.12	200	S5	1737	0.88
				200	S6	1679	0.7

Table 5.5 Test conditions for Leighton Buzzard sand

The dense samples were prepared by raining the sand from a height of 400mm above the top of the box. The loose samples were prepared by tipping the sand gently from a small

container allowing no free fall and avoiding sloping of the sand surface during placement. The measured densities of the loose samples were quite accurate but, because of the loss of some particles when the sand was falling, measurement of the density of the dense samples may not have been exact.

5.7 Results

When the vertical force has been applied in a shear box test, shearing is started. Failure is assumed to have occurred when a peak in the curve relating shear stress to the shear displacement of the box has been observed. The standard approach used to interpret results from a shear box test is summarised in Figure 5.4a. The shear stress (τ_{yx}) and the vertical stress (σ_{yy}) are measured on the central plane.

The direct shear angle of friction is defined as

$$\phi_{ds} = \tan^{-1} \left(\frac{\tau_{yx}}{\sigma_{yy}} \right) \quad \dots Eqn \quad 5.2$$

Stress measurements could not be made on the central plane so the boundary measurements of the shear and vertical stresses were used. In this work, the shear stress is denoted by τ and the vertical stress by σ_v .

Palmeira (1987) discussed another method for the interpretation of results of shear tests. Jewell (1980) and Dyer (1985) reported that the horizontal plane in the centre of a shear box is a direction of zero extension. This observation and the assumption that the axes of principal stresses and principal strain increments coincide are used to form the method of interpretation illustrated in Figure 5.4b. The coincidence of the axes is fundamental to the theory of plasticity and was found to be true by Stroud (1971) in a simple shear box and by Dyer (1985) in a direct shear box. The direct shear angle of friction (ϕ_{ds}) is not measured on the plane of maximum stress ratio and therefore underestimates the maximum angle of friction

which can be obtained. The plane strain angle of friction (ϕ_{ps}) is the angle measured on the plane of maximum stress ratio (see Figure 5.4b). The two angles of friction can be related by the angle of dilation (ψ).


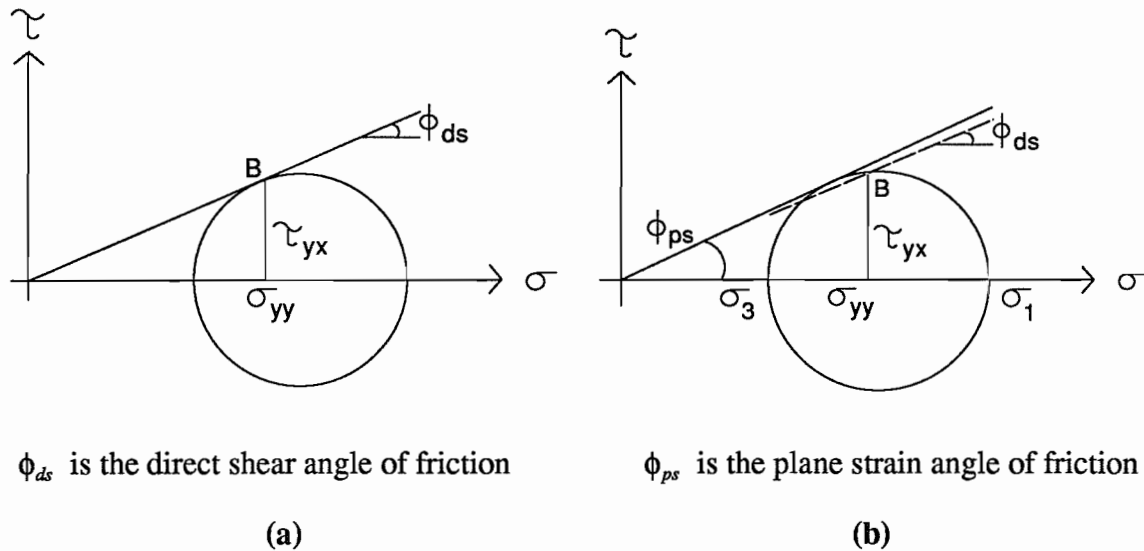


Figure 5.4 Shear test parameters

Note: σ_1 and σ_3 are the major and minor principal stresses

During shearing of a dense sample of material, it can be seen in Figure 5.5 that the band of material at the centre of the shear box dilates. To obtain the rate of dilation, the horizontal and vertical displacements are measured during a shear box test. The dense sample will dilate until it reaches a state when, during further shearing, the rate of dilation remains zero. This normally occurs towards the end of a test and is known as the critical state. If the sample is very loose, it will compress until it also reaches a condition in which the rate of dilation is zero. The angle of friction of the material in this state is termed the critical state angle of friction.

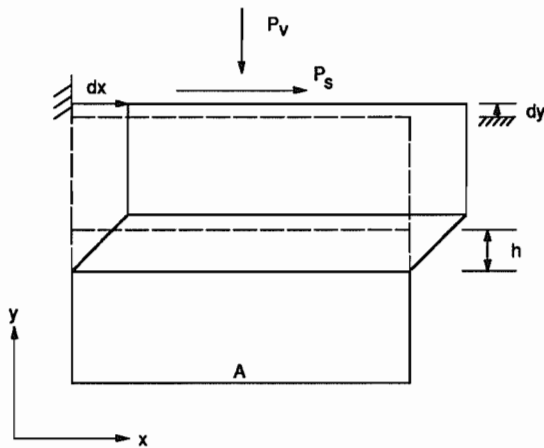

The vertical stress = $\sigma_v = P_v/A$ where A is the area of the shear box and P_v is the vertical force.

The shear stress = $\tau = P_s/A$ where P_s is the shear force.

The vertical strain increment = $dy/h = d\epsilon_{yy}$ and the

shear strain increment = $dx/h = d\gamma_{yx}$ where h is the deforming zone of the sample.

Therefore the rate of dilation is

$$\frac{dy}{dx} = \frac{d\epsilon_{yy}}{d\gamma_{yx}} = \tan \psi \quad \dots Eqn \quad 5.3$$

Figure 5.5 Definitions for the direct shear test (after Jewell, 1989)

The basic shear box data for series LA and LB are shown in Figures 5.6 to 5.8. The critical state direct shear angle of friction $(\phi_{ds})_{cv}$ tends to 42° when estimated from the extrapolation of the data at the end of the tests. It can be seen that a wide range of density was examined in series LA and as expected the data obtained from the dense samples showed an early and pronounced peak in shear strength but the loose samples achieved maximum shear strength gradually towards the end of the tests. The demolition debris data are shown in Figures 5.10 to 5.13 where $(\phi_{ds})_{cv}$ also tends to about 42° . The data from the tests on the samples containing particles larger than 37.5mm are shown in Figures 5.10 and 5.12. The peak stress ratio $(\tau/\sigma_v)_p$, where τ is the shear stress and σ_v is the vertical stress, for test D13 appears to be much higher than for the other tests. This may be partly due to the fact that in this test I_d was 0.9 whereas the highest I_d for tests D1 to D6 was 0.76. However, if the data for L1 in Figure 5.6 are examined, where $I_d = 0.9$, it can be seen that the $(\tau/\sigma_v)_p$ value is much lower than the high value of 2.2 which was obtained for D13.

Palmeira (1987) found that the direct shear angle of friction (ϕ_{ds}) was not significantly affected by the ratios L/D_{50} and H/D_{50} , where L was the length and H was the height of the shear box, for values varying from 38 to 1250 and from 20 to 1250 respectively. L/D_{50} was 30 and H/D_{50} was 18 for the demolition debris containing particles greater than 37.5mm where D_{50} for the material was 10mm. The particles therefore were too large to be tested satisfactorily in the 300mm shear box. This may have also contributed to the high $(\tau/\sigma_v)_p$ value for test D13. If a large particle lay directly in the plane of shear, then the measured shear stress would be much higher than if the sample was more uniform. The result from the test on the loose sample containing the large particles was similar to the results of the other tests in the DA series. For the tests on aggregates containing particles less than 37.5mm, the L/D_{50} values for limestone, demolition debris and crushed concrete were 49, 49 and 37 and the H/D_{50} values were 29, 29 and 23 respectively. Therefore for these tests the ratio of the scale of the box to the particle size was within the limits which Palmeira (1987) suggested.

The basic shear box data for crushed concrete are shown in Figures 5.14 to 5.17 where the trends in results appear to be similar to those for limestone and demolition debris. The sand results, illustrated in Figures 5.18 to 5.21, show that the peak stress ratio and dilation rates were much lower than for the aggregates and the critical state was reached after 15mm-20mm shear displacement whereas the aggregates had yet to reach the critical state after 30mm shear displacement. The sand reached the critical state quickly due to the smaller particle size and the greater uniformity of the material. The value of $(\phi_{ds})_{cv}$ for the sand, measured at the end of the tests, was between 29° and 30° .

The relationships between the peak direct shear angle of friction $(\phi_{ds})_p$ and $\rho_{d,peak}$ for the four materials are shown in Figure 5.22. Due to the difference in specific gravity of the materials (listed in Chapter 3) the $\rho_{d,peak}$ values of limestone were much higher. However, the $(\phi_{ds})_p$

values of limestone were similar to those of demolition debris and crushed concrete although the densities of these materials were much lower. Even at a low density of 1420kg/m^3 , the $(\phi_{ds})_p$ values of demolition debris and crushed concrete were 44° and 37° respectively. $(\phi_{ds})_p$ is plotted against I_d in Figure 5.23 where it can be seen that the relationships for the three aggregates are similar although crushed concrete had lower $(\phi_{ds})_p$ values. It was noticed during the compaction of crushed concrete that the fines in some tests formed sticky lumps and did not disperse evenly throughout the whole samples. This may have had some effect at low density when perhaps the large particles could not interlock closely. Demolition debris performed better than limestone at high values of I_d .

The peak direct shear angle of friction values ($(\phi_{ds})_p$) for the total A series are plotted against the rate of dilation (dy/dx) in Figure 5.24 to obtain an estimate of $(\phi_{ds})_{cv}$ for each of the aggregates. A good approximation for $(\phi_{ds})_{cv}$ can be obtained for the materials where the lines cross the abscissa. Using this method, $(\phi_{ds})_{cv}$ for the aggregates ranged between 37.5° and 40° with limestone achieving the highest value and crushed concrete the lowest. These $(\phi_{ds})_{cv}$ values appear to be lower than the approximation of 42° made earlier. The estimate of $(\phi_{ds})_{cv}$ from the end of the tests is likely to be less accurate because the critical state had not been reached in most cases (see Figures 5.6 to 5.17).

The relationships between $(\phi_{ds})_p$ and σ_v for series LB, DB, CB and SB are shown in Figure 5.25. The relationships were similar for demolition debris and limestone where $(\phi_{ds})_p$ did not vary very much. The data for sand followed a similar trend. However, crushed concrete had a slightly higher $(\phi_{ds})_p$ value at 50kN/m^2 and then $(\phi_{ds})_p$ decreased as σ_v increased. The range of $(\phi_{ds})_p$ obtained for all aggregates was quite small. It can be concluded from the data therefore that $(\phi_{ds})_p$ was influenced by density but was not very dependent on vertical stress.

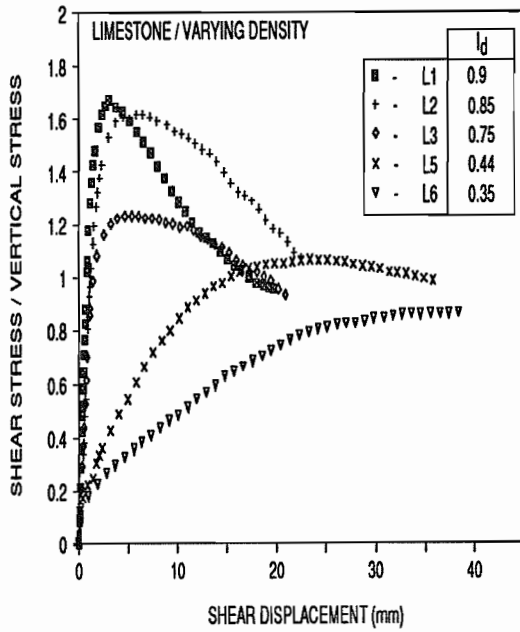


Figure 5.6 Stress ratio data for series LA

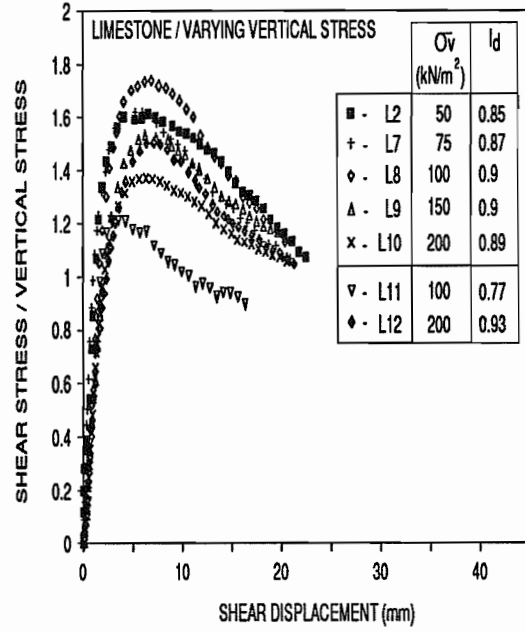


Figure 5.7 Stress ratio data for series LB

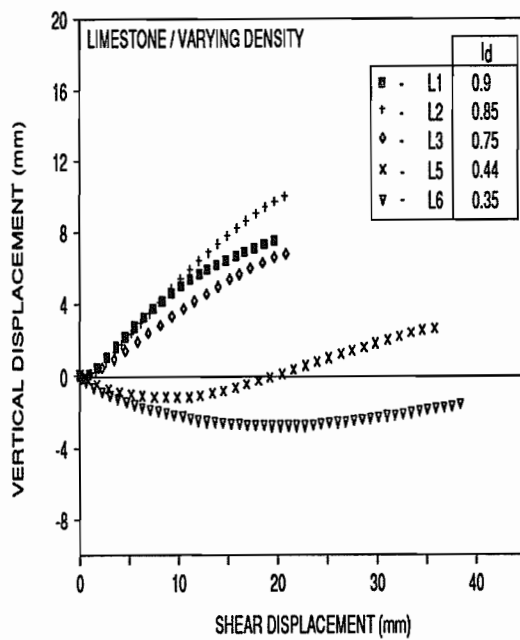


Figure 5.8 Vertical displacement data for series LA

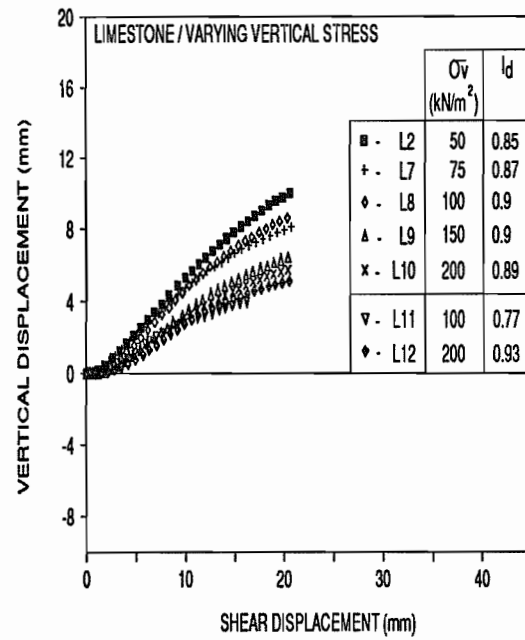


Figure 5.9 Vertical displacement data for series LB

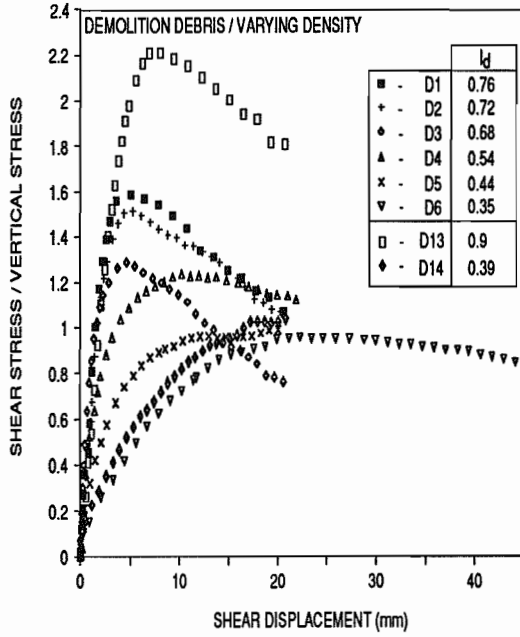


Figure 5.10 Stress ratio data for series DA

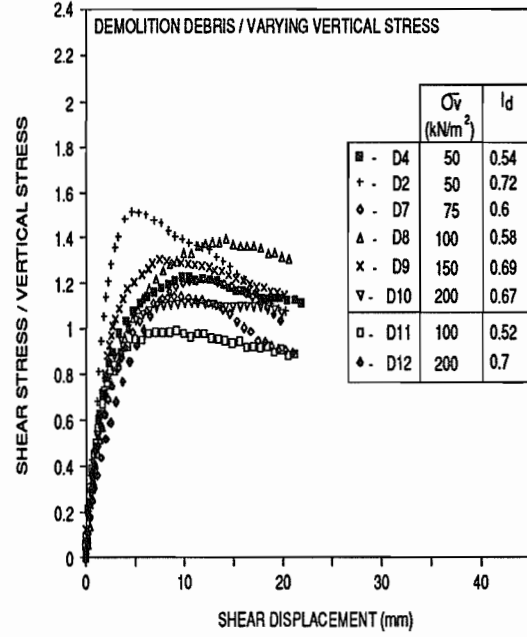


Figure 5.11 Stress ratio data for series DB

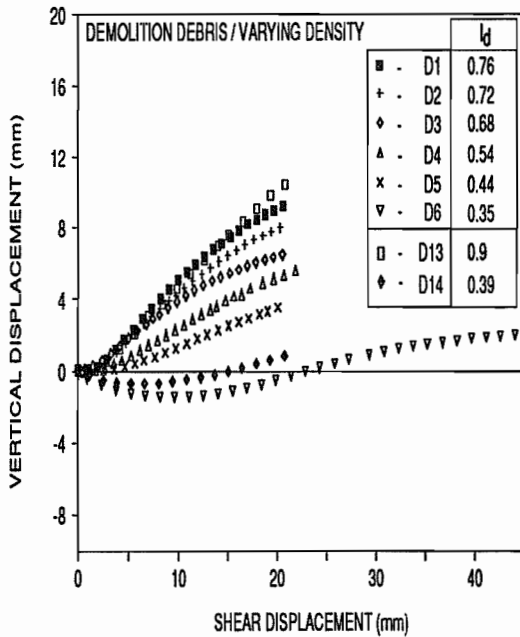


Figure 5.12 Vertical displacement data for series DA

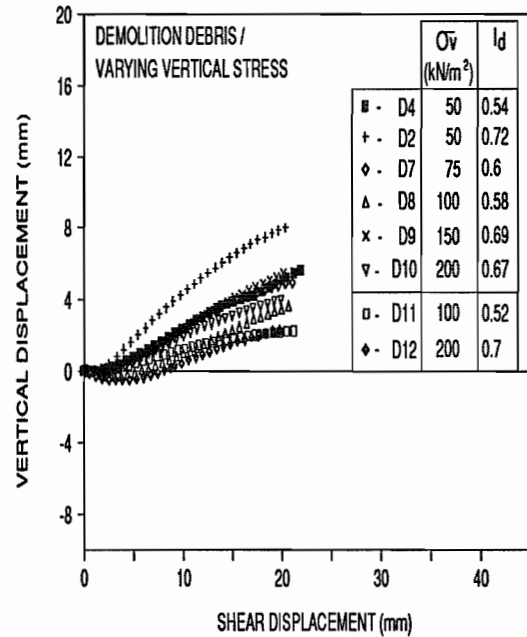


Figure 5.13 Vertical displacement data for series DB

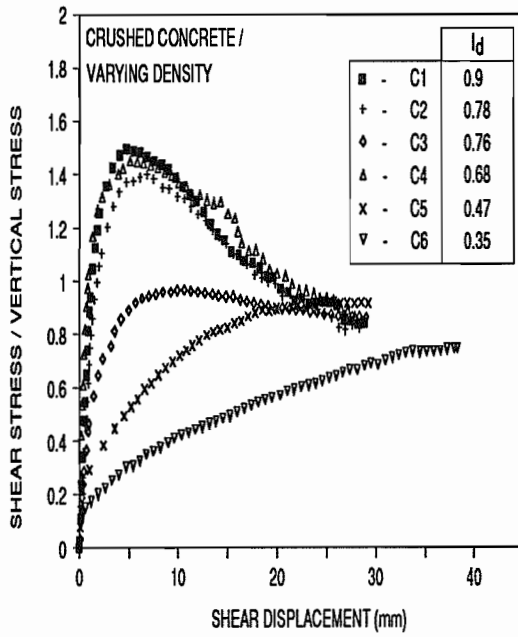


Figure 5.14 Stress ratio data for series CA

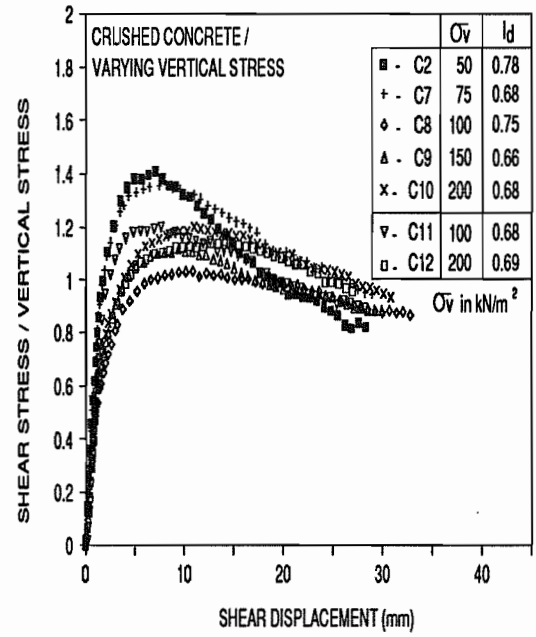


Figure 5.15 Stress ratio data for series CB

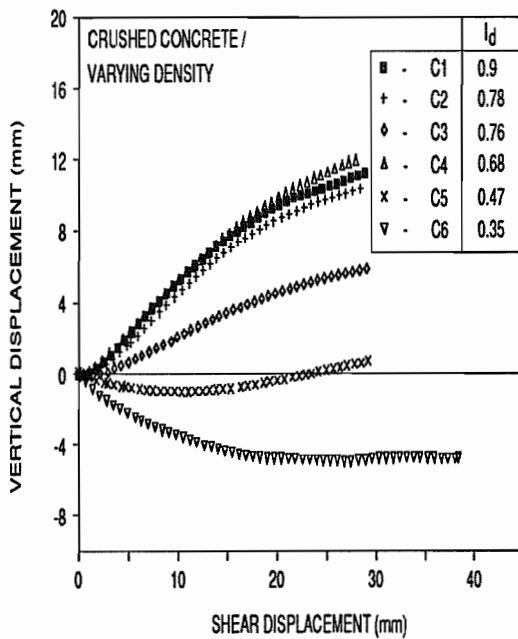


Figure 5.16 Vertical displacement data for series CA

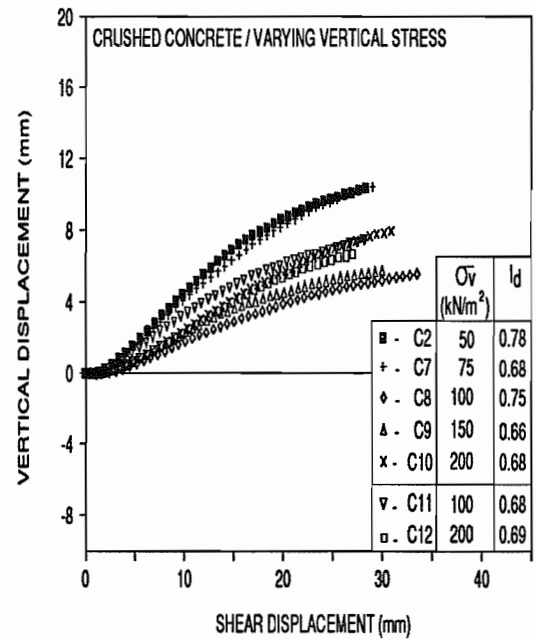


Figure 5.17 Vertical displacement data for series CB

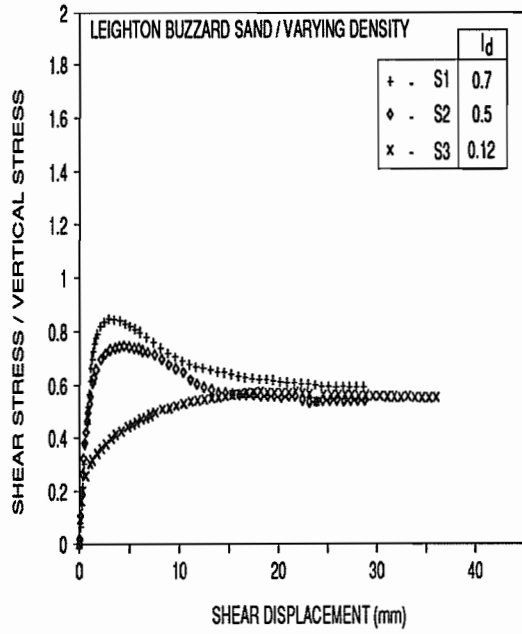


Figure 5.18 Stress ratio data for series SA

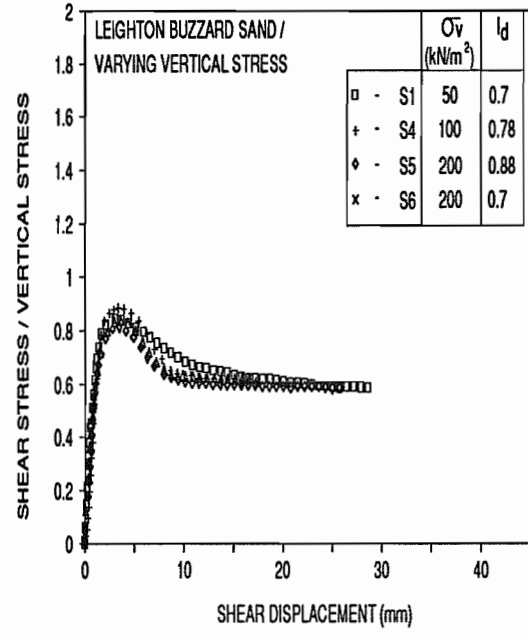


Figure 5.19 Stress ratio data for series SB

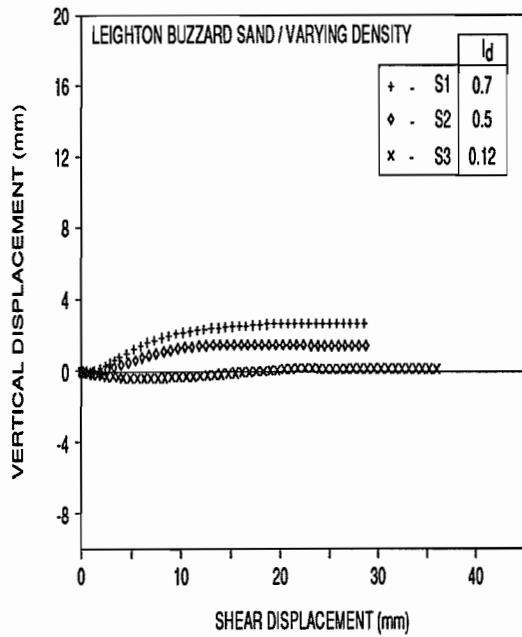


Figure 5.20 Vertical displacement data for series SA

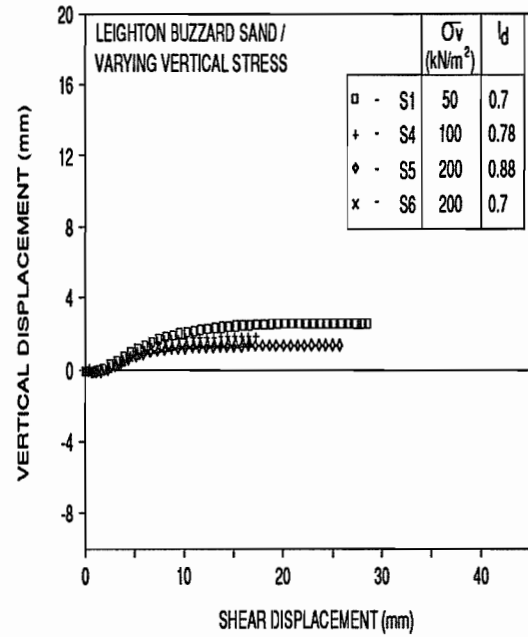


Figure 5.21 Vertical displacement data for series SB

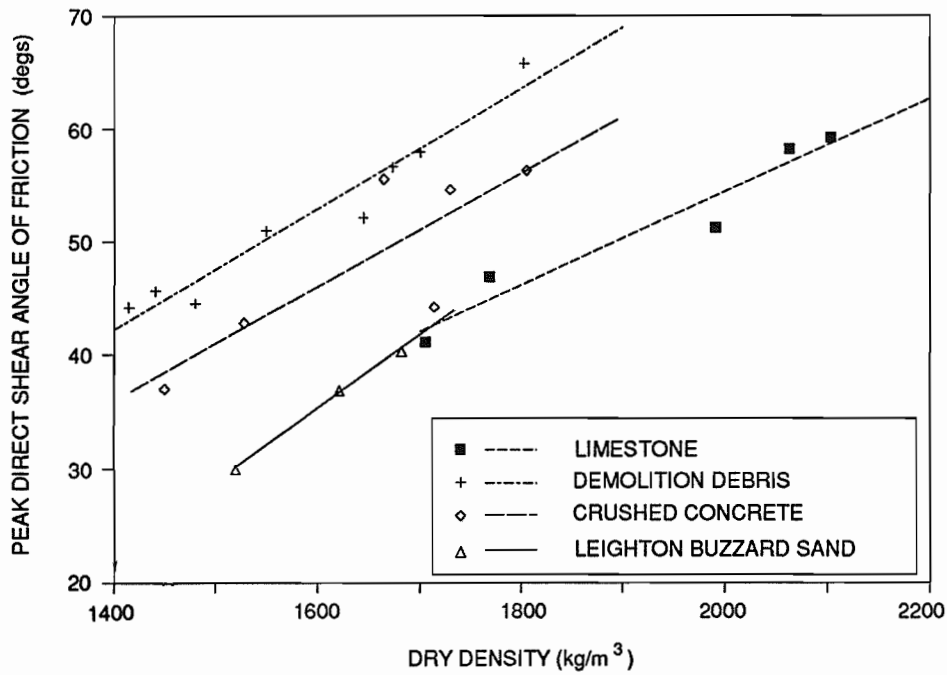


Figure 5.22 Influence of dry density on the peak direct shear angle of friction

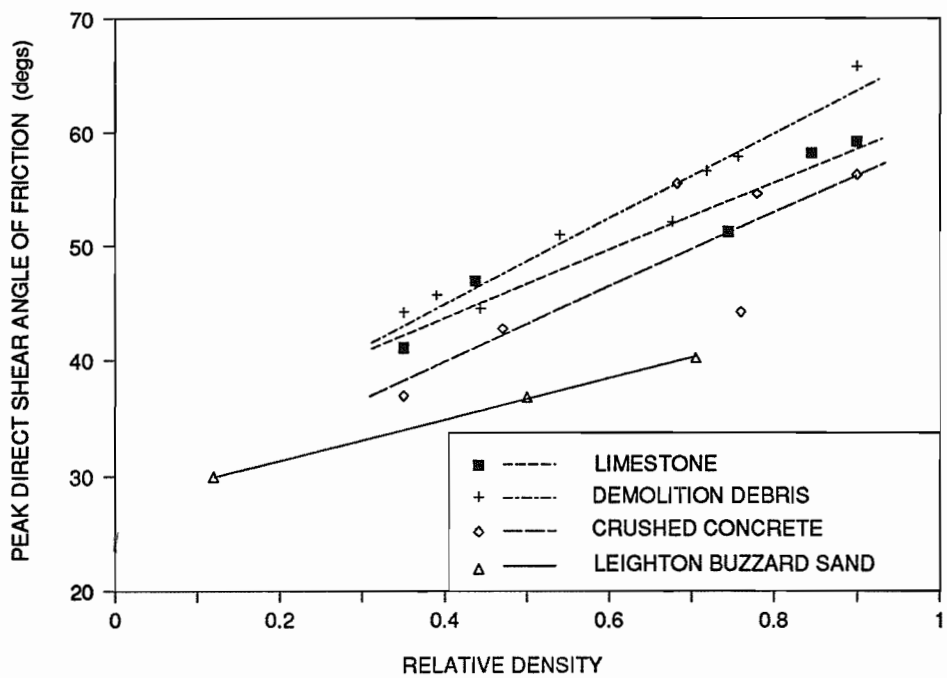


Figure 5.23 Influence of relative density on the peak direct shear angle of friction

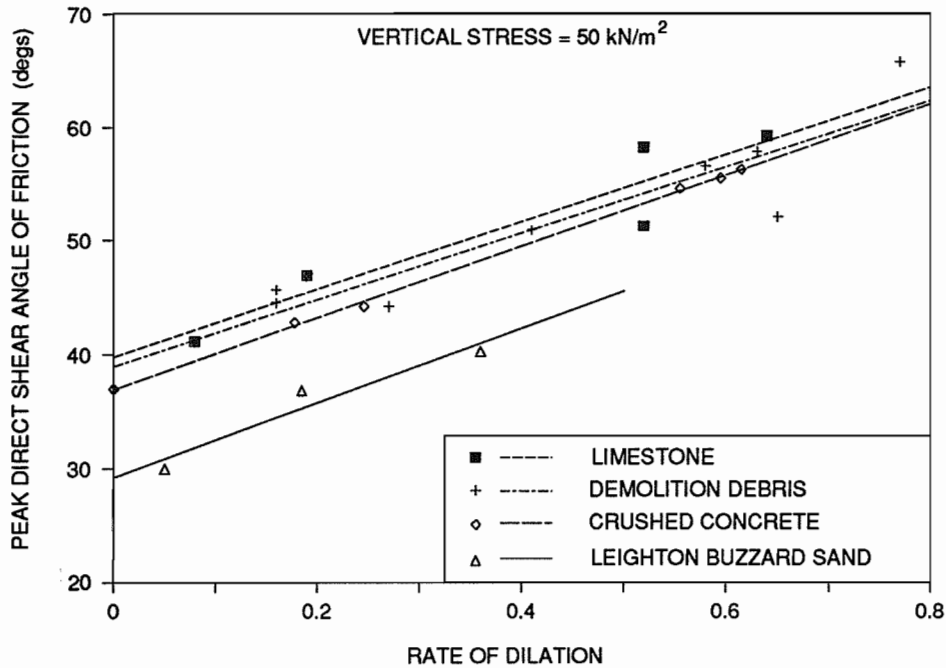


Figure 5.24 Peak rates of dilation for series A

In Figure 5.25, it can be seen for tests on limestone and demolition debris, conducted when the outer chamber of the shear box was flooded, that at a vertical stress of 100kN/m² the shear strength was lower than the results of similar tests conducted in a dry chamber. However, at a σ_v of 200kN/m², the shear strength appeared to be slightly higher. If the shear strength had dropped considerably in all tests conducted in the flooded chamber, it could be concluded that surface tension in the pore water of the unsaturated samples was causing high forces between the particles. These forces would have been reduced when the chamber was flooded and therefore the shear strength would also have been reduced. This phenomenon is normally associated with fine grained materials. Considerable scatter existed in the data and the effect of increased lubrication or surface tension in the pore water could not be determined quantitatively.

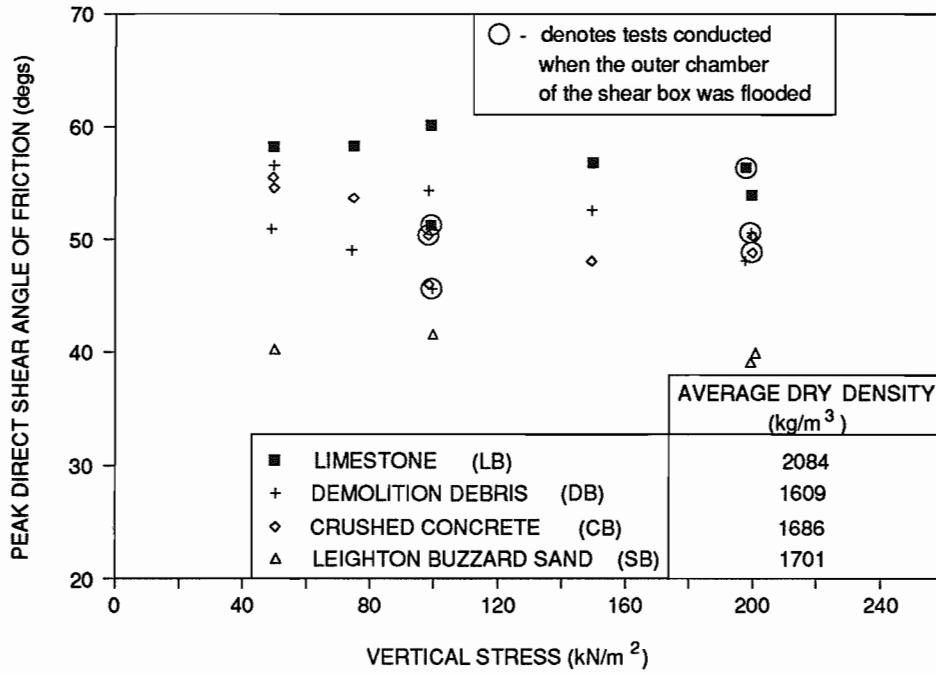


Figure 5.25 Influence of vertical stress on the peak direct shear angle of friction

5.8 Shear box tests for road sub-base materials

Earland and Pike (1985) produced a TRRL report describing a shear box test for the examination of the stability of granular sub-bases. They also made recommendations that the test could be used as a standard test for aggregates and suggested that it should be included in the British Standard for aggregate testing. A classification system for aggregates was established by comparing the results of a series of shear box tests with trafficking trials conducted on several aggregates. In the trafficking trials, conducted by Earland and Pike (1985), a 150mm thick layer of each aggregate was placed on a 250mm thick capping layer to provide a strip 5m in width. The lorries used for trafficking were restricted to channelled wheel paths. The $(\tau/\sigma_v)_p$ values from the shear box tests, which were conducted on the same materials in similar conditions, were plotted against the surface deformation caused by 1000 standard axles in the trials. From this plot, Earland and Pike (1985) produced the

following classification system for aggregates:-

- (a) **Low strength:** $(\tau/\sigma_v)_p$ less than 1.9. Materials in this category would not be suitable in sub-base layers but might be stable enough to be used as capping layer materials.
- (b) **Medium strength:** $(\tau/\sigma_v)_p$ between 1.9 and 2.8. Materials achieving these values may be stable in favourable conditions but their performance should be checked by a preliminary trafficking trial designed to simulate real conditions of service.
- (c) **High strength:** $(\tau/\sigma_v)_p$ above 2.8. Materials achieving these values should produce satisfactory sub-bases under normal construction traffic. A trafficking trial should be considered when exceptionally heavy lorries or plant are used, when there is extensive working in continuously wet weather or when poor drainage conditions exist.

For this shear box test (Earland and Pike, 1985), the aggregate was placed in a 300mm shear box between 96% and 98% of $\rho_{d,peak}$, where $\rho_{d,peak}$ was determined by the BS 5835 compaction test (1980). The vertical stress (σ_v) exerted on the material during the test was 10kN/m² which represented the surcharge expected to be placed on a sub-base on site. The rate of shear, specified by Earland and Pike (1985), was 1.0mm/min. Under these test conditions, $(\tau/\sigma_v)_p$ was reached rapidly and one of the major advantages of the test is that it is quick and the quality of an aggregate can be determined in a few hours. The mean of two tests is taken as the final result, if the difference between the two is less than 0.3.

This test was performed on limestone, crushed concrete and demolition debris to determine whether they could be used as satisfactory sub-base materials with regard to the classification system. The results are listed in Table 5.6.

AGGREGATE TYPE	$(\tau/\sigma_v)_p$
Limestone	3.2
Demolition debris	2.5
Crushed concrete	1.9

Table 5.6 Peak stress ratio values obtained using the TRRL shear box test

The result for crushed concrete was lower than that of demolition debris but both materials were in the medium strength category. Limestone, as expected, would provide a sub-base of high strength. The result for limestone was confirmed by Earland and Pike (1985) who also carried out similar tests on limestone from the same source in Somerset and found $(\tau/\sigma_v)_p$ to be 3. With regard to stability, the recycled aggregates could be used as road sub-base material, provided that a preliminary trafficking trial was carried out in conditions similar to those expected on site.

Earland and Pike (1985) found that the difference between $(\tau/\sigma_v)_p$ results for tests conducted on similar samples was 0.3. From the results of the tests conducted on limestone, demolition debris and crushed concrete, it was found that the differences were 0.3, 0.13 and 0.07 respectively.

5.9 Analysis

A flow rule analysis using Taylor's energy correction (1948) is presented in Section 5.9.1 for the data from the tests on the aggregates and sand which were presented in Section 5.7. In Section 5.9.2, the data is interpreted and analysed using Bolton's (1986) dilatancy index.

5.9.1 The flow rule analysis

A flow rule relates strains and stresses during the plastic flow of a material and therefore the balance of energy in a direct shear test can be examined by a flow rule. A soil element in the central region of the shear box after an increment of shear strain is examined. By using the energy correction proposed by Taylor (1948), it can be derived that the increment of energy per unit volume of this soil element is

$$\frac{\tau_{yx}}{\sigma_{yy}} + \frac{d\varepsilon_{yy}}{d\gamma_{yx}} = m \quad \dots Eqn \ 5.4$$

where τ_{yx}/σ_{yy} is the stress ratio measured on the central plane
and
 m is a constant which equals the stress ratio when the rate of dilation is zero.

Assuming that the horizontal is a direction of zero extension and that the axes of principal stresses and principal strain increments coincide, Eqn 5.4 reduces to

$$\frac{\tau_{yx}}{\sigma_{yy}} - \tan \psi = \sin \phi_{cv} \quad \dots Eqn \ 5.5$$

where ψ is the angle of dilation and

ϕ_{cv} is the critical state angle of friction (Jewell, 1989).

As measurements could not be made on the central plane, the boundary measurements of the stress ratio (τ/σ_v) and rate of dilation (dy/dx) were used in the analysis. For each test, the values between $(\tau/\sigma_v)_p$ and τ/σ_v at the end of the test were plotted against dy/dx . A selection of these graphs is presented in Figures 5.26 to 5.30. If there was a uniform zone of deforming material in the tests, then these plots should give 1:1 lines which would intersect the abscissa at $\sin \phi_{cv}$ (Jewell, 1989). This was not expected for the test data presented here because when a free top platen is used, rotation is apparent due to the non-symmetrical arrangement of the shear box (Jewell, 1989). Jewell (1989) also noted that measurement of the rate of dilation on the boundary of a shear box underestimates the rate of dilation on the central plane and he also found that even when a symmetrical direct shear box is used i.e. with a fixed top platen, the measured stress ratio is still higher than in a simple shear box arrangement (Jewell 1989). These conclusions by Jewell (1989) would suggest that the plot of τ/σ_v against dy/dx would give higher slopes than 1:1 for the data presented here.

In Figures 5.26 to 5.30, it can be seen that some data cross a 1:1 line and some have higher slopes. The data shown are for tests on reasonably dense material. The results from tests on loose samples were difficult to interpret as little data existed beyond the $(\tau/\sigma_v)_p$ value. For the following analysis a reasonably accurate value of ϕ_{cv} was needed.

Looking at Figures 5.26 and 5.27, it can be seen that two values of ϕ_{cv} could be obtained depending on whether a 1:1 line was drawn from the intersection of the data points with the abscissa or whether the line was drawn from the point of maximum rate of dilation back to the abscissa. Both lines were drawn on the graphs of test results where the data had a slope of less than 1 and consequently lower and upper limits of ϕ_{cv} were found. For plots where

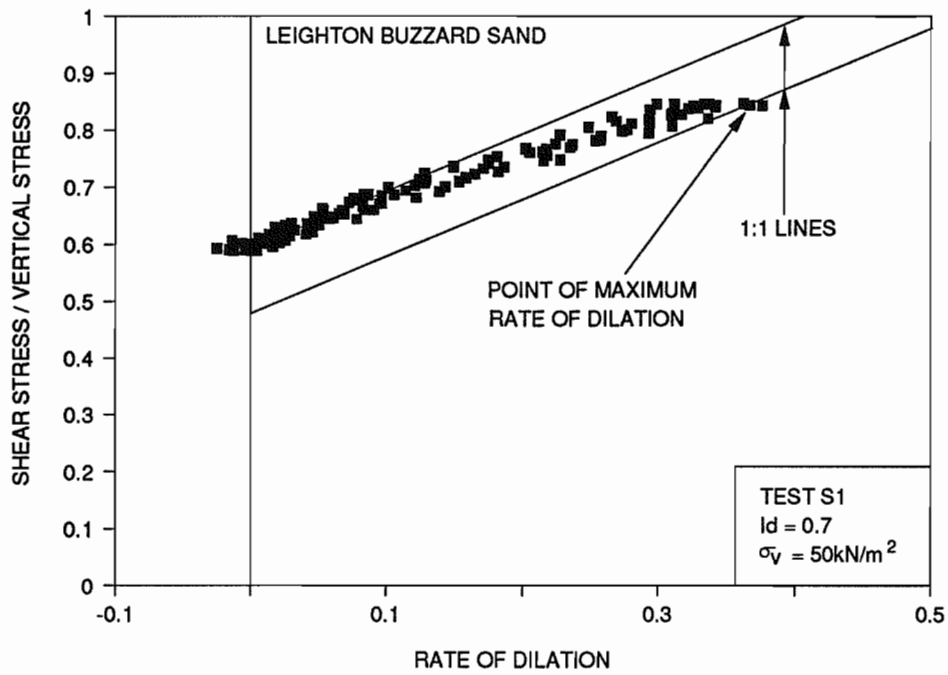


Figure 5.26 Relationship between stress ratio and rate of dilation for S1

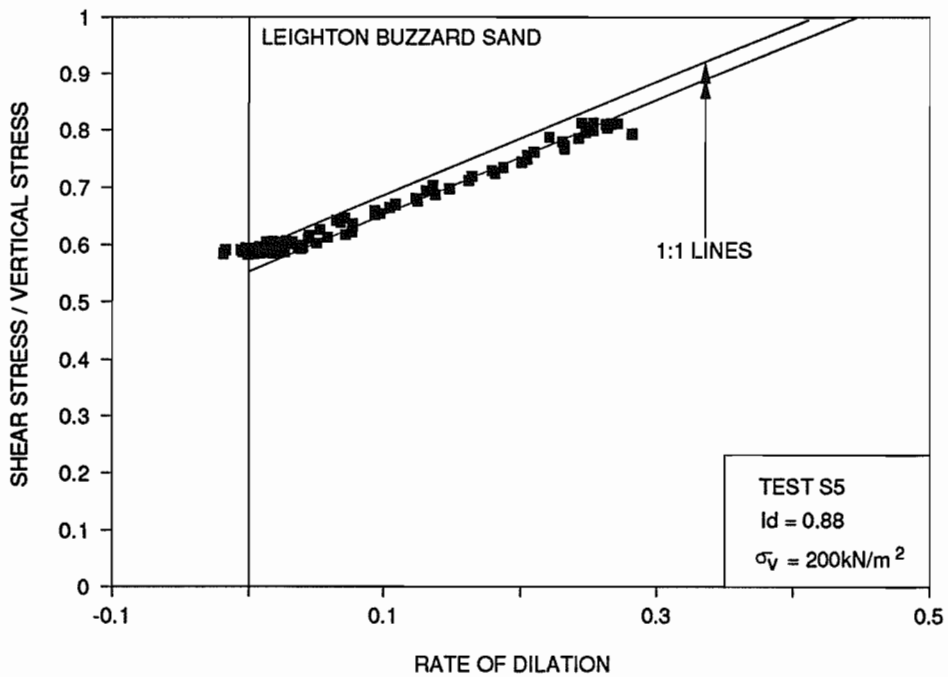


Figure 5.27 Relationship between stress ratio and rate of dilation for S5

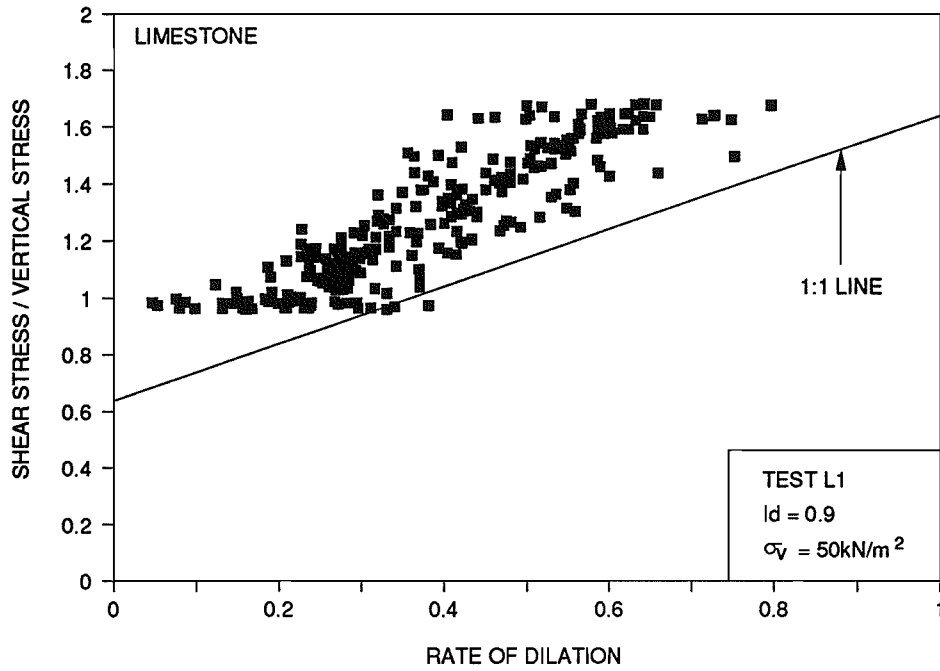


Figure 5.28 Relationship between stress ratio and rate of dilation for L1

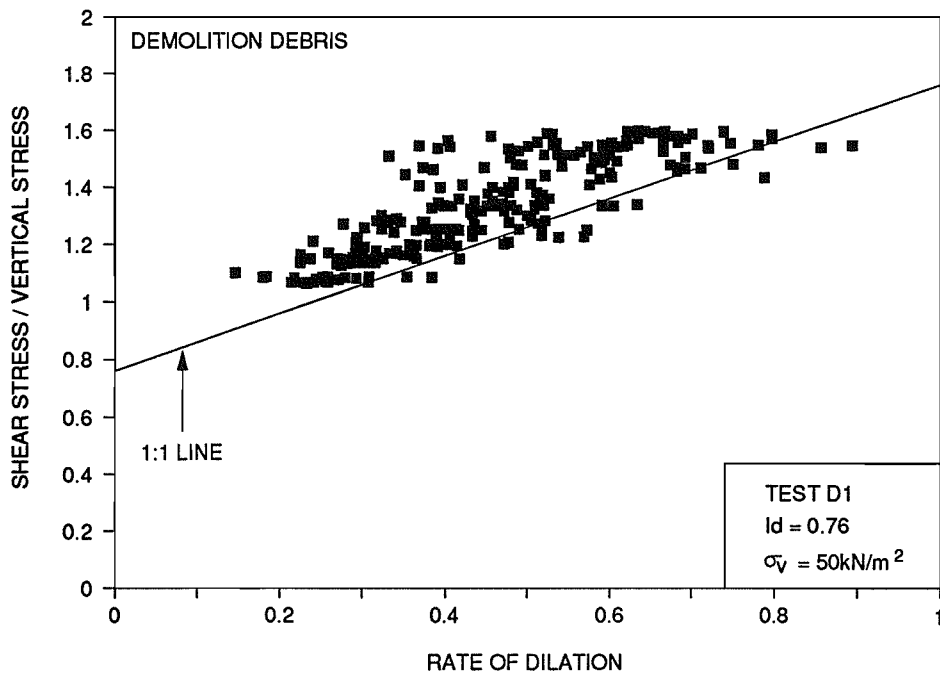


Figure 5.29 Relationship between stress ratio and rate of dilation for D1

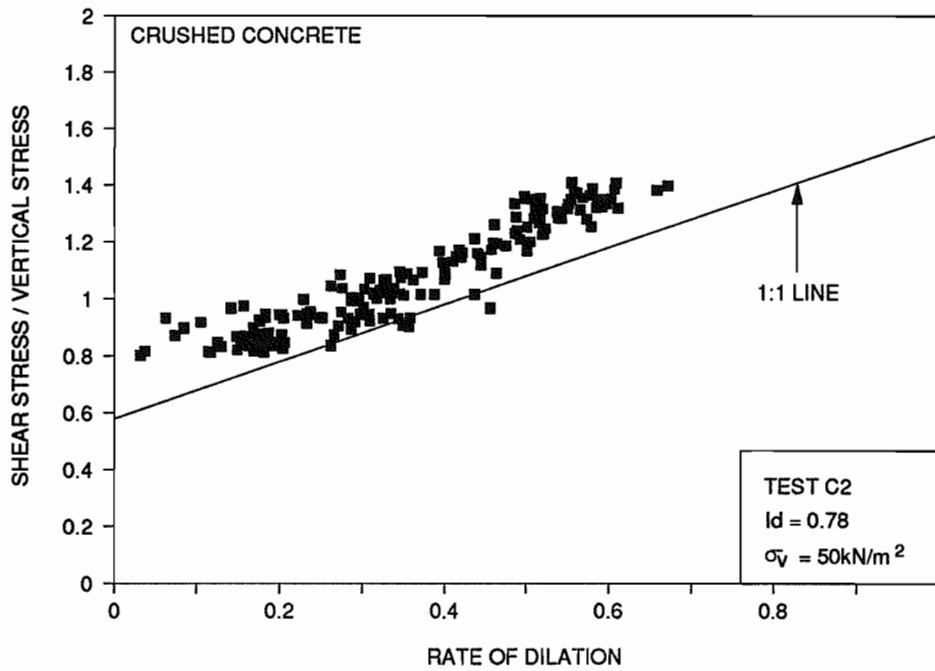


Figure 5.30 Relationship between stress ratio and rate of dilation for C2

the slope was greater than 1, the expected intersection of the data with the abscissa was taken to be ϕ_{cv} . This method of estimating ϕ_{cv} was similar to that used by Jewell (1989). The average upper and lower values of ϕ_{cv} , which are used in the following analysis, are listed in Table 5.7.

MATERIAL TYPE	ϕ_{cv} (degrees)	
	UPPER LIMIT	LOWER LIMIT
Leighton Buzzard sand	34.5	27
Limestone	45	35
Demolition debris	47	36
Crushed concrete	49	37

Table 5.7 Upper and lower limits of ϕ_{cv} used in the analysis

5.9.2 Analysis using dilatancy index

By using the values of ϕ_{cv} in Table 5.7 and the $(\phi_{ds})_p$ values for each of the tests, the peak plane strain angle of friction $(\phi_{ps})_p$ could be found using the following equation derived by Rowe (1969).

$$\tan \phi_{ds} = \tan \phi_{ps} \cos \phi_{cv} \quad \dots \text{Eqn } 5.6$$

Bolton (1986) developed a consistent treatment of both density and confining pressure in shear box tests by using a dilatancy index (I_r) which he defined as follows:-

$$I_r = I_d(Q - \ln p') - R \quad \dots \text{Eqn } 5.7$$

where I_d = relative density,
 Q = a constant depending on material type,
 p' = mean effective stress and
 R = a constant = 1.

Bolton (1986) stated that Q was dependent on the compressibility and mineralogy of the particles of material and found $Q = 10$ for quartz and felspar sands. It was suggested that for other materials Q could range from 5.5 for chalk to 8 for limestone.

To find I_r , the mean effective stress p' must be calculated. A formula for p' can be derived using the geometry of the Mohr circle of stress shown in Figure 5.31.

The mean principal stress is defined as

$$s = \frac{\sigma_1 + \sigma_3}{2} \quad \dots \text{Eqn } 5.8$$

and the maximum shear stress is

$$t = \frac{\sigma_1 - \sigma_3}{2} \quad \dots Eqn \ 5.9$$

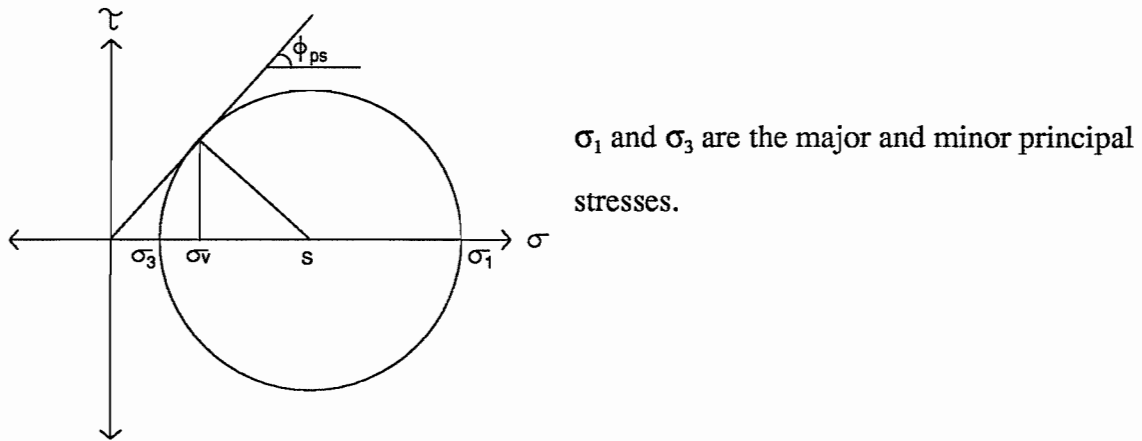


Figure 5.31 Mohr circle of stress

Stroud (1971) found in a simple shear box arrangement that the intermediate stress σ_2 was $0.74s$. By substituting this value into the equation for mean effective stress

$$p' = \frac{\sigma_1 + \sigma_2 + \sigma_3}{3} \quad \dots Eqn \ 5.10$$

it can be concluded that s is a good approximation for p' . From the geometry in Figure 5.31, the mean effective stress can be defined as

$$p' = \frac{\sigma_v}{\cos^2 \phi_{ps}} \quad \dots Eqn \ 5.11$$

Each of the aggregates was dealt with separately but both series A and B for each material were used in the analysis, regardless of vertical stress or density. Assuming a start value

of $Q = 10$, I_r was calculated for each test using Eqn 5.7. The I_r values were then plotted against the corresponding $(\phi_{ps})_p$ values. To examine the accuracy of the chosen value of Q , the following calculations were made.

Bolton (1986) stated that for plane strain

$$(\phi_{ps})_p - \phi_{cv} = 5I_r \quad \dots \text{Eqn } 5.12$$

For a range of $(\phi_{ps})_p$ from 35° to 70° , I_r values were calculated using Eqn 5.12 and the resulting linear relationship between $(\phi_{ps})_p$ and I_r was drawn on the same plot as the I_r obtained from the experimental data. By varying the value of Q in the calculations, the points on the graph were made to have the best fit to the calculated line.

This procedure was carried out for each material for the upper and lower limits of ϕ_{cv} and the results of the analysis can be seen in Figures 5.32 to 5.35. An intermediate value of ϕ_{cv} was obtained from these graphs. The determination for Leighton Buzzard sand in Figure 5.32 was influenced by the universal acceptance that ϕ_{cv} for Leighton Buzzard sand is 33° . The final values of Q and ϕ_{cv} from the analysis are listed in Table 5.8 along with ϕ_{cv} values which were determined from the loose heap test (Cornforth, 1973).

Cornforth (1973) stated that an approximation of ϕ_{cv} could be made by tipping a material quickly to form a loose heap and excavating from the toe until a smooth slope is formed. The angle of this slope to the horizontal is ϕ_{cv} and Cornforth (1973) found that it could be measured to an accuracy of 1° .

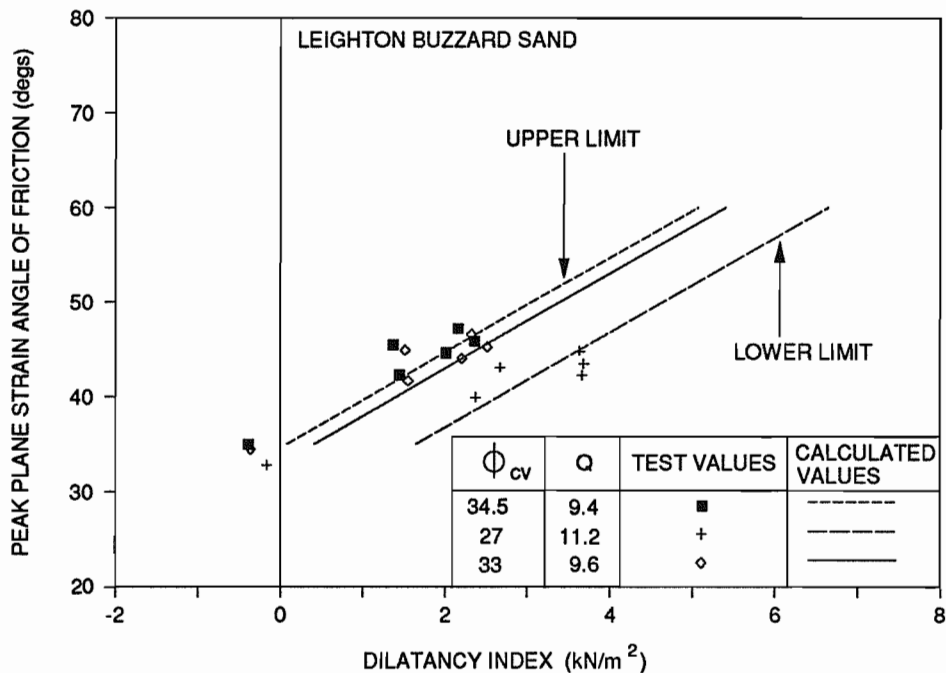


Figure 5.32 Determination of Q for Leighton Buzzard sand

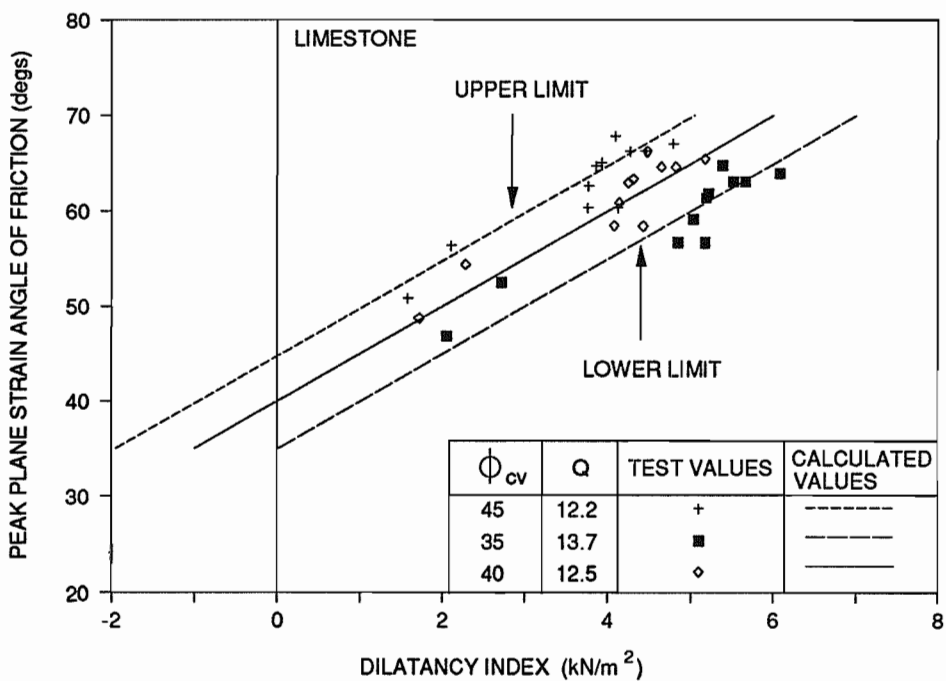


Figure 5.33 Determination of Q for limestone

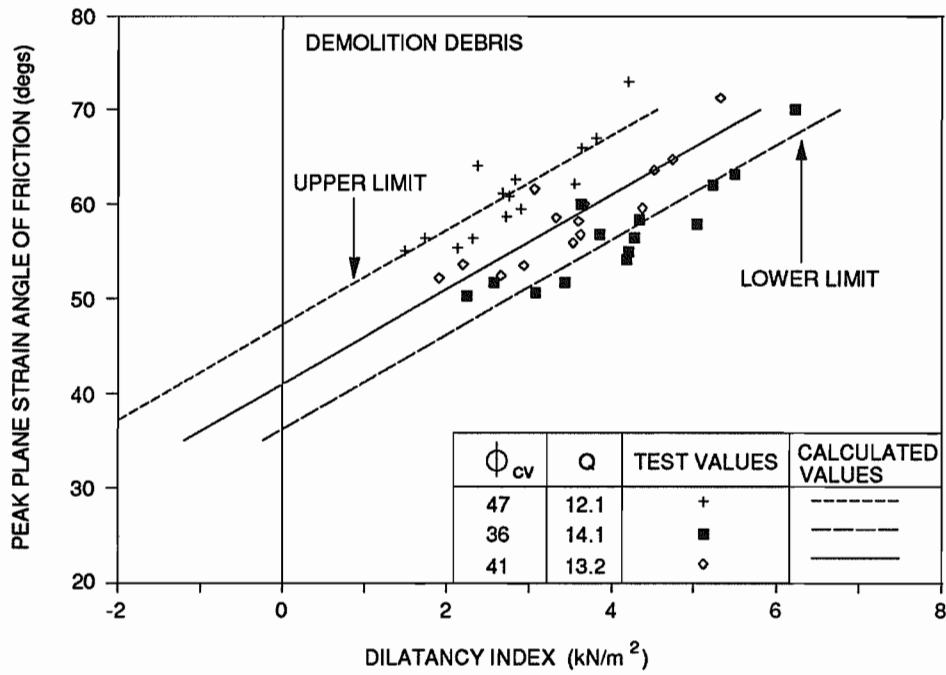


Figure 5.34 Determination of Q for demolition debris

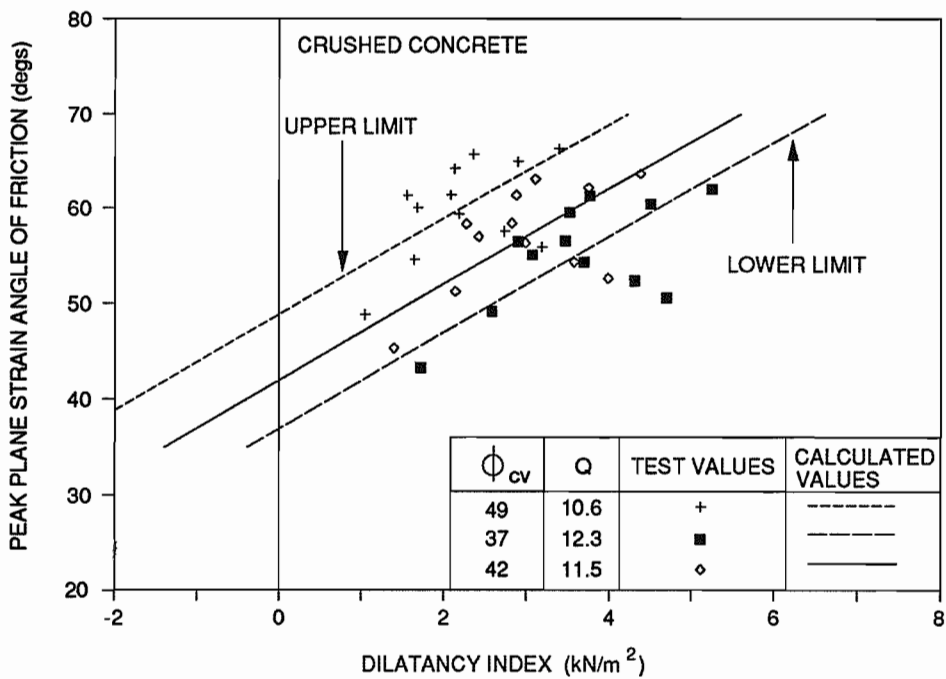


Figure 5.35 Determination of Q for crushed concrete

MATERIAL TYPE	ϕ_{cv} (degrees)	Q	ϕ_{cv} (degrees) Loose heap
Leighton Buzzard sand	33	9.6	33
Limestone	40	12.5	42.5
Demolition debris	41	13.2	37
Crushed concrete	42	11.5	39.5

Table 5.8 Results of analysis on shear box test data

A summary of the test data and the results of the analysis can be seen in Figures 5.36 to 5.39. For each material, calculated values of $(\phi_{ps})_p$ were plotted against p' for a range of I_d between 0.2 and 1. To obtain these calculated values, I_r was first determined for a range of I_d and p' using Eqn 5.7 and then $(\phi_{ps})_p$ was found using Eqn 5.12. The I_d of the test samples were also plotted as points on the figures. In general, the calculated values appeared to match the test data quite well.

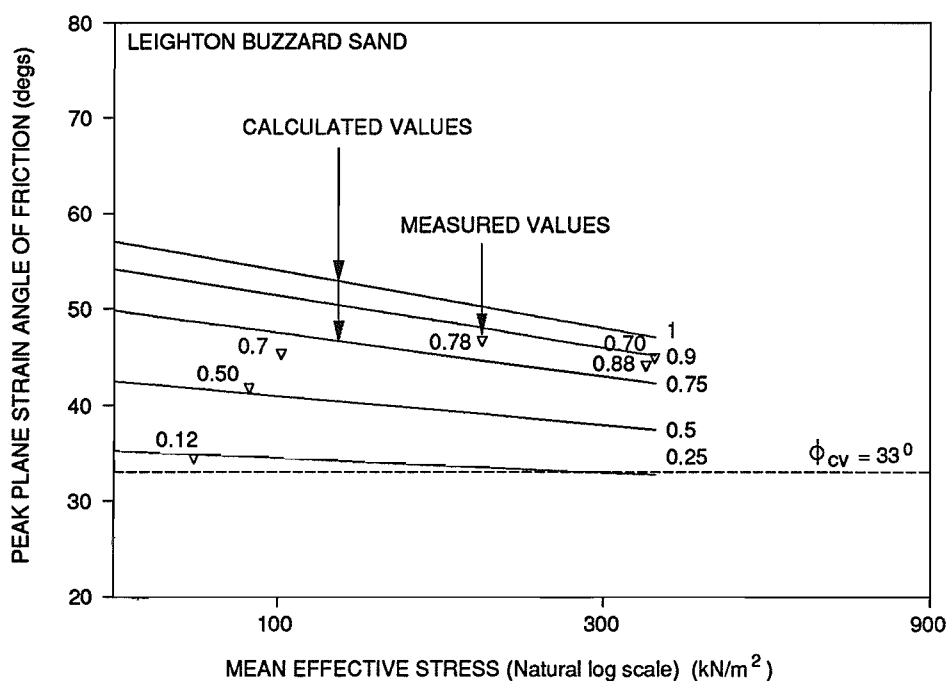


Figure 5.36 Comparison between calculations and experimental data for Leighton Buzzard sand

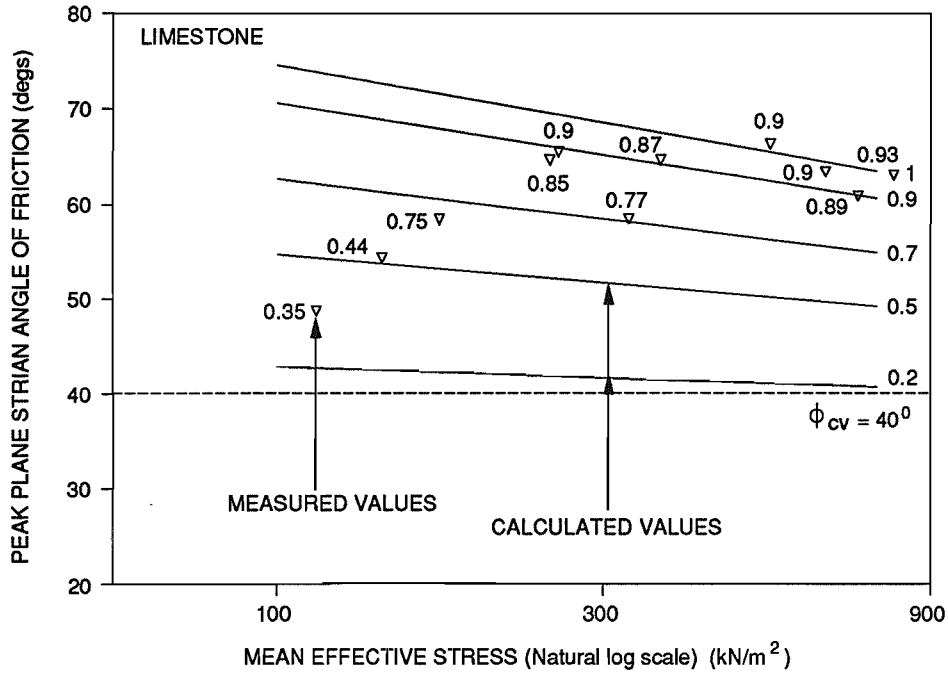


Figure 5.37 Comparison between calculations and experimental data for limestone

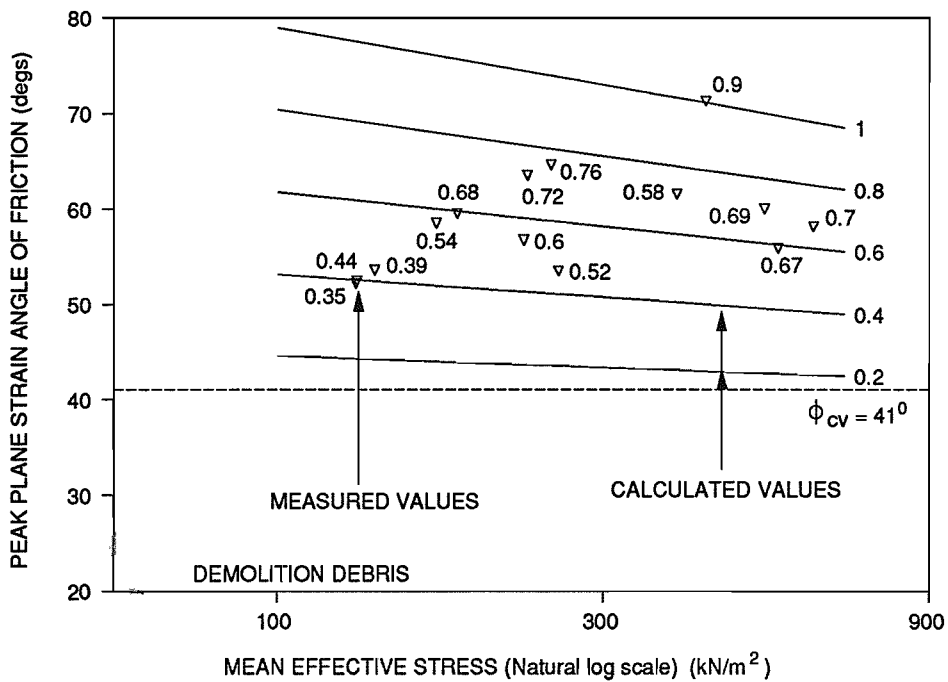


Figure 5.38 Comparison between calculations and experimental data for demolition debris

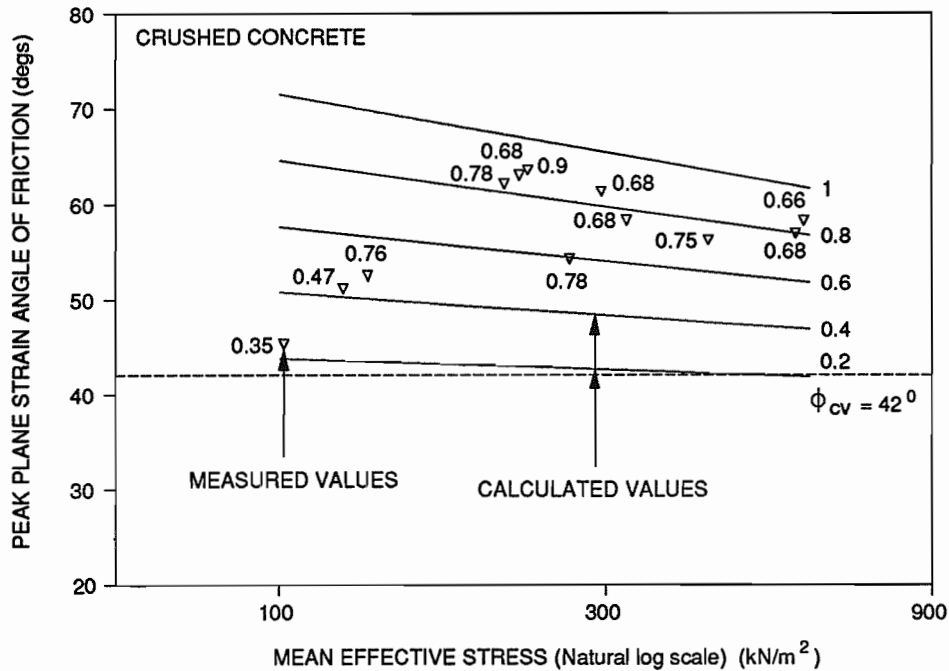


Figure 5.39 Comparison between calculations and experimental data for crushed concrete

5.10 Discussion

It is clear from Figure 5.22 that demolition debris and crushed concrete could be used successfully as backfill to structures because $(\phi_{ds})_p$ for both materials was found to be quite high, particularly for dense samples. These recycled aggregates could be considered as lightweight and this property along with high shear strength could be useful in operations where high quality gravel is used at present. In the TRRL report by Naish (1988), an investigation of the cost of backfill around bridge abutments and retaining walls was summarised. It was estimated that the use of a lower quality fill instead of granular fill, as defined by the Specification for Highway Works (1986), would reduce the cost of each structure by about £18,000 which would represent a reduction from 9% to 5% of the total cost of the structure. The use of recycled aggregates might reduce this cost further depending on the location of a particular site and the cost of transport.

Some tests, conducted when the chamber surrounding the shear box was full of water, exhibited low values of $(\phi_{ds})_p$ compared with the results of tests carried out when the chamber was dry. These lower values could be explained if pore suction had developed in the materials or if more lubrication between particles was provided by the additional water. However, some samples which were tested when the chamber was flooded exhibited higher shear strength. This is difficult to explain and it can only be concluded that the scatter in the data, caused by the variation in particle size of the samples, is too large to determine whether pore suction existed. Pore suction is normally associated with materials containing small grains and is unlikely to be a significant factor in the tests on the aggregates described earlier.

Bolton (1986) stated that Q depends on the mineralogy and compressibility of a material and suggested that Q should be lower for a material containing soft grains. It is not clear in his paper whether this recommendation was made specifically for small grained, uniform materials. It appears from the results quoted earlier in Section 5.9.2 that Q may be dependent on the coefficient of uniformity, the ratio of the shear box dimensions to the maximum particle size or angularity.

It was found by Bolton (1986) for tests on sands that Eqn 5.12 could be used between the limits of $0 < I_r < 4$ and he suggested that the upper limit of 4 should be used unless good low stress data was obtained for a particular material. This recommendation was not followed in this research because much of the test data was obtained at low stress levels and would have had to be ignored. All data from the tests on aggregates fitted the correlations well but these data suggest that the limit of

$$(\phi_{ps})_p - \phi_{cv} = 20^\circ \quad \dots Eqn \quad 5.13$$

is too conservative for well graded aggregates and should be extended to

$$(\phi_{ps})_p - \phi_{cv} = 25^\circ \quad \dots Eqn \quad 5.14$$

i.e. raising the upper limit of I_r to 5. It is agreed that Bolton's (1986) recommendation should be adhered to for sand as the data from this research were within the limits of Eqn 5.13.

When comparing the ϕ_{cv} values in Table 5.8, it can be seen that demolition debris achieved a value of 37° in the loose heap test which was 4° lower than that obtained in the analysis. However, the loose heap test result for limestone was 2.5° higher than the result from the analysis and for crushed concrete it was 2.5° lower. The accuracy of the loose heap test on well graded aggregates therefore was lower than the 1° accuracy which Cornforth (1973) found for tests on sands. However, it would be expected that the slope of a heap of material containing non-uniform and large particles would not be as well defined as that of a heap of sand where the particles are small and uniform. The mass of sand tested in the loose heap test was 2kg whereas the mass of aggregate tested was 15kg. The results of the tests on the aggregates suggest that an even larger quantity of aggregate would be required to obtain an accuracy of 1° .

5.11 Conclusions

- (i) There appeared to be little difference between the shear strength of limestone and that of the recycled aggregates and friction angles between 54° and 58° were obtained at high densities.
- (ii) With regard to Earland and Pike's (1985) shear box test for the determination of the suitability of aggregates for use as road sub-base material, limestone would be classed as high strength and the recycled materials as medium strength aggregates.

- (iii) The effect of flooding the outer chamber of the shear box apparatus caused a reduction in strength for some tests but an increase in others. The effect of pore suction could not be determined quantitatively due to the scatter in the results. It is likely that this scatter was caused by the variation in particle size and content of the aggregates.
- (iv) Although Bolton (1986) suggested that materials containing grains which were softer than quartz or felspar should have Q values (constant in the formula for dilatancy index) of less than 10, the Q values determined for the aggregates in this study ranged between 11.5 and 13.2.
- (v) The critical state angles of friction of the aggregates were found to be between 40° and 42° but the difference between the calculated and the measured values using the loose heap test varied between 2.5° and 4° . It was concluded that the 1° accuracy which Cornforth (1973) found for sands in the loose heap test could not be achieved for well graded aggregates unless very large quantities of material were used.

CHAPTER 6

FROST SUSCEPTIBILITY TESTS

6.1 Introduction

No materials placed within 450mm of any road surface in Britain should be susceptible to frost, as defined by the Transport and Road Research Laboratory test described by Roe and Webster (1984). Although long periods of freezing are uncommon in the British climate, severe winters do occur. These winters include 40 consecutive or near consecutive days of frost, the last one having been the winter of 1962/63.

It has been found that there is an increase in the number of road failures during and following severe winters. Deterioration of a road pavement can occur in three ways.

- a) When water penetrates the road surface, damage can be caused by the expansion of water as ice forms. This type of deterioration can be avoided by better construction and maintenance techniques and particularly if the road surface is sealed.
- b) A more serious type of damage can be caused to road surfaces by the formation of ice lenses in the lower layers which causes the road pavement to heave.
- c) When a pavement has been damaged by either of the ways described in a) or b), a further loss of strength may occur when the ice thaws because the material will have a higher moisture content and therefore a reduced bearing capacity. In this condition, the road is more likely to fail under traffic loading.

The frost heave test, described by Roe and Webster (1984), is a laboratory test simulating frost heave in the field. In this research, the frost heave of limestone and recycled aggregates

was examined because their potential use within 450mm of a road surface would require them not to be susceptible to frost, as stipulated by the Specification for Highway Works (1986).

6.2 The explanation of frost heave

The frost heave process was described by Croney and Jacobs (1967) and a summary of their explanation is given below. During an isolated cold night, when the temperature of the air above the road surface is several degrees below freezing point, the zero isotherm may penetrate the pavement as much as 100mm. If, during the following day, the temperature of the air rises above 0°C, the low temperatures in the pavement will also rise above freezing point within a few hours. However, if the temperature remains below 0°C for about three days, the zero isotherm may penetrate up to 300mm and following a ten day period, penetration may be more than 375mm. From measurements made by Croney and Jacobs (1967) during the winter of 1962/63, it was deduced that a much slower rate of penetration occurred at depths greater than 375mm. If after ten days, for example, the air temperature rises above freezing point for a few days this would not reduce the maximum penetration of the frost in the pavement but the temperature in the top 100mm could rise above 0°C. During a particularly severe winter, the surfacing and the top part of the base may be subjected to many cycles of freezing and thawing but the lower layers would remain frozen and the freezing front (boundary of the freezing zone) would continue to move downwards.

The layers in a road pavement which are most susceptible to frost heave are the sub-base and the subgrade. The pore spaces in these layers are generally large enough to accommodate the expansion of water contained in them when freezing starts. However, during freezing more water rises from the unfrozen material by capillary action. The pore spaces do not

have the capacity to hold this extra water when it expands on freezing. Figure 6.1 illustrates the situation in a road pavement when the top layer becomes frozen. Croney and Jacobs (1967) explained the capillary movement which causes the upward flow of water as follows:-

At temperatures above 0°C , the water in moist porous materials has a negative pressure or suction which is due to the surface tension and absorption forces (Croney and Jacobs, 1967). Suction increases rapidly with decreasing moisture content. Croney and Jacobs (1967) conducted tests under a 150mm thick concrete pavement in Harmondsworth in January 1963. It was found in these tests when water froze in the pores of a material that a pressure gradient developed between the ice and the unfrozen water below. Above the level of the zero isotherm the suction increased to a value between 10 and 100 times the suction below the freezing zone. It was concluded from these tests that the rate at which the water flowed upwards depended on the permeability of the unfrozen material and the amount of water present.

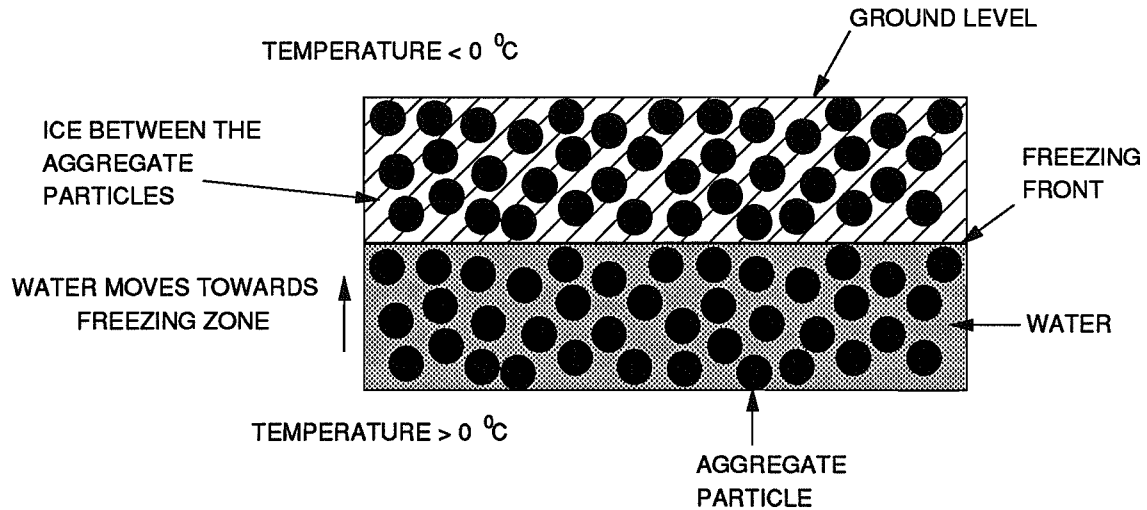


Figure 6.1 Situation in a road pavement when freezing starts

It was found by Croney and Jacobs (1967) that clean granular materials do not have the potential to hold enough water to cause frost heave. Frost heave is inhibited in clays because of low permeability even though clays are capable of retaining large quantities of water. Burns (1977) conducted full scale tests on road pavements constructed in 1.5m deep test pits at TRRL. It was concluded from these tests that the frost heave of most materials would be significantly reduced if the water table was low.

When a road pavement thaws, the water which was drawn up during freezing drains downwards at a rate which is dependent on the permeability of the material. As the water drains, it draws some smaller particles with it causing a decrease in the dry density of the material. Therefore if frost heave occurs again at a later stage the material should be capable of holding more water than before and this is likely to cause further damage to the pavement.

6.3 Development of the frost heave test

The development of a frost heave test started before 1967 and its progression is listed in a series of TRRL reports. The first report was written by Croney and Jacobs (1967) but this report did not describe the test in such a way that it could be carried out in a standardised manner. Therefore another report SR318 was produced by TRRL in 1977 to provide a description of the test which was less ambiguous. In 1981, some changes were introduced to make the test more stringent and another report MM64 was written by TRRL. The existing standard test description is SR829 which was written by Roe and Webster in 1984.

The aim of the report by Croney and Jacobs (1967) was to classify materials as frost susceptible, marginal or not frost susceptible. It included an appendix containing typical frost heave results for a range of materials. The object of this information was to help engineers to decide on the suitability of particular aggregates for pavement construction.

The test was only to be carried out on materials which fell in the marginal category so that tests and costs would be kept to a minimum. However the test was included as a compliance test in Road Note 29 written by the DoE in 1970.

6.4 Frost heave testing

The frost heave tests were carried out at Nottingham University on carboniferous limestone, demolition debris and crushed concrete. The tests involved placing compacted specimens of material in a chamber with the bottom ends of the specimens in contact with water. The temperature of the water was maintained at a constant temperature of 4°C but the air temperature was reduced well below freezing to -17°C. The resulting heave of the aggregate was measured after 96 hours.

6.4.1 Preparing the test specimens

The procedure for preparing the specimens is described in detail by Roe and Webster (1984). Trial samples were made a few days before the test to confirm that samples of adequate stability could be produced at the optimum moisture content (OMC) and peak dry density ($\rho_{d,peak}$) values which were obtained using the compactibility test for aggregates described in BS 5835 (1980). The material was oven-dried and particle grading tests were conducted on the samples before and after preparation of the frost heave specimens. Particles greater than 37.5mm in size were removed. The amount of water required to bring the material to its optimum moisture content was added and mixing took place in a concrete mixer. The aggregate was then allowed to equilibrate overnight in a sealed container.

Each sample was compacted in a tapered, steel cylindrical mould of internal diameter 102mm with end plugs, as shown in Figure 6.2. The bottom end plug was placed on the floor and the steel cylinder was slid over it. The required mass of material needed for the specimen had

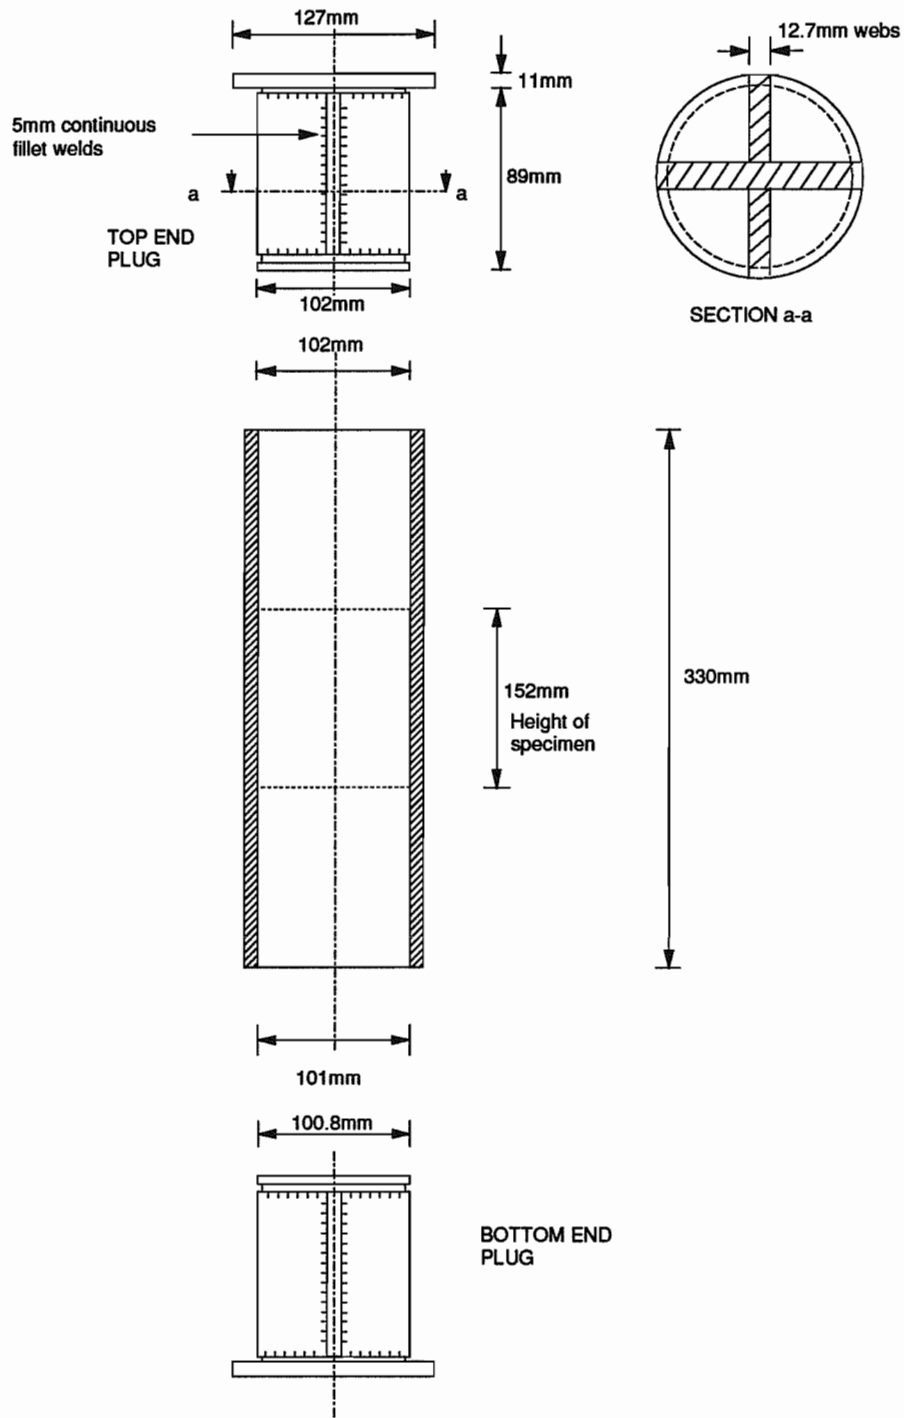


Figure 6.2 Mould and end plugs for sample preparation (after Roe and Webster, 1984)

been calculated beforehand by using the volume of the container and $\rho_{d,peak}$. One third of this mass was placed in the mould and levelled roughly. The layer was compacted using a vibrating hammer connected to a flat, circular plate (illustrated in Plate 6.1) until the material was about 185mm from the top of the mould. Another portion of the material was added and compacted until the top of the layer was 135mm from the top of the mould. The last third was added and compacted slightly before the top end plug was inserted into the cylinder. The vibrating hammer was applied to the plug and compaction was continued until the gap between the mould and the plug caps was not greater than 4mm in total. The height of the sample was 154mm with a 2mm tolerance.

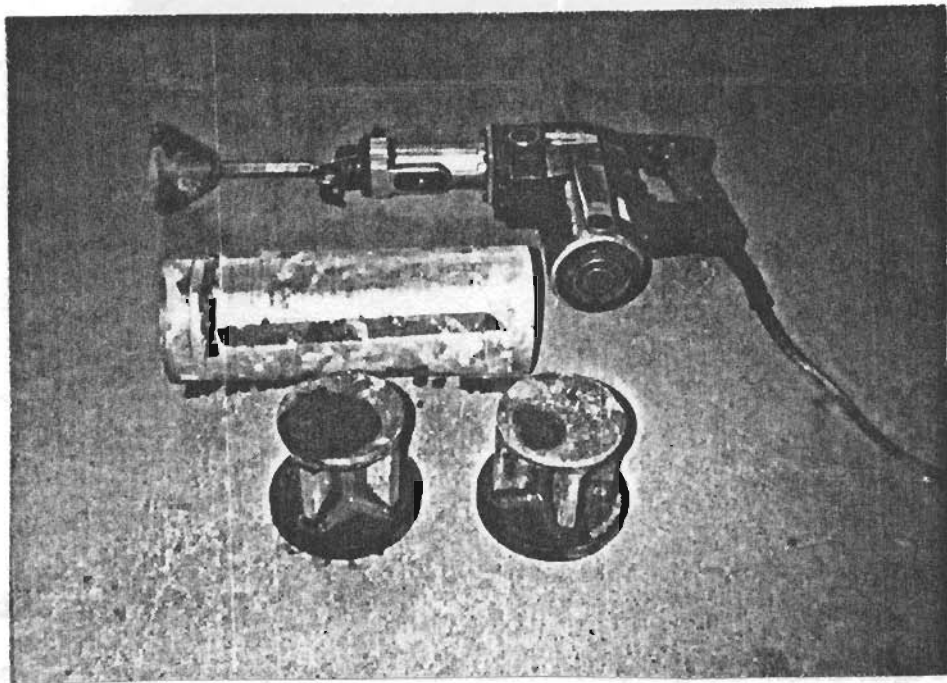


Plate 6.1 Vibrating hammer and mould for the preparation of frost heave test specimens

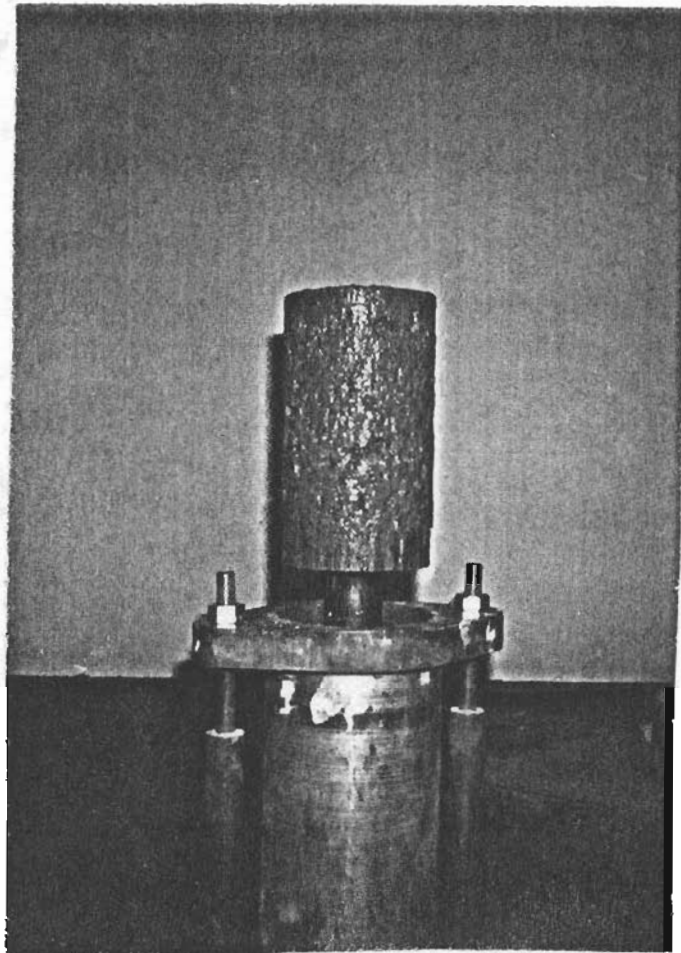


Plate 6.2 Stable sample after extrusion

Both end plugs were removed and the sample was extruded, as illustrated in Plate 6.2. After extrusion the sample was required to stand without collapsing and without large quantities of the aggregate falling away. A waxed sheet of paper was wrapped around the specimen and was secured with adhesive tape leaving a 50mm length of paper protruding above the top of the specimen. A 95mm diameter Tufnol disc of 5mm thickness, with a 10mm diameter recess located centrally in one side, was placed on top of the specimen with the recess uppermost. The specimen was then placed on a 102mm diameter porous ceramic

disc of 13mm thickness with a pore size of 110 μm . The sample and the discs were placed in a copper carrier. The specimen attachments were weighed before sample preparation and were weighed again with the specimen so that the actual density achieved after compaction could be determined. The discs and carrier are shown in Plate 6.3.

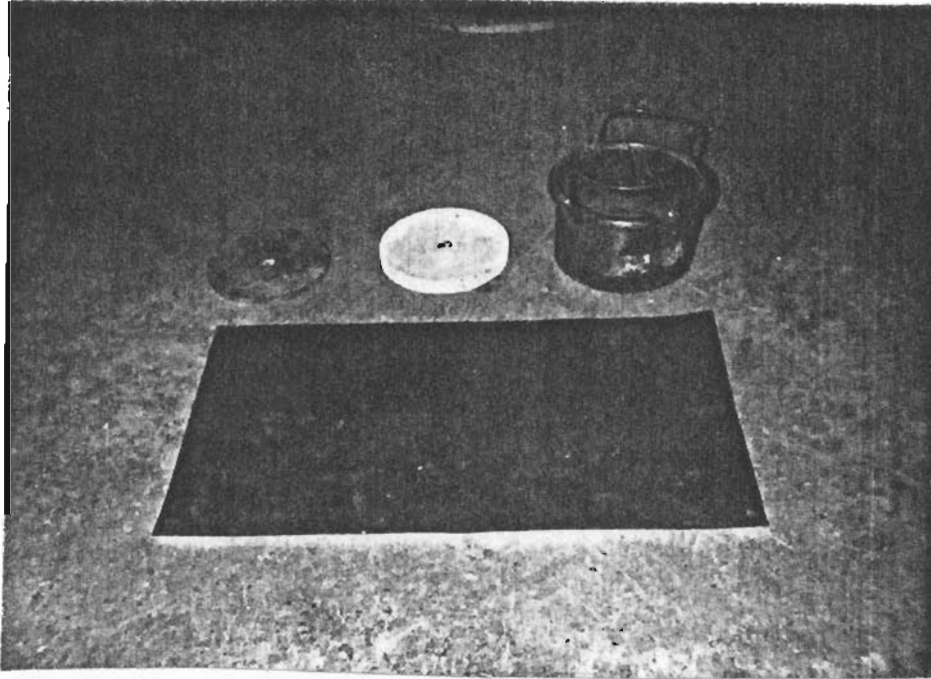


Plate 6.3 Discs and specimen carrier used to support the frost heave specimens

6.4.2 Test conditions

It was stated earlier that frost heave is dependent on the flow of water from below. However, it was decided to test the three aggregates at two other moisture contents as well as OMC, one below and one above OMC, to establish whether frost heave was also influenced by the moisture content at which the material was placed. To examine a wide range of moisture content, it was decided initially that tests should be carried out at 0.5 OMC and 1.5 OMC.

Three samples at each test condition were tested in accordance with Roe and Webster (1984). Table 6.1 includes the moisture content and density values at which the limestone specimens were tested.

TEST REF.No.	COMPACTION TARGET VALUES			MEASURED VALUES	
	ρ_b (kg/m ³)	MOISTURE CONTENT (%)	ρ_d (kg/m ³)	MOISTURE CONTENT (%)	ρ_d (kg/m ³)
L1	2361	1.75	2320	1.98 (0.56 OMC)	2074
L2	2401	3.5	2320	3.34 (0.95 OMC)	2316
L3	2442	5.25	2320	3.8 (1.08 OMC)	2071

Table 6.1 Test conditions of the limestone specimens

Note: ρ_b and ρ_d denote bulk density and dry density respectively

The target density and moisture content for L2 were $\rho_{d,peak}$ and OMC. Although samples L1 and L3 were prepared at different moisture contents, the target density remained at 2320kg/m³ so that stable samples could be obtained. However, it was clear during compaction that this density could not be achieved for these two test conditions. Compaction of these samples was continued until an increase in compaction time did not change the volume of the material. When this stage had been reached the specimens were extruded. As they remained stable, it was decided to use these samples in the frost heave test. It can be seen in Table 6.1 that L3 had a moisture content much lower than the target value. This was due to a large quantity of water running from the sample during mixing.

Initially, the choice of test conditions for demolition debris was similar to that for limestone. The demolition debris had a water absorption of 8% which was much higher than the value of 0.45% for limestone and consequently the moisture contents of the samples for the frost heave tests on demolition debris were also higher. However, it was difficult to obtain stable

samples at a moisture content of 0.5 OMC. The OMC for demolition debris was found to be 13% using the BS 5835 (1980) compaction test and consequently 0.5 OMC was lower than the water absorption value. Therefore there was not enough water present in these samples to bind the aggregate together. It was also impossible to obtain stable samples of the material at a moisture content of 1.5 OMC. To rectify this situation new target moisture contents were calculated as follows:-

$$\text{Low moisture content} = OMC - (OMC - W_a)/2 \quad \dots \text{Eqn } 6.1$$

$$\text{High moisture content} = OMC + (OMC - W_a)/2 \quad \dots \text{Eqn } 6.2$$

where W_a was the water absorption of the aggregate.

Stable samples could be obtained when these moisture contents were used. The test conditions of the demolition debris specimens are listed in Table 6.2.

TEST REF.No.	COMPACTION TARGET VALUES			MEASURED VALUES	
	ρ_b (kg/m ³)	MOISTURE CONTENT (%)	ρ_d (kg/m ³)	MOISTURE CONTENT (%)	ρ_d (kg/m ³)
D1	2010	10.5	1820	10.94 (0.84 OMC)	1815
D2	2060	13	1820	13 (OMC)	1824
D3	2090	15	1820	14.6 (1.12 OMC)	1802

Table 6.2 Test conditions of the demolition debris specimens

Crushed concrete had a water absorption value lower than 0.5 OMC so the same approach was adopted as that for limestone i.e. the target moisture content values were 0.5 OMC, OMC and 1.5 OMC. When the trial specimens were prepared it was concluded, after several attempts, that the target density of 2000kg/m³ for C3 was too high. Therefore the target

value for C3 was changed to the maximum density which could be obtained for this test condition in the trial samples. The moisture content and density values of the crushed concrete samples are listed in Table 6.3.

TEST REF.No.	COMPACTION TARGET VALUES			MEASURED VALUES	
	ρ_b (kg/m ³)	MOISTURE CONTENT (%)	ρ_d (kg/m ³)	MOISTURE CONTENT (%)	ρ_d (kg/m ³)
C1	2103	5.13	2000	6.3 (0.6 OMC)	1838
C2	2205	10.25	2000	8.3 (0.8 OMC)	2002
C3	2125	15.5	1840	13.2 (1.28 OMC)	1904

Table 6.3 Test conditions of the crushed concrete specimens

6.4.3 Setting up the self-refrigerating unit

The self-refrigerating unit (SRU), in which freezing was carried out, consisted of a large insulated box of internal dimensions 600mm x 600mm x 550mm. A wooden cradle for holding nine specimens was placed on supports above the water bath at the bottom of the chamber. Roe and Webster (1984) required that three specimens should be tested at each test condition, so for one test run in the SRU an aggregate at three moisture contents was tested. The SRU can be seen in detail in Figure 6.3 and the cradle is shown in Figure 6.4. The height of water in the water bath was maintained level with a constant level device (CLD) which was located at the side of the SRU. The test procedure by Roe and Webster (1984) states that the water should be maintained at a level so that the top of the porous disc under each specimen is not covered with water but damp i.e. the water level is about 1mm below the top of the porous disc.

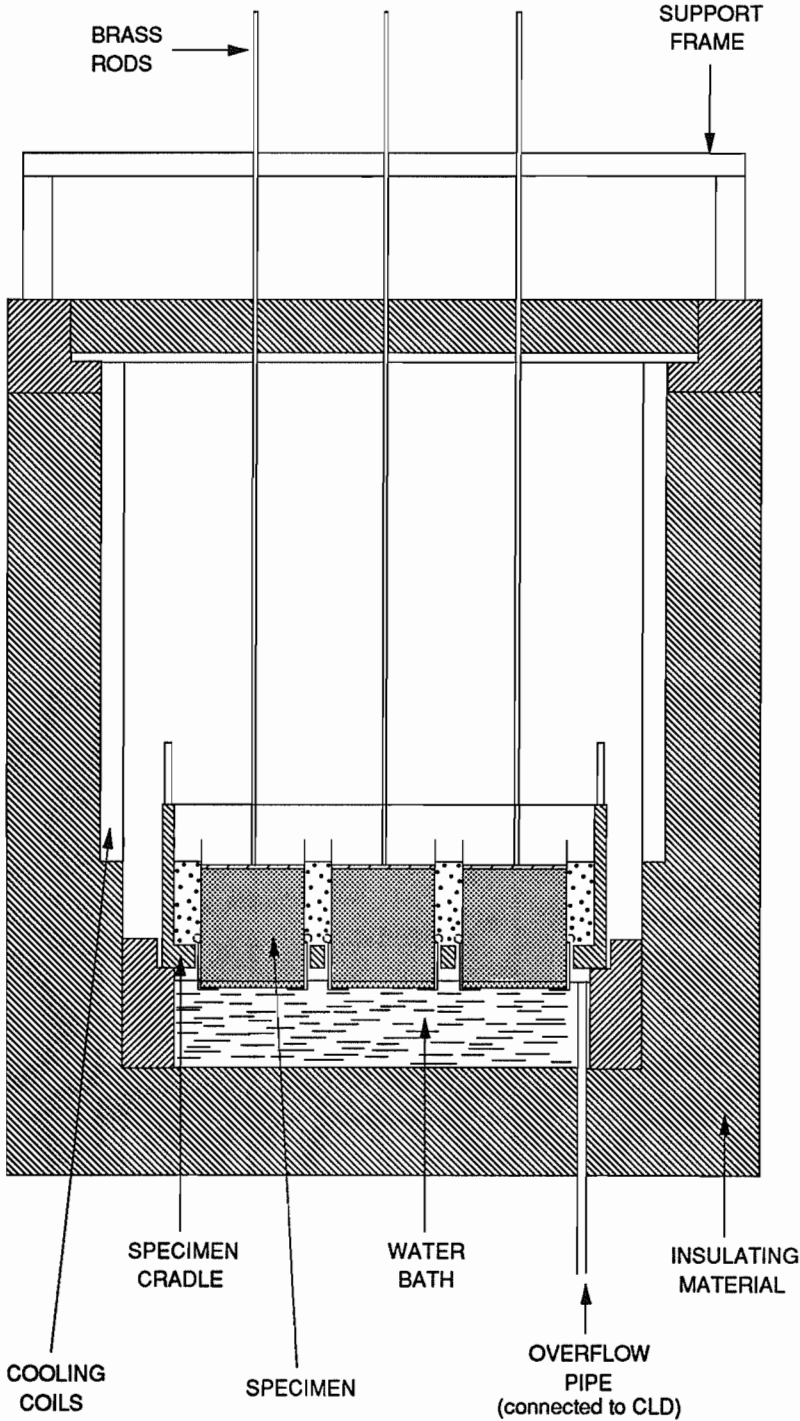


Figure 6.3 The self-refrigerating unit (after Roe and Webster, 1984)

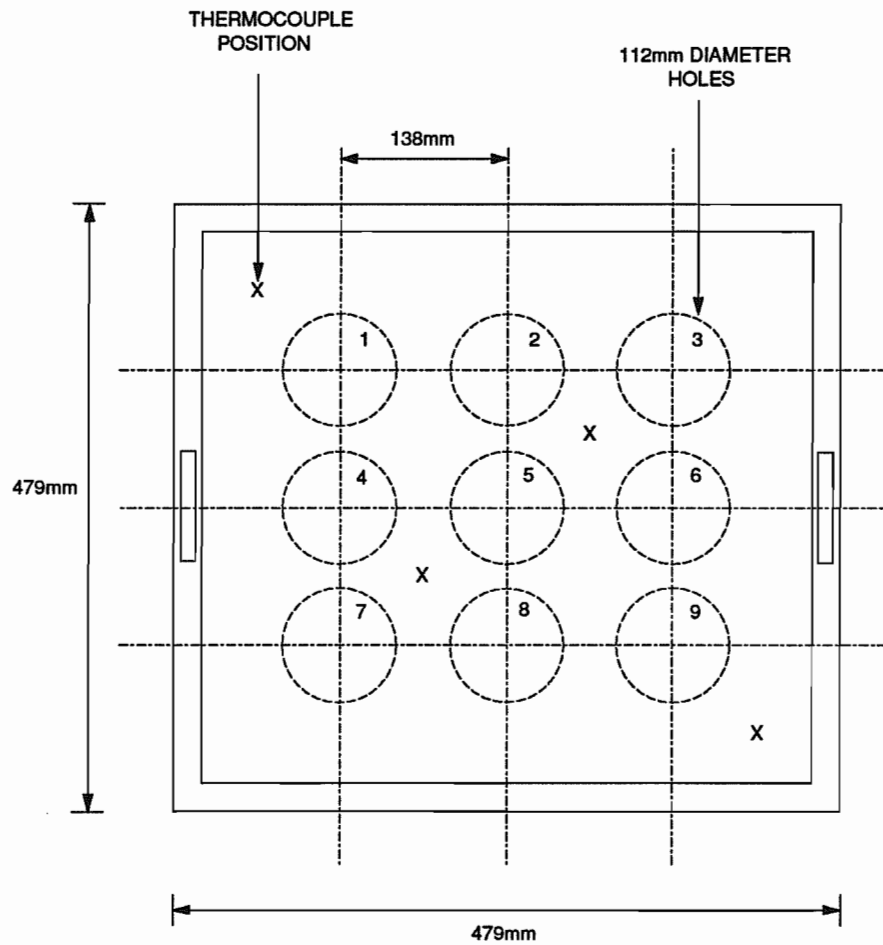


Figure 6.4 Specimen cradle (after Roe and Webster, 1984)

6.4.4 Placing the specimens in the SRU

Following the test procedure described by Roe and Webster (1984), each specimen was placed in a hole in the cradle. The holes were numbered in the sequence shown in Figure 6.4. The specimens to be placed in holes 1,3,5,7 and 9 had thermocouples placed between the carriers and the porous discs so that the temperature of the water could be monitored daily. Another thermocouple was placed under the Tufnol disc at the top of specimen 5 so that the junction of the thermocouple was in contact with the top of the specimen.

When the specimens were in position in the cradle and the thermocouples had been placed, the cradle was filled with a coarse sand to the same level as the tops of the specimens. Four more thermocouples were attached to wooden rods so that their junctions were 50mm from the bottom of the rods. These thermocouples were then placed in the sand to correspond with the positions marked X in Figure 6.4. The lid of the SRU was then closed.

To monitor the heave of the specimens, brass rods were passed through a datum frame on top of the SRU (Plate 6.4) and through the lid of the SRU until the ends were located in the central recesses of the Tufnol discs on top of the specimens. Small pieces of cotton wool were placed loosely in the gaps between the rods and the lid to prevent ice forming around the rods.

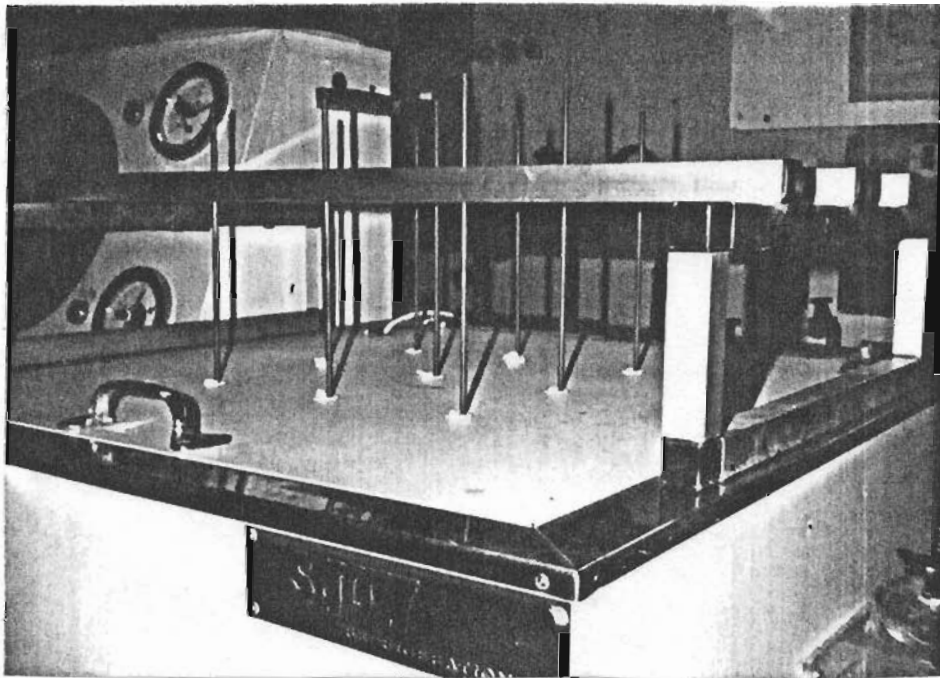


Plate 6.4 Brass rods protruding from the SRU

The SRU was then left at room temperature for 115 hours so that the specimens could equilibrate. When this period had elapsed, the distances between the tops of the brass rods and the top of the lid were measured to the nearest 0.5mm and the temperature of each thermocouple was recorded. The controls on the SRU for maintaining the correct water and air temperatures were switched on. The water was kept at a temperature of between 3°C and 4.5°C and the air temperature was maintained in the range -16°C to -18°C. The temperatures were continually monitored during the test using a chart recorder. If at any time the temperatures were found to be outside the limits listed above, the test would have had to be abandoned. Frost heave was recorded every 24 hours and at 96 hours the last set of readings was taken.

6.5 Classification of materials

To determine whether a material in a particular test condition is frost susceptible, the mean frost heave of three specimens should be calculated (Roe and Webster, 1984).

- a) If the mean frost heave is less than 9mm, the material is classed as not frost susceptible.
- b) If the mean is greater than 15mm, the material is classified as frost susceptible.
- c) However, if the mean heave is in the range 9.1mm to 14.9mm, the material shall be regarded as 'not proven' (Roe and Webster, 1984).

If a material is classified in the last category, samples must be sent to two other laboratories for further testing. If the overall mean frost heave determined by the three laboratories is less than 12mm the material can be classified as not frost susceptible.

6.6 Results

The results for all tests are listed in Table 6.4. Frost heave is caused by ice lenses forming in the material, one of which is illustrated in Plate 6.5. L2, D2 and C2 were the samples closest to OMC and $\rho_{d,peak}$. The 3.5mm frost heave of the L2 samples was very low and was well below the 9mm limit. Limestone was classified therefore as not frost susceptible. However, the mean frost heave of the demolition debris (D2) samples was 12.3mm which indicated that demolition debris was in the 'not proven' range.

The moisture content of crushed concrete (C2) was 0.8 OMC which was much lower than expected. To obtain an indication of the likely frost heave at OMC, the frost heave results of the tests conducted on crushed concrete were plotted against moisture content. There appeared to be a direct relationship between initial moisture content and frost heave for crushed concrete which is shown in Figure 6.5. By interpolation of the results on the plot, a frost heave of 18mm was obtained at OMC (10%) which implied that crushed concrete would be classified as frost susceptible.

TEST REF. No.	MOISTURE CONTENT	SAMPLE 1 HEAVE (mm)	SAMPLE 2 HEAVE (mm)	SAMPLE 3 HEAVE (mm)	MEAN FROST HEAVE (mm)	STANDARD DEVIATION (mm)
L1	0.56 OMC	5.5	7	9	7.2	1.43
L2	0.95 OMC	5	2.5	3	3.5	1.08
L3	1.08 OMC	4	3.5	3	3.5	0.41
D1	0.84 OMC	12	12.5	13	12.5	0.41
D2	OMC	12	12	13	12.3	0.47
D3	1.12 OMC	10.5	10.5	11	10.7	0.48
C1	0.6 OMC	4	3.5	3.5	3.7	0.236
C2	0.8 OMC	10	10	13	11	1.414
C3	1.28 OMC	30	30	33	31	1.414

Table 6.4 Frost heave results for all materials

Demolition debris should have been tested at two other laboratories to satisfy the requirements of Roe and Webster (1984) but restrictions on finance for this research did not allow further testing. Enquiries were made of the suppliers of the aggregates to determine if frost heave tests had been carried out by them on the materials. Foster Yeoman Ltd. (1989) had carried out frost heave tests on limestone but Hughes & Salvidge Ltd. (1989) had not conducted tests on demolition debris. Fitzpatrick & Sons Ltd. (1989) had carried out frost heave tests on crushed concrete but not on the material supplied for this research.

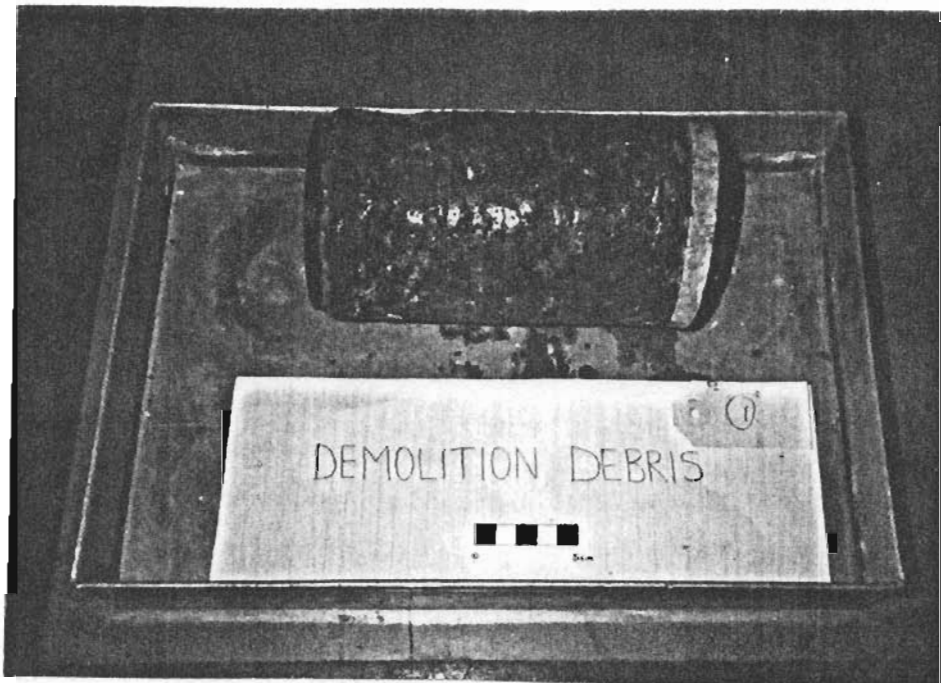


Plate 6.5 Ice lens formed in demolition debris frost heave specimen

The values listed in Table 6.4 for limestone were lower than the 4mm-6mm range of results obtained by Foster Yeoman Ltd. (1989). The samples tested by the supplier had particle

gradings which fell almost centrally in the Type 1 grading envelope but the particle gradings of the samples for this research fell towards the fine side of the Type 1 grading limits. The particle gradings of limestone can be seen in Figure 6.6.

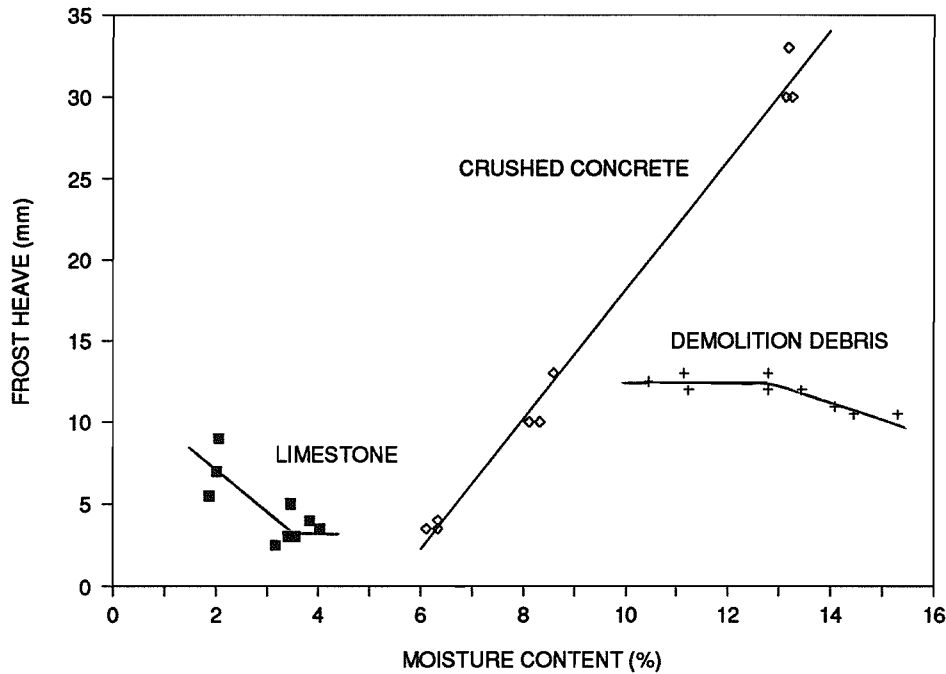


Figure 6.5 Influence of initial moisture content on frost heave

Normally high frost heave is associated with large quantities of fines in the material (Jones and Hurt, 1980). The proportion of limestone passing the 75µm sieve was 8% which is close to the fine side of the Type 1 grading envelope whereas the fines content of the suppliers’ samples was 5%. This is the opposite of what would be expected when examining the frost heave results.

The limestone used in this research was coated with a red powder-like substance which the suppliers deduced was most likely to be a mixture of clay and silt. Clay, as a mass, is not likely to be susceptible to frost but it is doubtful if, in very small quantities, it would reduce the heave of limestone. Silty soils are likely to heave due to a moderate permeability and

an ability to retain a high proportion of unfrozen water (Croney and Jacobs, 1967). The quantity of silt in the limestone samples was likely to be very small and should not have affected the heave of the limestone samples significantly. The presence of clay and silt, however, may have had a binding effect on the limestone when water was added which may have stabilised the samples and consequently reduced frost heave.

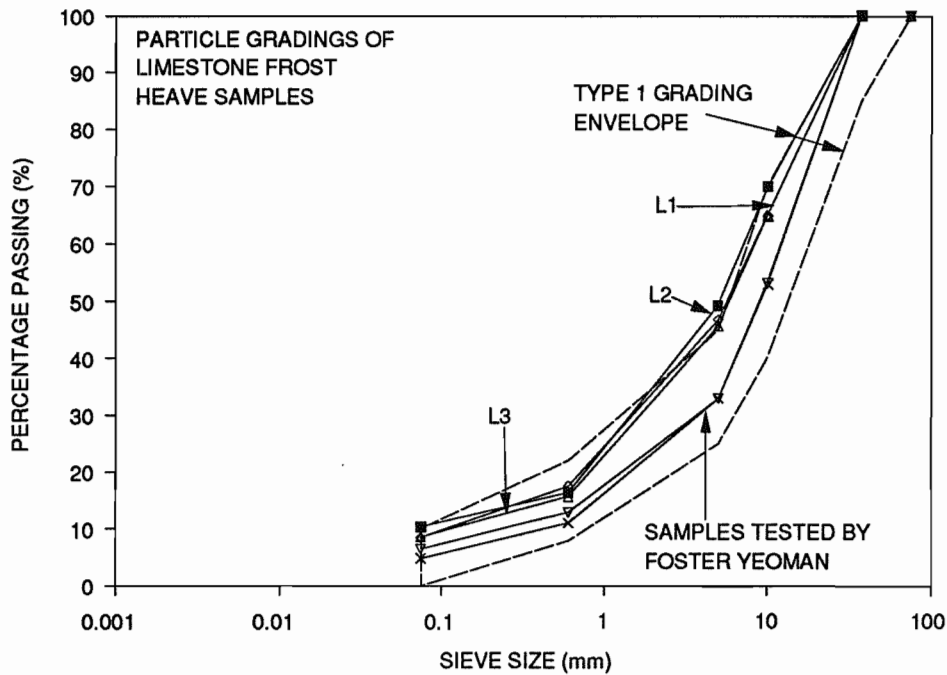


Figure 6.6 Particle gradings of limestone

Although Fitzpatrick & Sons Ltd. (1989) had not conducted frost heave tests on the batch of crushed concrete used in this research, tests had been conducted on crushed concrete from two other sites in 1985 and 1986. The frost heave results for these materials were 14.7mm and 21.2mm at OMC and $\rho_{d,peak}$. The value of 18mm which was noted earlier is within this

range and would suggest that the high value obtained in this research was representative and not due to an unsatisfactory test procedure. Particle gradings of the supplier's material were not available.

The relationship between frost heave and moisture content was shown in Figure 6.5. A direct linear relationship between frost heave and the initial moisture content was apparent for crushed concrete. At a high moisture content, the frost heave of crushed concrete was excessive in comparison with that of the other aggregates. High frost heave is associated with the flow of large quantities of water into the material from below. The C3 samples were in a saturated condition before the frost heave test commenced and it does not seem likely that they would have been capable of taking in any more water. Therefore, in this case, it would appear that the voids in the compacted aggregate were not large enough to accommodate the expansion of water which was already contained in them. Frost heave might be dependent, not only on the flow of water into the material, but also on its initial moisture content.

To determine the increase in height of a saturated crushed concrete specimen (C3), due to the expansion of the initial moisture content, the following calculation was performed.

Using a moisture content of 13.2% and a ρ_d value of 1904kg/m^3 (see Table 6.3)

$$\rho_b = 2155\text{kg/m}^3$$

$$\text{The volume of the specimen} = 1.24 \times 10^{-3}\text{m}^3$$

$$\text{Therefore the mass of the specimen} = 2.673\text{kg}$$

$$\text{and the mass of solids} = 2.36\text{kg}$$

$$\text{The total mass of water in the specimen} = 0.313\text{kg}$$

It was considered that the expansion of water in the voids between the particles was more likely to cause heave of the specimens than the water contained within the aggregate particles. In Chapter 3, the water absorption of crushed concrete was found to be 3.76%.

$$\begin{array}{l} \text{Therefore, the mass of free water in the} \\ \text{specimen} \end{array} = 0.224\text{kg}$$

By using 1000kg/m^3 as the density of water and this mass of 0.224kg

$$\text{the volume of free water in the specimen} = 2.24 \times 10^{-4}\text{m}^3$$

$$\begin{array}{l} \text{The total height of the frost heave} \\ \text{specimen} \end{array} = 0.152\text{m}$$

$$\begin{array}{l} \text{The height corresponding to the volume} \\ \text{of free water} \end{array} = 0.0274\text{m}$$

The volume of water increases by 9% on freezing (Neville, 1973).

$$\begin{array}{l} \text{After freezing the volume of free water} \\ \text{would be} \end{array} = 2.44 \times 10^{-4}\text{m}^3$$

$$\begin{array}{l} \text{and its height within the specimen would} \\ \text{increase be} \end{array} = 0.0298\text{m}$$

$$\begin{array}{l} \text{Therefore the increase in height of the} \\ \text{specimen on freezing} \end{array} = 2.4\text{mm}$$

A frost heave of 31mm was recorded for C3 and therefore the increase in height of the specimen due to expansion of the initial free water does not appear to be significant. If the pores within the particles were not capable of containing the expansion of the absorbed water on freezing, some water might be pushed out of the pores into the voids between the particles. This would increase the quantity of free water and consequently the height of the specimen on freezing would be increased. If the total moisture content of the specimen was assumed to be free water then the increase in height of the specimen, when frozen, would be 3.45mm. This assumption leads to an over estimate because some part of the total

moisture content would remain within the crushed concrete particles. However, the increase in height of the specimen is still too small to be significant in a sample which exhibits a frost heave of 31mm.

When a similar calculation was conducted for C1 it was found that the increase in height of the specimen due to the expansion of the initial free water content was 0.64mm and a value of 1.24mm was determined for C2 which was the sample prepared close to OMC and $\rho_{d,peak}$. It cannot be concluded therefore that the initial moisture content had a major influence on the frost heave of crushed concrete, although it did have some effect. Further tests would need to be carried out to determine other contributing factors to the apparent high frost heave.

The particle gradings of the crushed concrete samples are shown in Figure 6.7. The C3 samples had large proportions of particles passing the 75 μ m sieve and this may have contributed to the high frost heave exhibited. C2, which had the smallest quantity of particles passing the 75 μ m sieve, achieved a heave of 11mm compared with a heave of 3.7mm exhibited by C1 whose fines content was slightly higher. There does not appear to be a direct relationship between frost heave and the quantity of fines in the samples because the variation in fines content of C1, C2 and C3 was very small.

Moisture content did not appear to influence the frost heave of the other materials directly but it is apparent that as the moisture content increased, the frost heave decreased slightly (Figure 6.5). It can be seen, at a moisture content of OMC or greater, that the frost heave of limestone remained unchanged. A decrease in frost heave was exhibited for demolition debris as the moisture content increased. Unfortunately, the lowest frost heave of 10.7mm was still above the 9mm limit. The particle grading of demolition debris falls to the fine side of the Type 1 grading envelope as can be seen in Figure 6.8. It would be interesting to determine whether samples containing coarser gradings of the three aggregates would exhibit

less frost heave.

Standard deviations for the frost heave data are listed in Table 6.4. It is interesting to note that the results for demolition debris were the most consistent. It was expected that the frost heave of samples containing various constituents would vary more than that of more uniform materials. It is difficult enough to prepare identical samples with regard to particle size without the additional problem of various constituents in the aggregate. The results for limestone and crushed concrete were not very consistent, considering the uniformity of the aggregates. The particle grading of these well graded materials encompassed a wide range of particle size. It was difficult to obtain similar samples in a 102mm diameter mould when the material contained particles up to 37.5mm in size.

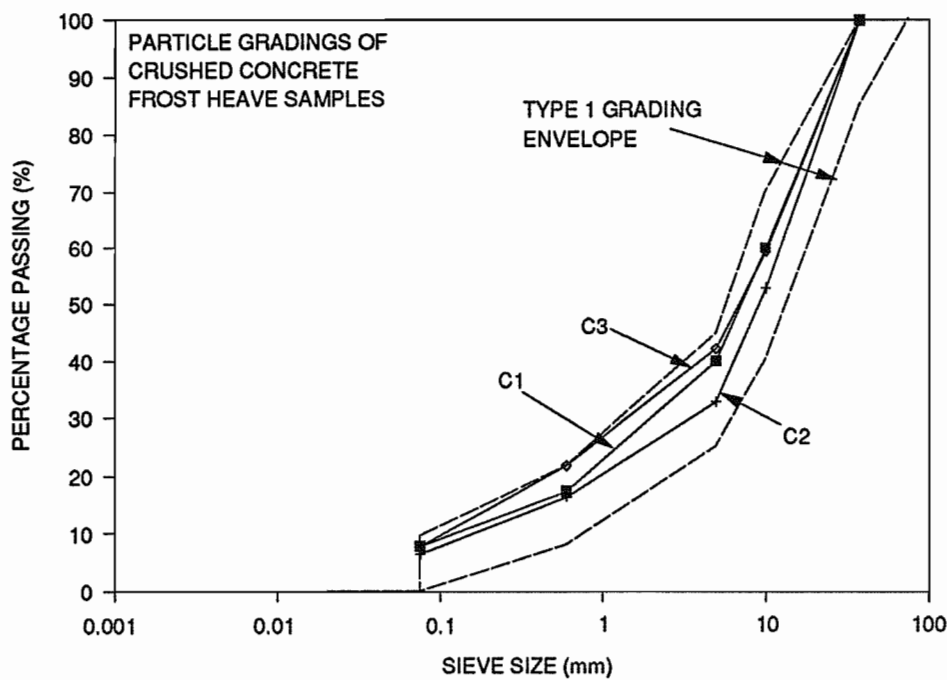


Figure 6.7 Particle gradings of crushed concrete

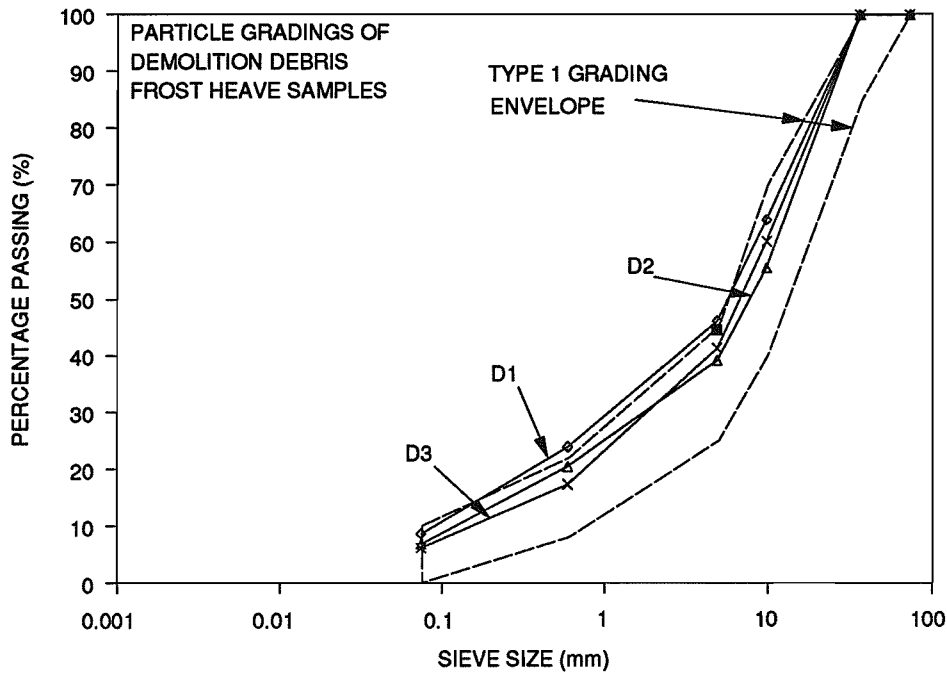


Figure 6.8 Particle gradings of demolition debris

6.7 Discussion

At a moisture content below OMC, crushed concrete had quite low frost heave results. On the basis of the results for crushed concrete presented earlier, severe problems might be caused on site if water moved laterally into a layer of the material or if a perched water table existed. Predicting the movement of water into a sub-base after construction is virtually impossible. The data suggest that crushed concrete should not be used as a sub-base material until other factors contributing to its apparent susceptibility to frost have been determined.

The results of the frost heave tests presented earlier were both disappointing and confusing. The demolition debris was made up of various constituents but was less susceptible to frost than crushed concrete which was a cleaner and more uniform material. The results for demolition debris were also more consistent than the frost heave results of the other materials.

It was surprising that no direct relationship between moisture content and frost heave existed for demolition debris, similar to that which was noticed for crushed concrete. It appears that water absorption did not play a major part in the frost heave process because demolition debris exhibited lower frost heave than crushed concrete but its water absorption was much higher. It was disappointing that the results of the tests did not pronounce demolition debris either frost susceptible or not frost susceptible. However, it has been found by Jones (1989) that several natural aggregates also fall into the 'not proven' category where further testing is required at other laboratories.

Croney and Jacobs (1967) found that the addition of cement to aggregates reduced frost heave. It was found by Sweere (1989) in a field trial that crushed concrete and demolition debris, used as sub-base materials in road pavements, exhibited better resistance to rutting three months after construction than when the material was first placed. This led Sweere (1989) to believe that recycled aggregates had a self-cementing effect. It may be that this binding effect would also reduce frost heave.

In general, crushed concrete and demolition debris both contain large quantities of cement. However, the cement might act better as a stabiliser if it was not attached to the particles. If crushed concrete was agitated in a concrete mixer, for example, or if it was placed in a system where it could be brushed using wire brushes, most of the cement should fall from the particles. The self-cementing effect of the recycled materials might not be very obvious with regard to the Roe and Webster (1984) test but it might be of considerable significance in the field. It would be interesting to conduct a field trial to try to determine the influence of the self-cementing effect of recycled materials on frost heave.

For both natural and recycled aggregates the main point for discussion, with regard to the frost susceptibility of sub-bases, is the construction of a layer which needs to be both stiff

and permeable. The Department of Transport is soon to issue an Advice Note on the measurement of permeability. In the Specification for Highway Works (1986) there is no requirement concerning the permeability of sub-base materials but at the Symposium on Unbound Aggregates in Roads (1989) it was concluded that more emphasis should be put on permeability when deciding the grading and type of material. A permeable sub-base would have the advantage of low capillary rise and consequently frost-heave would be reduced. However, the main object of using a sub-base layer in a road pavement is to provide a platform for construction traffic and therefore it should be a stiff, closely packed layer. It is evident therefore that the functions of a sub-base are in direct conflict with each other. More use should be made of open packed material in a capping layer below the sub-base to provide sufficient drainage.

6.8 Conclusions

- (i) On the basis of results presented earlier, limestone would be classed as not frost susceptible but it appeared that crushed concrete was highly susceptible to frost. The frost heave of demolition debris was in the inconclusive range but its results were the most consistent. Further testing at other laboratories would be required to confirm its susceptibility to frost.

- (ii) Although the frost heave of crushed concrete appeared to be directly influenced by the initial moisture content of the specimens, the increase in volume of the material due to the expansion of this water on freezing was calculated and found to be relatively insignificant. The apparent dependence of frost heave on the initial moisture content was not noticed for tests conducted on limestone and demolition debris and further testing would be required to determine other contributing factors to frost heave.

- (iii) At the Symposium on Unbound Aggregates in Roads (1989), it was concluded that testing of sub-base materials should become more site orientated. It is likely that recycled materials would be found to be less frost susceptible if they were examined on site some time after compaction, due to the self-cementing effect noticed by Sweere (1989). The condition of a sample in a 102mm diameter mould is not likely to be very representative of site conditions particularly when particles up to 37% of the diameter of the mould are included.
- (iv) A capping layer should be constructed under the sub-base to act as a drainage layer because it is considered that the requirements of a sub-base layer to be both stiff and permeable are too demanding. This was also concluded at the Symposium on Unbound Aggregates in Roads (1989).

CHAPTER 7

RECYCLED AGGREGATE CONCRETE

7.1 Introduction

In the future it may be useful to find new sources of aggregate for the production of concrete due to the increase in demand for and decrease in supply of natural aggregate. Increasing numbers of concrete buildings are being demolished and the difficulty of disposing of the rubble has prompted an interest in the possibility of using crushed concrete as aggregate in new concrete (Nixon, 1978).

7.1.1 Mix design

In principle, the mix design of recycled aggregate concrete is not different from that of conventional concrete and the same mix design procedures can be used. In practice, slight modifications are required. Hansen (1985) concluded that for the DoE (Department of Environment) mix design, written by Teychenné, Franklin and Erntroy in 1982, the following modifications would be necessary when using recycled aggregate. This design method will be referred to hereafter as the DoE (1982) mix design.

- a) When designing a concrete mix using recycled aggregate of variable quality, a higher standard deviation should be employed in order to determine a target mean strength on the basis of a required characteristic strength.
- b) When coarse recycled aggregate is used with natural sand, it may be assumed at the design stage that the free water/cement ratio required for a certain compressive

strength will be the same for recycled aggregate concrete as for conventional concrete. If trial mixes show that the compressive strength is lower than required, an adjustment of the water/cement ratio should be made.

- c) For a recycled aggregate mix to achieve the same slump, the free water content will need to be approximately 10 litres/m³ higher than for conventional concrete.
- d) If the free water content of a recycled aggregate concrete is increased, the cement content will also need to be higher to maintain the same water/cement ratio.
- e) Trial mixes should be made to obtain the required workability and the most suitable water/cement ratio.

7.1.2 Workability

Ravindrarah (1985) found when recycled aggregate was used as the coarse fraction and natural sand as the fines in a concrete mix that an increase in free water of 8% was needed to achieve the same workability as that of natural aggregate concrete. Hansen and Narud (1983) reported needing a 5% higher free water content than for control mixes. Similarly, Mulheron and O'Mahony (1988) found when crushed concrete aggregate was used as the coarse fraction that the mixes were slightly harsher and less workable than the conventional aggregate mixes.

Frondistou-Yannas (1977) and Buck (1976) both reported that there appeared to be little difference in workability when recycled aggregate was used as the coarse fraction with a natural sand but Buck (1976) noticed that the slump was lower if recycled aggregate was used for both the coarse and fine fractions. Hansen and Marga (1988) agreed with this and stated that an increase in free water content of 14% was required when the total aggregate content in a mix consisted of recycled aggregate. An unusual result was reported by Yamato

et al (1988) who found that workability was increased considerably when recycled aggregate was used. It is thought that this result was specific to his research and the type of aggregate used.

7.1.3 Strength of concrete

Hansen (1985) stated that the compressive, tensile and flexural strength of recycled aggregate concrete could be equal to or higher than that of conventional concrete, if the same or a lower water/cement ratio was used. In practice, however, the strength of recycled aggregate concrete is often found to be lower. Frondistou-Yannas (1977) reported a 4%-14% drop in compressive strength whereas Kemi and Nakagawa (1978), Ravindrarajah (1985), Yamato et al (1988), Mulheron and O'Mahony (1988), Nishibayashi and Yamura (1988) and Kasai (1985) all reported a reduction of between 14% and 32%. Nixon (1978) found in a series of tests that the compressive strength of the original concrete, from which the recycled aggregate was obtained, did not appear to affect the compressive strength of the recycled aggregate concrete very much. Kashino and Takahashi (1988) noted when less than 30% of natural aggregate in a concrete mix was replaced by recycled aggregate that there appeared to be no change in compressive strength.

7.1.4 Young's modulus

In the research reports mentioned in Section 7.1.3, values of Young's modulus were also quoted. All noted a reduction of 15%-40% in the Young's modulus of recycled aggregate concrete which was attributed to the large amount of weak, old mortar attached to the aggregate. Kasai (1985) reported a 10%-20% reduction in Young's modulus for concrete made with coarse recycled aggregate and natural sand. The lower Young's modulus of recycled aggregate concrete in general is explained by Frondistou-Yannas (1977). Recycled

aggregate normally has a lower modulus than natural aggregate. As the modulus of concrete is dependent on the modulus of the aggregate present, the lower modulus of recycled aggregate concrete is not surprising.

7.1.5 Shrinkage and creep

Helmuth and Turk (1967) reported that the drying shrinkage of cement paste increases linearly with its porosity. Therefore if the porosity of the paste could be reduced, e.g. by decreasing the water/cement ratio, the shrinkage of cement paste would also be reduced. Mulheron (1986) noted an increase in shrinkage of 58%-95% more than control concrete depending on whether crushed concrete or demolition debris was used in the recycled aggregate concrete; demolition debris giving the worst result. Shrinkage of concrete also depends on the Young's modulus of the aggregate present and it is likely that the low modulus of the mortar in the recycled materials would cause an increase in shrinkage.

Mulheron (1986) found a 40%-100% increase in creep for concrete made using coarse recycled aggregate and natural sand. Ravindrarajah (1985) and Hansen (1985) also observed higher creep than for conventional aggregate concrete. Nishibayashi and Yamura (1988) also found the creep of recycled aggregate concrete made with coarse recycled aggregate and natural sand to be 50% higher than that of conventional aggregate concrete. The presence of aggregate in concrete restrains the volume change of the cement paste and therefore reduces creep. However, if the aggregate in concrete has a low modulus, e.g. recycled aggregate, then its ability to reduce creep is lower.

7.1.6 Impurities

Mulheron (1986) found the levels of chloride in natural and recycled aggregate to be below the point of detection. If recycled aggregate was to be produced from the crushing of a

bridge deck or a concrete carriageway from a road or an airport, it is expected that the level of soluble chloride might be excessive and consequently the aggregate produced would not be suitable for aggregate in concrete. Chloride has little significant influence on the properties of plain concrete but in reinforced concrete the presence of chlorides initiates corrosion of embedded steel (BRE, 1980) and (BRE, 1982).

Other impurities, known to cause problems, are timber and vegetable matter from soil. The level of contamination in any recycled aggregate depends on the source of the aggregate and the method of production and control. Wood can be removed in flotation operations which are usually only employed by the larger fixed-site recycling plants. Organic matter is considered to be a harmful impurity in aggregate intended for use in concrete (Collis and Fox, 1985). Humus and oil, for example, can retard or even prevent the hydration of cement when present even in small quantities (Sherwood and Roeder, 1965).

Kemi and Nakagawa (1978) tested concrete containing increasing levels of paint, asphalt, gypsum, wood, soil and plaster. The compressive strength of the most heavily contaminated concrete was 85% that of the control concrete specimens. The Building Contractors Society of Japan (1981) determined the percentage of six contaminants which, when added to crushed concrete to be used as aggregate in new concrete, would cause no more than a 15% reduction in the compressive strength. The maximum percentages by volume were found to be 7% plaster, 5% soil, 4% wood, 3% gypsum, 2% asphalt and 0.2% paint. The Dutch standard (CUR, 1986) for recycled materials to be used as aggregates in concrete includes stricter limits on contamination. The quantity of asphalt is limited to 1% and the amount of wood present should be less than 0.6% (see Section 2.3.2).

Graf (1973) and Gaede (1957) decided that the allowable level of soluble sulphate in recycled aggregate concrete should be maintained between 0.5% and 1%. When present in sufficient quantity, sulphate in aggregate reacts with cement compounds if the aggregate is used in

concrete manufacture. This results in excessive expansion and ultimately the deterioration of hardened concrete in wet or damp conditions (Lea, 1970). The British Standard for aggregate to be used in concrete, BS 882 (1983), does not specify sulphate limits for natural aggregates.

7.2 An examination of recycled aggregate concrete

Slabs of reinforced concrete produced in a laboratory, ranging in size from 800mm x 800mm x 150mm to 1200mm x 1200mm x 150mm were crushed in a single jaw crusher operation. When the slabs were too large to be fed directly into the crusher they were first broken up by a demolition ball. The 5mm-10mm fraction was sieved out in the laboratory and this was used as the coarse aggregate fraction for a series of recycled aggregate concrete mixes. Natural sand was used as the fine aggregate in all mixes, in view of previous work by Hansen (1985).

7.2.1 Mix design of recycled aggregate concrete

The mix for the concrete slabs was originally designed by other research workers for non-destructive testing in another project. Thames valley gravel was used as the coarse aggregate fraction and the strength of the concrete was 60N/mm². A decision was taken by the research workers to use a mix with a high sand content. The first set of mixes for this research, set A, was based on the same design to allow a direct comparison of control and recycled concretes. Three control and three recycled mixes were made with different water/cement ratios. In set B, the same recycled aggregate was used but the mix design was based on the DoE method (1982) and again three control and three recycled mixes were made. In all cases, the water content of the recycled aggregate mixes was increased to allow for the higher water absorption of the aggregate and the free water content was increased further by 8% following the recommendation by Ravindrarajah (1985). The cement content

was also increased to maintain the original water/cement ratio. The mix proportions are listed in Table 7.1. The lower specific gravity of recycled aggregate was taken into account in other research by Hansen (1985) and Ravindrarajah (1985) but for the mix designs presented here it was decided that the same mass of aggregate would be used for all mixes. All aggregate was oven-dried before use but not pre-soaked before mixing.

Mix No.	CEMENT	FINE AGGREG	COARSE AGGREG	TOTAL WATER	FREE W/C RATIO	SLUMP (mm)
	Mass (kg) of constituents per m ³					
SET A						
C1	493	1004	670	212	0.36	10
R1	532	1004	670	255	0.35	50
C2	493	1004	670	233	0.4	115
R2	532	1004	670	229	0.3	10
C3	493	1004	670	246	0.45	190
R3	532	1004	670	279	0.4	190
SET B						
C4	580	744	839	236	0.35	35
R4	626	744	839	293	0.35	170
C5	580	744	839	265	0.4	190
R5	626	744	839	261	0.3	40
C6	580	744	839	293	0.45	235
R6	626	744	839	325	0.4	215

Note: C = control, R = recycled

Table 7.1 Mix quantities and slump

The following specimens from each mix were cast for various tests; six 100mm cubes for compressive strength tests at 7 days and 28 days, one cylinder of diameter 150mm and length 300mm for a Young's modulus test and tensile splitting strength test, and two 100mm x 100mm x 200mm specimens for shrinkage and creep tests.

For comparison purposes, some control and some recycled mixes in each set were made to have similar workability. The corresponding pairs can be seen in Table 7.1. In the following presentation of results, the properties of concrete mixes with similar water/cement ratios are also compared.

7.2.2 Workability of concrete mixes

The slump of the fresh concrete was measured in accordance with BS 1881: part 102 (1983). In Figure 7.1, it can be seen that there were similar relationships between slump and water/cement ratio for both the recycled and control mixes. The slump values for all mixes are listed in Table 7.1. The workability of the recycled aggregate mixes was higher than that of the control mixes. This is explained by Neville (1973). If aggregate is not pre-soaked before mixing, it becomes coated with cement paste which prevents ingress of water for saturation of the aggregate. It is likely if the aggregate does not absorb a quantity of water equivalent to its water absorption before mixing that it might draw water from the cement paste later and affect the bond between the aggregate and the paste.

The recycled aggregate used in this research was produced in a jaw crusher where the lowest jaw setting was 70mm-85mm. This material may have been less angular than the aggregate used by Ravindrarajah (1985) which was produced in a jaw crusher at a setting of 20mm. If the aggregate was less angular, the need for using less water than suggested by Ravindrarajah (1985) could be explained. Trial mixes could not be carried out because there was a limited supply of recycled aggregate for the work.

7.2.3 Compressive strength results

Compressive strength tests were carried out in accordance with BS 1881: part 116 (1983) and the results are summarised along with density of the concrete in Table 7.2. All concretes

achieved high strength within 7 days and by 28 days the average compressive strength in both sets was similar. The tensile splitting strengths of the concretes in set B appeared to be slightly lower than those in set A but the Young's moduli of the concretes in both sets were similar.

Mix No.	FREE W/C RATIO	COMPRESSIVE STRENGTH (N/mm ²)		TENSILE STRENGTH (N/mm ²)	DENSITY (kg/m ³)	YOUNG'S MODULUS (kN/mm ²)
		7 DAYS	28 DAYS			
SET A						
C1	0.36	57	65	5.27	2424	30.2
R1	0.35	54.5	63.5	5.03	2345	30.1
C2	0.4	53	58	4.96	2377	26.5
R2	0.3	61.5	69.5	5.1	2378	35.6
C3	0.45	47	54.5	4.81	2363	25.8
R3	0.4	49	58	4.67	2317	28.5
SET B						
C4	0.35	58.5	62.5	4.6	2414	29.2
R4	0.35	54.5	65.5	4.3	2319	34.9
C5	0.4	50	57.5	4.6	2360	32.7
R5	0.3	65	73	4.45	2359	32.8
C6	0.45	42.5	53	4.2	2378	26.3
R6	0.4	44.5	57.5	4.3	2300	26.5

Table 7.2 Properties of hardened concrete

In Figure 7.2, the increase in compressive strength with age is shown for set A and a similar relationship for set B is illustrated in Figure 7.3. The rates of increase in strength of C2 and R3 were similar to those of C5 and R6 where these four mixes had the same water/cement ratio of 0.4. The recycled aggregate concretes had lower strengths at 7 days but by 28 days they had attained the same strength as the controls. It is apparent in Figure 7.4 that, as expected, the higher the water/cement ratio, the lower the strength appeared to be for the mixes.

In Figure 7.5, control and recycled mixes of the same slump were compared and it was found that the compressive strength of the recycled mixes was higher in most cases by 6%-17%. This was due to the lower water/cement ratios which were used in the recycled aggregate concrete mixes to achieve similar workability to that of the natural aggregate concretes.

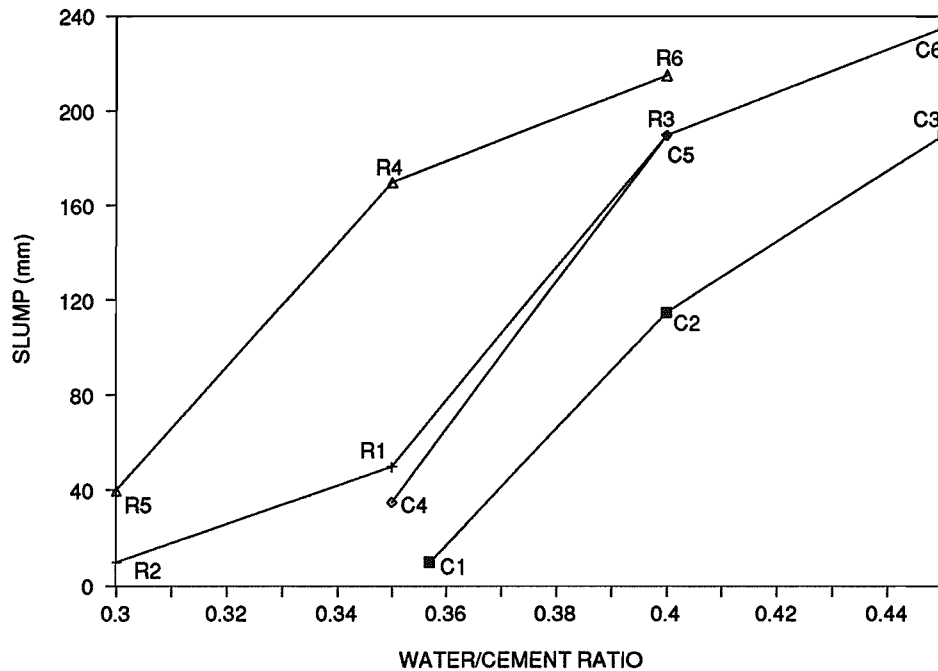


Figure 7.1 Influence of water/cement ratio on slump

If, however, compressive strength is compared on the basis of similar water/cement ratio, as in Figure 7.4, the results can be perceived in another way. In this approach, the control mixes of set A were stronger by 0%-3.7% but in set B the recycled aggregate concrete specimens were stronger than the controls by 0%-5%. This showed that, by adding 8% more water and cement, the original objective of producing recycled aggregate concrete with a compressive strength comparable with that of conventional aggregate concrete was achieved. The tensile splitting strength of the concretes is best compared when examining mixes of similar water/cement ratio in Table 7.2. The recycled aggregate concretes had

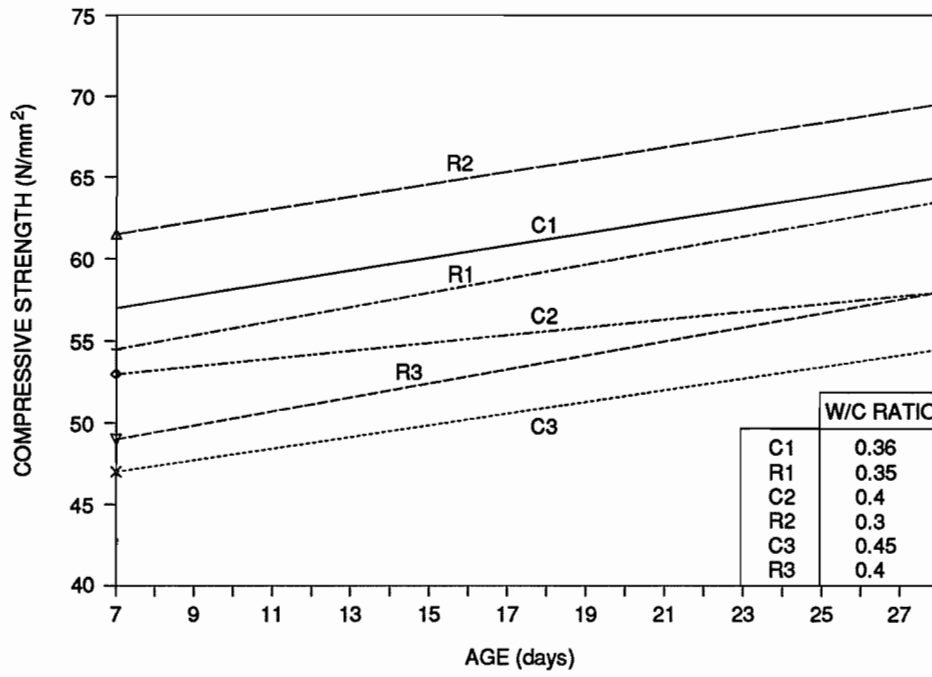


Figure 7.2 Strength development for set A

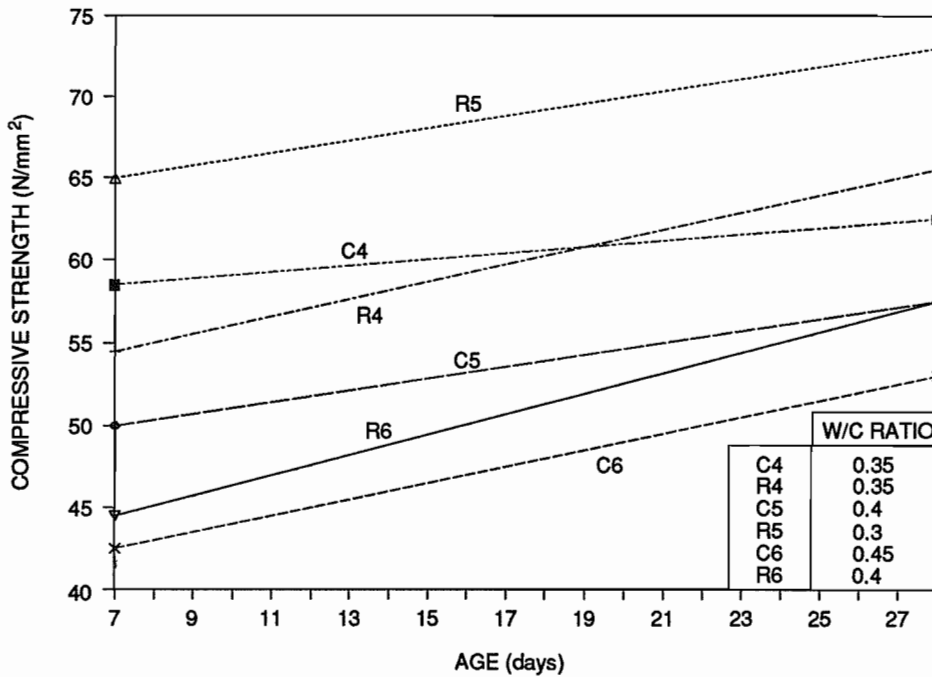


Figure 7.3 Strength development for set B

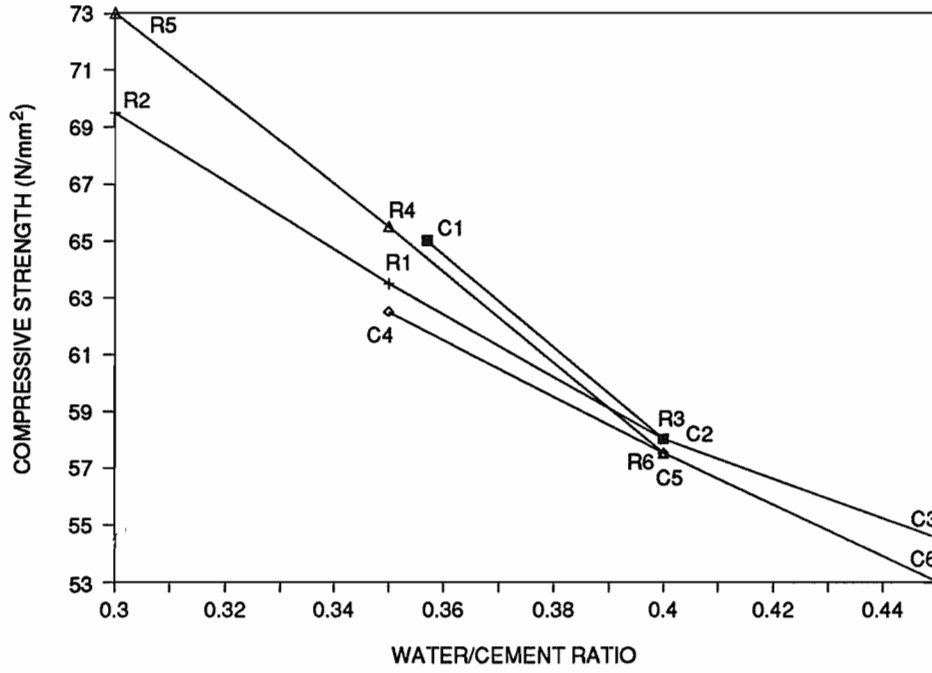


Figure 7.4 Influence of water/cement ratio on compressive strength

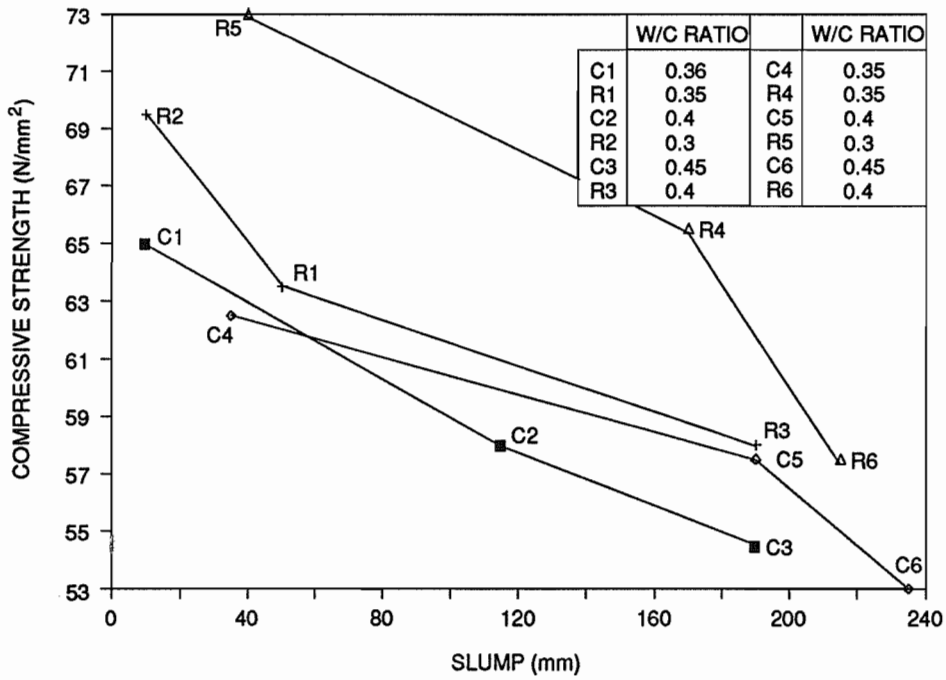


Figure 7.5 Relationship between compressive strength and slump

tensile splitting strengths which were lower by 4.5%-7%.

The density of recycled aggregate concrete was about 2%-4% lower than that of control concrete. The old mortar present in the recycled aggregate particles is likely to have contributed to the lower density of the concrete.

7.2.4 Young's modulus results

Young's modulus tests were carried out in accordance with BS 1881: part 121 (1983) using a 200 mm Demec strain gauge to monitor strains in the concrete. The Young's modulus results were listed in Table 7.2. Figure 7.6 shows the relationship between Young's modulus and compressive strength. Trends in the results appear to be similar for recycled and control mixes from each set. On the basis of equal compressive strength, the Young's moduli of conventional concretes in set A were 2.3%-8% lower than those of the recycled aggregate concretes. The large quantity of sand in the mixes of set A may have contributed to the improved Young's modulus of the recycled aggregate concretes. When examining the results for set B, however, it appears that at lower compressive strengths the moduli of recycled aggregate concretes were 80% those of the controls but at strengths of 61-62 N/mm² the moduli of the control concretes were 92%-100% those of the recycled aggregate concretes.

From these results it can be seen that in most cases the recycled aggregate concretes had higher Young's moduli than the controls and this conclusion disagrees with the results of Ravindrarajah (1985) for similar tests. This contradiction is most likely due to the different recycled aggregates used and the difference in mix design, particularly for set A.

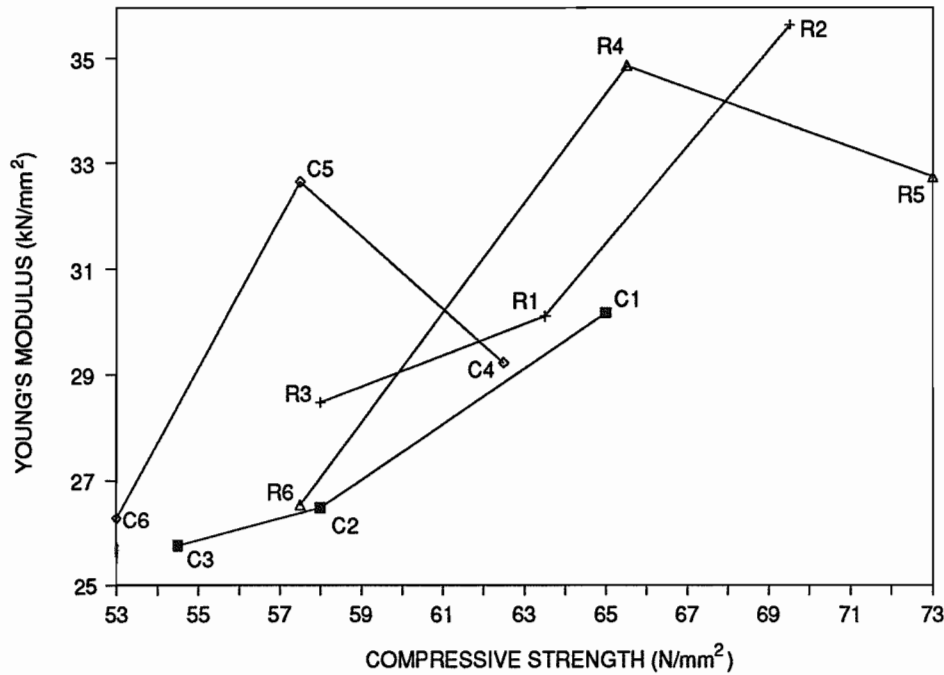


Figure 7.6 Relationship between Young's modulus and compressive strength

7.2.5 Shrinkage

Apparent deformations were monitored from the day after casting. For the first 28 days, the specimens were in a curing tank and all concrete specimens expanded considerably, especially the recycled aggregate concrete due to the high water absorption of the aggregate caused by old mortar coating the particles. The aggregates were not pre-soaked before casting and this is thought to be another reason for the high expansion of the concretes in the curing tank.

When the specimens were removed from the curing tank they were coated with two coats of bitumen paint to provide a seal so that constant humidity would be maintained to some extent. Shrinkage was monitored on all four sides of the specimens using 100mm Demec gauges. The results for set A and set B are plotted in Figures 7.7 and 7.9 respectively.

Mixes C1 and C4, both with a water/cement ratio of 0.35, achieved the lowest shrinkage whereas the recycled aggregate concrete with the highest water/cement ratio of 0.4 in set A, i.e. R3, exhibited high shrinkage. However, R6 which also had a water/cement ratio of 0.4 exhibited shrinkage which was similar to that of other concretes in set B. There appeared to be little difference in shrinkage when the two sets of mixes were compared except for C1 which achieved a shrinkage of 56% that of the other concretes in set A and also exhibited less shrinkage than the concretes in set B. This was encouraging because, in the mix design for set A, a higher sand content was included and therefore higher shrinkage was expected.

In general, if a concrete mix contains a large quantity of sand there is more surface area of aggregate to be coated by cement which allows more cement to be hydrated. The larger the amount of hydrated cement paste in concrete, the higher the shrinkage is expected to be. Restraint to shrinkage is normally provided by the aggregate contained in the concrete and Neville (1973) stated that the presence of unhydrated cement in concrete would also contribute to a reduction in shrinkage.

The recycled aggregate concretes in this study contained 8% more cement than the natural aggregate concretes as well as the extra cement in the old mortar surrounding the recycled aggregate particles. There was likely to be more potential for shrinkage in the recycled aggregate concrete due to this extra cement. It is clear from the results that recycled aggregate did not provide the same restraint to shrinkage as conventional aggregate but the difference appeared to be quite small in most cases. The recycled aggregate was of lower modulus than the natural aggregate and therefore its ability to restrain shrinkage was lower.

In Figures 7.8 and 7.10, it can be seen that the weight change of the specimens appeared to be dependent on temperature up to an age of 100 days but that the temperature had little influence as the concrete grew older. It can be concluded therefore that two coats of bitumen

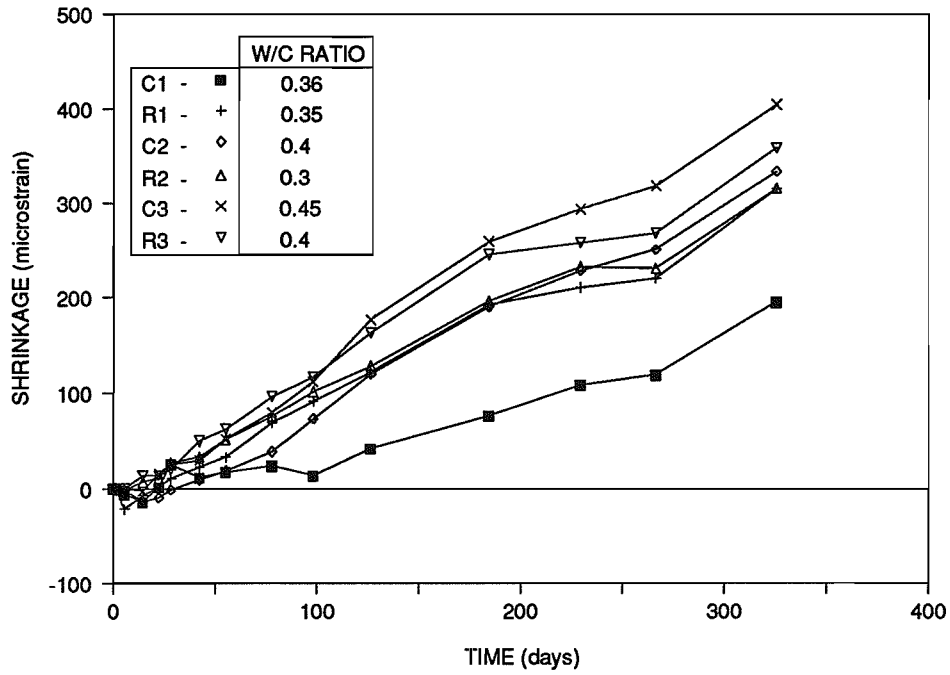


Figure 7.7 Shrinkage of the concrete specimens in set A

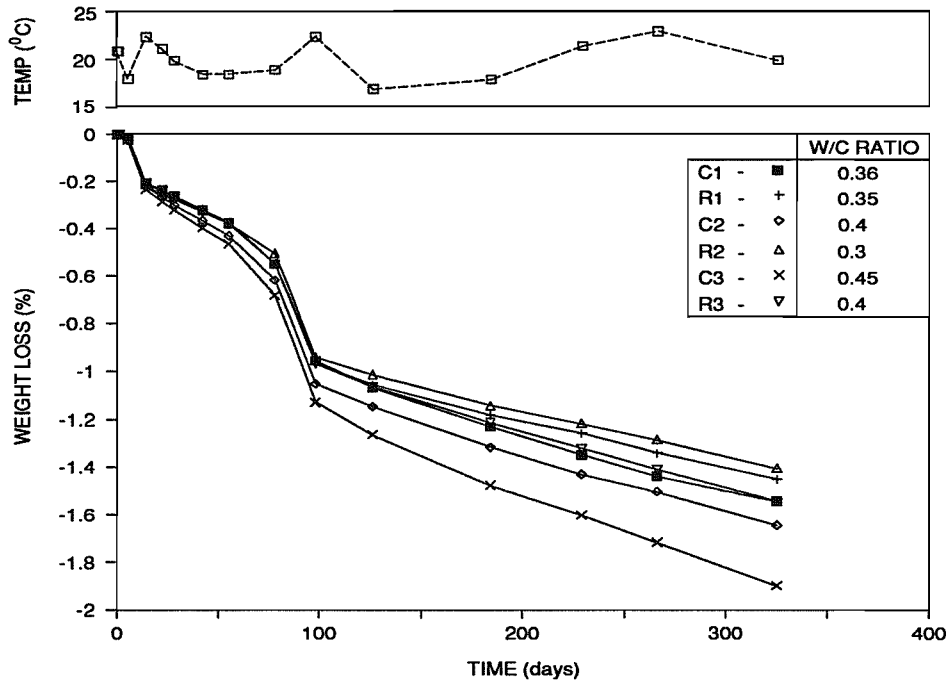


Figure 7.8 Weight change of the concrete specimens in set A

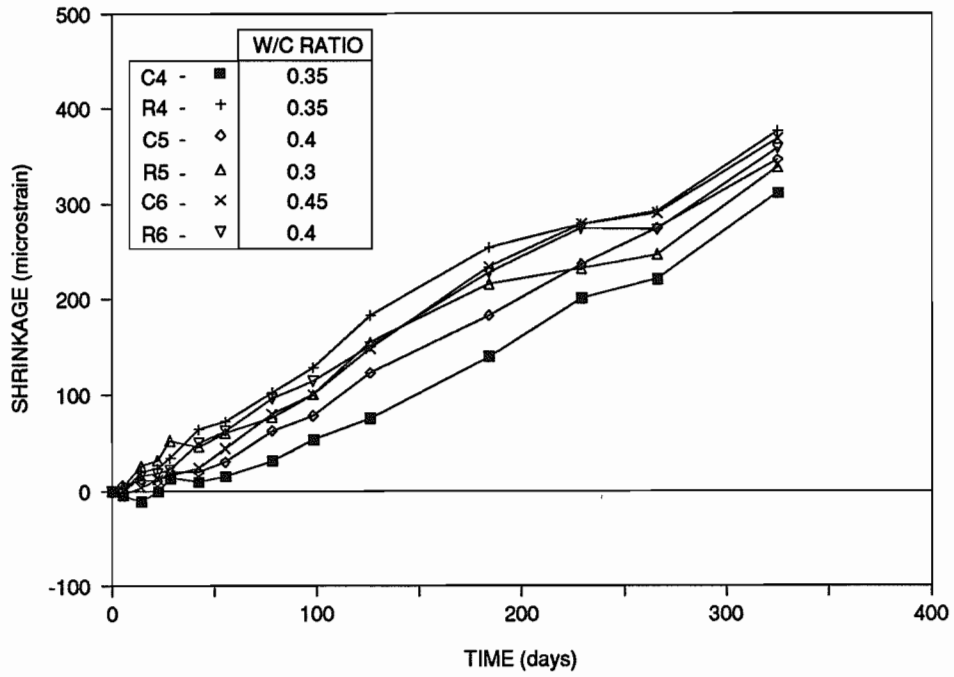


Figure 7.9 Shrinkage of the concrete specimens in set B

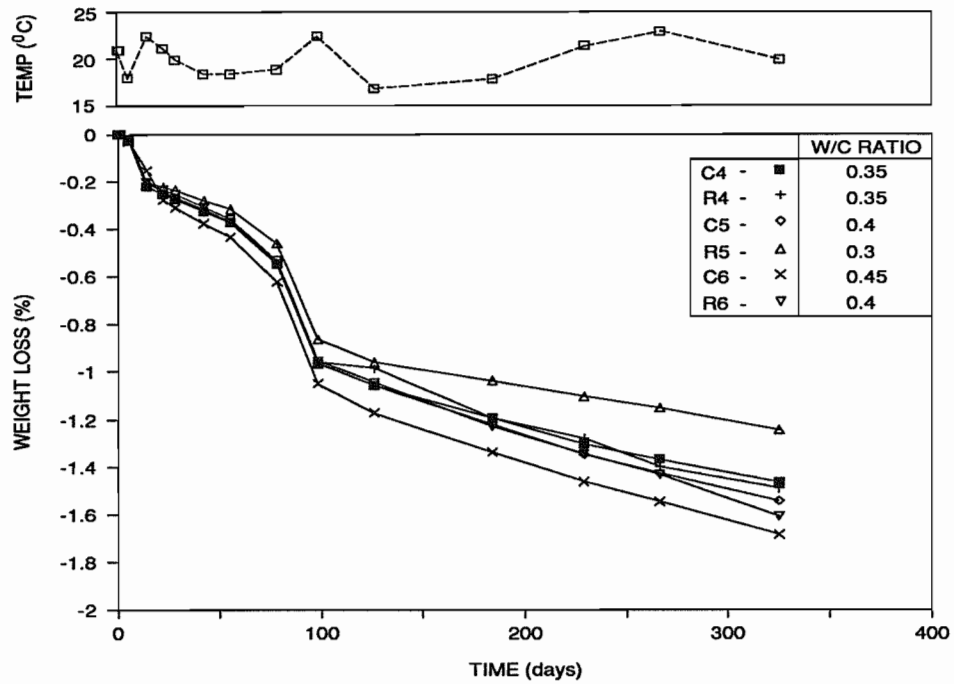


Figure 7.10 Weight change of the concrete specimens in set B

paint were not sufficient for complete protection from environmental conditions. Although the weight loss (defined by Neville, 1973) was relatively small, the loss of water would have caused some drying shrinkage.

7.2.6 Creep

Creep tests were performed on 100mm x 100mm x 200mm specimens stacked in pairs in a conventional creep rig at the University of Surrey. The creep apparatus had seven loading bays in all but only six were in use for this test. An overall view of the rig is provided in Plate 7.1 and a more detailed drawing of an individual loading bay is shown in Figure 7.11.

The specimens were painted with two coats of bitumen paint but the top and bottom faces were left untouched. These faces were then smoothed with a metal file and sandpaper to provide flat surfaces so that high stress concentrations would be avoided when the specimens were loaded. Each pair of specimens, when placed in position in the rig, was separated by a flat steel plate of 5mm thickness.

The stress in the system was maintained using a Greer-Mercier hydraulic accumulator and was applied to each pair of specimens through a flexible diaphragm at the base of each bay. Readings could not be taken on all four sides due to the structure of the creep apparatus so the specimens were orientated to allow access to three sides. Trial loadings were carried out at low stresses to check that the specimens were not loaded eccentrically. Creep was monitored using a 100mm Demec gauge. The stress on the specimens was maintained at 14.7N/mm^2 subjecting them to stress/strength ratios between 0.2 and 0.28. Although comparisons would normally be made for similar stress/strength ratios, only some of the concretes could be compared on that basis.

Creep for both sets of mixes is plotted in Figures 7.12 and 7.13. The recycled aggregate concretes with the highest water/cement ratios exhibited the highest creep because creep, like shrinkage, is dependent on the amount of hydrated cement paste in the concrete and on the modulus of the aggregate. R5 which had a low water/cement ratio appeared to creep very little. The low water/cement ratio of this mix would have produced a smaller quantity of cement paste and consequently it would be expected that creep would be low. However, creep is also dependent on the strength of concrete but because strength and water/cement ratio are related it is difficult to conclude which factor has the greatest effect on creep (Neville, 1973).



Plate 7.1 Concrete specimens in the creep apparatus

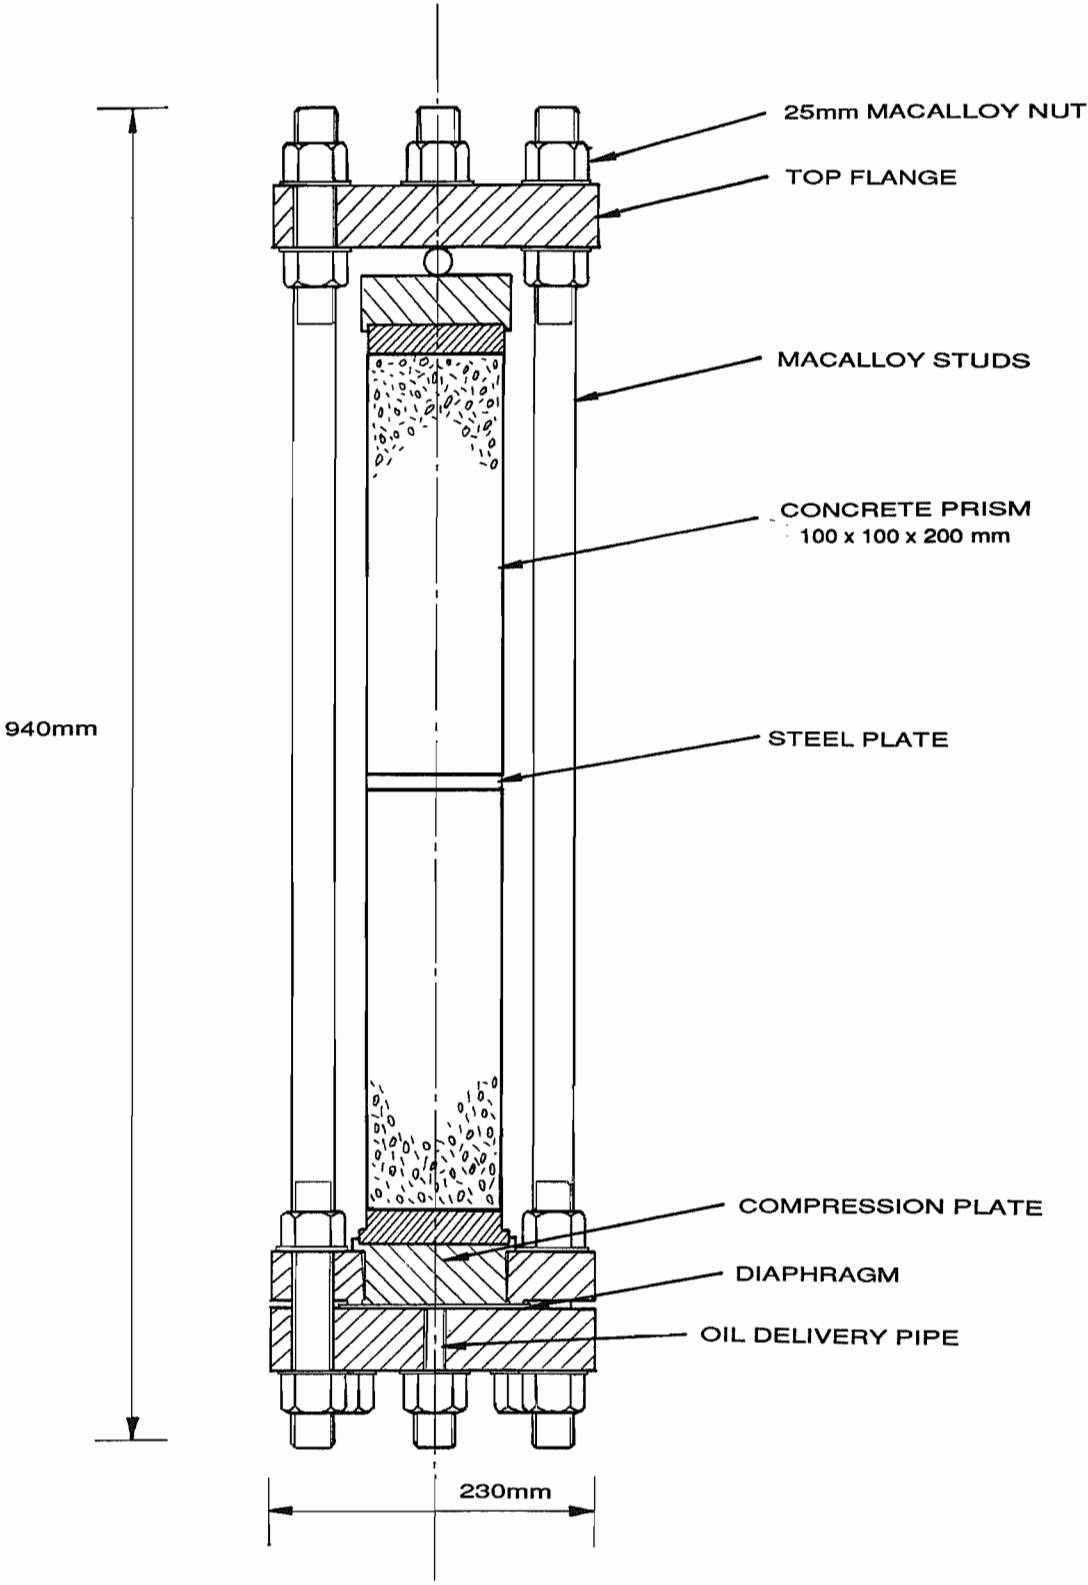


Figure 7.11 Details of a loading bay in the creep apparatus (after Edgington, 1969)

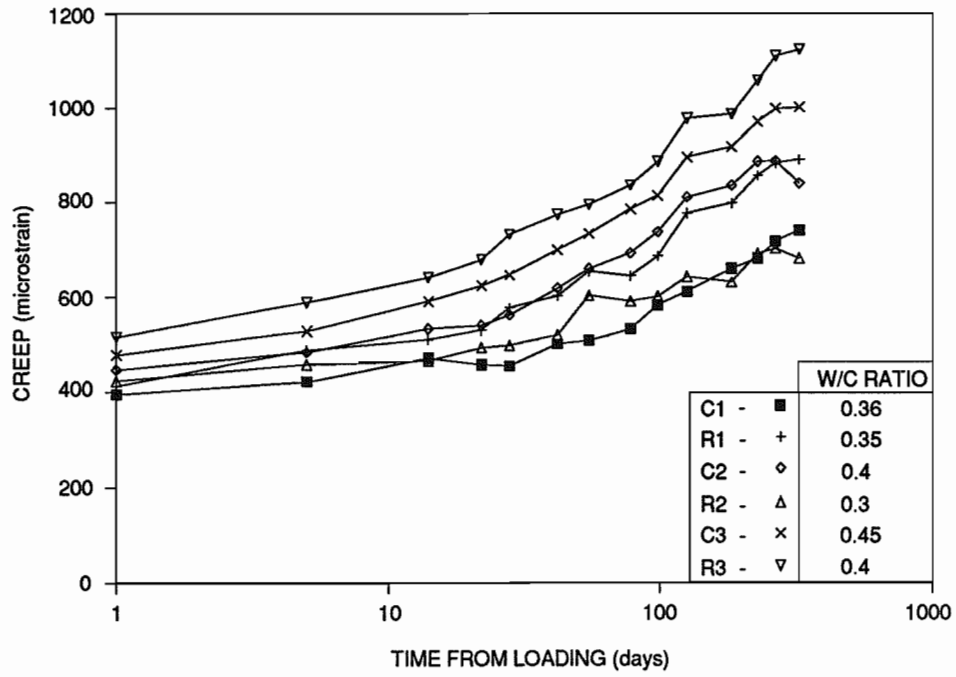


Figure 7.12 Creep of the concrete specimens in set A

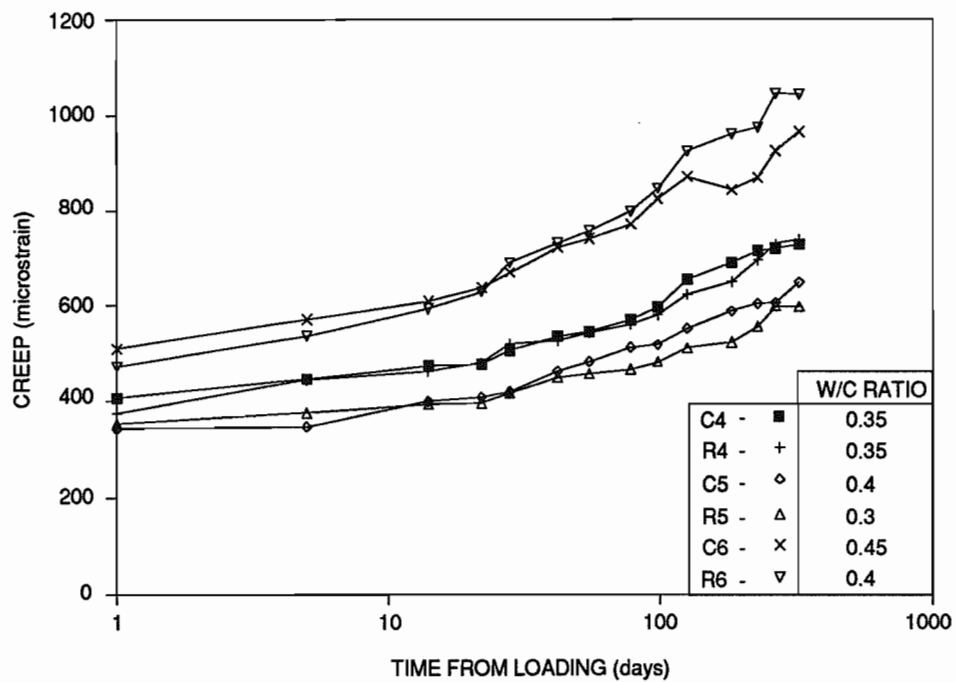


Figure 7.13 Creep of the concrete specimens in set B

7.3 Discussion

At the mix design stage, two decisions were taken which made this work different from other research in the field of recycled aggregate for use as aggregate in concrete. First, the specific gravity of the recycled aggregate was not taken into account so that each mix had the same mass of aggregate. It was considered that it would be easier to observe the effect of recycled aggregate on the properties of concrete by adopting this method. Secondly, the aggregates were not pre-soaked before mixing so that an accurate estimate of the water content in the mixes could be made. It is likely if recycled aggregate was to be used extensively for aggregate in concrete that its specific gravity would be taken into account at the mix design stage. Although the aggregate was not pre-soaked before mixing the results of the tests on hardened concrete appeared to be better than those of other researchers. It is suggested, however, due to the complex nature of concrete that it would be safer to pre-soak aggregates so that no movement of water would take place into the aggregate after mixing. Pre-soaking of aggregate could not be omitted from the procedure of concrete manufacture without further research.

When recycled aggregate concrete and conventional concrete were compared on the basis of strength and Young's modulus, it was noted earlier in this chapter that recycled aggregate concrete performed very well. This may be due to the following reasons.

- (i) The recycled aggregate was clean and the original and new mixes were both made in a laboratory under controlled conditions.
- (ii) It was considered that the porosity of the recycled aggregate would have had a large influence on the Young's modulus of the concrete. However, the angular particles of the recycled aggregate, compared with the smooth particles in the control mixes, provided greater particle interlock which apparently counteracted the effect of

porosity. The high compressive strength of the recycled aggregate concretes could also be attributed to the angular particles because the mechanical bond in concrete is dependent on the surface shape and texture of the aggregate.

The rate of gain in strength of the recycled aggregate concretes appeared to be very consistent and it is clear from Figures 7.2 and 7.3 that a prediction of the 28 day strength of the recycled aggregate concretes would be more accurate than for the controls.

When Figures 7.7 and 7.8 were examined it was observed that after 100 days there was almost a linear relationship between shrinkage and weight loss which may mean that as the concrete aged the water loss from the sealed specimens was largely responsible for shrinkage. A similar relationship is apparent in Figures 7.9 and 7.10 for set B. It can be seen from Figure 7.14 that the slopes of the lines are similar and that the recycled aggregate concretes exhibited the highest shrinkage whereas, as expected, the control mix with a water/cement ratio of 0.45 exhibited the highest weight loss. Similar relationships exist for the second set of mixes.

It is apparent from Figure 7.15 that the water/cement ratio and the type of aggregate did not have a major effect on shrinkage. The relationship between shrinkage and water/cement ratio was very similar for concretes made with both types of aggregate. This is encouraging because the problems expected with the use of recycled aggregate concrete in the civil engineering industry are mainly associated with shrinkage and creep.

It can be seen in Figure 7.16 that there appears to be a linear relationship between creep and stress/strength ratio for each type of concrete. Both recycled and natural aggregate concretes exhibited an increase in creep as the stress/strength ratio increased but at a stress/strength ratio of 0.26 the control concretes achieved only 65% of the creep exhibited by the recycled

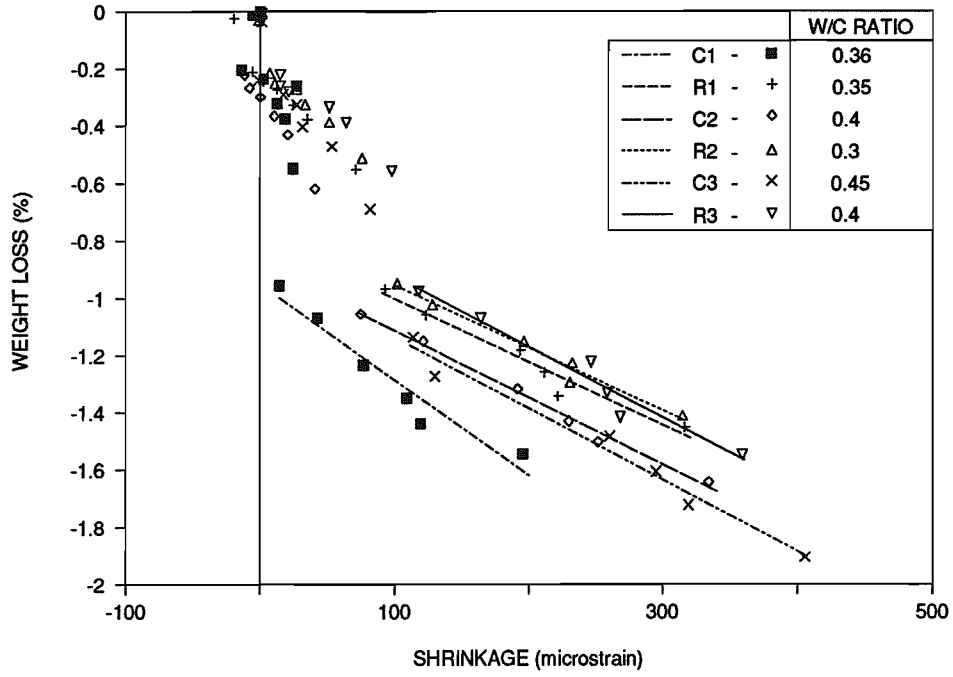


Figure 7.14 Relationship between weight loss and shrinkage for set A

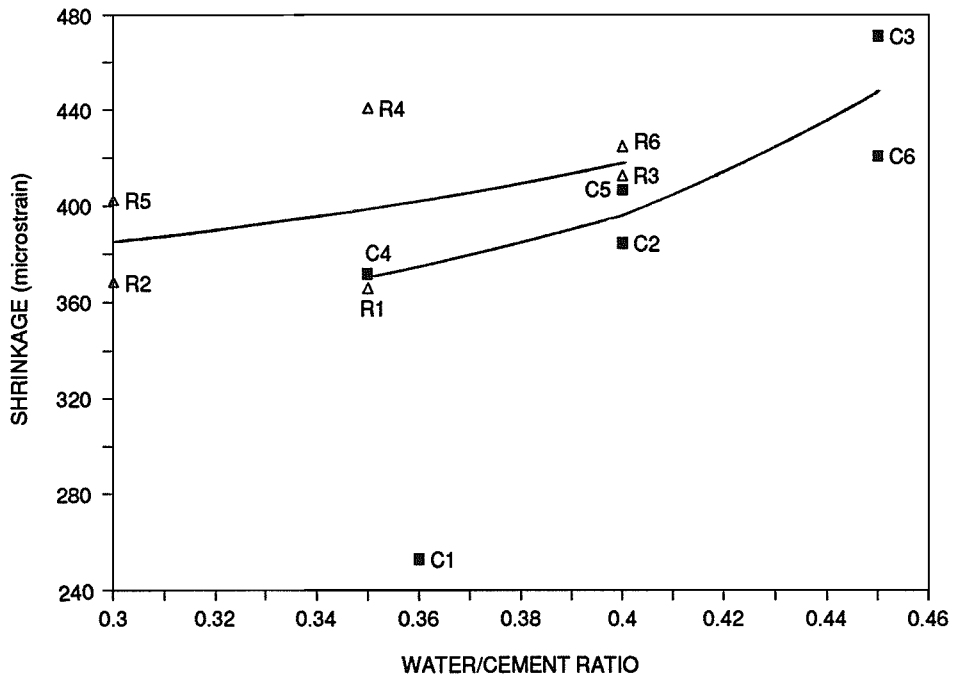


Figure 7.15 Relationship between shrinkage and water/cement ratio

aggregate concretes. As the strength of concrete is dependent on the water/cement ratio, it follows that the concretes with the highest stress/strength ratios also have the highest water/cement ratios. Therefore the influence of water/cement ratio on creep follows the same trend as the influence of stress/strength ratio, as can be seen in Figure 7.17.

7.4 Conclusions

- (i) The 8% increase in free water in the recycled aggregate mixes, which was suggested by Ravindrarajah (1985), was too high to achieve a workability similar to that of the control concretes. It is likely that the water allowed in the mixes for water absorption of the aggregate was not completely used because the aggregates were not pre-soaked before mixing. This would imply that the free water was higher and consequently the workability would have been improved.
- (ii) At early ages, the recycled aggregate concretes had lower compressive strengths but by 28 days had achieved the strengths of corresponding controls at more consistent rates.
- (iii) The difference in the compressive strength of recycled aggregate concrete and conventional concrete was insignificant and the large differences found by other researchers, mentioned in Section 7.1.3, were not observed. In this study, the conventional aggregate consisted of smooth particles whereas the recycled aggregate particles were very angular. The better particle interlock in the recycled aggregate concretes would have contributed to the high strength.
- (iv) In most cases, the recycled aggregate concretes achieved the same or higher Young's moduli. This also disagrees with the findings of other researchers but may be explained by the same reasons mentioned in Conclusion (iii).

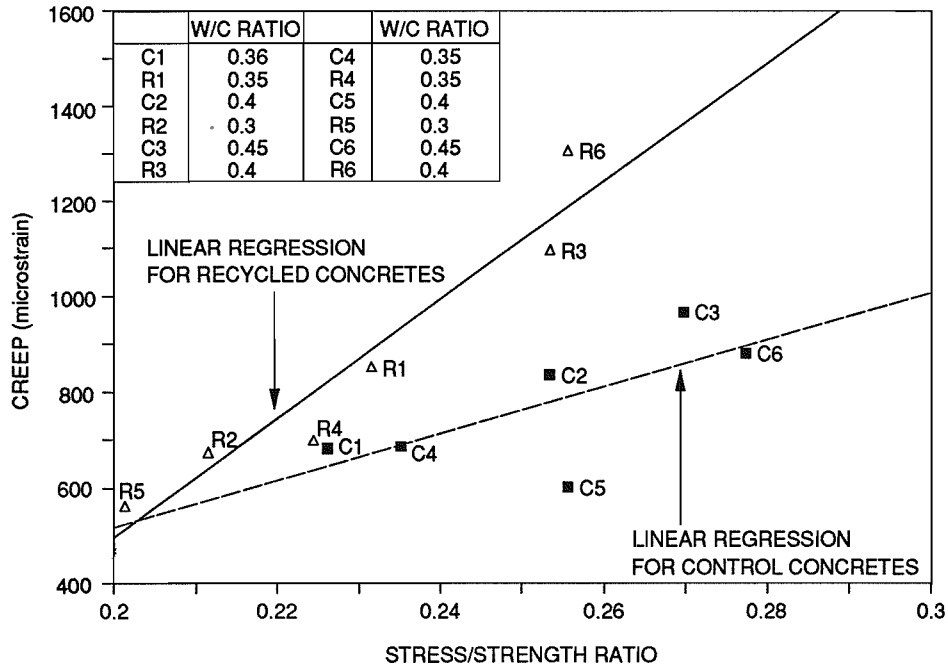


Figure 7.16 Relationship between creep and stress/strength ratio

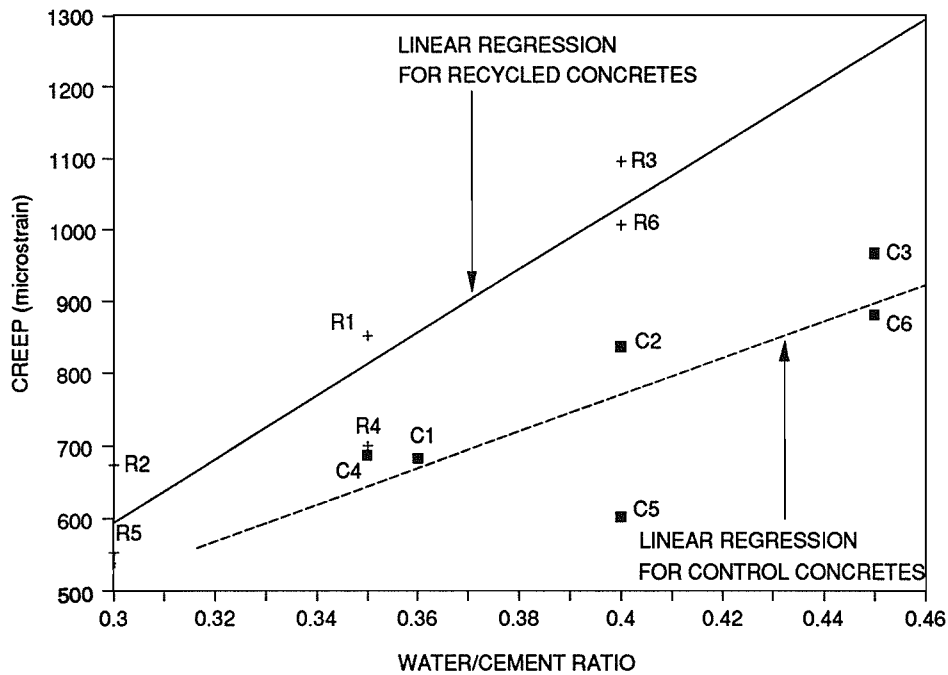


Figure 7.17 Relationship between creep and water/cement ratio

- (v) The control concrete with the lowest water/cement ratio achieved the least shrinkage whereas both types of concrete made with high water/cement ratios exhibited high shrinkage. It was evident that shrinkage, to a large extent, was not very sensitive to water/cement ratio or the type of aggregate used.
- (vi) Greater creep was exhibited in the recycled aggregate concrete particularly when a high water/cement ratio was used. This was attributed to the lower modulus of the crushed concrete aggregate and the larger quantity of hydrated cement paste in the recycled aggregate concrete. At a low water/cement ratio there appeared to be little difference in creep or shrinkage when the two types of concrete were compared.
- (vii) The recycled aggregate in this research was very clean and the work was carried out in laboratory conditions. The results from this chapter could not be used as a direct guide for the manufacture of recycled aggregate concrete in industry unless the aggregate had been processed carefully and was clean. Small quantities of contaminants could hinder the hydration of cement and produce concrete which was not durable. If, in the future, recycled aggregate was to be considered for use as structural concrete, then the aggregate would need to be tested to examine chloride and sulphate contamination.
- (viii) As Hansen (1985) suggested, trial mixes should be conducted where possible before making recycled aggregate concrete. It appears from the results of this research that better properties might be achieved if recycled aggregate was not pre-soaked before mixing and if low water/cement ratios were used. However, the data from this study is limited and further research would be required to confirm these conclusions.

CHAPTER 8

DISCUSSION

This chapter is divided into two parts. In Section 8.1, data from previous chapters are brought together to show some overall trends for the behaviour of recycled aggregates and recommendations are made on the placement of these materials, particularly for use in road sub-base layers. In Section 8.2, a more general view is taken on the use of recycled materials in civil engineering. This section includes suggestions for altering material which does not comply with existing specifications and some ideas are discussed concerning ways in which the civil engineering industry may come to terms with and use recycling of construction waste to its advantage.

8.1 Global review of test results

In Section 3.7, the results of density tests conducted on limestone and demolition debris in the Portsmouth field trial were presented. A series of laboratory density tests were also carried out, the results of which were presented in Section 4.1.3. It is interesting to observe whether the laboratory compaction test described in BS 5835 (1980) can reproduce site densities, as Pike and Acott (1975) suggested it would.

The limestone used on site had a specific gravity of 2.61 whereas the specific gravity of the limestone aggregate tested in the laboratory was 2.69. Therefore a comparison on the basis of dry density was not possible. However, when the results were presented in the form of V_s (proportion of volume occupied by solids), the particle packing on site could be compared with that achieved in the laboratory. The maximum V_s obtained on site was 96.5% and the

minimum was 82% with an average for all tests of 90.3%. The peak dry density of 2320kg/m³ which was obtained in the laboratory converts to a V_s of 86%. It is apparent therefore that V_s on site was higher which suggests that site compaction was more effective.

A similar comparison can be made for the results of density determination on demolition debris. It can be seen in Section 3.7 that the maximum V_s obtained on site in the upper layer was 85.3% and the minimum was 70.9% with an average of 79.9% for all density tests. The V_s corresponding to the maximum density in the laboratory was 73.4%. Therefore the difference between the peak V_s obtained in the laboratory and the average density obtained on site was 6.5% whereas the difference for limestone was 4.3%. It can be concluded therefore that site compaction was again more effective than that produced in the BS 5835 compaction test (1980).

One of the objects of this research was to establish the best condition in which to place recycled material and limestone so that the best performance with regard to compaction, shear strength, bearing capacity and frost heave could be achieved. Figures 8.1, 8.3 and 8.5 show the laboratory results of ϕ_{ds} , CBR and frost heave plotted against V_s for limestone, demolition debris and crushed concrete. Figures 8.2, 8.4 and 8.6 display the same data plotted against free water content. The results presented in these figures have already been presented in Chapters 4, 5 and 6. As might be expected, ϕ_{ds} increases as V_s increases (Figure 8.1). No relationship between ϕ_{ds} and free water content could be observed because the tests were conducted at similar moisture contents. CBR was found to be dependent on V_s although the relationship was not as clearly defined as that for ϕ_{ds} due to large scatter in the results, which can be seen in Figure 8.3. In Section 4.2.3, it was found that although CBR was primarily a function of V_s , there also existed some influence of free water content on CBR. When the moisture content was increased the CBR was greatly reduced. This can be seen in Figure 8.4 but the trend is not as definite as the dependence of CBR on V_s .

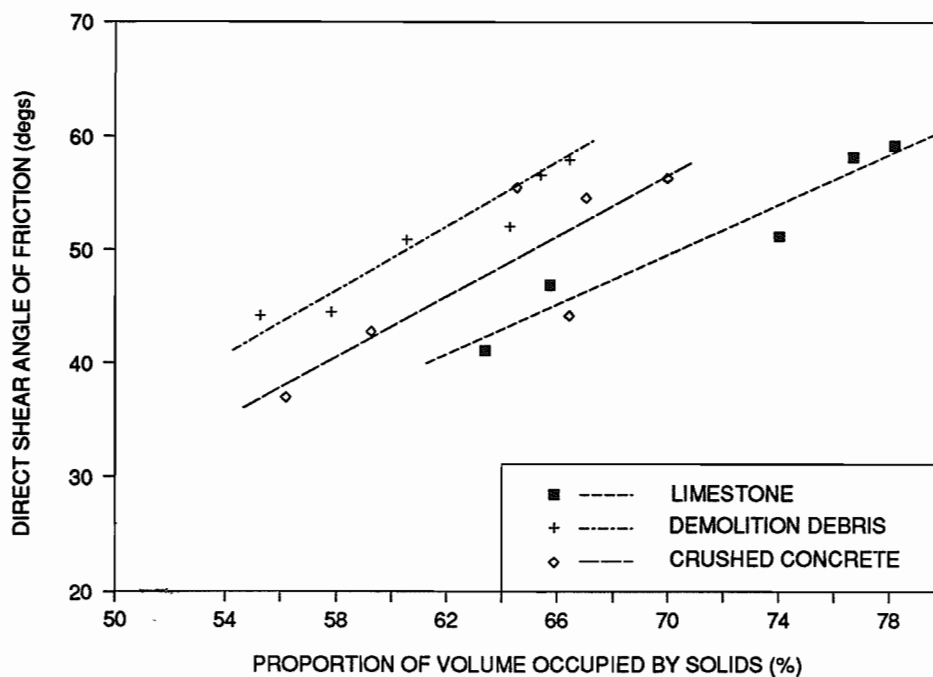


Figure 8.1 Influence of the proportion of volume occupied by solids on the direct shear angle of friction

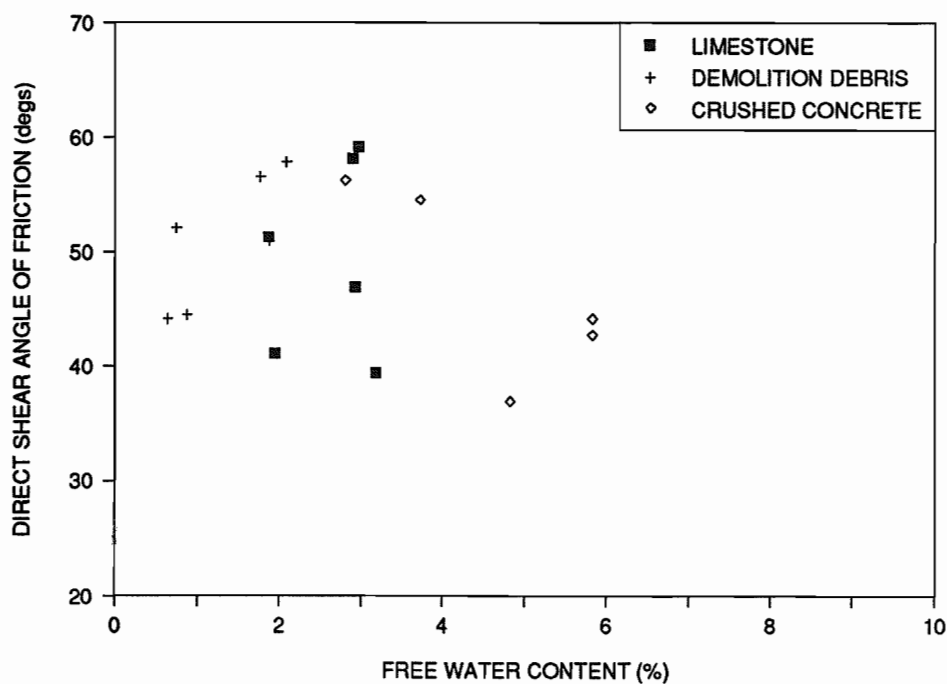


Figure 8.2 Influence of free water content on the direct shear angle of friction

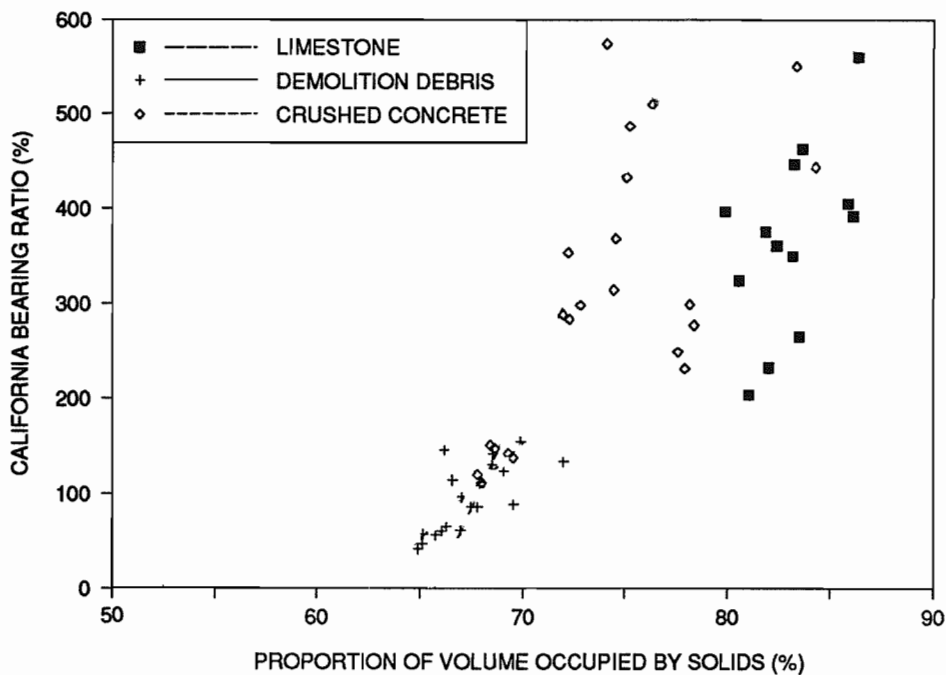


Figure 8.3 Influence of the proportion of volume occupied by solids on CBR

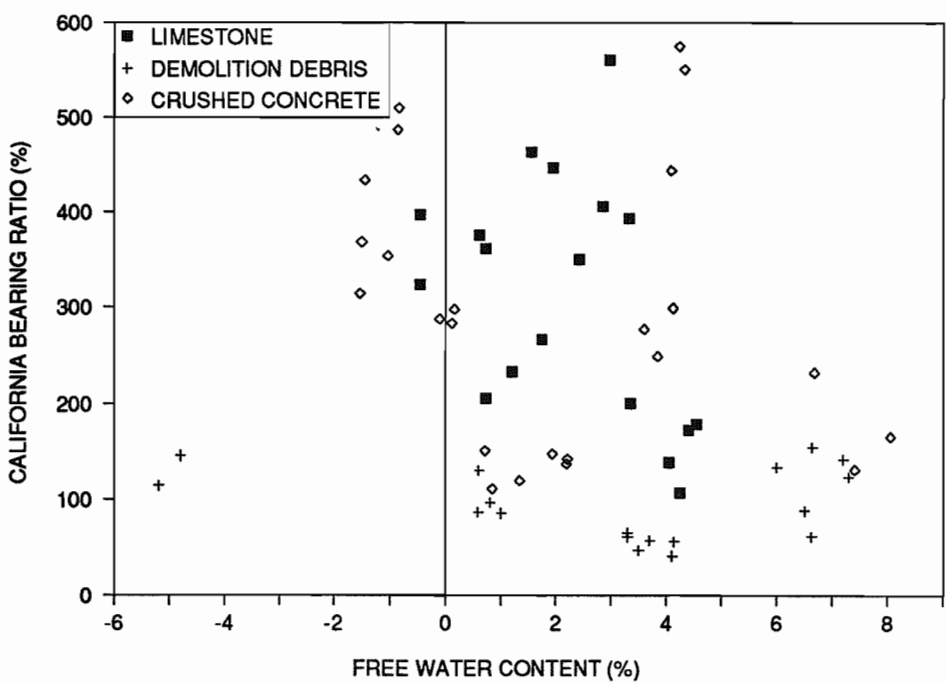


Figure 8.4 Influence of free water content on CBR

shown in Figure 8.3. Definite trends did not exist for the frost susceptibility results shown in Figures 8.5 and 8.6 except for the apparent dependence of the frost susceptibility of crushed concrete on free water content. In most cases the frost heave samples for each material were compacted at a similar density and therefore a relationship between frost heave and V_s could not be observed.

The values of V_s and free water content which produced the best and worst performance of the materials were noted from Figures 8.1 to 8.6 and are listed in Tables 8.1 and 8.2. The peak V_s and optimum free water content, obtained from compaction tests on the materials, are also listed in these tables.

PARAMETER	V_s (%)					
	LIMESTONE		DEMOLITION DEBRIS		CRUSHED CONCRETE	
	Best	Worst	Best	Worst	Best	Worst
ϕ_{ds}	78 (59 ⁰)	63 (41 ⁰)	66 (57 ⁰)	55 (44 ⁰)	70 (56 ⁰)	56 (37 ⁰)
CBR	86 (550%)	80 (100%)	70 (155%)	65 (41%)	75 (566%)	67 (111%)
Frost heave	86 (3mm)	75 (6mm)	69 (10mm)	71 (13mm)	70 (3.5mm)	75 (30mm)
Compaction	86	80	73	66	77.5	66

Table 8.1 The influence of V_s on the performance of the materials

Some conclusions can be made from the data in these tables. For limestone to achieve the highest CBR and lowest frost heave values, a V_s of 86% was required. However, the highest V_s attained in the shear box tests was 78%. If shear box tests were conducted on samples at a V_s of 86% it is likely that ϕ_{ds} would have been higher because of the direct relationship between V_s and ϕ_{ds} and it is suggested therefore that limestone should be placed at a V_s of

86%. The peak density which was achieved in the compaction tests also corresponded to a V_s of 86%. It can be seen in Table 8.1, when limestone was compacted at a V_s of 80% or less, that the material was in its worst condition with respect to ϕ_{ds} , CBR and frost heave.

PARAMETER	FREE WATER CONTENT (%)					
	LIMESTONE		DEMOLITION DEBRIS		CRUSHED CONCRETE	
	Best	Worst	Best	Worst	Best	Worst
ϕ_{ds}	2.6* (59 ⁰)	2.6* (39 ⁰)	1.3* (56 ⁰)	1.3* (44 ⁰)	4.5* (56 ⁰)	4.5* (37 ⁰)
CBR	2.3 (550%)	4 (100%)	7 (155%)	4 (41%)	4 (566%)	1 (111%)
Frost heave	3 (3mm)	1.5 (6mm)	7 (10mm)	3 (13mm)	2.5 (3.5mm)	9.5 (30mm)
Compaction	3.1	2.4	5	1.1	5.3	2.5

Table 8.2 The influence of free water content on the performance of the materials

- * For each material all shear box tests were conducted at a similar moisture content.

In Table 8.2, it is apparent that limestone performed best at a free water content of 2%-3%. However, the free water content which corresponded to the lowest density in the compaction tests was 2.4%. The highest frost heave was achieved at a free water content of 1.5% but the lowest CBR of 100% was obtained at a relatively high free water content of 4%.

The V_s at which demolition debris achieved its best performance with regard to CBR and frost heave was 69%-70% which is slightly higher than the value of 66% which was obtained in the shear box tests. These data suggest that demolition debris could be placed at a V_s of 69%-70% which is 4% lower than the peak V_s obtained in the compaction tests. The lowest V_s obtained in the compaction tests was 66% and when V_s was below this value the performance of the material deteriorated with respect to ϕ_{ds} and CBR. Surprisingly, the

highest frost heave was observed when V_s was increased to 71%.

It can be seen in Table 8.2 that there was a large difference between the free water content of 7% required to achieve the highest CBR and lowest frost heave and the value of 1.3% which was obtained in the shear box tests. It was considered that the latter value was too low and that demolition debris should be placed at a free water content closer to that achieved at peak density in the compaction tests i.e. 5%-7%. Results quoted in Table 8.2 for demolition debris confirmed the observation made on the limestone data that material performance deteriorated with decreasing free water content.

The V_s at which crushed concrete achieved low frost heave and high shear strength was 70% with the highest CBR value attained at a V_s of 75%. It appears that a V_s in the range of 75%-77.5% would be the most suitable to achieve high values of ϕ_{ds} , CBR and density but a frost heave of 30mm was observed at a V_s of 75%. This excessive heave was more likely to be caused by the high moisture content of the samples and not by the level of particle packing. The lowest CBR and ϕ_{ds} values were obtained at a V_s of less than 67% which was close to the V_s corresponding to the lowest density achieved in the compaction tests.

The data suggest that crushed concrete should be placed at a free water content of 4%-4.5% which is slightly lower than the free water content of 5.3% obtained at peak density in the compaction tests. The initial moisture content of the crushed concrete samples appeared to have considerable influence on frost heave and at a free water content of 4% the frost heave of crushed concrete was 10mm. The behaviour of crushed concrete with regard to frost heave needs to be studied further to investigate the apparent dependency of frost heave on the initial moisture content and the benefits from setting action with time.

The above interpretation of the data in Tables 8.1 and 8.2 is made on the basis of the best and worst performance of the materials exhibited in laboratory tests. The behaviour of

frost heave, however, was not investigated fully and the free water content did not appear to have a large influence on frost heave except for the apparent dependence of frost heave on the initial moisture content of crushed concrete.

It was noted earlier that higher V_s values were achieved on site than in the laboratory at lower moisture contents. In general, CBR and ϕ_{ds} increase as V_s increases and therefore the material should be compacted to the maximum V_s level attainable for a particular compactive effort at the moisture content required to achieve this maximum V_s . It was stated in Section 6.7 that to prevent frost heave damage to granular layers, a high permeability is desirable. However, if high values of CBR and ϕ_{ds} are to be achieved, a dense stiff layer would be required. This again reinforces the need for open packed capping layers to be used which would prevent capillary rise and therefore reduce frost heave.

8.2 Recycling in civil engineering

Considering the amount of repairs carried out on British roads every year, the design and construction of road pavements using natural aggregate in the unbound layers could be improved. Although road pavement deterioration cannot always be attributed to a weakened sub-base, it has been found, even when natural aggregate is used, that a sub-base can be damaged by frost heave or can be subjected to excessive deformations by construction traffic at an early age. The data from this research suggest that a road constructed using recycled aggregate in the sub-base layer would not be unlike a structure containing a natural aggregate sub-base. This observation could only be confirmed by conducting field trials using accelerated traffic loading or by placing recycled aggregate in the sub-base of a lower class road and monitoring its performance under normal traffic loading. It would be unhealthy to try to remove all scepticism of recycled aggregates until extensive research of this type has been conducted.

In recent years, demolition contractors have been forced to recycle construction waste due to high dumping costs, particularly in large cities. Some contractors have purchased basic mobile crushing and screening plant to recycle construction waste and use the recycled product either on the same site or locally. This is worthwhile but in a sense demolition contractors have been forced to bypass a step in what might be referred to as the ideal progression of recycling in the construction industry. The setting up of recycling plants by individual contractors, without some standard guidance on the production of high quality recycled material, could result in the production of many recycled products of variable content and quality.

The most efficient way of promoting recycling in the British civil engineering industry would have been to produce a standard to which recycled aggregates should comply. This might have had the effect of reducing the number of mobile recycling plants being installed. Alternatively, it could have encouraged demolition contractors to unite their efforts by setting up sophisticated, stationary recycling plants around large cities to which all construction waste could be brought for recycling. These recycling plants would be capable of recycling all grades of contaminated material with the guarantee of producing a good quality aggregate. The producer of recycled aggregate at a recycling plant should ensure that the aggregate complies with any existing specification for the purpose for which the aggregate is required. Random testing should also be undertaken at the site where the recycled aggregate is used.

A fixed site recycling plant would serve both as a dumping site and a source of aggregate. In some cases, however, demolition contractors might prefer to use mobile crushing plant for particular demolition contracts. Both stationary and mobile recycling plants are likely to have important roles to play in the demolition industry.

Three situations are likely to arise for a demolition contractor.

- (i) The rubble from a structure under demolition is not to be reused as a high quality aggregate on the same site. If the rubble is to be used as capping material or to bring up levels on the site, then the demolition contractor would be justified in using a mobile recycling plant.
- (ii) A structure is demolished and the rubble is needed for reuse on the same site but in the form of a high quality aggregate. The client could only be guaranteed of a high quality product if the rubble was recycled in a plant with good cleaning systems, particularly if the structure was made up of several types of material. The demolition contractor in this case has three options.
 - a) A sophisticated recycling plant could be brought on to the site. Normally the expense incurred would not be justified unless the structure was very large and took a considerable length of time to demolish.
 - b) A mobile crushing plant could be used and the demolition contractor could aim to produce a recycled product which would pass the required specifications although his success in this objective would not be guaranteed.
 - c) The rubble could be sent to a large fixed site recycling plant which would guarantee the quality of the recycled product.
- (iii) The third situation involves the recycling of relatively clean rubble e.g. a concrete slab in a road pavement. Fitzpatrick & Sons Ltd. (1989) proved that a Type 1 graded sub-base material could be produced using mobile crushing plant on a road

maintenance contract and Somerset County Council (1989) used crushed concrete, obtained from the break up of the concrete slab of the M5 motorway near Taunton, as Type 1 sub-base material.

It can be seen that there is a place for both types of recycling operation in the civil engineering industry. The most efficient system would be a combination of both types of plant to be made available i.e. to have fixed site recycling plants placed around major cities and also mobile crushing plants for recycling on particular sites.

The installation of any type of recycling plant is likely to cause environmental problems locally. Proper controls on dust and noise should be organised at the initial stages of design and installation of the plant. Old quarry sites are ideal locations for recycling plants. Although the location of a quarry would have been governed by the mineral reserves present there would also have been some consideration given to its proximity to residential areas. If sufficient excavation had taken place the floor level of the quarry would be below ground level. Therefore, noise barriers for the recycling plant would already be in existence.

Dust could be controlled by the use of precipitators where dust from the crushers is cycloned off into an enclosed unit. Stockpiles of aggregate should also be sprinkled with water when the weather is hot and dry. Discarding or reusing fines and dust is a problem which has been encountered by producers of crushed rock and in recycling plants in Europe although some crusher fines have been used in the manufacture of low quality bricks (Mulheron, 1990).

8.3 Possible uses of recycled materials

In Section 2.3.1, some possible uses of recycled materials were listed and in this section some conclusions are made on the ability of the recycled aggregates examined in this study

to pass the compliance tests. As stated previously, both crushed concrete and demolition debris could be used as road sub-base material but the frost susceptibility of any recycled material to be used in a particular job would need to be determined. However, as specified in Clauses 803 and 804 of the Specification for Highway Works (1986), the use of demolition debris is not allowed for use as sub-base material. From the results of tests conducted on demolition debris in this research it is likely that it could be considered for use as sub-base material.

If the sulphate content of recycled aggregate was found to be below 1.9g of SO_3 per litre then it could be used as the aggregate in lower grade, cement bound material for use in roads, as defined in Clauses 1035, 1036 and 1037 of the Specification for Highway Works (1986).

The particle grading of material to be used as pipe bedding is different to the well graded aggregate required for sub-base. Depending on the grade of pipe bedding required, the particle size of the material should be in the ranges of 20mm-5mm, 14mm-5mm or 40mm-5mm (Clause 503 of the Specification for Highway Works, 1986). To obtain these gradings, some screening would be necessary to remove large particles and fines. The recycled material would also have to be tested to ensure that its sulphate content was less than 1.9g/litre. Material to be used as backfilling to pipe bays should not have more than 3% of its particles passing the 0.075mm sieve and the maximum particle size should be 20mm (Clause 512). These limits on grading are more restrictive than those for sub-base aggregate.

Clause 505 of the Specification for Highway Works (1986) requires material for use as backfilling of trenches to be non-plastic and to have a 10% fines value greater than 50kN. These requirements are similar to those for material to be used as backfilling to earth retaining structures (Clause 513). It can be seen in Sections 3.4 and 3.5 that both crushed concrete

and demolition debris complied with these requirements.

There are four grades of fill to structures listed in Clause 610 of the Specification for Highway Works (1986). From the results of the tests conducted on crushed concrete and demolition debris it can be concluded that the recycled materials would comply with the requirements for all four grades. If organic matter in the recycled materials was found to be below 2% by mass and the sulphate content was less than 1% by mass then the materials could also be used as aggregate for cement stabilised capping, as defined in Clause 614.

In Chapter 3, it was evident that a Type 1 certified limestone did not comply fully with the Type 1 sub-base requirements. In general, the only test which is performed on a conventional aggregate to be used as sub-base material is a particle grading test. If recycled material is to be used for a particular job, it usually must undergo all tests listed in the Specification for Highway Works (1986). One of the conclusions of this study is that conventional aggregate is as likely to fail the compliance tests as recycled aggregate. For consistency and the fair treatment of secondary materials in construction, it is suggested that all aggregates should undergo the same series of tests.

If a recycled aggregate fails the compliance tests, then there are several ways in which its performance may be improved. Altering the particle grading at the recycling plant should not be difficult if screens are available and if the jaw crushers are set at the correct setting to produce the required grading. The susceptibility of recycled materials to frost might be found to be lower if frost heave tests were conducted three months after placement of the aggregates rather than immediately after compaction. If further research proved that frost susceptibility did not improve with time, the addition of cement to recycled aggregate could reduce frost heave and improve its bearing capacity and shear strength. The partial replacement of recycled material with natural aggregate is likely to improve its performance

but this partly defeats the purpose of recycling i.e. slowing down, as much as possible, the depletion of natural aggregate. If a sample of recycled material appears to be plastic then it is more than likely to have been contaminated with clay fines. This would have occurred if the fine material had not been removed before crushing. Again, in this case the recycling process would need to be altered if an acceptable material was to be obtained.

There is likely to be some scope for using recycled aggregate as aggregate in new concrete and extensive research has been conducted in this area. If precautions were taken e.g. increasing the cement content to achieve adequate strength or increasing the size of a concrete member to allow for shrinkage, then recycled aggregate concrete could compare well with conventional aggregate concrete. It might be more difficult to convince clients to use recycled aggregate in concrete than it is to persuade them to use recycled aggregate as sub-base and fill material. It is unlikely that there would be a large demand for recycled aggregate for use in structural concrete although some use might be made of crushed concrete as aggregate in lean concrete.

8.4 Estimates of errors

Estimates of the accuracy of the test data, particularly of the density and CBR results presented in Chapter 4, were not made. This creates difficulty when results are compared. An estimate of the errors likely to arise could have been made if several other tests were conducted but this would have taken considerable time. However, the consequence of errors in the measurement of specific gravity can be examined. In Figure 4.4, for example, the percentage air voids lines were calculated using a specific gravity of 2.56. If the specific gravity was within 0.5 of this value and the 0% air voids line was calculated using a specific gravity of 2.61, then all data points on the figure would fall to the left of the 0% air voids line. This 19% error in specific gravity would be the minimum error, if the dry density measurements were assumed to be accurate.

CHAPTER 9

CONCLUDING REMARKS

In this chapter, the main conclusions of the research on recycled aggregates are presented. Some conclusions were made earlier at the end of each chapter which were more specific to the chapter subjects. Ideas for further research in the field of recycled materials and in aggregates in general are also discussed with some recommendations for the production of a standard for recycled materials in Britain.

9.1 Conclusions

In Chapter 2, it became clear that Britain was well behind other countries in its attitude to recycling of construction waste. The construction industries of other countries have accepted recycling as a useful, alternative source of aggregate and have written standards to which recycled aggregates should comply. These standards mainly include allowable limits of contamination in the recycled materials.

Britain is relatively rich in natural aggregate reserves and therefore the civil engineering industry did not seriously consider the recycling of construction waste until dumping became expensive and an increased awareness of the environment became evident in recent years. In comparison, the Netherlands has poor reserves of natural aggregate and has developed sophisticated recycling plant which incorporates several sorting and cleaning techniques to produce high quality recycled aggregate for use in construction. This confirms that the technology and equipment exist to produce reusable aggregate from demolition waste.

At the Symposium on Unbound Aggregates in Roads (1989), it was decided that the plasticity test described in BS 1377 (1975) was not satisfactory for the determination of the plasticity of aggregates and that ideally a new test should be designed for this purpose. However, it was also recognised that the development of such a test might be difficult.

Some of the standard compliance tests involve testing aggregate in cylindrical moulds. The CBR test is conducted on material less than 20mm in particle size which is compacted in a 152mm diameter mould. Aggregate to be tested in the 150mm diameter mould of the BS 5835 (1980) compaction test is required to contain particles less than 37.5mm in size whereas in the frost heave test, particles up to 37.5mm in size are tested in a 102mm diameter mould. The three tests are conducted on aggregate which is to be used for the same purpose but the laboratory tests are conducted on different gradings. These gradings may also be unlike the grading of aggregate to be placed on site. This approach to aggregate testing is inconsistent and Dawson and Jones (1989), in the conclusions of the Symposium on Unbound Aggregates in Roads, stated that some effort should be made to standardise the grading and the ratio of the mould diameter to the maximum particle size.

In Chapter 8, it was found that limestone should be placed at peak dry density and optimum moisture content, as defined in the BS 5835 compaction test (1980), to achieve high values of CBR, ϕ_{ds} and frost heave. The results from tests on demolition debris suggest that it could perform well when placed at a density slightly below peak and at a moisture content below optimum. Crushed concrete should perform well if it is placed at peak density and optimum moisture content or slightly below.

Although the recycled materials could be described as lightweight aggregates, their shear strength was found to be similar to that of limestone. The shear box test method, which was developed by Earland and Pike (1985) to examine aggregate for use as sub-base material,

was conducted on limestone and the recycled materials. From the results of these tests it was concluded that demolition debris and crushed concrete would be classified in the medium strength category and limestone in the highest strength category.

The critical state angles of friction of the recycled materials and of limestone were in the range of 40° - 42° and were considerably higher than the 33° value which was obtained for Leighton Buzzard sand. The value of Q , defined by Bolton (1986) as a constant depending on the mineralogy and compressibility of a material, was found for the aggregates to be greater than 10. This contradicted the suggestion by Bolton (1986) that materials with particle grains softer than quartz or felspar would have Q values less than 10. The results of this research suggest that Q may be dependent on the particle grading, the ratio of the size of the box to the maximum particle size in the sample or the angularity of the particles. The accuracy of the Cornforth (1973) loose heap test for the determination of the critical state angle of friction was found to be lower for well graded aggregates than for uniform, small grained sands.

The results from this research confirm that the requirement of a sub-base to be both a stiff and permeable layer is too demanding. More use should be made of a free draining capping layer which would reduce the risk of frost heave occurring in the sub-base. This conclusion was also noted at the Symposium on Unbound Aggregates in Roads (1989).

No definite conclusion could be made on the frost susceptibility of demolition debris because further testing, as required by Roe and Webster (1984), could not be conducted at other laboratories. Crushed concrete was found to be frost susceptible. The data suggest that in most cases the frost heave results of recycled materials would fall in the inconclusive or the frost susceptible ranges. However, the self-cementing ability of recycled aggregates

may mean that the susceptibility of these materials to frost would decrease with time. Problems concerning frost susceptibility are also evident for many natural aggregates (Jones, 1989) and are not specific to recycled materials.

It can be concluded for the recycled aggregate concrete, examined in Chapter 7, that an increase in free water of 8% was too high to achieve a workability similar to that of natural aggregate concrete. There appeared to be little difference in the compressive strength and the Young's modulus of recycled aggregate concrete when compared to conventional concrete. The shrinkage and creep data presented in Chapter 7 suggest that a low water/cement ratio should be used in recycled aggregate concrete.

The use of mobile and stationary recycling plants was discussed in Chapter 8 and it was concluded that both would be useful, depending on the construction rubble produced during demolition and the quality of material required for reuse. The installation of a recycling plant is liable to cause objections from residents in its immediate vicinity but the environmental problems are likely to be no worse than those caused by the producers of crushed rock.

The possible uses of recycled material were also discussed in Chapter 8 where it was noted that recycled aggregate could be used as trench fill, pipe bedding, fill to structures, capping material, sub-base material and cement bound material in roads. The compliance tests for these uses are different but it is likely that recycled material could be made to conform by varying the grading, removing fines or by adding cement in some cases.

Less discrimination would exist against recycled aggregates if all aggregates were subjected to the same series of compliance tests. Some effort is required to help recycled aggregates gain the same respected status as natural aggregates and to ensure that all potential aggregates are treated fairly.

9.2 Suggestions for a standard on recycled materials in Britain

This research study was mainly involved with the physical properties of recycled materials and their ability to perform as construction aggregates. The investigation did not include a full examination of the contaminants in the materials. If a standard for use in Britain is produced, it is suggested that the contaminant levels listed in the Dutch standard, Centre Row (1988), should be used until further research has been conducted in Britain.

In the Specification for Highway Works (1986), compliance tests and limits for different uses of aggregate are listed. Recycled aggregate would be required to satisfy the requirements in this specification. It is suggested that a standard for recycled material should concentrate more on the sources from which construction rubble could be recycled, methods of production and quality control in the recycling process. Some recommendations might also be made on the placement of material on site to avoid segregation and to ensure the achievement of consistent density.

In the concluding remarks of the Symposium on Unbound Aggregates in Roads, compiled by Dawson and Jones (1989), it was stated that the classification of aggregates should be based on an internationally accepted set of tests. An international set of limits for these tests would not be possible due to mineral variation in different countries and climatic influences. Some countries would require frost heave specifications whereas others might need restrictions on the placement of wet aggregate in hot weather. The method of production and quality control of recycled materials could be quite similar internationally but the limits on contamination and rubble source might need to be altered due to the various aggregates and construction materials used in different countries.

Dawson and Jones (1989) concluded that testing of aggregates should take place at the location of aggregate production, on site during placement and that the final construction

should also be checked to ensure that the aggregate has achieved design expectations. This echoes the recommendations made earlier for recycled aggregate production. It was suggested that extensive testing should take place at recycling plants and that random testing should also be conducted at the locations where the aggregate is used.

The most effective approach to aggregate assessment would be a combination of laboratory and site testing. Ideally, testing on site should extend to a site trial which could be conducted on a small area before the road construction commenced, using materials and conditions similar to those expected to be employed in the main construction. If the Specification for Highway Works (1986) included the requirement of a site trial for sub-base material, it is likely that a rapidly gained respect would be achieved for recycled materials on the basis of their ability to self-cement with time. The inclusion of site trials would increase the cost of road construction. However, highway engineers have wished for some time to move more towards site testing (Symposium on Unbound Aggregates in Roads, 1989) because it is considered that the results of laboratory tests do not relate to the actual demands required of an aggregate on site.

9.3 Further research

During the course of this research it became clear that there was much scope for further research into, not only the properties of recycled aggregates, but also aggregates in general. In this section, the ideas for further work can be divided into two groups. First, the areas for possible research on aggregates are examined and secondly some ideas are presented for research which would be considered necessary for the rapid progression of recycled material to a respected status as aggregate for construction.

In Chapter 5, an analysis using Bolton's dilatancy index (1986) was conducted on data from shear box tests on limestone, demolition debris and crushed concrete. Values of Q (a

constant, depending on material type) were obtained from this analysis for the three aggregates. Bolton (1986) analysed tests on uniformly graded sands, for which he concluded that Q was 10. It was found in Chapter 5 that the Q value corresponding to each of the aggregates was greater than 10. This contradicts the conclusion made by Bolton (1986) that Q depends on mineralogy and compressibility and that Q for materials containing grains which are softer than quartz or felspar would be less than 10. The wet, well graded aggregates with particle sizes ranging from 37.5mm to less than 0.075mm were quite different to the small grained, uniform sands used by Bolton (1986) for his analysis. To confirm the findings of this research an intermediate step would be necessary i.e. the analysis of data from a series of tests on aggregates in a dry condition at various gradings so that the influence of particle grading on Q could be determined.

It would also be interesting to conduct a similar analysis on test data obtained from samples containing various maximum particle sizes to determine whether the ratio of the dimensions of the shear box to the maximum particle size affects Q . Another possible influence on Q may be the angularity of the particles. A further investigation could be carried out on rounded gravel and crushed rock particles to establish any dependency of Q on angularity.

In Chapter 6, a series of frost susceptibility tests was conducted on the limestone and recycled aggregates. An attempt was made to measure the influence of initial moisture content on the frost heave of the samples but the data for crushed concrete were the only results to show any definite trend. Calculations using these data suggested that the initial moisture content was not significant with respect to frost heave. However, the data were limited and it would be interesting to determine whether the initial moisture content of frost heave test specimens and of unbound road pavement layers affects the total frost heave exhibited. It may be easier to accomplish this when the design and construction of a new frost heave apparatus at Nottingham University have been completed (Baba, 1990). In this apparatus, it will be

possible to measure the frost heave, the penetration of frost heave and water intake of aggregate samples during a test. The water intake therefore could be related to frost heave. Instrumentation to measure thaw weakening is also under development at Nottingham University for use in the proposed frost heave apparatus (Baba, 1990).

Demolition debris should have been tested at two other laboratories to fulfil the requirements of Roe and Webster (1984) because its frost heave was found to be in the inconclusive range. However, the aggregates could only be tested at one laboratory due to financial restraints on the research contract. It would also be useful to confirm, by further testing, the high frost heave results measured on the saturated crushed concrete specimens.

Another possible research project would be the determination of the effect of impurities on frost susceptibility. This could be accomplished by conducting frost heave tests on samples of demolition debris or crushed concrete containing varying quantities of brick, gypsum, soil and wood. The effect of these contaminants on the plasticity, shear strength, CBR and compaction of recycled aggregates would be another interesting research subject. Several investigations have been conducted on the effect of contamination in recycled aggregate for use as aggregate in concrete (Hansen, 1985) but very little has been reported on the contamination of recycled aggregate for sub-base.

It was suggested by Croney and Jacobs (1967) that stabilisation of an aggregate by the addition of cement helps to improve its resistance to frost heave. Further research could be conducted on stabilised samples of recycled aggregate to determine the quantity of cement needed to reduce the frost heave to less than 9mm. Sweere (1989) noted the ability of recycled aggregate to self-cement after some time under load. It would be interesting to determine whether this ability would also reduce frost heave. Cores of material would need to be extracted from a sub-base layer, which had undergone 2-3 months traffic loading or

some form of accelerated loading, to evaluate the influence of this binding effect.

One final suggestion for further research on frost heave would be a study of the heave of aggregate obtained from crushing lean concrete and structural concrete to determine the effect of mortar in the aggregate on frost heave. The higher cement content in structural concrete might be sufficient to stabilise recycled aggregate made from it and therefore reduce frost heave.

The work in this research consisted of an examination of the physical properties of recycled aggregate without a chemical analysis. It appears that the next step should be an examination of the chemical properties. The quantity of sulphates, chlorides and other contaminants such as alkali-silica reacted concrete in the material would need to be known, particularly if it was to be placed near reinforcement.

The CBR test which was conducted on the aggregates is considered to be a crude stiffness test at large strains. It would be interesting to measure the elastic stiffness of compacted recycled materials. Sweere and Galjaard (1989) stated that stiffness is more important than shear strength in a sub-base layer because when the stiffness is increased the tensile strains in the asphalt layer become smaller. Consequently the life expectancy of the road pavement is increased (Sweere, 1989). A repeated load triaxial test has been developed at Delft University (Sweere, Penning and Vos, 1987) and another has been constructed at Nottingham University (Brown, O'Reilly and Pappin, 1989) to test the stiffness of aggregates for use in the unbound layers of road pavements. This test involves cycling the confining and deviator stresses, on a sample of 300mm in height and 150mm in diameter, to represent approximately the effects of repeated loading in a road pavement. For elastic behaviour, the results from the triaxial apparatus were found to be representative of those obtained in the field (Brown, O'Reilly and Pappin, 1989).

It would be interesting to conduct this triaxial test on the recycled materials used in this research to compare their performance with results of similar tests on limestone. Sweere, Penning and Vos (1987) conducted triaxial tests on recycled aggregate and found that the resilient modulus compared well with that of a conventional aggregate. Due to the complexity of the instrumentation and set up of the triaxial test, Sweere, Penning and Vos (1987) concluded that the test could not be used for routine testing of aggregates.

REFERENCES

- Aides to the Secretary of State for the Environment (1989)* - personal communication.
- ASTM (1982)* Standard specification for concrete aggregates, C33-82. American Society for Testing and Materials.
- Baba, H.U. (1990)* Influence of constituents and stress history on freeze-thaw behaviour of soils. Summary of proposed research. First BGS Young Geotechnical Engineers' Symposium. University of Sheffield.
- Biczysko, S.J. (1985)* Permeable sub-bases in highway pavement construction. Proc. 2nd Symposium on Unbound Aggregates in Roads (UNBAR 2). University of Nottingham.
- Biczysko, S.J. (1989)* Specifications and standards for unbound aggregates in roads and their use in the U.K. Proc. 3rd Symposium on Unbound Aggregates in Roads (UNBAR 3). University of Nottingham.
- Black, W.P.M. (1961)* Calculations of laboratory and in situ values of CBR from bearing capacity data. *Géotechnique*, 11: 1: 14-21.
- Boesman, B. (1985)* Crushing and separating techniques for demolition material. EDA (European Demolition Association)/RILEM Conference on Demo-Recycling. (Rotterdam) Part 2. Reuse of concrete and brick materials.
- Bolton, M.D. (1986)* The strength and dilatancy of sands. *Géotechnique*, 36: 1: 65-78.
- Bowles, J.E. (1984)* Physical and Geotechnical Properties of Soils. McGraw-Hill.
- Brady, K.C. (1989)* - personal communication
- Brady, K.C., Awcock, I. and Wightman, N.R. (1983)* A comparison of shear strength measurements using two sizes of shear box. LR 1105. Transport and Road Research Laboratory.
- BRE (1980)* Deterioration due to corrosion in reinforced concrete. Information paper 1P12/80. British Research Establishment.
- BRE (1982)* The durability of steel in concrete. BRE Digest 263. Part 1. Mechanism of protection and corrosion. British Research Establishment.
- British Standard 812: Methods for sampling and testing of mineral aggregates, sands and fillers.*
- Part 2 (1975)* Methods for determination of physical properties.
- Part 3 (1975)* Methods for determination of mechanical properties.
- Part 102 (1985)* Methods for determination of particle size distribution. British Standard Institution. London.
- British Standard 882 (1983)* Specification for aggregates from natural sources for concrete. British Standard Institution. London.
- British Standard 1377 (1975)* Methods of test for soils for civil engineering purposes. British Standard Institution. London.

- British Standard 1881 (1983)** Testing concrete.
Part 102 Method for determination of slump.
Part 116 Method for determination of compressive strength of concrete cubes.
Part 121 Method for determination of the static modulus of elasticity in compression.
 British Standard Institution. London.
- British Standard 5835 (1980)** Compactibility test for graded aggregates. Part 1. British Standard Institution. London.
- British Standard 5930 (1981)** Code of practice for site investigations. British Standard Institution. London.
- British Standard 6543 (1985)** The use of industrial by-products and waste materials in building and civil engineering. British Standard Institution. London.
- Brown, S.F. (1985)** Structural role of the granular layer. Proc. 2nd Symposium on Unbound Aggregates in Roads (UNBAR 2). University of Nottingham.
- Brown, S.F., O'Reilly, M.P. and Pappin, J.W. (1989)** A repeated load triaxial apparatus for granular materials. Proc. 3rd Symposium on Unbound Aggregates in Roads (UNBAR 3). University of Nottingham.
- Buck, A.D. (1976)** Recycled Concrete. The Military Engineer. Vol. 68. No. 442. pp 99. U.S.A. March/April.
- Building Contractors Society of Japan (1981)** Proposed standard for the use of recycled aggregate and recycled aggregate concrete. Committee on disposal and reuse of construction waste (in English).
- Burns, J. (1977)** The effect of water table on the frost susceptibility of a road making material. SR305. Transport and Road Research Laboratory.
- Centre Row (1988)** Stichting centrum voor regelgeving en onderzoek in de grond-, water- en wegenbouw en de verkeer techniek. Resten zijn geen afval (meer). Publikatie 12.
- Cobbe, M.I. and Threadgold, L. (1988)** Compaction control by the moisture condition test - a new approach. Journal of the Institution of Highways and Transportation. December.
- Collis, L. and Fox, R.A. (1985)** Aggregates: Sand, Gravel and Crushed Rock Aggregates for Construction Purposes. Engineering Geology Special Publication No. 1. Geological Society.
- Cornforth, D.H. (1973)** Prediction of drained strength of sands from relative density measurements in evaluation of relative density and its role in geotechnical projects involving cohesionless soils. American Society for Testing and Materials. Spec. Tech. Publ. 523, 281-303.
- Croney, D. and Jacobs, J.C. (1967)** The frost susceptibility of soils and road materials. LR90. Transport and Road Research Laboratory.
- Crushing Converts Rubble into Sub-base Aggregate (1971)** Roads and Streets. May. U.S.A.
- CUR (1986)** Betonpuingranulaat en metselwerk puingranulaat als toeslagmateriaal voor beton. Civieltechnisch centrum uitvoering research en regelgeving. Rapport 125.

Danish Concrete Association (1989) Recommendation for the use of recycled aggregates in concrete of passive environmental class. Publication No.34.

Dawson, A.R. and Jones, R.H. (1989) Conclusions and recommendations for the use of unbound aggregates in roads. Proc. 3rd Symposium on Unbound Aggregates in Roads (UNBAR 3). University of Nottingham.

DIN 4226 (1983) Zuschlag für Beton. Ausgabe 04 (in German).

DoE (1989) Mineral Planning Guidance. MPG6: Guidelines for aggregates provision in England and Wales. Department of the Environment. Welsh Office. HMSO.

DoE (1970) Road Note 29. A guide to the structural design of pavements for new roads. Department of the Environment. HMSO.

Dunn, C.S. (1966) The stability of aggregates used in road sub-bases. Roads and Road Construction. 44 (519). 77-81.

Dyer, M.R. (1985) Observation of the stress distribution in crushed glass with applications to soil reinforcement. D.Phil. Thesis. University of Oxford.

Earland, M.G. and Pike, D.C. (1985) Stability of gravel sub-bases. RR64. Transport and Road Research Laboratory.

Edens Project: Showcase for Recycling (1980) Rural and Urban Roads. 18.3. 34-35. March. U.S.A.

Edgington, J. (1969) Drawings of equipment prepared for the Department of Civil Engineering, University of Surrey.

Environmental Resources Ltd. (1980) Demolition waste. A report for the Commission of the European Communities. The Construction Press.

Fitzpatrick & Sons Ltd. (1989) - personal communication

Foster Yeoman Ltd. (1989) - personal communication

Frondistou-Yannas, S. (1977) Waste concrete as aggregate for new concrete. Journal of the American Concrete Institute. August. U.S.A.

Fujii, T. (1988) Strength and drying shrinkage behaviour of concrete using concrete crushed aggregate. Proc. 2nd International RILEM Symposium. Demolition and Reuse of Concrete and Masonry. Vol.2. Reuse of demolition waste. Japan.

Gaede, K. (1957) Dt aussch stahlbeton. 126, 1957.

Gorle, D. and Saeys, L. (1988) Reuse of crushed concrete as a road base material. Proc. 2nd International RILEM Symposium. Demolition and Reuse of Concrete and Masonry. Vol.2. Reuse of demolition waste. Japan.

Graf, O. (1973) Crushed brick concrete, sandstone concrete and rubble concrete. U.S. Army Engineer. Translation No. 73-1. Waterways Experimental Station, CE, Mississippi.

Griffiths-McGee Demolition Co. Ltd. (1988) - personal communication.

Hansen, T.C. (1985) Recycled aggregates and recycled aggregate concrete, 2nd state-of-the-art report developments 1945-1985. RILEM Technical Committee - 37 - DRC.

Hansen, T.C. and Marga, M. (1988) Strength of recycled concrete made from coarse and fine recycled concrete aggregates. Proc. 2nd International RILEM Symposium. Demolition and Reuse of Concrete and Masonry. Vol.2. Reuse of demolition waste. Japan.

Hansen, T.C. and Narud, H. (1983) Strength of recycled concrete made from crushed concrete coarse aggregate. Concrete International Design and Construction. Vol. 5, No.1. January.

Head, K.H. (1980) Manual of Soil Laboratory Testing. Vol.1. Soil classification and compaction tests. Pentech Press. London.

Head, K.H. (1982) Manual of Soil Laboratory Testing. Vol.2. Permeability, shear strength and compressibility. Pentech Press. London.

Helmuth, R.A. and Turk, D.H. (1967) The reversible and irreversible drying shrinkage of hardened portland cement. Journal Res. Dev. Labs. Portland Cement Association. Vol.9. No.2. 8-21.

Hill, J. (1985) Relevance and interpretation of laboratory tests. Proc. 2nd Symposium on Unbound Aggregates in Roads (UNBAR 2). University of Nottingham.

Hughes and Salvidge Ltd. (1988) - personal communication.

Hughes and Salvidge Ltd. (1989) - personal communication.

Ikeda, T., Yamane, S. and Sakamoto, A. (1988) Strengths of concrete containing recycled concrete aggregate. Proc. 2nd International RILEM Symposium. Demolition and Reuse of Concrete and Masonry. Vol.2. Reuse of demolition waste. Japan.

Jacobsen, J.B., Elle, M. and Lauritzen, E.K. (1988) On-site use of regenerated demolition debris. Proc. 2nd International RILEM Symposium. Demolition and Reuse of Concrete and Masonry. Vol.2. Reuse of demolition waste. Japan.

Japan Road Association (1984) Technical guideline for recycling and utilizing waste pavement materials.

Jewell, R.A. (1980) Some effects of reinforcement on the mechanical behaviour of soils. Ph.D. Thesis. University of Cambridge.

Jewell, R.A. (1989) Direct shear tests in sand. Géotechnique, 39: 2: 309-322.

Jones, R.H. (1985) Prevention of frost heave damage. Proc. 2nd Symposium on Unbound Aggregates in Roads (UNBAR 2). University of Nottingham.

Jones, R.H. (1989) - personal communication.

Jones, R.H. and Hurt, K.G. (1980) The prediction of the frost susceptibility of limestone and sub-base materials. The Highway Engineer. January.

Jones, R.H. and Jones, H.A. (1989) Granular layers in pavement foundations. Proc. 3rd Symposium on Unbound Aggregates in Roads (UNBAR 3). University of Nottingham.

Kakizaki, M., Harada, M., Soshiroda, T., Kubota, S., Ikeda, T. and Kasai, Y. (1988) Manufacturing of recovered aggregate through disposal and recovery of demolished concrete structures. Proc. 2nd International RILEM Symposium. Demolition and Reuse of Concrete and Masonry. Vol.2. Reuse of demolition waste. Japan.

Kango Tools Ltd. (1989) - personal communication

Kasai, Y. (1985) Studies into the reuse of demolished concrete in Japan. EDA (European Demolition Association)/RILEM Conference on Demo-Recycling. (Rotterdam) Part 2. Reuse of concrete and brick materials.

Kashino, N. and Takahashi, Y. (1988) Experimental studies on placement of recycled aggregate concrete. Proc. 2nd International RILEM Symposium. Demolition and Reuse of Concrete and Masonry. Vol.2. Reuse of demolition waste. Japan.

Kawamura, M. and Torii, K. (1988) Reuse of recycled concrete aggregate for pavement. Proc. 2nd International RILEM Symposium. Demolition and Reuse of Concrete and Masonry. Vol.2. Reuse of demolition waste. Japan.

Kemi, T. and Nakagawa, M. (1978) Study on recycled aggregates and recycled aggregate concrete. Building Contractors Society Concrete Journal. Vol.16. No.7. 18-31. Committee for the disposal and the recycling of construction waste. Japan.

Kennedy, J. and Clark, A.J. (1986) Reconstruction trials for East Sussex County Council employing mix-in-place recycling with cement and glass-fibre reinforced surface dressing. Cement and Concrete Association. Technical Report 565.

Lambe, T.W. and Whitman, R.V. (1979) Soil Mechanics (SI version). Wiley. New York.

Lea, F.M. (1970) The Chemistry of Cement and Concrete. Edmund Arnold. London.

Lee, I.K., White, W. and Ingles, O.G. (1983) Geotechnical Engineering. Pitman. London.

Lindsell, P. and Mulheron, M. (1985) Recycling of demolition debris. A report for the Institute of Demolition Engineers.

Marek, C.R. (1972) Promising replacements for conventional aggregates for highway use. Nat. Coop. Hwy. Res. Prog. Report 135. Transportation Research Board. Washington D.C.

Mather, B. (1980) Crushed concrete as concrete aggregate. Adhesion problems in the recycling of concrete. NATO Conference series. Series VI. Materials Science. Vol.4.

Mayhew, H.C. (1985) Proc. of the 2nd Symposium on Unbound Aggregates in Roads (UNBAR 2). Discussion. University of Nottingham.

Meyerhof, G.G. (1951) The ultimate bearing capacity of foundations. Géotechnique, 2: 4: 301-332.

Miller, R.H. and Collins, R.J. (1976) Waste materials as potential replacements for highway aggregates. Nat. Coop. Hwy. Res. Prog. Report 166. Transportation Research Board. Washington D.C.

Morlion, D., Venstermans, J. and Vyncke, J. (1988) Demolition waste of the Zandvliet lock as aggregate for concrete. Proc. 2nd International RILEM Symposium. Demolition and Reuse of Concrete and Masonry. Vol.2. Reuse of demolition waste. Japan.

Mukai, T. and Kikuchi, M. (1988) Properties of reinforced concrete beams containing recycled aggregate. Proc. 2nd International RILEM Symposium. Demolition and Reuse of Concrete and Masonry. Vol.2. Reuse of demolition waste. Japan.

Mulheron, M. (1986) A preliminary study of recycled aggregates. A report for the Institute of Demolition Engineers.

Mulheron, M. (1988) The recycling of demolition debris: current practice, products and standards in the U.K. Proc. 2nd International RILEM Symposium. Demolition and Reuse of Concrete and Masonry. Vol.2. Reuse of demolition waste. Japan.

Mulheron, M. (1990) personal - communication

Mulheron, M. and O'Mahony, M.M. (1988) The durability of recycled aggregate and recycled aggregate concrete. Proc. 2nd International RILEM Symposium. Demolition and Reuse of Concrete and Masonry. Vol.2. Reuse of demolition waste. Japan.

Naish, M.G. (1988) A cost survey of backfill around bridge abutments and retaining walls in South East England. CR112. Transport and Road Research Laboratory.

Neville, A.M. (1973) Properties of Concrete. Pitman. London.

New Civil Engineer (1989) Stone prices set to rise as supplies dwindle. Magazine of the Institution of Civil Engineers. 26th January.

Nishibayashi, S. and Yamura, K. (1988) Mechanical properties and durability of concrete from recycled coarse aggregate prepared by crushing concrete. Proc. 2nd International RILEM Symposium. Demolition and Reuse of Concrete and Masonry. Vol.2. Reuse of demolition waste. Japan.

Nixon, P.J. (1978) Recycled concrete as an aggregate for concrete - a review. 1st state-of-the-art report RILEM Technical Committee -37-DRC. Materials and structures (RILEM). No. 65. Sept/Oct 371-378.

Palmeira, E.M. (1987) The study of soil-reinforcement interaction by means of large scale laboratory tests. D.Phil. Thesis. University of Oxford.

Penning, A. (1989) Specifications for materials used as an unbound aggregate. Proc. 3rd Symposium on Unbound Aggregates in Roads (UNBAR 3). University of Nottingham.

Pike, D.C. and Acott, S.M. (1975) A vibrating hammer test for compactibility of aggregates. SR 140 UC. Transport and Road Research Laboratory.

Ravindrarah, R. (1985) Properties of concrete made with crushed concrete as coarse aggregate. National University of Singapore.

Rijkwaterstaat (1978) Eisen 1978 voor bouwstoffen in de wegenbouw, Staatsuitgeverij 's-Gravenhage.

Roe, P.G. and Webster, D.C. (1984) Specification for the TRRL frost-heave test. SR829. Transport and Road Research Laboratory.

- Rowe, P.W. (1969)** The relation between the shear strength of sands in triaxial compression, plane strain and direct shear. *Géotechnique* 19: 1: 75-86.
- Sadler, T.B. (1973)** A crushing success: aggregate from concrete. *Public Works*. April. U.S.A.
- Schulz, R.R. (1988)** Concrete with recycled rubble - developments in West Germany. Proc. 2nd International RILEM Symposium. Demolition and Reuse of Concrete and Masonry. Vol.2. Reuse of demolition waste. Japan.
- Sherwood, P.T. and Roeder, A.R. (1965)** Organic impurities in sand that interfere with the hydration of portland cement. *The Surveyor and Municipal Engineer*. July.
- Somerset County Council (1989)** Contract details of the M5 motorway reconstruction using permeable sub-base.
- Specification for Highway Works (1986)** Department of Transport. HMSO.
- Straube, E., Beckedahl, H. and Gerlach, A. (1989)** Design of pavement thicknesses incorporating alternative granular materials. Proc. 3rd Symposium on Unbound Aggregates in Roads (UNBAR 3). University of Nottingham.
- Stroud, M.A. (1971)** The behaviour of sand at low stress levels in the simple shear apparatus. Ph.D. Thesis. University of Cambridge.
- Suss, G.H. (1989)** Natural and waste material - a chance for competition. Proc. 3rd Symposium on Unbound Aggregates in Roads (UNBAR 3). University of Nottingham.
- Sweere, G.T.H. (1989)** Structural contribution of self-cementing granular bases to asphalt pavements. Proc. 3rd Symposium on Unbound Aggregates in Roads (UNBAR 3). University of Nottingham.
- Sweere, G.T.H. and Galjaard, P.J. (1989)** In situ determination of granular basecourse stiffness. Proc. 3rd Symposium on Unbound Aggregates in Roads (UNBAR 3). University of Nottingham.
- Sweere, G.T.H., Penning, A. and Vos, E. (1987)** Development of a structural design procedure for asphalt pavements with crushed rubble sub-bases. Proc. 6th International Conference for Structural Design of Asphalt Pavements. Vol. 1. Ann Arbor. U.S.A.
- Symposium on Unbound Aggregates in Roads (UNBAR 3) (1989)** Discussion. University of Nottingham.
- Taylor, D.W. (1948)** Fundamentals of Soil Mechanics. Wiley. New York.
- Terzaghi, K. (1943)** Theoretical Soil Mechanics. Wiley. New York.
- Teychenné, D.C., Franklin, R.E. and Erntroy, H.C. (1982)** Design of normal concrete mixes. Department of the Environment. HMSO.
- TRRL (1981)** MM64. Specification for the TRRL frost heave test. Transport and Road Research Laboratory.
- TRRL (1977)** SR318. The LR90 frost heave test - interim specification for use with granular materials. Transport and Road Research Laboratory.

Verney Report (1976) Aggregates: the way ahead. HMSO (ISBN 0 11 759175)

Vesic, A.S. (1975) Bearing capacity of shallow foundations. Foundation Engineering Handbook. Edited by Winterkorn, H.F. and Fang, H.Y. Van Nostrand Reinhold. New York.

Yamato, T., Emoto, Y., Soeda, M. and Sakamoto, Y. (1988) Some properties of recycled aggregate concrete. Proc. 2nd International RILEM Symposium. Demolition and Reuse of Concrete and Masonry. Vol.2. Reuse of demolition waste. Japan.

Yoda, K., Yoshikane, T., Nakashima, Y. and Soshiroda, T. (1988) Recycled cement and recycled concrete in Japan. Proc. 2nd International RILEM Symposium. Demolition and Reuse of Concrete and Masonry. Vol.2. Reuse of demolition waste. Japan.

Yoshikane, T. (1988) The instances of concrete recycled for base course material in Japan. Proc. 2nd International RILEM Symposium. Demolition and Reuse of Concrete and Masonry. Vol.2. Reuse of demolition waste. Japan.