

केंद्रीय पेट्रोसायन अभियांत्रिकी एवं  
प्रौद्योगिकी संस्थान (सिपेट)

(पूर्व में सेंट्रल इंस्टिट्यूट ऑफ प्लास्टिक्स इंजीनियरिंग एण्ड टेक्नोलॉजी)  
इंस्टिट्यूट ऑफ पेट्रोकेमिकल्स टेक्नोलॉजी (आई.पी.टी.)  
रसायन एवं पेट्रोसायन विभाग  
रसायन एवं उर्वरक मंत्रालय, भारत सरकार  
एच. आई. एल. कॉलोनी, एडयार रोड, पातालम्  
उद्योगमंडल पी.ओ. कोच्चि, केरल - 683 501  
फोन : 0484-2547741, 2546740  
ई-मेल: kochi@cipet.gov.in, cipetkochi@gmail.com  
वेबसाइट : www.cipet.gov.in



सिपेट CIPET

परीक्षण रिपोर्ट

TEST REPORT

**CENTRAL INSTITUTE OF PETROCHEMICALS  
ENGINEERING & TECHNOLOGY (CIPET)**  
(Formerly Central Institute of Plastics Engineering & Technology)  
**INSTITUTE OF PETROCHEMICALS TECHNOLOGY (IPT)**  
Department of Chemicals & Petrochemicals  
Ministry of Chemicals & Fertilizers, Govt. of India  
HIL Colony, Edayar Road, Pathalam  
Udyogamandal P.O., Kochi, Kerala-683 501  
Ph: 0484-2546740  
E-mail:kochi@cipet.gov.in, cipetkochi@gmail.com  
Web : www.cipet.gov.in

क्र.सं. / SI.No. **12619**

**ANALYSIS REPORT**

Issued to:

**M/s. WRAP INDIA POLYMERS Private Limited**  
**Plot No. 18, Sector - 8, IMT Manesar,**  
**Gurgaon – 122 050.**

Page 1 of 4

**Test Report No : 241072**

**Date: 06.02.2025**

**Customer Ref. No. & date : Letter dt 17.06.2024**

**Work order Ref.No. : 199/24-25**

**As per Standard: : As per part C**

**PART A: PARTICULARS OF SAMPLE SUBMITTED**

- a) Name of the sample : Compostable Film as stated by the party  
b) Grade / Variety / type / Size / Class etc. : Nil  
c) Code No. : Nil  
d) Quantity (pcs/mtr/gm/nos) : 4 Kg  
e) Mode of Packing : Sealed carton  
(Sealed cartoon/polypouch/container or not)  
f) Date of receipt of sample : 24.06.2024  
g) Date of Performance of test : 05.07.2024 - 04.02.2025  
h) Any other information : Interim Report No. 24812 dt. 14.11.2024  
i) Unique Sample ID : 240684

**PART B: SUPPLEMENTARY INFORMATION**

- a) Reference to sampling procedure : Drawn & Supplied by the party  
b) Supporting documents for measurements taken and results : As per part -C  
derived like graphs, tables, sketches and / or Photographs as  
appropriate to test report, if any ( to be attached )  
c) Deviation from the test methods as prescribed in relevant : ---  
ASTM/ISO/BIS / Work instructions, if any

**Dr. S. Anbudayanidhi**  
**Manager (Technical)**  
**Authorized Signatory**

**Dr. K.A. Rajesh**  
**Director & Head**  
**Authorized Signatory**

केंद्रीय पेट्रोरसायन अभियांत्रिकी एवं  
प्रौद्योगिकी संस्थान (सिपेट)

(पूर्व में सेन्ट्रल इंस्टिट्यूट ऑफ प्लास्टिक्स इंजीनियरिंग एण्ड टेक्नोलॉजी)

इंस्टिट्यूट ऑफ पेट्रोकेमिकल्स टेक्नोलॉजी (आई.पी.टी.)

रसायन एवं पेट्रोरसायन विभाग

रसायन एवं उर्वरक मंत्रालय, भारत सरकार

एच. आई.एल. कॉलोनी, एडयार रोड, पातालम्

उद्योगमंडल पी.ओ. कोच्चि, केरल - 683 501

फोन : 0484-2547741, 2546740

ई-मेल: kochi@cipet.gov.in, cipetkochi@gmail.com

वेबसाइट : www.cipet.gov.in



सिपेट CIPET

परीक्षण रिपोर्ट

TEST REPORT

CENTRAL INSTITUTE OF PETROCHEMICALS  
ENGINEERING & TECHNOLOGY (CIPET)

(Formerly Central Institute of Plastics Engineering & Technology)

INSTITUTE OF PETROCHEMICALS TECHNOLOGY (IPT)

Department of Chemicals & Petrochemicals

Ministry of Chemicals & Fertilizers, Govt. of India

HIL Colony, Edayar Road, Pathalam

Udyogamandal P.O., Kochi, Kerala-683 501

Ph: 0484-2546740

E-mail:kochi@cipet.gov.in, cipetkochi@gmail.com

Web : www.cipet.gov.in

क्र.सं. / Sl.No. 12619

ANALYSIS REPORT

Page 2 of 4


PART C: TEST RESULTS

Report No.:241072

Date: 06.02.2025

Sl. No	Name of the test	Test Method/ Standard	Unit	Results Obtained	Specified Requirement as per ISO : 17088-2021
Sample details: Compostable Film as stated by the party					
1.	Material Identification	FTIR/DSC	--	Poly(lactic Acid) (PLA) and Poly(butylene adipate - co- terephthalate) (PBAT)	--
2.	Disintegration (Dry mass remains in 2mm sieve after 84 days)	ISO 20200:2023	%	8.10	Not more than 10% of its original dry mass
3.	Ultimate aerobic biodegradation (with reference to 100% degradation of positive reference)	ISO 14855-1:2012	%	91.58 (at the end of 127 days)	> 90% (At the end of the test period not more than 180 days)
4.	Plant Growth study Monocotyledon(Paddy) % Seed emergence  Dicotyledon(Tomato) % Seed emergence	OECD : 208 Guidelines	%  %	93  92	> 90% of those from the corresponding blank compost

Note: The detailed observation on biodegradability test is enclosed as Annexure. I

  
Dr. S. Anbudayanidhi  
Manager (Technical)  
Authorized Signatory

  
Dr. K.A. Rajesh  
Director & Head  
Authorized Signatory

केंद्रीय पेट्रोसायन अभियांत्रिकी  
एवं प्रौद्योगिकी संस्थान (सिपेट)

(पूर्व में सेंट्रल इंस्टिट्यूट ऑफ प्लास्टिक्स इंजीनियरिंग एण्ड टेक्नोलॉजी)

इंस्टिट्यूट ऑफ पेट्रोसायन टेक्नोलॉजी (आई.पी.टी.)

रसायन एवं पेट्रोसायन विभाग

रसायन एवं उर्वरक मंत्रालय, भारत सरकार

एच.आई.एल.कॉलनी, एडयार रोड, पातालम्

उद्योगमंडल पी.ओ., कोच्चि, केरल - 683 501

फोन : 0484-2547741, 2546740

ई-मेल : kochi@cipet.gov.in, cipetkochi@gmail.com

वेबसाईट : www.cipet.gov.in



CENTRAL INSTITUTE OF PETROCHEMICALS  
ENGINEERING & TECHNOLOGY (CIPET)

(Formerly Central Institute of Plastics Engineering & Technology)

INSTITUTE OF PETROCHEMICALS TECHNOLOGY (IPT)

Department of Chemicals & Petrochemicals

Ministry of Chemicals & Fertilizers, Govt. of India

HIL Colony, Edayar Road, Pathalam

Udyogamandal P.O., Kochi, Kerala - 683 501

Ph: 0484-2547741, 2546740

E-mail:kochi@cipet.gov.in, cipetkochi@gmail.com

Web : www.cipet.gov.in

Continuation Sheet

ANALYSIS REPORT


Page 3 of 4


PART C: TEST RESULTS

Report No.:241072

Date: 06.02.2025

Sl. No	Name of the test	Test Method/ Standard	Unit	Results Obtained	Specified Requirement as per ISO : 17088-2021
5.	Acute Ecotoxic Effects to earthworm				
a.	Survival of adult earthworm at the end of 7 days	ISO 11268-1:2012	%	100	> 90% of those from the corresponding blank compost
b.	Survival of adult earthworm at the end of 14 days		%	100	
c.	Biomass at the end of 14 days		%	92.40	
6	Chronic Ecotoxic Effects to earthworm				
a.	Survival of adults earthworm at the end of 28 days	ISO 11268-2:2023	%	96.87	> 90% of those from the corresponding blank compost
b.	Offspring at the end of 56 days		%	93.6	
c.	Biomass at the end of 56 days		%	91.64	

  
Dr. S. Anbudayanidhi  
Manager (Technical)  
Authorized Signatory

  
Dr. K.A. Rajesh  
Director & Head  
Authorized Signatory

केंद्रीय पेट्रोरसायन अभियांत्रिकी  
एवं प्रौद्योगिकी संस्थान (सिपेट)

(पूर्व में सेंट्रल इंस्टिट्यूट ऑफ प्लास्टिक्स इंजीनियरिंग एण्ड टेक्नोलॉजी)

इंस्टिट्यूट ऑफ पेट्रोरसायन टेक्नोलॉजी (आई.पी.टी.)

रसायन एवं पेट्रोरसायन विभाग

रसायन एवं उर्वरक मंत्रालय, भारत सरकार

एच.आई.एल.कॉलनी, एडयार रोड, पातालम्

उद्योगमंडल पी.ओ., कोच्चि, केरल - 683 501

फोन : 0484-2547741, 2546740

ई-मेल : kochi@cipet.gov.in, cipetkochi@gmail.com

वेबसाईट : www.cipet.gov.in



सिपेट CIPET

CENTRAL INSTITUTE OF PETROCHEMICALS  
ENGINEERING & TECHNOLOGY (CIPET)

(Formerly Central Institute of Plastics Engineering & Technology)

INSTITUTE OF PETROCHEMICALS TECHNOLOGY (IPT)

Department of Chemicals & Petrochemicals

Ministry of Chemicals & Fertilizers, Govt. of India

HIL Colony, Edayar Road, Pathalam

Udyogamandal P.O., Kochi, Kerala - 683 501

Ph: 0484-2547741, 2546740

E-mail:kochi@cipet.gov.in, cipetkochi@gmail.com

Web : www.cipet.gov.in

Continuation Sheet

ANALYSIS REPORT

Page 4 of 4

PART C: TEST RESULTS

Report No.: 241072


Date: 06.02.2025


Sl. No.	Property	Test method / Standard	Unit	Results obtained	Specified Requirements (Max.) as per IS 17899 T:2022
7.	<u>Heavy Metal Analysis</u> (on dry mass basis)				
	Arsenic (As)	IS 3025 (Part 37):2022	mg / kg	0.0244	10
	Copper (Cu)	IS 3025 (Part 42):1992		0.8045	300
	Nickel (Ni)	IS 3025 (Part 54):2003		0.8744	50
	Zinc (Zn)	IS 3025 (Part 49):1994		0.3993	1000
	Chromium (Cr)	IS 3025 (Part 52):2003		0.5234	50
	Mercury (Hg)	IS 3025 (Part 48):1994		0.0175	0.15
	Cadmium(Cd)	IS 3025 (Part 41):2023		0.3535	5
	Lead (Pb)	IS 3025 (Part 47):1994		0.8983	100

PART D: REMARKS: NIL

Note

1. This Test Report / Certificate is issued only for the samples submitted to the laboratory.
2. The results stated above related only to the items tested.
3. The quality of the subsequent production lot has to be ensured by the purchaser.
4. This Test Report shall not be reproduced except in full without the written approval of the laboratory.
5. Any anomaly/discrepancy in this report should be brought to the notice of the laboratory within 30 days from the date of issue.
6. Subcontracted Tests (if any): Nil

  
Dr. S. Anbudayanidhi  
Manager (Technical)  
Authorized Signatory

  
Dr. K.A. Rajesh  
Director & Head  
Authorized Signatory

केंद्रीय पेट्रोरसायन अभियांत्रिकी  
एवं प्रौद्योगिकी संस्थान (सिपेट)

(पूर्व में सेंट्रल इंस्टिट्यूट ऑफ प्लास्टिक्स इंजीनियरिंग एण्ड टेक्नोलॉजी)

इंस्टिट्यूट ऑफ पेट्रोरसायन टेक्नोलॉजी (आई.पी.टी.)

रसायन एवं पेट्रोरसायन विभाग

रसायन एवं उर्वरक मंत्रालय, भारत सरकार

एच.आई.एल.कॉलनी, एडयार रोड, पातालम्

उद्योगमंडल पी.ओ., कोच्चि, केरल - 683 501

फोन : 0484-2547741, 2546740

ई-मेल : kochi@cipet.gov.in, cipetkochi@gmail.com

वेबसाईट : www.cipet.gov.in



सिपेट CIPET

CENTRAL INSTITUTE OF PETROCHEMICALS  
ENGINEERING & TECHNOLOGY (CIPET)

(Formerly Central Institute of Plastics Engineering & Technology)

INSTITUTE OF PETROCHEMICALS TECHNOLOGY (IPT)

Department of Chemicals & Petrochemicals

Ministry of Chemicals & Fertilizers, Govt. of India

HIL Colony, Edayar Road, Pathalam

Udyogamandal P.O., Kochi, Kerala - 683 501

Ph: 0484-2547741, 2546740

E-mail: kochi@cipet.gov.in, cipetkochi@gmail.com

Web : www.cipet.gov.in

Continuation Sheet

ANNEXURE-I

Page 1 of 6

TR. NO.: 241072

ANALYSIS RESULT

Date: 06.02.2025

OBSERVATION FOR BIODEGRADABILITY TEST AS PER ISO 17088:2021

**Name of the Customer:**

**M/s. WRAP INDIA POLYMERS Private Limited**  
**Plot No. 18, Sector - 8, IMT Manesar,**  
**Gurgaon - 122050**

**1. Sample Details:** Compostable Film as stated by the party.


The average thickness of film sample was observed as 57 microns.


**2. Material Identification by FTIR & DSC:** Poly (lactic acid) (PLA) and  
Poly (butylene Adipate - co- Terephthalate) (PBAT)

**3. Observations:**

a. Conditions of reaction Mixture

Origin of Compost	: Livestock excrement, municipal and vegetable waste
Reaction Temperature	: 58°C (±2°C)
Dry Solid (%)	: 53.93 %
Volatile content (%)	: 33.33%
CO <sub>2</sub> evolved during 1 <sup>st</sup> 10 days in blank vessels	: 54.02 mg/g of volatile solids of compost
Test Duration (Days)	: 127 Days
Reference material	: Cellulose
Volume of reaction Vessel	: 3000ml

  
**Dr. S. Anbudayanidhi**  
**Manager (Technical)**  
**Authorized Signatory**

  
**Dr. K.A. Rajesh**  
**Director & Head**  
**Authorized Signatory**

केंद्रीय पेट्रोसायन अभियांत्रिकी  
एवं प्रौद्योगिकी संस्थान (सिपेट)

(पूर्व में सेंट्रल इंस्टिट्यूट ऑफ प्लास्टिक्स इंजीनियरिंग एण्ड टेक्नोलॉजी)

इंस्टिट्यूट ऑफ पेट्रोसायन टेक्नोलॉजी (आई.पी.टी.)

रसायन एवं पेट्रोसायन विभाग

रसायन एवं उर्वरक मंत्रालय, भारत सरकार

एच.आई.एल.कॉलनी, एडयार रोड, पातालम्

उद्योगमंडल पी.ओ., कोच्चि, केरल - 683 501

फोन : 0484-2547741, 2546740

ई-मेल : kochi@cipet.gov.in, cipetkochi@gmail.com

वेबसाईट : www.cipet.gov.in



सिपेट CIPET

CENTRAL INSTITUTE OF PETROCHEMICALS  
ENGINEERING & TECHNOLOGY (CIPET)

(Formerly Central Institute of Plastics Engineering & Technology)

INSTITUTE OF PETROCHEMICALS TECHNOLOGY (IPT)

Department of Chemicals & Petrochemicals

Ministry of Chemicals & Fertilizers, Govt. of India

HIL Colony, Edayar Road, Pathalam

Udyogamandal P.O., Kochi, Kerala - 683 501

Ph: 0484-2547741, 2546740

E-mail:kochi@cipet.gov.in, cipetkochi@gmail.com

Web : www.cipet.gov.in

Continuation Sheet

Page 2 of 6

TR. NO.:241072

ANALYSIS RESULT

Date: 06.02.2025

b. pH of test medium


Sl. No	Composting Vessel (Material with test medium)	pH (Before)	pH (After)
1	Sample 1	7.2	7.3
2	Sample 2	7.3	7.4
3	Sample 3	7.3	7.3
4	Blank	7.3	7.4
5	Blank	7.3	7.4
6	Blank	7.3	7.4
7	Positive 1	7.2	7.4
8	Positive 2	7.2	7.4
9	Positive 3	7.3	7.4
10	Negative	7.3	7.5
11	Negative	7.3	7.5
12	Negative	7.4	7.5

4. Result:

Percentage biodegradation relative to positive reference

Mean(%) : 91.58 %

The reference material- cellulose (%) : ~100%

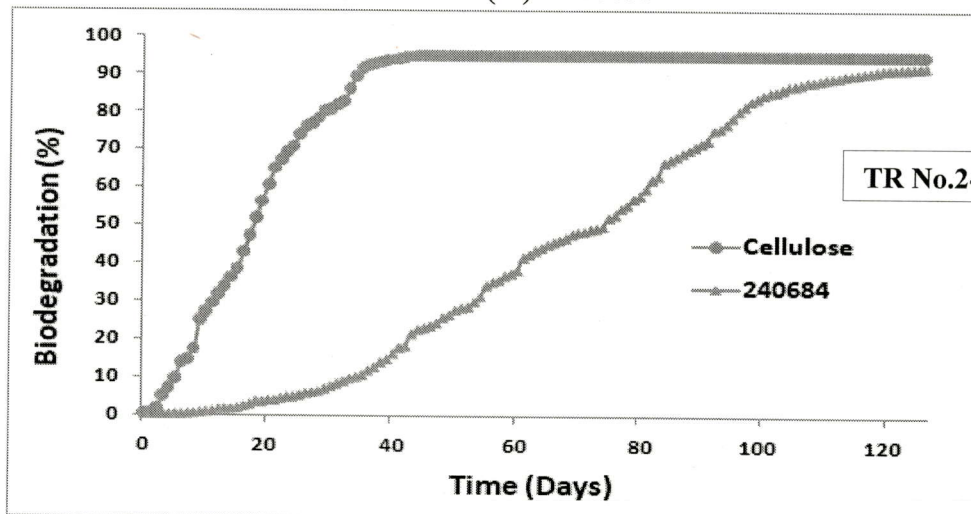

Dr. S. Anbudayanidhi  
Manager (Technical)  
Authorized Signatory

Dr. K.A. Rajesh  
Director & Head  
Authorized Signatory

केंद्रीय पेट्रोरसायन अभियांत्रिकी  
एवं प्रौद्योगिकी संस्थान (सिपेट)

(पूर्व में सेन्ट्रल इंस्टिट्यूट ऑफ प्लास्टिक्स इंजीनियरिंग एण्ड टेक्नोलॉजी)

इंस्टिट्यूट ऑफ पेट्रोरसायन टेक्नोलॉजी (आई.पी.टी.)

रसायन एवं पेट्रोरसायन विभाग

रसायन एवं उर्वरक मंत्रालय, भारत सरकार

एच.आई.एल.कॉलनी, एडयार रोड, पातालम्

उद्योगमंडल पी.ओ., कोची, केरल - 683 501

फोन : 0484-2547741, 2546740

ई-मेल : kochi@cipet.gov.in, cipetkochi@gmail.com

वेबसाईट : www.cipet.gov.in



CENTRAL INSTITUTE OF PETROCHEMICALS  
ENGINEERING & TECHNOLOGY (CIPET)

(Formerly Central Institute of Plastics Engineering & Technology)

INSTITUTE OF PETROCHEMICALS TECHNOLOGY (IPT)

Department of Chemicals & Petrochemicals

Ministry of Chemicals & Fertilizers, Govt. of India

HIL Colony, Edayar Road, Pathalam

Udyogamandal P.O., Kochi, Kerala - 683 501

Ph: 0484-2547741, 2546740

E-mail:kochi@cipet.gov.in, cipetkochi@gmail.com

Page 3 of 6 www.cipet.gov.in

Continuation Sheet

TR. NO.:241072

ANALYSIS RESULT


Date: 06.02.2025

5. Visual observation of Sample

Description	Week 1	Week 7	Week 11	Week 14	Week 18
Structure	Film Sample	Fragmented Film Sample	Disintegrated Film Sample	--	--
Moisture	Adequate moisture level	Adequate moisture level	Adequate moisture level	Adequate moisture level	Adequate moisture level
Colour	Milky White	Dirty like	--	--	--
Fungal Development	Nil	Nil	Nil	Nil	Nil
Smell	Organic/ Dirt Like	Organic/ Dirt Like	Organic/ Dirt Like	Organic/ Dirt Like	Organic/ Dirt Like

6. Visual observation of compost

Description	Week 1	Week 7	Week 11	Week 14	Week 18
Structure	Fine Particles	Fine Particles	Fine Particles	Fine Particles	Fine Particles
Moisture	Adequate moisture level	Adequate moisture level	Adequate moisture level	Adequate moisture level	Adequate moisture level
Colour	Dark Brown	Dark Brown	Dark Brown	Dark Brown	Dark Brown
Fungal Development	Nil	Nil	Nil	Nil	Nil
Smell	Organic/ Dirt Like	Organic/ Dirt Like	Organic/ Dirt Like	Organic/ Dirt Like	Organic/ Dirt Like

  
Dr. S. Anbudayanidhi  
Manager (Technical)  
Authorized Signatory

  
Dr. K.A. Rajesh  
Director & Head  
Authorized Signatory

केंद्रीय पेट्रोरसायन अभियांत्रिकी  
एवं प्रौद्योगिकी संस्थान (सिपेट)

(पूर्व में सेंट्रल इंस्टिट्यूट ऑफ प्लास्टिक्स इंजीनियरिंग एण्ड टेक्नोलॉजी)

इंस्टिट्यूट ऑफ पेट्रोरसायन टेक्नोलॉजी (आई.पी.टी.)

रसायन एवं पेट्रोरसायन विभाग

रसायन एवं उर्वरक मंत्रालय, भारत सरकार

एच.आई.एल.कॉलनी, एडयार रोड, पातालम्

उद्योगमंडल पी.ओ., कोच्चि, केरल - 683 501

फोन : 0484-2547741, 2546740

ई-मेल : kochi@cipet.gov.in, cipetkochi@gmail.com

वेबसाईट : www.cipet.gov.in



**PP**  
सिपेट CIPET

**CENTRAL INSTITUTE OF PETROCHEMICALS  
ENGINEERING & TECHNOLOGY (CIPET)**

(Formerly Central Institute of Plastics Engineering & Technology)

**INSTITUTE OF PETROCHEMICALS TECHNOLOGY (IPT)**

Department of Chemicals & Petrochemicals

Ministry of Chemicals & Fertilizers, Govt. of India

HIL Colony, Edayar Road, Pathalam

Udyogamandal P.O., Kochi, Kerala - 683 501

Ph: 0484-2547741, 2546740

E-mail:kochi@cipet.gov.in, cipetkochi@gmail.com

Web : www.cipet.gov.in

Continuation Sheet

Page 4 of 6


TR. NO.:241072

ANALYSIS RESULT

Date: 06.02.2025


Sample Details: Compostable Film as stated by the party.

7. FTIR Analysis

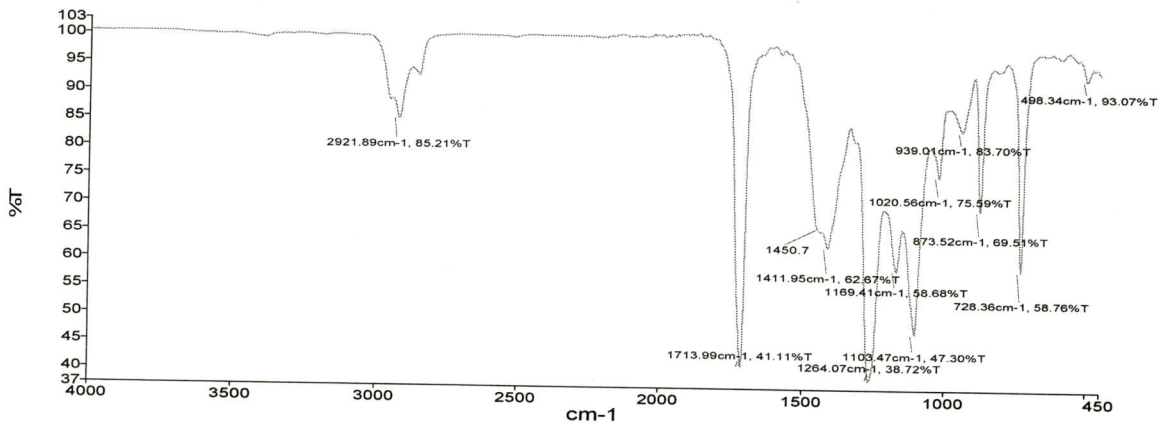

Wave number(cm <sup>-1</sup> )	Nature of Bond
2921.89	C-H stretching vibration
1713.99	C=O stretching vibration
1450.7	C-H bending vibration
1411.95	C=C stretching vibration
1264.07	C-O stretching vibration

8. DSC Analysis

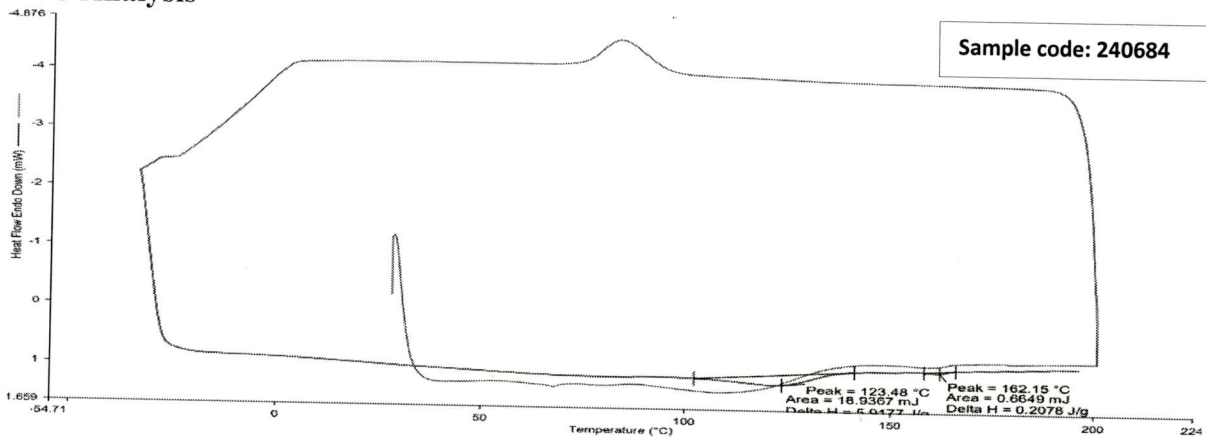

**Comment:** The above DSC & FTIR analysis indicates the above sample is Poly (lactic acid) (PLA) and Poly (butylene Adipate - co- Terephthalate) (PBAT).

*S. Anbudayanidhi*  
**Dr. S. Anbudayanidhi**  
Manager (Technical)  
Authorized Signatory

*Dr. K.A. Rajesh*  
**Dr. K.A. Rajesh**  
Director & Head  
Authorized Signatory

केंद्रीय पेट्रोसायन अभियांत्रिकी  
एवं प्रौद्योगिकी संस्थान (सिपेट)

(पुर्व में सेन्ट्रल इंस्टिट्यूट ऑफ प्लास्टिक्स इंजीनियरिंग एण्ड टेक्नोलॉजी)

इंस्टिट्यूट ऑफ पेट्रोसायन टेक्नोलॉजी (आई.पी.टी.)

रसायन एवं पेट्रोसायन विभाग

रसायन एवं उर्वरक मंत्रालय, भारत सरकार

एच.आई.एल.कॉलनी, एडयार रोड, पातालम्

उद्योगमंडल पी.ओ., कोच्चि, केरल - 683 501

फोन : 0484-2547741, 2546740

ई-मेल : kochi@cipet.gov.in, cipetkochi@gmail.com

वेबसाईट : www.cipet.gov.in



CENTRAL INSTITUTE OF PETROCHEMICALS  
ENGINEERING & TECHNOLOGY (CIPET)

(Formerly Central Institute of Plastics Engineering & Technology)

INSTITUTE OF PETROCHEMICALS TECHNOLOGY (IPT)

Department of Chemicals & Petrochemicals

Ministry of Chemicals & Fertilizers, Govt. of India

HIL Colony, Edayar Road, Pathalam

Udyogamandal P.O., Kochi, Kerala - 683 501

Ph: 0484-2547741, 2546740

E-mail:kochi@cipet.gov.in, cipetkochi@gmail.com

Web : www.cipet.gov.in

Continuation Sheet



Page 5 of 6

TR. NO.:241072

ANALYSIS RESULT


Date: 06.02.2025

9. DISINTEGRATION- AFTER 12 WEEKS

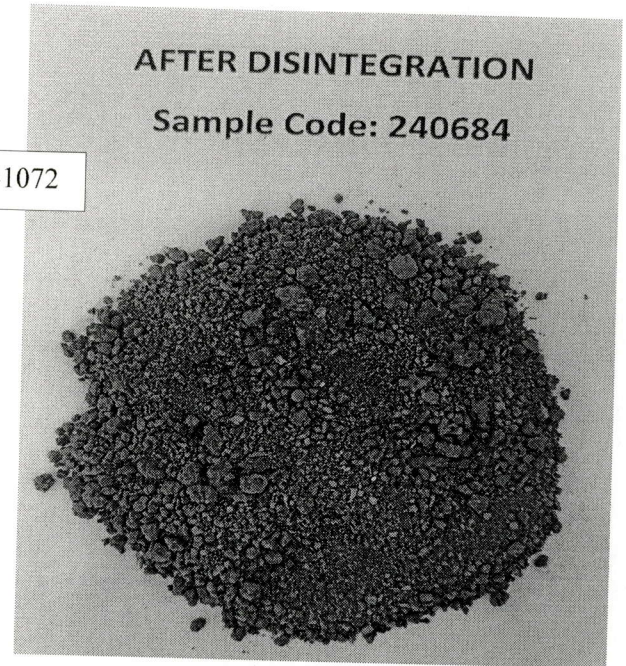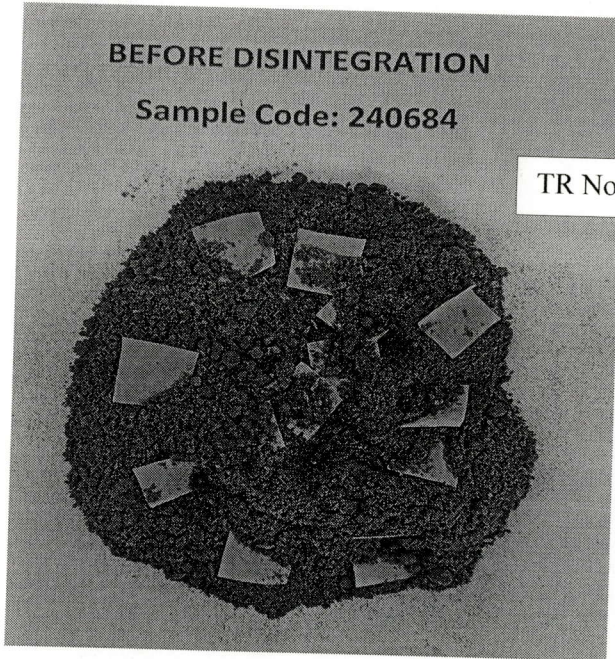

The disintegration of the supplied sample by passing through 2 mm sieve after 12 week in composting condition as per ISO 17088-2021 was found not more than 10% of original dry mass remain.

10. SEED GERMINATION AND PLANT GROWTH STUDY

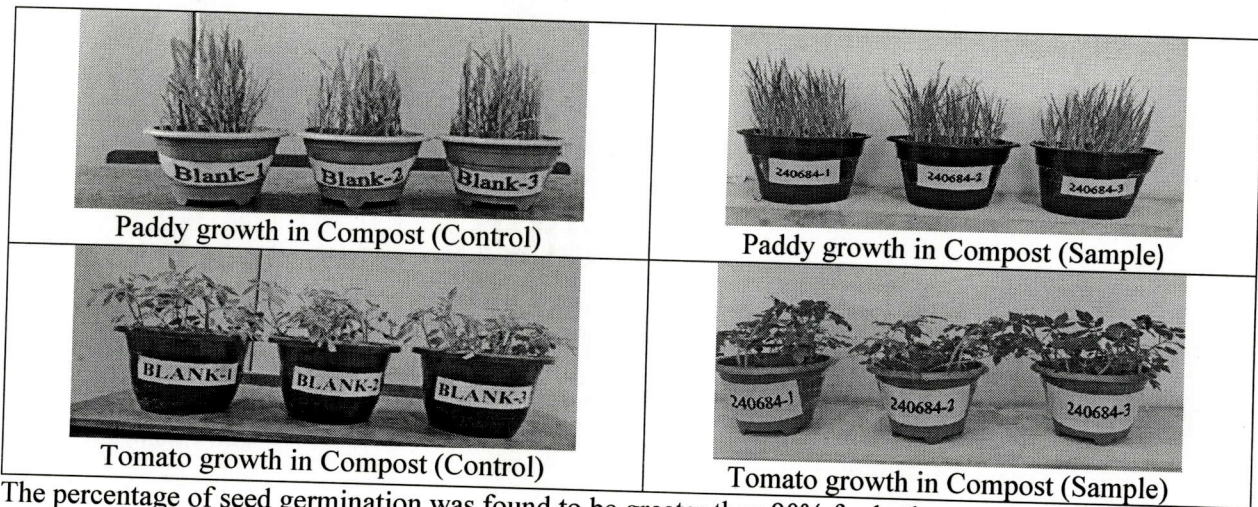

The percentage of seed germination was found to be greater than 90% for both control and sample.

*S. Anudh*  
Dr. S. Anbudayanidhi  
Manager (Technical)  
Authorized Signatory

*K.A. Rajesh*  
Dr. K.A. Rajesh  
Director & Head  
Authorized Signatory

केंद्रीय पेट्रोसायन अभियांत्रिकी  
एवं प्रौद्योगिकी संस्थान (सिपेट)

(पूर्व में सेंट्रल इंस्टिट्यूट ऑफ प्लास्टिक्स इंजीनियरिंग एण्ड टेक्नोलॉजी)

इंस्टिट्यूट ऑफ पेट्रोसायन टेक्नोलॉजी (आई.पी.टी.)

रसायन एवं पेट्रोसायन विभाग

रसायन एवं उर्वरक मंत्रालय, भारत सरकार

एच.आई.एल.कॉलनी, एडयार रोड, पातालम्

उद्योगमंडल पी.ओ., कोच्चि, केरल - 683 501

फोन : 0484-2547741, 2546740

ई-मेल : kochi@cipet.gov.in, cipetkochi@gmail.com

वेबसाइट : www.cipet.gov.in



**PP**  
सिपेट CIPET

**CENTRAL INSTITUTE OF PETROCHEMICALS  
ENGINEERING & TECHNOLOGY (CIPET)**

(Formerly Central Institute of Plastics Engineering & Technology)

**INSTITUTE OF PETROCHEMICALS TECHNOLOGY (IPT)**

Department of Chemicals & Petrochemicals

Ministry of Chemicals & Fertilizers, Govt. of India

HIL Colony, Edayar Road, Pathalam

Udyogamandal P.O., Kochi, Kerala - 683 501

Ph: 0484-2547741, 2546740

E-mail:kochi@cipet.gov.in, cipetkochi@gmail.com

Page 6 of 6 www.cipet.gov.in


Continuation Sheet

**TR. NO.:241072**


**ANALYSIS RESULT**

**Date: 06.02.2025**

**11. Acute & Chronic Ecotoxicity effects to Earthworm**

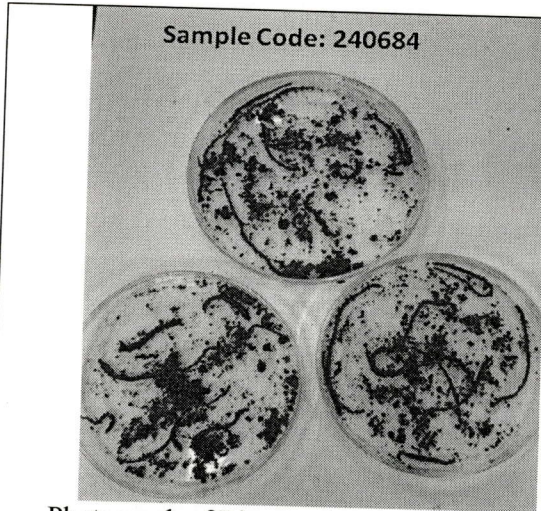


Photograph of Live earthworm in the sample compost at the end of 7 days

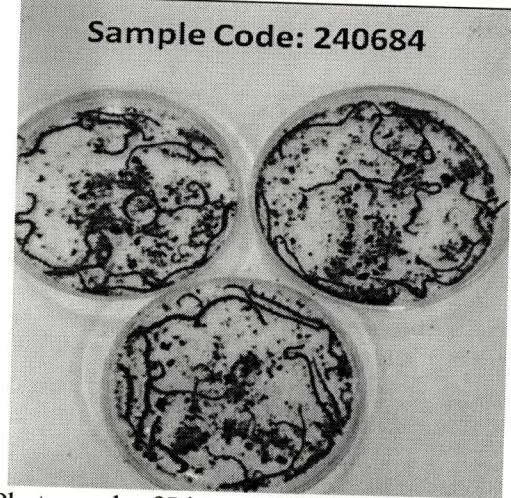


Photograph of Live earthworm in the sample compost at the end of 14 days

The surviving adult earthworms grown in the sample compost exposed to the test material after an incubation period of 14 days is more than 90 % of those from the corresponding blank compost not exposed to any material.

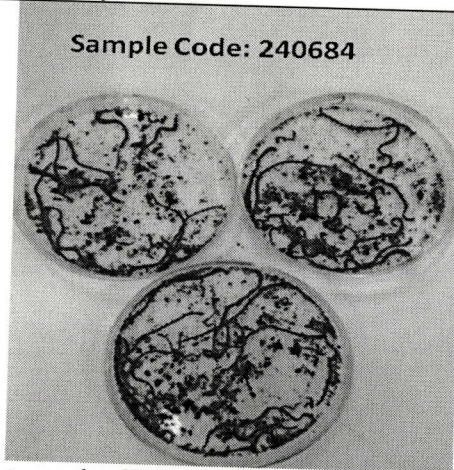

Photograph of Live earthworms in the sample compost at the end of 28 days.

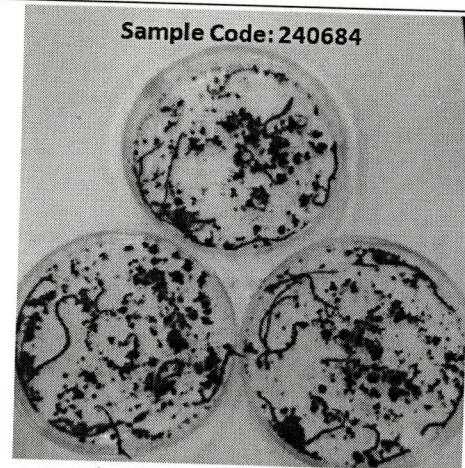

Photograph of Live earthworm in the sample compost at the end of 56 days.

The surviving adult earthworms grown in the sample compost exposed to the test material after an incubation period of 28 days and the counted number of offspring after an incubation period of 56 days is more than 90 % of those from the corresponding blank compost.

*S. Anudh*  
**Dr. S. Anbudayanidhi**  
Manager (Technical)  
Authorized Signatory

*K.A. Rajesh*  
**Dr. K.A. Rajesh**  
Director & Head  
Authorized Signatory