



THE STANDARD
IN TIG WELDING

TECHNICAL GUIDE
SPECIFICATIONS FOR TIG WELDING





WORLDWIDE



**THE STANDARD
IN TIG WELDING**

TABLE OF CONTENTS

TIG Torch Connection Diagrams

Gas-Cooled Torches	3
Water-Cooled Torches	3

Characteristics of Current Types for TIG Welding

DC Straight Polarity	4
DC Reverse Polarity	4
AC High Frequency	4
Selecting Correct Torch Nozzle	5
Gas Lens Benefits	5

Shield Gas Selection and Use

Guide for Shield Gas Flows, Current Settings, Cup Selection	6
Tungsten Electrode Tip Shapes and Current Ranges	6
Correct Torch and Rod Positioning	6

Tungsten Selection and Preparation

Tungsten Tip Preparation	7
Tungsten Extension and Grinding	7
Color Code for Tungsten Electrodes	7

Tungsten Characteristics and Penetration Profiles

Tungsten Electrode Characteristics	8
Tungsten Electrode Current Ranges	8
Weld Penetration Profiles	9

Typical Manual TIG Welding Parameters

Aluminum	10
Titanium	10
Magnesium	10
Deoxidized Copper	11
Stainless Steel	11
Low Alloy Steel	11

Typical Manual TIG Welding Parameters






Excessive Electrode Consumption	12
Erratic Arc	12
Inclusion of Tungsten or Oxides in Weld	12
Porosity in Weld Deposit	12
Cracking in Welds	12
Inadequate Shielding	12
Arc Blow	12
Short Parts Life	12

FIND US ON:




INSTAGRAM:
@ckworldwide

The information in this manual represents the best judgement of CK Worldwide, Inc. and is intended for use by experienced personnel. Never operate any equipment without carefully reading, understanding, and following all of the related safety rules and practices. CK Worldwide makes no claims, expressed or implied, as to the viability of this information for any application or use. The individual user is solely responsible for any and all uses of the information contained herein, since CK Worldwide has no means to confirm the correct use of, or control any of the variables to the use of any and all information herein.

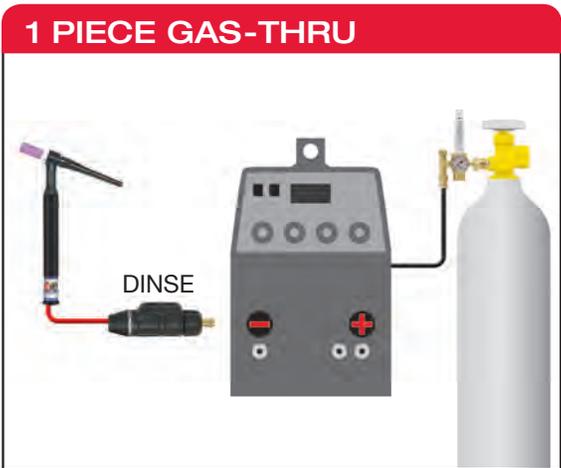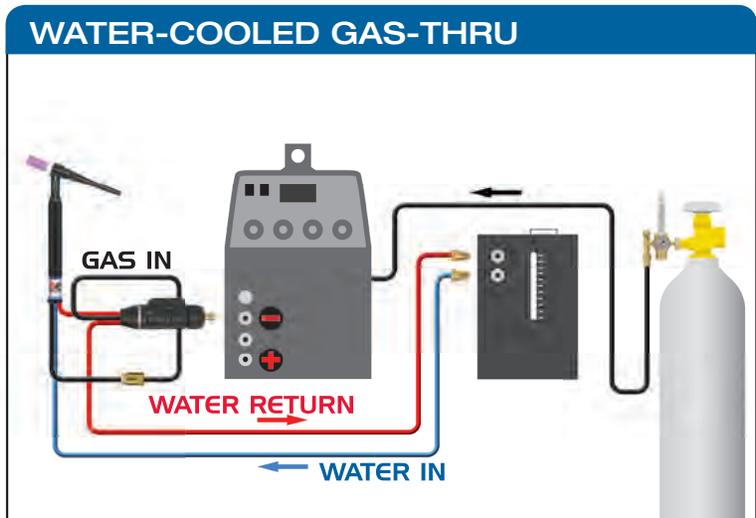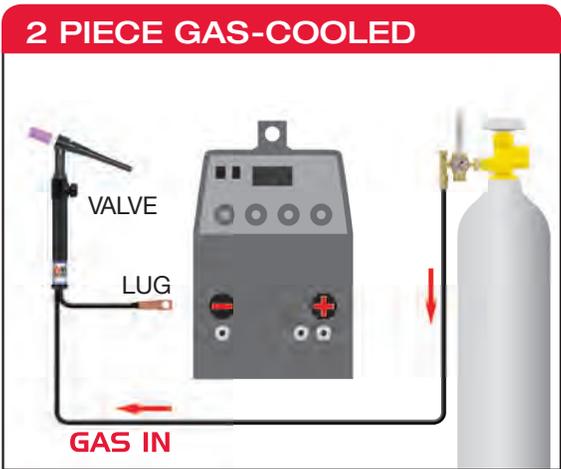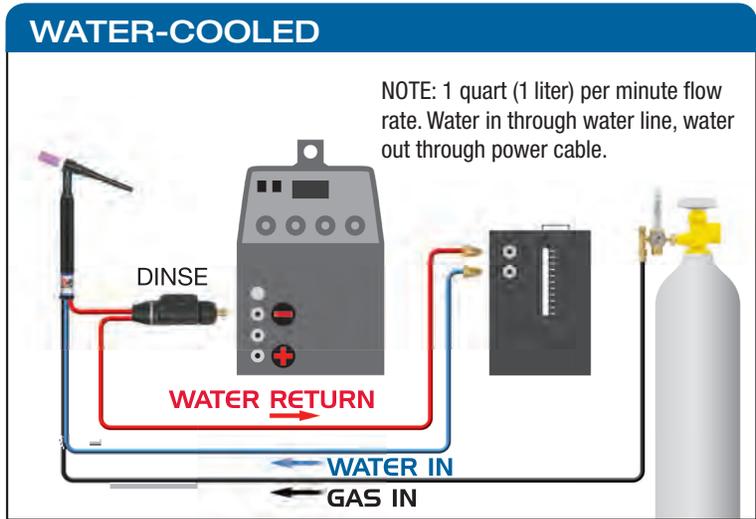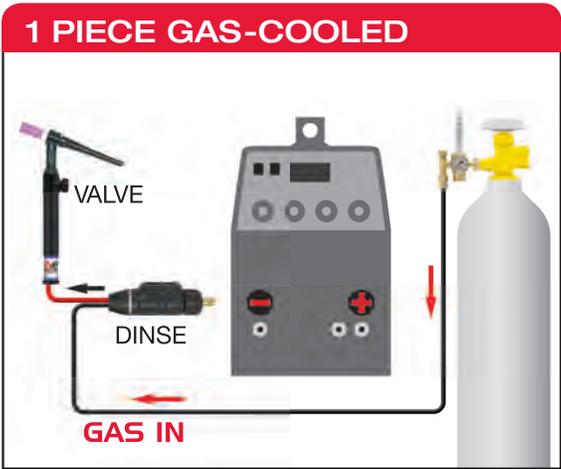

CHARACTERISTICS OF CURRENT TYPES FOR GAS TUNGSTEN ARC WELDING


When TIG welding, there are three choices of welding current. They are: Direct Current Straight Polarity (DCSP), Direct Current Reverse Polarity (DCRP), and Alternating Current with or without High Frequency stabilization (ACHF). Each of these has its applications, advantages, and disadvantages. A look at each type and its uses will help the operator select the best current type for the job. The type of current used will have a great effect on the penetration pattern as well as the bead configuration. The diagrams below show arc characteristics of each current polarity type.

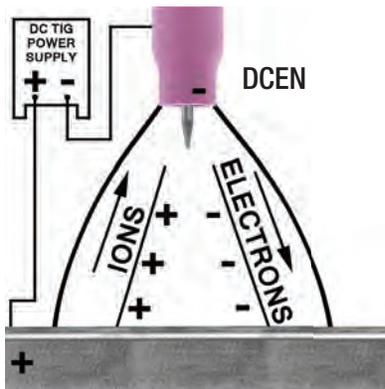

TIG WELDING DCSP

Direct Current Straight Polarity produces deep penetration by concentrating heat in the joint area. No cleaning action occurs with this polarity.


CURRENT TYPE	DCSP
ELECTRODE POLARITY	Electrode negative
OXIDE CLEANING ACTION	No
HEAT BALANCE IN THE ARC	70% of work end 30% at electrode end
PENETRATION PROFILE	Deep narrow
ELECTRODE CAPACITY	Excellent

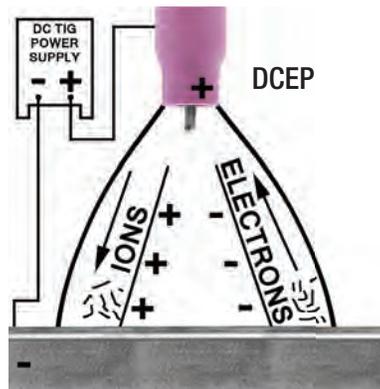

TIG WELDING DCRP

Direct Current Reverse Polarity produces the best cleaning action as the argon ions flowing towards the work strike with sufficient force to break up oxides on the surface.

CURRENT TYPE	DCRP
ELECTRODE POLARITY	Electrode positive
OXIDE CLEANING ACTION	Yes
HEAT BALANCE IN THE ARC	30% of work end 70% at electrode end
PENETRATION PROFILE	Shallow wide
ELECTRODE CAPACITY	Poor

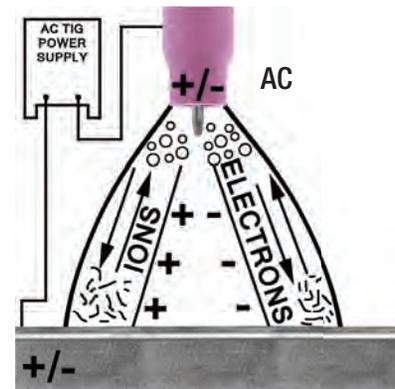

TIG WELDING WITH ACHF

Alternating Current High Frequency combines the weld penetration on the negative half cycle with the cleaning action of the positive half cycle. High frequency re-establishes the arc which breaks each half cycle on transformer based machines.

CURRENT TYPE	ACHF
ELECTRODE POLARITY	Alternating
OXIDE CLEANING ACTION	Yes (once every half cycle)
HEAT BALANCE IN THE ARC	50% of work end 50% at electrode end
PENETRATION PROFILE	Medium
ELECTRODE CAPACITY	Good

DCSP mainly used on: Stainless Steel, Mild Steel, Nickel, Copper, Titanium

ACHF mainly used on: Aluminum, Magnesium

DCRP mainly used on: Thin Material

SELECTING THE CORRECT TORCH NOZZLE

CUP CHART



ALUMINA

High impact resistance
Low thermal shock
(Aluminum Oxide)



CERAMIC

High thermal shock
Low impact resistance
(Lava)



SUPER CUP

High thermal shock
High impact resistance
(Silicon Nitride)




PYREX

High visibility
Low thermal shock
Low impact resistance
(Pyrex)



GAS LENS BENEFITS

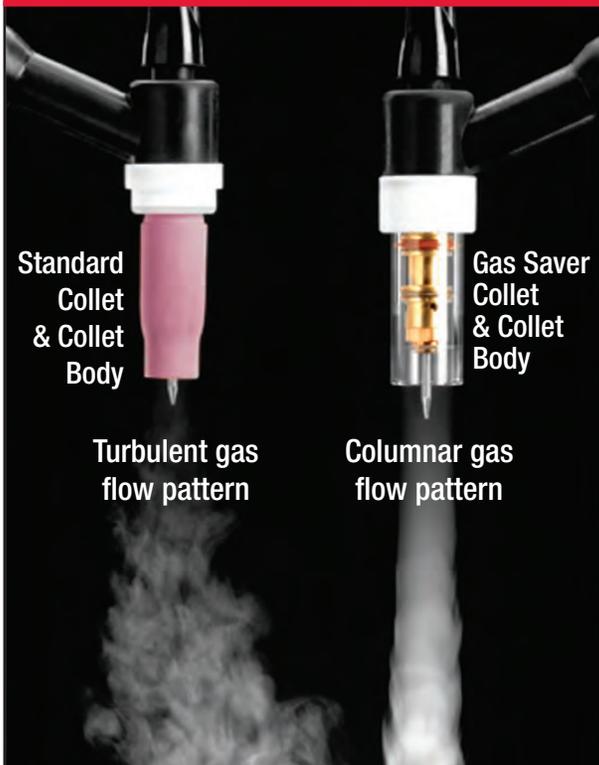

- 40% Argon savings
- Columnar flow gas pattern
- Longer electrode stick-out
- Lower gas flow rates
- Better visibility
- Longer parts life
- Cleaner welds

GUIDE FOR SHIELD GAS FLOWS, CURRENT SETTINGS & CUP SELECTION


Electrode Diameter	Cup Size	WELDING CURRENT (AMPS)				TUNGSTEN TYPE		ARGON FLOW FERROUS METALS		ARGON FLOW ALUMINUM	
		AC Pure	AC Thoriated	DCSP Pure	DCSP Thoriated	Standard Body CFH (L/MN)	Gas Lens Body CFH (L/MN)	Standard Body CFH (L/MN)	Gas Lens Body CFH (L/MN)		
.020" (0.5mm)	3, 4, or 5	5-15	5-20	5-15	5-20	5-8 (3-4)	5-8 (3-4)	5-8 (3-4)	5-8 (3-4)		
.040" (1.0mm)	4 or 5	10-60	15-80	15-70	20-80	5-10 (3-5)	5-8 (3-4)	5-12 (3-6)	5-10 (3-5)		
1/16" (1.6mm)	4, 5, or 6	50-100	70-150	70-130	80-150	7-12 (4-6)	5-10 (3-5)	8-15 (4-7)	7-12 (4-6)		
3/32" (2.4mm)	6, 7, or 8	100-160	140-235	150-220	150-250	10-15 (5-7)	8-10 (4-5)	10-20 (5-10)	10-15 (5-7)		
1/8" (3.2mm)	7, 8, or 10	150-210	220-325	220-330	240-350	10-18 (5-9)	8-12 (4-6)	12-25 (6-12)	10-20 (5-10)		
5/32" (4.0mm)	8 or 10	200-275	300-425	375-475	400-500	15-25 (7-12)	10-15 (5-7)	15-30 (7-14)	12-25 (6-12)		
3/16" (4.8mm)	8 or 10	250-350	400-525	475-800	475-800	20-35 (10-17)	12-25 (6-12)	25-40 (12-19)	15-30 (7-14)		
1/4" (6.4mm)	10	325-700	500-700	750-1000	700-1000	25-50 (12-24)	20-35 (10-17)	30-55 (14-26)	25-45 (12-21)		

For pure helium shielding gas, double flow rates shown. For argon-helium mixes with below 30% helium content, use figures shown. Always adjust gas flows to accommodate best shielding results.

TUNGSTEN ELECTRODE TIP SHAPES AND CURRENT RANGES

ELECTRODE DIAMETER		DIAMETER AT TIP		INCLUDED ANGLE	CURRENT RANGE	PULSED CURRENT RANGE
Millimeters	Inches	Millimeters	Inches			
1.0mm	.040"	.125mm	.005"	12°	2-15 amps	2-25 amps
1.0mm	.040"	.250mm	.010"	20°	5-30 amps	5-60 amps
1.6mm	1/16"	.500mm	.020"	25°	8-50 amps	8-100 amps
1.6mm	1/16"	.800mm	.030"	30°	10-70 amps	10-140 amps
2.4mm	3/32"	.800mm	.030"	35°	12-90 amps	12-180 amps
2.4mm	3/32"	1.100mm	.045"	45°	15-150 amps	15-250 amps
3.2mm	1/8"	1.100mm	.045"	60°	20-200 amps	20-300 amps
3.2mm	1/8"	1.500mm	.060"	90°	25-250 amps	25-350 amps

CORRECT TORCH AND ROD POSITIONING

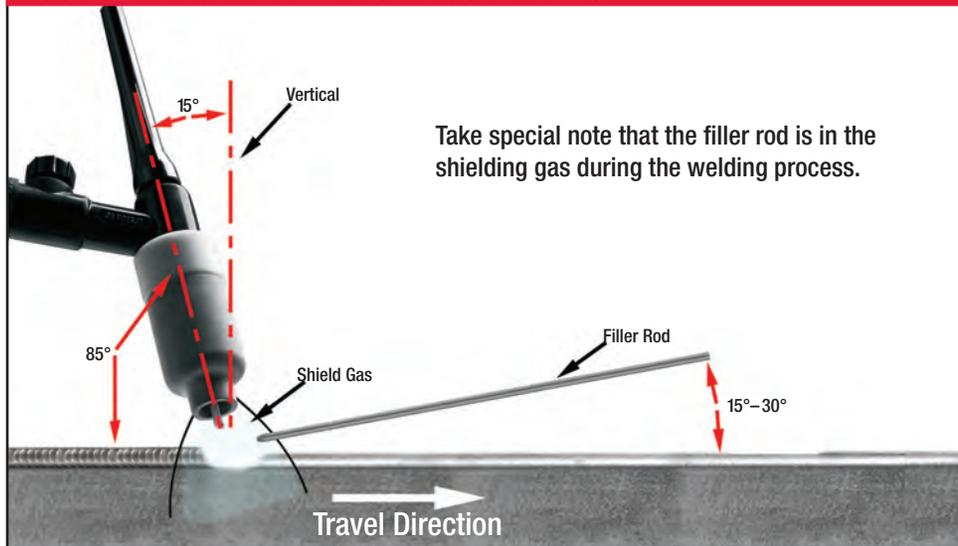

TUNGSTEN TIP PREPARATION

DC TIG WELDING

Flat: 1/4 TO 1/2 X DIA
Taper Length: 2-3 X DIA

AC TIG WELDING

Typical Tip Geometry for Inverter
Typical Tip Geometry for Transformer
Maximum Ball Size: 1 X DIA

Ball tip by arcing on non-ferrous metal at low current DCRP (EP) then slowly increase current to form the desired ball diameter. Return setting to AC.

TUNGSTEN EXTENSION

STANDARD PARTS

General Purpose 3 X DIA

GAS LENS PARTS

General Purpose 3 X DIA
MAX: 6 X DIA. (In draft-free areas)

TUNGSTEN GRINDING

Use a medium (60 grit or finer) diamond or aluminum oxide wheel.

- Grind longitudinally (never radially)
- Truncate (blunt) end
- Diameter of flat spot determines amperage capacity

The included angle determines weld bead shape and size. Generally, as the included angle increases, penetration increases and bead width decreases.
*Refer to page 5

COLOR CODE FOR TUNGSTEN ELECTRODES

Designation		Chemical Composition Impurities ≤ 0.1%		TIP COLOR
ISO 6848	AWS A5.12	OXIDE ADDITIVE	TUNGSTEN	
WT20	EWTh-2	ThO ₂ : 1.70–2.20%	2% THORIATED	Red
WP	EWP	~~~~~	PURE	Green
WL15	EWLa-1.5	LaO ₂ : 1.30–1.70%	1.5% LANTHANATED	Gold
WC20	EWCe-2	CeO ₂ : 1.80–2.20%	2% CERIATED	Gray
WL20	EWLa-2	La ₂ O ₃ : 1.80–2.20%	2% LANTHANATED	Blue
WZ8	EWZr-8	ZrO ₂ : 0.70–0.90%	0.8% ZIRCONIATED	White
LaYzr™	EWG	La ₂ O ₃ : 1.3–1.7%; Y ₂ O ₃ : 0.06–0.10%; ZrO ₂ : 0.6–1.0%	1.5% LANTHANATED 0.8% YTTRIATED 0.8% ZIRCONIATED	Chartreuse

TUNGSTEN ELECTRODE CHARACTERISTICS

Tungsten	Color Code	Characteristics
Pure	 Green	Provides good arc stability for AC welding. Reasonably good resistance to contamination. Lowest current carrying capacity. Least expensive. Maintains a balled end. Used on transformer based machines only.
2% Ceriated	 Gray	Similar performance to thoriated tungsten. Easy arc starting, good arc stability, long life. Possible replacement for thoriated.
2% Thoriated	 Red	Easier arc starting. Higher current capacity. Greater arc stability. High resistance to weld pool contamination. Difficult to maintain balled end on AC.
1.5% Lanthanated	 Gold	Similar performance to thoriated tungsten. Easy arc starting, good arc stability, long life, high current capacity. 1.5% possible replacement for thoriated. 2% possible replacement for Pure.
2% Lanthanated	 Blue	Similar performance to thoriated tungsten. Easy arc starting, good arc stability, long life, high current capacity. 1.5% possible replacement for thoriated. 2% possible replacement for Pure.
.8% Zirconiated	 White	Excellent for AC welding due to favorable retention of balled end, high resistance to contamination, and good arc starting. Preferred when tungsten contamination of weld is intolerable. Possible replacement for Pure.
LaYZr™	 Chartreuse*	Best for use on automated or robotic applications. Runs cooler than 2% Thoriated with longer life. Low to medium amperage range.

*Substitute for Purple (Same oxide blend).

TUNGSTEN ELECTRODE CURRENT RANGES

Tungsten Diameter in inches (mm)	Gas Cup (Inside Diameter)	TYPICAL CURRENT RANGE				
		Direct Current, DC		Alternating Current, AC		
		DCEN	70% Penetration		(50/50) Balanced Wave, AC	
		Ceriated	Zirconiated	Ceriated	Zirconiated	Ceriated
.040" (1.0mm)	#6 (3/8")	15–80 amps	20–60 amps	15–80 amps	10–30 amps	20–60 amps
1/16" (1.6mm)	#6 (3/8")	70–150 amps	50–100 amps	70–150 amps	30–80 amps	60–120 amps
3/32" (2.3mm)	#8 (1/2")	150–250 amps	100–160 amps	140–235 amps	60–130 amps	100–180 amps
1/8" (3.2mm)	#8 (1/2")	250–400 amps	150–200 amps	225–325 amps	100–180 amps	160–250 amps

All values are based on the use of Argon as a shielding gas. Other current values may be employed depending on the shielding gas, type of equipment, and application. DCEN = Direct Current Electrode Negative (Straight Polarity)

WELD PENETRATION PROFILE			
Gas Type	 30° Angle .005" FLAT	 60° Angle .010" FLAT	 90° Angle .020" FLAT
100Ar 100% Argon			
75Ar-25He 75% Argon 25% Helium			
50Ar-50He 50% Argon 50% Helium			
25Ar-75He 25% Argon 75% Helium			
100He 100% Helium			
95Ar-5H₂ 95% Argon 5% Hydrogen			

ALUMINUM (ACHF)

METAL GAUGE	JOINT TYPE	TUNGSTEN SIZE	FILLER ROD SIZE	CUP SIZE	SHIELD GAS FLOW			WELDING AMPERES	TRAVEL SPEED
					TYPE	CFH (L/MN)	PSI		
1/16" (1.6mm)	BUTT	1/16" (1.6mm)	1/16" (1.6mm)	4, 5, 6	ARGON	15 (7)	20	60-80	12" (307.2mm)
	FILLET							70-90	10" (256mm)
1/8" (3.2mm)	BUTT	3/32" (2.4mm)	3/32" (2.4mm)	6, 7	ARGON	17 (8)	20	125-145	12" (307.2mm)
	FILLET		1/8" (3.2mm)					140-160	10" (256mm)
3/16" (4.8mm)	BUTT	1/8" (3.2mm)	1/8" (3.2mm)	7, 8	ARGON/ HELIUM	21 (10)	20	195-220	11" (258.6mm)
	FILLET							210-240	9" (230.4mm)
1/4" (6.4mm)	BUTT	3/16" (4.8mm)	1/8" (3.2mm)	8, 10	ARGON/ HELIUM	25 (12)	20	260-300	10" (256mm)
	FILLET							280-320	8" (204.8mm)

ALUMINUM

The use of TIG welding for aluminum has many advantages for both manual and automatic processes. Filler metal can be either wire or rod and should be compatible with the base alloy. Filler metal must be dry, free of oxides, grease, or other foreign matter. If filler metal becomes damp, heat for 2 hours at 250°F (121°C) before using. Although ACHF is recommended, DCRP has been successful up to 3/32" (2.4mm), DCSP with helium shield gas is successful in mechanized applications.

TITANIUM (DCSP)

METAL GAUGE	JOINT TYPE	TUNGSTEN SIZE	FILLER ROD SIZE	CUP SIZE	SHIELD GAS FLOW			WELDING AMPERES	TRAVEL SPEED
					TYPE	CFH (L/MN)	PSI		
1/16" (1.6mm)	BUTT	1/16" (1.6mm)	NONE	4, 5, 6	ARGON	15 (7)	20	90-110	10" (256mm)
	FILLET							110-150	8" (204.8mm)
1/8" (3.2mm)	BUTT	3/32" (2.4mm)	1/16" (1.6mm)	5, 6, 7	ARGON	15 (7)	20	190-220	9" (230.4mm)
	FILLET							210-250	7" (179.2mm)
3/16" (4.8mm)	BUTT	3/32" (2.4mm)	1/8" (3.2mm)	6, 7, 8	ARGON	20 (10)	20	220-250	8" (204.8mm)
	FILLET							240-280	7" (179.2mm)
1/4" (6.4mm)	BUTT	1/8" (3.2mm)	1/8" (3.2mm)	8, 10	ARGON	30 (15)	20	275-310	8" (204.8mm)
	FILLET							290-340	7" (179.2mm)

TITANIUM

Small amounts of impurities, particularly oxygen and nitrogen, cause embrittlement of molten or hot titanium when above 500°F (260°C). The molten weld metal in the heat-affected zones must be shielded by a protective blanket of inert gas. Titanium requires a strong, positive pressure of argon or helium as a backup on the root side of the weld, as well as long, trailing, protective tail of argon gas to protect the metal while cooling. Purge chambers and trailing shields are available from CK Worldwide to assist in providing quality results.

MAGNESIUM (ACHF)

METAL GAUGE	JOINT TYPE	TUNGSTEN SIZE	FILLER ROD SIZE	CUP SIZE	SHIELD GAS FLOW			WELDING AMPERES	TRAVEL SPEED
					TYPE	CFH (L/MN)	PSI		
1/16" (1.6mm)	BUTT	1/16" (1.6mm)	3/32" (2.4mm)	5, 6	ARGON	13 (5)	15	60	20" (512mm)
	FILLET		1/8" (3.2mm)					60	
1/8" (3.2mm)	BUTT	3/32" (2.4mm)	1/8" (3.2mm)	7, 8	ARGON	19 (9)	15	115	17" (435.2mm)
	FILLET		5/32" (4.0mm)					115	
1/4" (6.4mm)	BUTT	3/16" (4.8mm)	5/32" (4.0mm)	8	ARGON	25 (12)	15	100-130	22" (563.2mm)
	FILLET							110-135	20" (512mm)
1/2" (12.8mm)	BUTT	1/4" (6.4mm)	3/16" (4.8mm)	10	ARGON	35 (17)	15	260	10" (256mm)
	FILLET								

MAGNESIUM

Magnesium was one of the first metals to be welded commercially by TIG. Magnesium alloys are in three groups, they are: (1) aluminum-zinc-magnesium, (2) aluminum-magnesium, and (3) manganese-magnesium. Since magnesium absorbs a number of harmful ingredients and oxidize rapidly when subjected to welding heat, TIG welding in an inert gas atmosphere is distinctly advantageous. The welding of magnesium is similar, in many respects, to the welding of aluminum. Magnesium requires a positive pressure of argon as a backup on the root side of the weld.



DEOXIDIZED COPPER (DCSP)

METAL GAUGE	JOINT TYPE	TUNGSTEN SIZE	FILLER ROD SIZE	CUP SIZE	SHIELD GAS FLOW			WELDING AMPERES	TRAVEL SPEED
					TYPE	CFH (L/MN)	PSI		
1/16" (1.6mm)	BUTT	1/16" (1.6mm)	1/16" (1.6mm)	4, 5, 6	ARGON	18 (9)	15	110-140	12" (307.2mm)
	FILLET							130-150	10" (256mm)
1/8" (3.2mm)	BUTT	3/32" (2.4mm)	3/32" (2.4mm)	4, 5, 6	ARGON	18 (9)	15	175-225	11" (258.6mm)
	FILLET							200-250	9" (230.4mm)
3/16" (4.8mm)	BUTT	1/8" (3.2mm)	1/8" (3.2mm)	8, 10	HELIUM	36 (17.5)	15	190-225	10" (256mm)
	FILLET							205-250	8" (204.8mm)
1/4" (6.4mm)	BUTT (2)	3/16" (4.8mm)	1/8" (3.2mm)	8, 10	HELIUM	36 (17.5)	15	225-260	9" (230.4mm)
	FILLET							250-280	7" (179.2mm)

DEOXIDIZED COPPER

Where extensive welding is to be done, the use of deoxidized (oxygen-free) copper is preferable over electrolytic tough pitch copper. Although TIG welding has been used occasionally to weld zinc-bearing copper alloys, such as brass and commercial bronzes, it is not recommended because the shielding gas does not suppress the vaporization of zinc. For the same reason zinc bearing filler rods should not be used. There is some preference of helium for the inert atmosphere in welding thickness above 1/8" (3.2mm) because of the improved weld metal fluidity. Preheating recommendations should be followed.

STAINLESS STEEL (DCSP)

METAL GAUGE	JOINT TYPE	TUNGSTEN SIZE	FILLER ROD SIZE	CUP SIZE	SHIELD GAS FLOW			WELDING AMPERES	TRAVEL SPEED
					TYPE	CFH (L/MN)	PSI		
1/16" (1.6mm)	BUTT	1/16" (1.6mm)	1/16" (1.6mm)	4, 5, 6	ARGON	11 (5.5)	20	80-100	12" (307.2mm)
	FILLET							90-100	10" (256mm)
1/8" (3.2mm)	BUTT	1/16" (1.6mm)	3/32" (2.4mm)	4, 5, 6	ARGON	11 (5.5)	20	120-140	12" (307.2mm)
	FILLET							130-150	10" (256mm)
3/16" (4.8mm)	BUTT	3/32" (2.4mm)	1/8" (3.2mm)	5, 6, 7	ARGON	13 (6)	20	200-250	12" (307.2mm)
	FILLET	3/32" (2.4mm) 1/8" (3.2mm)						225-275	10" (256mm)
1/4" (6.4mm)	BUTT	1/8" (3.2mm)	3/16" (4.8mm)	8, 10	ARGON	13 (6)	20	275-350	10" (256mm)
	FILLET							300-375	8" (204.8mm)

STAINLESS STEEL

In TIG welding of stainless steel, welding rods having the AWS-ASTM prefixes of E or ER can be used as filler rods. However, only bare uncoated rods should be used. Light gauge metals less than 1/16" (1.6mm) thick should always be welded with DCSP using argon gas. Follow the normal precautions for welding stainless such as: Clean surfaces; dry electrodes; use only stainless steel tools and brushes, keep stainless from coming in contact with other metals.

LOW ALLOY STEEL (DCSP)

METAL GAUGE	JOINT TYPE	TUNGSTEN SIZE	FILLER ROD SIZE	CUP SIZE	SHIELD GAS FLOW			WELDING AMPERES	TRAVEL SPEED
					TYPE	CFH (L/MN)	PSI		
1/16" (1.6mm)	BUTT	1/16" (1.6mm)	1/16" (1.6mm)	4, 5, 6	ARGON	15 (7)	20	95-135	15" (384mm)
	FILLET							95-135	15" (384mm)
1/8" (3.2mm)	BUTT	1/16" (1.6mm) 3/32" (2.4mm)	3/32" (2.4mm)	4, 5, 6	ARGON	15 (7)	20	145-205	11" (258.6mm)
	FILLET							145-205	11" (258.6mm)
3/16" (4.8mm)	BUTT	3/32" (2.4mm)	1/8" (3.2mm)	7, 8	ARGON	16 (6.5)	20	210-260	10" (256mm)
	FILLET							210-260	10" (256mm)
1/4" (6.4mm)	BUTT	1/8" (3.2mm)	5/32" (4.0mm)	8, 10	ARGON	18 (8.5)	20	240-300	10" (256mm)
	FILLET (2)							240-300	10" (256mm)

LOW ALLOY STEEL

Mild and low carbon steels with less than 0.30% carbon and less than 1" (2.5cm) thick, generally do not require preheat. An exception to this allowance is welding on highly restrained joints. These joints should be preheated 50 to 100°F (10 to 38°C) to minimize shrinkage cracks in the base metal. Low alloy steels such as the chromium-molybdenum steels will have hard heat affected zones after welding, if the preheat temperature is too low. This is caused by rapid cooling of the base material and the formation of martensitic grain structures. A 200 to 400°F (93 to 204°C) preheat temperature will slow the cooling rate and prevent the martensitic structure.

TROUBLESHOOTING GUIDE

PROBLEM	CAUSE	SOLUTION
Excessive Electrode Consumption	Inadequate gas flow	Increase gas flow
	Improper size electrode for current required	Use larger electrode
	Operating of reverse polarity	Use larger electrode or change polarity
	Electrode contamination	Remove contaminated portion, then prepare again
	Excessive heating inside torch	Replace collect, try wedge collet or reverse collet
	Electrode oxidizing during cooling	Increase gas post flow time to 1 sec. per 10 amps
	Shield gas incorrect	Change to proper gas (no oxygen or Co2)
Erratic Arc	Incorrect voltage (arc too long)	Maintain short arc length
	Current too low for electrode size	Use smaller electrode or increase current
	Electrode contaminated	Remove contaminated portion, then prepare again
	Joint too narrow	Open joint groove
	Contaminated shield gas, dark stains on the electrode or weld bead indicate contamination	Most common cause is moisture or aspirated air in gas stream. Use welding grade gas only. Find the source of the contamination and eliminate it promptly.
	Base metal is oxidized, dirty or oily	Use appropriate chemical cleaners, wire brush or abrasives prior to welding.
Inclusion of Tungsten or Oxides in Weld	Poor scratch starting technique	Many codes do not allow scratch starts. Use copper strike plate. Use high-frequency arc starter.
	Excessive current for tungsten size used	Reduce current or use larger electrode
	Accidental contact of electrode with puddle	Maintain proper arc length
	Accidental contact of electrode to filler rod	Maintain a distance between electrode and filler metal
	Using excessive electrode extension	Reduce electrode extension to recommended limits
	Inadequate shielding or excessive drafts	Increase gas flow, shield arc from wind, or use gas lens
	Wrong gas	Do not use Ar-O2 or Ar-Co2 GMA (MIG) gases for TIG welding
	Heavy surface oxides not being removed	Use ACHF, adjust balance control for maximum cleaning, or wire brush and clean the weld joint prior to welding.
Porosity in Weld Deposit	Entrapped impurities, hydrogen, air, nitrogen, water vapor	Do not weld on wet material. Remove condensation from line
	Defective gas hose or loose connection	Check hoses and connections for leaks
	Filler material is damp (particularly aluminum)	Dry filler metal in oven prior to welding
	Filler material is oily or dusty	Replace filler metal
	Alloy impurities in the base metal such as sulphur, phosphorus, lead and zinc	Change to a different alloy composition which is weldable. These impurities can cause a tendency to crack when hot.
	Excessive travel speed with rapid freezing of weld trapping gases before they escape	Lower the travel speed
	Contaminated gas shield	Replace the shielding gas
Cracking in Welds	Hot cracking in heavy section or with metals which are hot shorts	Preheat, increase weld bead cross-section size, change weld bead contour.
	Crater cracks due to improperly breaking the arc or terminating the weld at the joint edge	Reverse direction and weld back into previous weld at edge. Use remote or foot control to manually down slope current.
	Post weld cold cracking, due to excessive joint restraint, rapid cooling, or hydrogen embrittlement	Preheat prior to welding, use pure to non-contaminated gas. Increase the bead size. Prevent craters or notches. Change the weld joint design.
	Centerline cracks in single pass welds	Increase bead size. Decrease root opening, use preheat, prevent craters.
	Underbead cracking from brittle microstructure	Eliminate sources of hydrogen, joint restraint, and use preheat.
Inadequate Shielding	Gas flow blockage or leak in hoses or torch	Locate and eliminate blockage or leak.
	Excessive travel speed exposes molten weld to atmospheric contamination	Use slower travel speed or carefully increase the flow rate to a safe level below creating excessive turbulence. Use trailing shield cup.
	Wind or drafts	Set up screens around the weld area
	Excessive electrode stickout	Reduce electrode stickout. Use a larger size cup.
	Excessive turbulence in gas stream	Change to gas saver parts or gas lens parts.
Arc Blow	Induced magnetic field from DC weld current	Change to ACHF current. Rearrange the split ground connection.
	Arc is unstable due to magnetic influences	Reduce weld current and use arc length as short as possible.
Short Parts Life	Short water cooled leads life	Verify coolant flow direction, return flow must be on the power cable lead.
	Cup shattering or breaking in use	Change cup size or type, change tungsten position, refer to CK Worldwide technical specifications available at www.CKWorldwide.com
	Short collet life	Ordinary style is split and twists or jams, change to wedge style.
	Short torch head life	Do not operate beyond rated capacity, use water cooled model, do not bend rigid torches.
	Gas hoses ballooning, bursting or blowing off while hot	Incorrect flowmeter, TIG flowmeters operate at 35 psi with low flows. MIG flowmeters operate with high flows at 65 psi or more.



CONNECT WITH US ON:



Phone: 1.800.426.0877 Fax: 1.800.327.5038
 CK Worldwide, Inc., PO Box 1636, Auburn, WA 98071

TRADEMARK NOTICES:
 Gas Saver® Safe-Loc® Flex-Loc® Super-Flex®
 Trim-Line® Max-Flo® Fail-Safe® Steady-Grip® and LaYZr® are
 registered trademarks of CK Worldwide, Inc.

www.CKWORLDWIDE.com

© 2016/2023 CK Worldwide, Inc. All rights reserved.